

NAT'L INST OF STAND & TECH R.I.C.




A11104 142040

A11100 988703

NBS
PUBLICATIONS

NAT'L INST OF STANDARDS & TECH H.T.C.
A11100988703
/NBS monograph
QC100 .U556 V25-16;1979 C.1 NBS-PUB-C 19

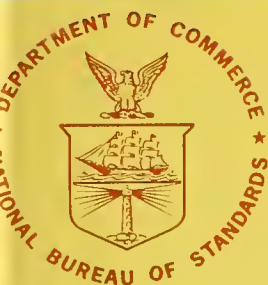

NBS MONOGRAPH 25—SECTION 16

U.S. DEPARTMENT OF COMMERCE / National Bureau of Standards

Standard X-ray Diffraction Powder Patterns

QC
100
U556
o.25-16
1979
c.2

NATIONAL BUREAU OF STANDARDS

The National Bureau of Standards¹ was established by an act of Congress on March 3, 1901. The Bureau's overall goal is to strengthen and advance the Nation's science and technology and facilitate their effective application for public benefit. To this end, the Bureau conducts research and provides: (1) a basis for the Nation's physical measurement system, (2) scientific and technological services for industry and government, (3) a technical basis for equity in trade, and (4) technical services to promote public safety. The Bureau's technical work is performed by the National Measurement Laboratory, the National Engineering Laboratory, and the Institute for Computer Sciences and Technology.

THE NATIONAL MEASUREMENT LABORATORY provides the national system of physical and chemical and materials measurement; coordinates the system with measurement systems of other nations and furnishes essential services leading to accurate and uniform physical and chemical measurement throughout the Nation's scientific community, industry, and commerce; conducts materials research leading to improved methods of measurement, standards, and data on the properties of materials needed by industry, commerce, educational institutions, and Government; provides advisory and research services to other Government agencies; develops, produces, and distributes Standard Reference Materials; and provides calibration services. The Laboratory consists of the following centers:

Absolute Physical Quantities² — Radiation Research — Thermodynamics and Molecular Science — Analytical Chemistry — Materials Science.

THE NATIONAL ENGINEERING LABORATORY provides technology and technical services to the public and private sectors to address national needs and to solve national problems; conducts research in engineering and applied science in support of these efforts; builds and maintains competence in the necessary disciplines required to carry out this research and technical service; develops engineering data and measurement capabilities; provides engineering measurement traceability services; develops test methods and proposes engineering standards and code changes; develops and proposes new engineering practices; and develops and improves mechanisms to transfer results of its research to the ultimate user. The Laboratory consists of the following centers:

Applied Mathematics — Electronics and Electrical Engineering² — Mechanical Engineering and Process Technology² — Building Technology — Fire Research — Consumer Product Technology — Field Methods.

THE INSTITUTE FOR COMPUTER SCIENCES AND TECHNOLOGY conducts research and provides scientific and technical services to aid Federal agencies in the selection, acquisition, application, and use of computer technology to improve effectiveness and economy in Government operations in accordance with Public Law 89-306 (40 U.S.C. 759), relevant Executive Orders, and other directives; carries out this mission by managing the Federal Information Processing Standards Program, developing Federal ADP standards guidelines, and managing Federal participation in ADP voluntary standardization activities; provides scientific and technological advisory services and assistance to Federal agencies; and provides the technical foundation for computer-related policies of the Federal Government. The Institute consists of the following centers:

Programming Science and Technology — Computer Systems Engineering.

¹Headquarters and Laboratories at Gaithersburg, MD, unless otherwise noted; mailing address Washington, DC 20234.

²Some divisions within the center are located at Boulder, CO 80303.


Standard X-ray Diffraction Powder Patterns Section 16—Data for 86 Substances

Marlene C. Morris, Howard F. McMurdie, Eloise H. Evans,
Boris Paretzkin, and Johan H. de Groot

International Centre for
Diffraction Data

Camden R. Hubbard and Simon J. Carmel

National Measurement Laboratory
National Bureau of Standards
Washington, D.C. 20234

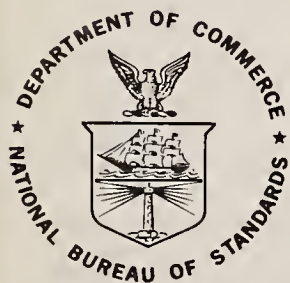

JCPDs®

International Centre for
Diffraction Data

Monograph #25 section 16
U.S. DEPARTMENT OF COMMERCE, Juanita M. Kreps, Secretary

Luther H. Hodges, Jr., Under Secretary

Jordan J. Baruch, Assistant Secretary for Science and Technology

NATIONAL BUREAU OF STANDARDS, Ernest Ambler, Director

Issued October 1979

Library of Congress Catalog Card Number: 53-61386

National Bureau of Standards Monograph 25

Section 16--Data for 86 Substances

Nat. Bur. Stand. (U.S.), Monogr. 25--Sec. 16, 190 pages (Oct. 1979)

CODEN: NBSMA6

U.S. GOVERNMENT PRINTING OFFICE

WASHINGTON: 1979

For sale by the Superintendent of Documents, U.S. Government Printing Office, Washington, D.C. 20234

Stock No. 003-003-02128-8, Price \$5

(Add 25 percent additional for other than U.S. mailing)

CONTENTS

Page

Introduction..... 1

Experimental patterns:

Acetanilide, C_8H_9NO	7
Ammonium hydrogen arsenate, $NH_4H_2AsO_4$...	9
Ammonium titanium fluoride, $(NH_4)_2TiF_6$	10
p-Anisic acid, $C_8H_8O_3$	11
Antimonic acid, $H_{14}Sb_{14}O_{21}(OH)_{42}$	13
Antimony oxide, Sb_6O_{13}	14
Antimony tin, $SbSn$	15
Barium bromide hydrate, $BaBr_2 \cdot 2H_2O$	16
Barium chlorate, $Ba(ClO_3)_2$	17
Barium iodide hydrate, $BaI_2 \cdot 2H_2O$	18
Barium phosphate, $Ba_2P_2O_7$, (high form)...	19
Barium thiosulfate hydrate, $BaS_2O_3 \cdot H_2O$...	20
o-Bromobenzoic acid, $C_7H_5BrO_2$	22
Cadmium borate, CdB_4O_7	24
Cadmium phosphate, $Cd_2P_2O_7$	26
Cadmium phosphate, $Cd_3(PO_4)_2$	27
Calcium aluminum iron oxide (brownmillerite), $Ca_4Al_2Fe_2O_{10}$	28
Calcium boride, CaB_6	29
m-Chlorobenzoic acid, $C_7H_5ClO_2$	30
Chromium chloride hydrate, $CrCl_3 \cdot 6H_2O$...	31
Chromium sulfate, $Cr_2(SO_4)_3$	33
Copper lead hydroxide sulfate, linarite, $CuPb(OH)_2(SO_4)$	34
Dichlorotetraaquo chromium (III) chloride dihydrate, $[Cr(H_2O)_4Cl_2]Cl \cdot 2H_2O$	31
p-Fluorobenzoic acid, $C_7H_5FO_2$	36
Gold chloride, $AuCl$	37
Iron phosphate hydrate (vivianite), $Fe_3(PO_4)_2 \cdot 8H_2O$	38
Iron sulfate, $Fe_2(SO_4)_3$	39
Lead bromide hydroxide, $PbBr(OH)$	40
Lithium calcium aluminum boron hydroxy silicate, liddicoatite, $Ca(Li,Al)_3Al_6B_3Si_6O_{27}(O,OH)_3(OH,F)$...	42
Lithium chromium oxide hydrate, $Li_2CrO_4 \cdot 2H_2O$	44
Lithium tin oxide, Li_2SnO_3	45
Magnesium sulfate hydrate (kieserite), $MgSO_4 \cdot H_2O$	46
Manganese phosphate, $Mn_3(PO_4)_2$	47
Manganese sulfate hydrate (szmikite), $MnSO_4 \cdot H_2O$	49
Mercury sulfate, $HgSO_4$	50
Mercury sulfate, Hg_2SO_4	52
Nicotinic acid, $C_6H_5NO_2$	54
Oxalic acid hydrate, $C_2H_2O_4 \cdot 2H_2O$	55
Picric acid, $C_6H_3N_3O_7$	56
Potassium chromium sulfate, $KCr(SO_4)_2$...	58
Potassium iron sulfate (yavapaiite), $KFe(SO_4)_2$	59
Potassium nitrosyl ruthenium chloride, $K_2NORuCl_5$	61
Silver thiocyanate, $AgCNS$	62
Sodium aluminum fluoride (chiolite), $Na_5Al_3F_{14}$	63
Sodium borate, $Na_2B_4O_7$	64
Sodium borate hydroxide hydrate (borax), $Na_2B_4O_5(OH)_2 \cdot 8H_2O$	66

Sodium silicon fluoride (malladrite), Na_2SiF_6	68
Sodium titanium oxide, $Na_2Ti_3O_7$	69
Strontium chromium oxide, Sr_2CrO_4	71
Thallium, α -Tl.....	73
Thallium fluoride, TlF	74
Thallium hydrogen phthalate, $C_8H_5O_4Tl$...	75
Thallium oxide (avicennite), Tl_2O_3	77
Uric acid (phase 1), $C_5H_4N_4O_3$	78
Zinc chlorate hydrate, $Zn(ClO_4)_2 \cdot 6H_2O$...	79
Zinc phosphate, α - $Zn_3(PO_4)_2$	80
Zinc phosphate, β - $Zn_3(PO_4)_2$	81
Zinc phosphate, γ - $Zn_3(PO_4)_2$	83
Zinc phosphate hydrate (hopeite), $Zn_3(PO_4)_2 \cdot 4H_2O$	85

Calculated patterns:

Aluminum iron antimony oxide, bahianite, $Al_{5.66}Fe_{0.09}Sb_{2.95}O_{16}$	87
Antimony iron titanium oxide hydroxide, derbylite, $SbFe_4Ti_3O_{13}(OH)$	89
Benactyzine hydrochloride, $C_{20}H_{26}ClNO_3$...	92
Beryllium calcium iron magnesium aluminum phosphate hydroxide hydrate, roscherite (monoclinic), $Be_2Ca(Fe_{0.3}Mg_{0.7})_2Al_{0.67}(PO_4)_3(OH)_3$ $\cdot 2H_2O$	96
Beryllium calcium manganese aluminum iron phosphate hydroxide hydrate, roscherite (triclinic), $Be_4Ca_2(Mn_{3.91}Mg_{0.04}Ca_{0.05})(Al_{1.13}Fe_{0.42}$ $Mn_{1.12})(PO_4)_6(OH)_4 \cdot 6H_2O$	100
Calcium borate hydrate, hexahydroborite, $Ca[B(OH)_4]_2 \cdot 2H_2O$	104
Calcium chromium iron titanium oxide, loveringite, $Ca_{72}RE_{33}(Y,Th,U,$ $Pb)_{0.05}Ti_{12.48}Fe_{3.38}Cr_{2.24}Mg_{0.92}Zr_{0.58}$ $Al_{3.9}V_{2.1}Mn_{0.04}O_{38}$	106
Calcium hydrogen phosphate sulfate hydrate, $Ca_2HPO_4SO_4 \cdot 4H_2O$	109
Cannabidiol, $C_{21}H_{30}O_2$	111
L-Cocaine hydrochloride, $C_{17}H_{22}ClNO_4$	114
Codeine hydrobromide hydrate, $C_{18}H_{22}BrNO_3 \cdot 2H_2O$	117
Copper arsenate (trippkeite), $CuAs_2O_4$...	120
α -Dihydrophyllocladene, hartite (or bombiccite), $C_{20}H_{34}$	122
(-)-Ephedrine hydrochloride, $C_{10}H_{16}ClNO$...	124
Haloperidol, $C_{21}H_{23}ClFNO_2$	127
Imipramine hydrochloride, $C_{19}H_{25}ClN_2$	129
Morphine hydrochloride hydrate, $C_{17}H_{20}ClNO_3 \cdot 3H_2O$	133
Naloxone hydrochloride hydrate, $C_{19}H_{22}ClNO_4 \cdot 2H_2O$	136
Palladium selenium (palladseite), $Pd_{17}Se_{15}$	139
Phencyclidine hydrochloride, $C_{17}H_{26}ClN$...	141
Phenobarbital, form III, $C_{12}H_{12}N_2O_3$	144
Potassium barium iron titanium oxide, $K_{1.16}Ba_{0.72}Fe_{0.36}Ti_{5.58}O_{13}$	147
Procaine hydrochloride, $C_{13}H_{21}ClN_2O_2$	149
Psilocin, $C_{12}H_{16}N_2O$	152
Psilocybin methanolate, $C_{13}H_{21}N_2O_4P$	154

CONTENTS - (continued)

Sodium barbital, $C_8H_{11}N_2NaO_3$	157
Δ^9 -Tetrahydrocannabinolic acid B, $C_{22}H_{30}O_4$	160
Vinbarbital, form I, $C_{11}H_{16}N_2O_3$	162

Cumulative indices

(Circular 539, Volumes 1-10 and
Monograph 25, Sections 1-16 inclusive)

1. Inorganic.....	164
2. Organic formula.....	179
3. Organic name.....	181
4. Mineral.....	183

STANDARD X-RAY DIFFRACTION POWDER PATTERNS

Previous work has been published as a book entitled *Powder Diffraction Data from the Joint Committee on Powder Diffraction Standards Associateship at the National Bureau of Standards* (1976) (JCPDS--International Centre for Diffraction Data, 1601 Park Lane, Swarthmore, PA 19081). The volume is sold with an accompanying search manual, and contains 949 card images of patterns of experimental data, published originally as Circular 539 (vols. 1-10) and Monograph 25, Sections 1-12, and most of Section 13.

Individual copies of the Circular and Monograph are still available and may be obtained from the National Technical Information Service, 5285 Port Royal Road, Springfield, VA 22161. If a publication listed below is identified with a number, it must be used in ordering. All are available in hardcopy or microfiche; the price is not fixed and will be furnished on request.

NBS Publication	Number	NBS Publication	Number
Circular 539, Volume 1	.PB 178 902	Monograph 25, Section 1	PB 178 429
Volume 2	.PB 178 903	Section 2	.PB 178 430
Volume 3	.PB 178 904	Section 3	.PB 178 431
Volume 4	.PB 178 905	Section 4	
Volume 5	.PB 178 906	Section 5	
Volume 6	.PB 178 907	Section 6	
Volume 7	.PB 178 908	Section 7	
Volume 8	.PB 178 909	Section 8	.PB 194 872
Volume 9	.PB 178 910	Section 9	COM 72-50002
Volume 10.	.PB 178 911	Section 10.	COM 72-51079
		Section 11.	COM 74-50183
		Section 12.	COM 75-50162
		Section 13.	.PB 254 073
		Section 14.	.PB 272 372
		Section 15.	.PB 287 182

Also, until the present supply is exhausted, the following issues are for sale from the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402. Order by given catalog number, and add 25% to the price, for other than U.S. mailing.

	<u>Catalog Number</u>	<u>Price</u>
Section 12.	SN 003-003-01376-5	1.50
Section 13.	SN 003-003-01629-2	1.80
Section 14.	SN 003-003-01842-2	2.75
Section 15.	SN 003-003-01986-1	4.00

STANDARD X-RAY DIFFRACTION POWDER PATTERNS

Section 16. --- Data for 86 Substances

by

Marlene C. Morris, Howard F. McMurdie, Eloise H. Evans,
Boris Paretskin, and Johan H. de Groot
JCPDS - International Centre for Diffraction Data

and

Camden R. Hubbard and Simon J. Carmel
National Bureau of Standards

Standard x-ray diffraction patterns are presented for 86 substances. Fifty-eight of these patterns represent experimental data and 28 are calculated. The experimental x-ray powder diffraction patterns were obtained with an x-ray diffractometer. All d-values were assigned Miller indices determined by comparison with computed interplanar spacings consistent with space group extinctions. The densities and lattice constants were calculated and the refractive indices were measured whenever possible. The calculated x-ray powder diffraction patterns were computed from published crystal structure data. Both peak height and integrated intensities are reported for the calculated patterns.

Key words: Crystal structure; integrated intensities; lattice constants; peak intensities; powder patterns; reference intensities; standard; x-ray diffraction.

INTRODUCTION

The Powder Diffraction File is a continuing compilation of diffraction patterns gathered from many sources. Produced and published by the ¹JCPDS--International Centre for Diffraction Data, the File is used for identification of crystalline materials by matching d-spacings and diffraction intensity measurements. Under the partial sponsorship of the JCPDS, the program at the National Bureau of Standards contributes new data to this File. Our work also aids in the evaluation and revision of published x-ray data and in the development of diffraction techniques. This report presents information for 86 compounds (58 experimental and 28 calculated patterns), and is the twenty-sixth of the series of "Standard X-ray Diffraction Powder Patterns" ².

EXPERIMENTAL POWDER PATTERNS

CAS registry number. The Chemical Abstracts Service Registry Number is included, when available, to help identify the sample. This number forms the basis for computer aided searching of Chemical Abstracts.

¹JCPDS--International Centre for Diffraction Data, 1601 Park Lane, Swarthmore, PA. 19081. This Pennsylvania non-profit corporation functions in cooperation with the American Ceramic Society, the American Crystallographic Association, the American Society for Testing and Materials, The Clay Minerals Society, The Institute of Physics, the Mineralogical Association of Canada, the Mineralogical Society of America, The Mineralogical Society of Great Britain and Ireland, the National Association of Corrosion Engineers, and the Société Française de Minéralogie et de Cristallographie.

²See previous page for other published volumes.

Sample. The samples used to make NBS patterns were obtained from a variety of sources or were prepared in small quantities in our laboratory. Appropriate annealing or recrystallization of the samples improved the quality of most of the patterns. A check of phase purity was provided by indexing the x-ray pattern.

Optical data. When reported, optical measurements were made by grain immersion methods, in white light, using oils standardized in sodium light, in the refractive index range 1.49 to 2.1 [Hartshorne and Stuart, 1970].

The names of the sample colors were selected from the ISCC-NBS Centroid Color Charts [1965].

Interplanar spacings. For spacing determinations, a shallow holder was packed with a sample mixed with an internal standard. Choice of the standard was determined by the need for low angle and unobstructed reflections. The amount of standard was estimated so that the intensity of its strongest peak would be about equal to the intensity of the strongest peak of the sample.

To avoid errors associated with aberrations at the very top of the peaks, the readings of 2 θ were taken at positions about 20% of the way down from the top, and in the center of the peak width. The K α_2 peaks were occasionally read to assist in establishing a K α_1 peak position, but K α_2 peaks were not reported.

At low angles, K α_1 and K α_2 peaks were unresolved for both the sample and the internal standard. The internal standard corrections were established from the theoretical values for K α_1 and were applied to the unresolved low angle peaks, as well as to the resolved K α peaks in the higher angle regions. If the internal standard correction varied along the length of the pattern, linear interpolations were used.

The internal standards used were of high purity (99.99%). The lattice constants used for them at 25 °C are given in Table 1; the 2 θ angles were computed using cell dimensions uncorrected for index of refraction.

Table 1

Calculated 2 θ Angles, CuK α_1 λ = 1.540598Å			
hkl	W a=3.16524Å ±.00004	Ag a=4.08651Å ±.00002	Si a=5.43088Å ±.00004
110	40.262		
111		38.112	28.443
200	58.251	44.295	
211	73.184		
220	86.996	64.437	47.303
310	100.632		
311		77.390	56.123
222	114.923	81.533	
321	131.171		
400	153.535	97.875	69.131
331		110.499	76.377
420		114.914	
422		134.871	88.032
511/333		156.737	94.954
440			106.710
531			114.094
620			127.547
533			136.897
444			158.638

The new internal standard Si powder is available as Standard Reference Material 640 [1974]. The lattice constant for the Si was refined from multiple powder data measurements made with tungsten as an internal standard [Swanson et al., 1966]. Cell parameter data were also collected for single crystal from the boules ground to prepare the powder. The lattice parameters from the two methods agreed within 3 parts in 10⁵ [Hubbard et al. 1975]. D-spacing results using SRM 640 will be in agreement with patterns recorded in this series of monographs since 1966.

All of our spacing measurements were recorded at 25 ± 1 °C on a diffractometer equipped with a focusing graphite or lithium fluoride crystal monochromator located between the sample and the scintillation counter. Pulse height discrimination was used as well. All measurements were performed using copper radiation: λ (CuK α_1 , peak)=1.540598Å [Deslattes and Henins, 1973].

Structure, lattice constants. The space groups were listed with short Hermann-Mauguin symbols as well as the space group numbers given in the *International Tables for X-ray Crystallography*, Vol. I [1952].

Orthorhombic cell dimensions were arranged according to the Dana convention $b > a > c$ [Palache et al., 1944]. Monoclinic and triclinic lattice constants were transformed if necessary in order

to follow the convention of *Crystal Data* [1973].

A computer program [Evans et al., 1963] assigned hkl's and refined the lattice constants. Cell refinement was based only upon 2 θ_{obs} values which could be indexed without ambiguity. The program minimized the value $\sum(\theta_{\text{obs}} - \theta_{\text{calc}})^2$. The estimated standard deviations (e.s.d.'s) of the reciprocal cell parameters were determined from the inverse matrix of the normal equations. The program calculated the e.s.d.'s of the direct cell constants by the method of propagation of errors. Since 1973, the e.s.d.'s derived by the computer program have been increased by 50% in order to reflect more truly the uncertainty in the lattice constants. A similar increase should also be applied to all lattice constants in earlier publications of this series. The e.s.d.'s in the least significant figures are given in parentheses following the lattice constants.

In indexing cubic patterns, multiple hkl's were not utilized in the refinement or reported. Instead, the single appropriate index having the largest h was listed. The number of significant figures reported for d-values varied with the symmetry and crystallinity of each sample.


Densities. These were calculated from the specified lattice constants, the Avogadro number 6.0220943×10^{23} [Deslattes et al., 1974] and atomic weights published by the International Union of Pure and Applied Chemistry [1972].

Figure of merit. Several figures of merit ratings are available for assessing indexed powder data. M_{20} [de Wolff, 1968] is a criterion for the reliability of the unit cell and indexing. A value of $M_{20} > 10$ will guarantee the essential correctness of the indexing provided there are not more than 2 spurious lines ($X_{20} \leq 2$) [de Wolff, 1968]. All patterns reported in this publication have M_{20} between 20 and 233, and $X_{20} = 0$ unless noted otherwise. M_{20} was specified for any pattern indexed with a cell derived only through computer indexing from powder data, without further confirmation.


The accuracy and completeness of measured interplanar spacings is conveniently reported as F_N [Smith and Snyder, 1979]. The format used in this publication was $F_N = \text{overall value} (\frac{|\Delta 2\theta|}{N_{\text{poss}}})$, where N , the number of observed reflections was chosen as 30 or the maximum number of lines of the pattern, if the entire pattern had fewer than 30 lines. The "overall value" was the figure of merit, F_N , as defined by Smith and Snyder [1979], and $|\Delta 2\theta|$ was the average absolute magnitude of discrepancy between observed and calculated 2 θ values for the N lines. N_{poss} was the number of unique and resolvable diffraction lines allowed in the space group, up to the N^{th} observed and indexed line. In this publication, the value of F_N ranged from 31 to 118, with an average value of 61 for the 58 patterns from experimental data.

Intensity measurements. It was found that samples which gave satisfactory intensity patterns usually had an average particle size smaller than 10 μm , as recommended by Alexander et al. [1948]. In order to avoid the orientation effects which occur when powdered samples are packed or pressed,

a sample holder was made that had in its top face a rectangular cavity which extended to one end of the holder. To prepare the sample, a glass slide was clamped over the top face to form a temporary cavity wall (see Figure 1), and the powdered sample was allowed to drift into the end opening while the holder was held in a vertical position.

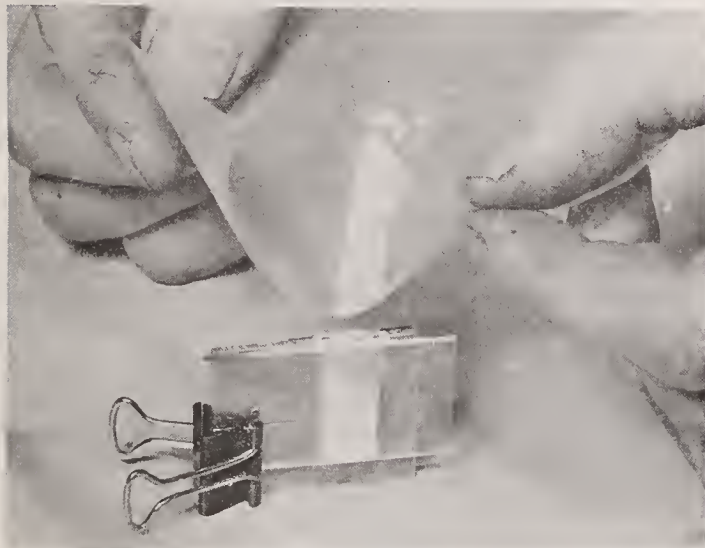

With the sample holder returned to a horizontal position, the glass slide was carefully removed so that the sample could be exposed to the x-ray beam (see Figure 2). If the sample powder did not flow readily, or was prone to orient excessively, approximately 50 volume percent of finely ground silica-gel was added as a diluent. The intensities of the diffraction lines were measured as peak heights above background and were expressed in percentages of the strongest line. Any intensity larger than 20 was rounded to the nearer multiple of 5. At least 3 patterns for intensity measurements were prepared for each sample to check reproducibility.

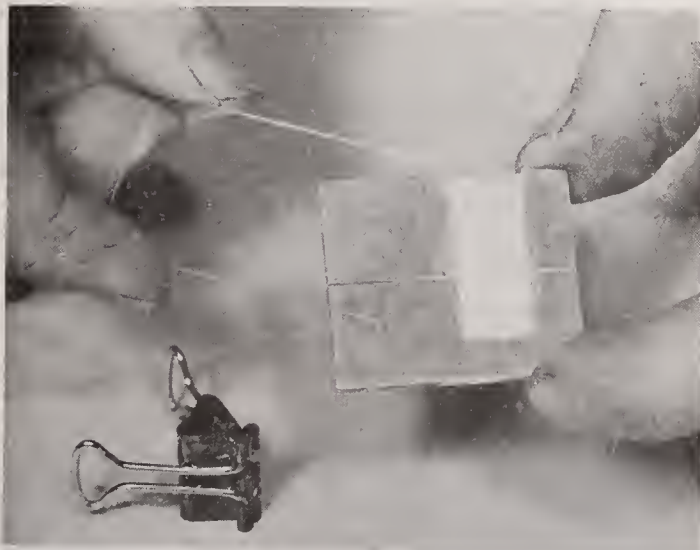

Reference Intensity Ratio, I/I_{corundum} . The reference intensity ratio, I/I_c , has been defined as the direct ratio of the intensity of the strongest reflection of a sample, to the intensity of the reflection 113 (hexagonal) of corundum ($\alpha\text{-Al}_2\text{O}_3$) [Visser and de Wolff, 1964]. In this publication, the ratios I/I_c were tabulated for copper $K\alpha$ radiation, for a 1:1 mixture by weight of the sample and corundum. Occasionally I/I_c was not determined because it was not feasible.

A procedure has been adopted, to achieve greater statistical accuracy [Hubbard and Smith, 1977]. For any weight fractions of sample and corundum, x_s and x_c ($x_s = 1 - x_c$), the intensities for reflection h of the sample and k of corundum were measured for several combinations of h and k usually within the same region of 2θ , to provide indications of possible preferred orientation, extinction, or other systematic errors. The reference intensity ratio is then given by

$$\frac{I(h_0)}{I_c(113)} = \frac{x_c}{x_s} \cdot \frac{I_c^{\text{rel}}(k)}{I^{\text{rel}}(h)} \cdot \frac{I(h)}{I(k)}$$

and (h_0) indicates specifically which reflection was chosen for tabulation purposes. For each of our patterns, the reflection (h_0) will be the one with $I=100$ since only copper radiation was used. Typically, at least 3 sets of reflections and 2 mountings of the mixture were used to obtain 6 or more values for the reference intensity ratio, I/I_c . These values yield the tabulated average $\langle I/I_c \rangle$. From these data, the estimated deviation, Δ , was obtained from

$$\Delta = \frac{\sum_{i=1}^n |(I/I_c)_i - \langle I/I_c \rangle|}{n}$$

where n is the number of measurements of the reference intensity ratio. The estimated deviation in the least significant figures is given in parentheses.

Format of tables. The printing of the data has been computerized. Superimposed reflections were treated in one of two ways. If a d-spacing had only two possible indices, an M was added to the d-spacing which was repeated on the next line, but with the second index. However, if there were more than two possible indices, a + sign was used in like manner. In both cases, the composite intensity was printed only once and aligned with the first reflection. The symbol "1L" in the intensity column was used to indicate "less than 1."

CALCULATED POWDER PATTERNS

Since some substances of interest are not readily available for experimental work, powder patterns were calculated from published crystal structure data. The FORTRAN program used for the computations was developed by Clark et al. [1973] and modified at NBS.

Lattice parameters. Before the computations of the patterns, any necessary changes were made

in the lattice constants in order to make them consistent with the revised value of $\lambda(\text{CuK}\alpha_1) = 1.540598\text{\AA}$ [Deslattes and Henins, 1973]. Both the altered and the original published values are given. A lattice constant arrangement which follows the convention of *Crystal Data* has been referred to as the "CD cell." In several of the calculated patterns, the literature lattice constants, the atom positions, and hence the final patterns were not given in the CD arrangement. For cross-reference purposes, the CD cell was calculated separately and included in the text.

Scattering factors. Whenever possible, the same scattering factors were used which the author of the reference article specified. Otherwise, the factors were taken directly from the *International Tables for X-ray Crystallography*, Vol. III, [1962]. The factors were corrected for dispersion if the author had done so.

Thermal parameters. The computer program used thermal parameter data of only two forms, the isotropic B 's ($\text{\AA}^2$) or the anisotropic β_{ij} 's in the following expressions:

$$e^{-B \sin^2 \theta / \lambda^2}$$

or

$$e^{-(h^2 \beta_{11} + k^2 \beta_{22} + l^2 \beta_{33} + 2hk\beta_{12} + 2hl\beta_{13} + 2kl\beta_{23})}.$$

Other thermal parameters (e.g. U_{ij}) were converted to one of these two forms. The isotropic parameters were used directly, if given by the structure reference. In a few of our patterns, anisotropic parameters were also used directly as given by the structure reference; in other work, instead of using given anisotropic parameters, approximately equivalent isotropic values were substituted as defined by:

$$B = 4 \left[\frac{\beta_{11} \beta_{22} \beta_{33}}{a^2 b^2 c^2} \right]^{1/3}$$

Structural information. The atom positions used in these calculated patterns varied somewhat in the degree of reliability. In our text, when the expression "the structure was determined by..." was used, the atomic parameters in the reference cited had been calculated from refinement of single crystal data. Otherwise, the atomic positions had been derived by analogy with similar compounds whose structure was known. In cases where isostructural relationships were used, the atoms were in fixed special positions or the ionic radii were closely related to the corresponding radii of the atoms in the known structure.

Integrated intensities. The theoretical integrated intensity of reflection i on the "absolute-relative" scale is I_i^{abs}/K , as defined by Hubbard et al. [1976] in the equation

$$\frac{I_i^{\text{abs}}}{K} = \frac{M_i L_p |F_i T_i|^2}{2\mu V^2}$$

where:

F is the structure factor
 T is the thermal correction

$$L_p = \frac{1 + \cos^2 2\theta}{\sin^2 \theta \cos \theta} \quad \text{is the Lorentz-polarization term}$$

M is the multiplicity for the reflection i
 μ is the linear absorption coefficient
 V is the volume of the unit cell.

When the largest integrated intensity was assigned a relative value of 100 and all other reflections were scaled relative to it, the intensities were placed on the relative intensity scale (I^{rel}). Reflections with I^{rel} less than 0.7 were omitted. Relative intensities were rounded to the nearest integer value before being listed, except that for phases whose structures were postulated or were based on analogy, any intensity above 20 was rounded further, to the nearer multiple of 5.

Scale factor (integrated intensities). The scale factor, γ , was defined to convert the tabulated I^{rel} to the "absolute-relative" scale [Hubbard et al., 1976]. That is:

$$\gamma = \frac{M' L_p' |F' T'|^2}{200 \mu V^2}$$

and

$$\frac{I^{\text{abs}}}{K} = \gamma I^{\text{rel}}$$

The primes denoted the values for the largest integrated intensity. In earlier Monographs (1969-1975), a different scale factor, k_{NBS} , was reported which is related to γ :

$$\frac{\gamma}{k_{\text{NBS}}} = \frac{1}{2\mu V^2}$$

From γ , the theoretical value of the Reference Intensity Ratio, I/I_c , was calculated:

$$I/I_c = \frac{\mu \rho_c}{\mu_c \gamma_c \rho}$$

where ρ is the density and the subscript c represents corundum ($\alpha\text{-Al}_2\text{O}_3$).

For refined structures, the value of I/I_c was given. For those phases whose structures were postulated or were based only on analogy to other powder patterns, I/I_c was not included.

I/I_c and γ are each based on the single strongest reflection, not on the overlapping sum of superimposed reflections.

Peak heights. The purpose of calculating peak height intensity was to provide a tabulated pattern similar to what might be obtained from experimental diffractometer measurements. For each predicted reflection, Cauchy profiles centered at both the α_1 and the α_2 peak positions were calculated and summed, forming a simulated powder pattern. The full width at half-maximum (FWHM)

was allowed to vary to represent the changing FWHM as a function of 2θ . [The values of the FWHM vs 2θ are given in Table 2.]. The resultant simulated powder pattern was then analyzed for peaks. In the regions of the predicted reflections several reflections could have identical or similar 2θ angles and produce only one composite peak in the simulated pattern. The 2θ angle of the composite peak was assigned the hkl of the reflection having the greatest contribution to the peak height intensity. If any other peak contributed more than 10% of the intensity toward the composite peak height intensity, a plus sign(+) was appended to the hkl.

Peaks due solely to α_2 lines were omitted. If a composite peak was formed by the overlap of an α_1 peak of reflection j with the α_2 peak of reflection i , the reflection j was listed separately only if it contributed a significant intensity (>10%) at the composite peak location.

The peak search routine located peaks only at 2θ angles which were a multiple of 0.02° .

Table 2

2θ CuK α_1	FWHM	2θ CuK α_1	FWHM
0°	0.12°	140	0.230
20	.12	145	.255
40	.12	150	.285
60	.125	155	.315
80	.130	160	.360
100	.135	162.5	.410
120	.155	165	.500
130	.185		

UNITS

In this publication the Ångström unit ($1\text{Å} = 100\text{pm}$) was selected for presentation of the d-spacings and lattice parameters to maintain consistency with (a) the earlier publications of Standard X-ray Diffraction Powder Patterns (Circular 539 volumes 1-10 and Monograph 25 sections 1-15), (b) the publications of the International Union of Crystallography: Acta Crystallographica and the Journal of Applied Crystallography, and (c) the continuing publication of cards and search manuals of the Powder Diffraction File (now consisting of nearly 30,000 entries). The PDF search manuals are based on the d-spacings in Å of the three strongest lines. Consistent with the choice of the Å unit for length, the volume of the unit cell is expressed in Å^3 ($=1 \times 10^{-30} \text{m}^3$). Other reported parameters and their units are density in g/cm^3 ($1 \text{gm/cm}^3 = 10^{-3} \text{kg/m}^3$) and the linear absorption coefficient in cm^{-1} .

ACKNOWLEDGMENTS

We would like to thank Mary Owen of the JCPDS Associateship for her assistance, particularly for key-punching the data and helping with the proof-reading of this manuscript. Appreciation is also expressed to the Text Editing Facilities of the National Measurement Laboratory of NBS for typing the manuscript.

REFERENCES

- Alexander, L., Klug, H. P. and Kummer, E. (1948). J. Appl. Phys., 19, No. 8, 742.
- Clark, C. M., Smith, D. K., and Johnson, G. G., Jr. (1973). A FORTRAN IV Program for Calculating X-ray Powder Diffraction Patterns, Version 5, Dept. of Geosciences, Pennsylvania State Univ., University Park, PA 16802.
- Crystal Data (1973). (3rd. Ed. Published jointly by the U.S. Department of Commerce, National Bureau of Standards, Washington, D.C. 20234, and the Joint Committee on Powder Diffraction Standards, 1601 Park La., Swarthmore, PA 19081).
- Deslattes, R. D. and Henins, A. (1973). Phys. Rev. Lett. 31, 972.
- Deslattes, R. D., Henins, A., Bowman, H. A., Schoonover, R. M., Carroll, C. L., Barnes, I. L., Machlan, L. A., Moore, L. J., and Shields, W. R. (1974). Phys. Rev. Lett. 33, 463.
- Evans, H. T., Jr., Appleman, D. E. and Handwerker, D. S. (1963), Report #PB 216188, U.S. Dept. of Commerce, National Technical Information Center 5285 Port Royal Rd., Springfield, VA 22151, \$3.50.
- Hartshorne, N. H. and Stuart, A. (1970). Crystals and the Polarizing Microscope (Edward Arnold and Co., London, 4th Ed.)
- Hubbard, C. R., Evans, E. H., and Smith, D. K., (1976). J. Appl. Cryst., 9, 169.
- Hubbard, C. R. and Smith, D. K. (1977). Advances in x-ray Analysis, 20, (Plenum Publishing Corporation, 227 West 17th St., New York, NY 10011) p. 27.
- Hubbard, C. R., Swanson, H. E., and Mauer, F. A. (1975). J. Appl. Cryst. 8, 45.
- International Tables for X-ray Crystallography, I (1952). (The Kynoch Press, Birmingham, Eng.), Ibid. III (1962) pp. 202, 210, 213, 214.
- International Union of Pure and Applied Chemistry (1972). Pure Appl. Chem. 30, Nos. 3-4, 639.
- ISCC-NBS Centroid Color Charts, SRM 2106, or Color Kit, SRM 2107 which contains both SRM 2106 and Color, an NBS Special Publication #SP 440. These can be obtained from the National Bureau of Standards, Office of Standard Reference Materials, Washington, D.C. 20234. Current prices will be quoted on request.
- Palache, C., Berman, H. and Frondel, C. (1944). Dana's System of Mineralogy (John Wiley and Sons, New York, 7th Ed.), I, 6.
- Smith, G. S. and Snyder, R. L. (1979). J. Appl. Crystallogr. 12, 60.
- Standard Reference Material 640 (1974), X-ray Diffraction Standards, obtainable from the National Bureau of Standards, Office of Standard Reference Materials, Washington, D.C. 20234. Current price will be quoted on request.
- Swanson, H. E., Morris, M. C., and Evans, E. H. (1966). Nat'l Bur. Std. U.S. Monogr. 25, Sec. 4, 3.
- Visser, J. W. and de Wolff, P. M. (1964). "Absolute Intensities," Report 641.109, Technisch Fysische Dienst, Delft, Netherlands.
- Wolff, P. M. de (1968). J. Appl. Crystallogr. 1, 108.

Acetanilide, C₈H₉NO

CAS registry no.
103-84-4

Sample

The sample is Standard Reference Material 141c of the National Bureau of Standards, obtained from J. T. Baker Co., Phillipsburg, NJ. It is used for checking microchemical procedures for the determination of carbon, hydrogen and nitrogen in organic matter.

Color

Colorless

Structure

Orthorhombic, Pcab (61), Z = 8. The structure was determined by Brown and Corbridge [1954] and refined by Brown [1966].

Lattice constants of this sample

a = 9.494(3) Å

b = 19.645(4)

c = 7.995(2)

a/b = 0.4833

c/b = 0.4070

Volume

1491. Å³

Density

(calculated) 1.204 g/cm³

Figure of merit

F₃₀ = 56.3 (0.013,40)

Reference intensity

I/I_{corundum} = 0.63(4)

Additional patterns

1. PDF card 18-1501 [Billig, B. and Greenberg, B., Polytechnic Institute of Brooklyn, 1965]
2. Morris et al. [1977]

References

- Brown, C. J. (1966). Acta Crystallogr. 21, 442.
- Brown, C. J. and Corbridge, D. E. C. (1954). Acta Crystallogr. 7, 711.
- Morris, M. C., McMurdie, H. F., Evans, E. H., Paretzkin, B., de Groot, J. H., Newberry, R., Hubbard, C. R., and Carmel, S. J. (1977). Nat. Bur. Std. U.S. Monogr. 25, Sec. 14, 38.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard W, a = 3.16524 Å				
d(Å)	I	hkl	2θ(°)	
9.81	90	0 2 0	9.01	
6.82	30	1 2 0	12.97	
5.84	65	1 1 1	15.17	
5.193	30	1 2 1	17.06	
4.913	5	0 4 0	18.04	
4.749	6	2 0 0	18.67	
4.469	30	1 3 1	19.85	
4.360	30	1 4 0	20.35	
4.273	8	2 2 0	20.77	
4.081	45	2 0 1	21.76	
3.994M	60	0 0 2	22.24	
3.994M		2 1 1	22.24	
3.917	55	0 1 2	22.68	
3.826	19	1 4 1	23.23	
3.768	40	2 2 1	23.59	
3.700	100	0 2 2	24.03	
3.620	30	1 1 2	24.57	
3.448	55	1 2 2	25.82	
3.411M	10	2 4 0	26.10	
3.411M		0 3 2	26.10	
3.305	7	1 5 1	26.96	
3.210	20	1 3 2	27.77	
3.097M	9	0 4 2	28.80	
3.097M		1 6 0	28.80	
2.773	5	2 3 2	32.26	
2.694	5	2 6 0	33.23	
2.658	2	3 4 0	33.69	
2.597	8	2 4 2	34.51	
2.549	7	1 7 1	35.18	
2.543	8	1 1 3	35.27	
2.535	7	0 6 2	35.38	
2.482	4	1 2 3	36.16	
2.455	2	0 8 0	36.58	
2.414	2	2 5 2	37.21	
2.378	6	1 8 0	37.80	
2.355	2	3 5 1	38.18	
2.308M	6	2 1 3	39.00	
2.308M		4 2 0	39.00	
2.297	7	0 7 2	39.18	
2.277+	6	3 6 0	39.55	
2.277+		4 0 1	39.55	

Acetanilide, C₈H₉NO (continued)

d(Å)	I	hkl	2θ(°)
2.214	2	3 4 2	40.73
2.191	5	2 3 3	41.17
2.148M	2	4 3 1	42.02
2.148M		1 5 3	42.02
2.099	2	3 5 2	43.07
2.067	3	2 7 2	43.76
2.056	4	1 9 1	44.00
2.030M	2	3 7 1	44.60
2.030M		4 1 2	44.60
2.027	4	3 1 3	44.67
1.969	3	4 5 1	46.05
1.965	2	0 10 0	46.17
1.947M	5	3 3 3	46.62
1.947M		1 1 4	46.62
1.923M	5	4 6 0	47.23
1.923M		1 10 0	47.23
1.919	5	1 2 4	47.32
1.895M	4	2 6 3	47.98
1.895M		1 7 3	47.98
1.885M	5	3 8 1	48.24
1.885M		4 4 2	48.24
1.879	6	1 9 2	48.41
1.870	4	1 10 1	48.65

Ammonium Hydrogen Arsenate, $\text{NH}_4\text{H}_2\text{AsO}_4$

Sample

The sample was obtained from Alfa Products, Danvers, MA.

Color

Colorless

Structure

Tetragonal, $I\bar{4}2d$ (122), $Z = 4$, isostructural with KH_2PO_4 . The structure was determined by Delain [1958] and refined by Khan and Bauer [1973].

Lattice constants of this sample

$$a = 7.6978(6) \text{ \AA}$$

$$c = 7.7193(7)$$

$$c/a = 1.0028$$

Volume

$$457.41 \text{ \AA}^3$$

Density

(calculated) 2.308 g/cm^3

Figure of merit

$$F_{30} = 76.2(0.012, 32)$$

Reference intensity

$$I/I_{\text{corundum}} = 4.3(2)$$

Additional pattern

1. PDF card 1-775 [Hanawalt et al., 1938]

References

Delain, C. (1958). C. R. Acad. Sci. Ser. C 247, 1451.

Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.

Khan, A. A. and Baur, W. H. (1973). Acta Crystallogr. B29, 2721.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$	
5.450	80	1 0 1	16.25	
3.847	65	2 0 0	23.10	
3.143	100	2 1 1	28.37	
2.725	15	2 0 2	32.84	
2.719	20	2 2 0	32.91	
2.438	4	1 0 3	36.83	
2.433M	4	3 1 0	36.92	
2.433M		3 0 1	36.92	
2.058M	45	3 2 1	43.96	
2.058M		3 1 2	43.96	
1.929	1	0 0 4	47.07	
1.924	3	4 0 0	47.20	
1.8166	9	3 0 3	50.18	
1.8142	9	4 1 1	50.25	
1.7252	10	2 0 4	53.04	
1.7218M	12	4 0 2	53.15	
1.7218M		4 2 0	53.15	
1.6427M	12	3 2 3	55.93	
1.6427M		3 3 2	55.93	
1.5738	6	2 2 4	58.61	
1.5106M	11	4 1 3	61.32	
1.5106M		5 0 1	61.32	
1.4058M	10	5 1 2	66.45	
1.4058M		5 2 1	66.45	
1.3629	6	4 0 4	68.83	
1.3607	4	4 4 0	68.96	
1.3231	2	3 0 5	71.21	
1.3213	2	4 3 3	71.32	
1.2847	5	4 2 4	73.68	
1.2829	3	6 0 0	73.80	
1.2519	4	1 1 6	75.95	
1.2489M	7	6 1 1	76.16	
1.2489M		5 3 2	76.16	
1.2175M	4	6 0 2	78.50	
1.2175M		6 2 0	78.50	
1.1900	2	4 1 5	80.68	
1.1877	1	5 4 1	80.87	
1.1376	2	3 1 6	85.24	
1.1352M	3	6 3 1	85.46	
1.1352M		6 1 3	85.46	
1.1120	1L	4 4 4	87.69	
1.0917	1L	1 0 7	89.76	
1.0886M	3	7 1 0	90.08	
1.0886M		7 0 1	90.08	
1.0675	2	6 4 0	92.37	
1.0501	2	2 1 7	94.37	
1.0476M	5	7 2 1	94.66	
1.0476M		5 5 2	94.66	
1.0296	2	6 2 4	96.86	
1.0113	1L	7 0 3	99.23	

Ammonium Titanium Fluoride, $(\text{NH}_4)_2\text{TiF}_6$

CAS registry no.
16962-40-7

Sample

The sample was donated by Harshaw Chemical Co., Cleveland, OH.

Color

Colorless

Structure

Hexagonal, $P\bar{3}m1$ (164), $Z = 1$, isostructural with K_2GeF_6 [Cox and Sharpe, 1953].

Lattice constants of this sample

$a = 5.9456(4) \text{ \AA}$

$c = 4.8053(5)$

$c/a = 0.8082$

Volume

$147.11 \text{ \AA}^3$

Density

(calculated) 2.235 g/cm^3

Figure of merit

$F_{24} = 98.9 (0.010, 25)$

Reference intensity

$I/I_{\text{corundum}} = 1.38(7)$

Reference

Cox, B. and Sharpe, A. G. (1953). J. Chem. Soc. 1953, 1783.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
$d(\text{Å})$	I	hkl	$2\theta(^\circ)$	
5.151	100	1 0 0	17.20	
4.808	25	0 0 1	18.44	
3.513	80	1 0 1	25.33	
2.972	14	1 1 0	30.04	
2.574	4	2 0 0	34.82	
2.527	6	1 1 1	35.49	
2.402	7	0 0 2	37.41	
2.269	85	2 0 1	39.69	
2.1767	7	1 0 2	41.45	
1.9451	2	2 1 0	46.66	
1.8686	10	1 1 2	48.69	
1.8035	14	2 1 1	50.57	
1.7569	20	2 0 2	52.01	
1.7165	1	3 0 0	53.33	
1.6167	4	3 0 1	56.91	
1.5293	2	1 0 3	60.49	
1.5130	9	2 1 2	61.21	
1.4863	10	2 2 0	62.43	
1.4284	3	3 1 0	65.27	
1.4197	4	2 2 1	65.72	
1.4102	5	1 1 3	66.22	
1.3964	3	3 0 2	66.96	
1.3690	5	3 1 1	68.48	
1.3601	5	2 0 3	68.99	

p-Anisic Acid, C₈H₈O₃

Synonym

1. 4-Methoxybenzoic Acid

CAS registry no.

100-09-4

Sample

The sample was NBS Standard Reference Material 142, a microanalytical standard for the methoxyl radical.

Color

Colorless

Structure

Monoclinic, P2₁/a (14), Z = 4 [Rokade et al., 1942]. A qualitative structure was done by Richards [1956].

Lattice constants of this sample

a = 16.899(4) Å
b = 10.971(3)
c = 3.976(2)
β = 95.41(2)°

a/b = 1.5403
c/b = 0.3624

Volume

733.86 Å³

Density

(calculated) 1.377 g/cm³

Figure of merit

F₃₀ = 40.4(0.016,48)

Additional pattern

1. PDF card 11-765 [Institute of Physics, University College, Cardiff, Wales, 1961]

References

Richards, J. P. G. (1956). Res. Appl. Ind. 9, S44.
Rokade, R. K., Khabaria, R. H., and Kapadia, M. R. (1942). J. Univ. Bombay 11, 37.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C					
Internal standard Si, a = 5.43088 Å					
d(Å)	I	hkl			2θ(°)
9.18	6	1	1	0	9.63
8.40	5	2	0	0	10.52
6.69	9	2	1	0	13.23
5.48	95	0	2	0	16.15
5.221	25	1	2	0	16.97
4.598	3	2	2	0	19.29
3.924M	14	4	1	0	22.64
3.924M		3	2	0	22.64
3.720M	12	0	1	1	23.90
3.720M		-2	0	1	23.90
3.569M	13	1	3	0	24.93
3.569M		1	1	1	24.93
3.523	100	-2	1	1	25.26
3.340	6	4	2	0	26.67
3.298	5	2	1	1	27.01
3.213M	3	5	1	0	27.74
3.213M		0	2	1	27.74
3.077	30	-2	2	1	29.00
2.983	2	3	1	1	29.93
2.921	3	-4	1	1	30.58
2.880	2	-3	2	1	31.03
2.869	2	5	2	0	31.15
2.802	3	6	0	0	31.91
2.754	3	4	0	1	32.48
2.745	2	0	4	0	32.60
2.707	1	1	4	0	33.06
2.673	5	4	1	1	33.50
2.626	2	1	3	1	34.12
2.606M	3	2	4	0	34.38
2.606M		-2	3	1	34.38
2.512	3	2	3	1	35.72
2.496	3	6	2	0	35.95
2.474	4	5	3	0	36.28
2.465M	5	3	4	0	36.42
2.465M		4	2	1	36.42
2.416	1	-5	2	1	37.19
2.398	1	-6	0	1	37.47
2.392	1	5	1	1	37.57
2.365	1	3	3	1	38.01
2.348	3	7	1	0	38.31
2.297	2	4	4	0	39.19
2.250	2	-1	4	1	40.05
2.240	1	5	2	1	40.22
2.227	1	6	3	0	40.48
2.207	1	-2	4	1	40.86

p-Anisic Acid, $C_8H_8O_3$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
2.200M	1	7 2 0	40.99
2.200M		4 3 1	40.99
2.196	2	-6 2 1	41.06
2.176	1	1 5 0	41.47
2.169	3	-5 3 1	41.61
2.149M	4	6 1 1	42.01
2.149M		2 4 1	42.01
2.125M	2	5 4 0	42.51
2.125M		2 5 0	42.51
2.102	3	8 0 0	43.00
2.065	3	8 1 0	43.81
2.043	2	3 5 0	44.31
2.037M	2	5 3 1	44.45
2.037M		6 2 1	44.45
2.008	1	7 3 0	45.11
1.999	1	-7 2 1	45.32
1.969	1	-2 0 2	46.05
1.964	2	8 2 0	46.19
1.961	2	6 4 0	46.25
1.945M	3	4 5 0	46.67
1.945M		4 4 1	46.67

Antimonic Acid, $\text{H}_{14}\text{Sb}_{14}\text{O}_{21}(\text{OH})_{42}$

Sample

The sample was prepared by dissolving Sb metal in warm HCl and HNO_3 (both concentrated). With constant stirring, the solution was poured into water at 80 °C. Stirring was continued overnight at 70 °C. The crystals formed were filtered off and dried in air at room temperature. The water content varies somewhat but causes little change in the x-ray pattern [Abe and Ito, 1968; Stewart et al., 1972]. The material is often referred to as " $\text{Sb}_2\text{O}_5 \cdot 4\text{H}_2\text{O}$."

Color

Colorless

Structure

Cubic, $\text{Fd}3\text{m}$ (227), $Z = 1$. The structure was determined by Baetsle and Huys [1968]. Dehydrated phases have powder patterns similar to that of $\text{H}_{14}\text{Sb}_{14}\text{O}_{21}(\text{OH})_{42}$ in d-spacings and cell size, but are quite distinct in relative intensities [Stewart et al., 1972].

Lattice constant of this sample

$a = 10.3553(7) \text{ \AA}$

Volume

$1110.4 \text{ \AA}^3$

Density

(calculated) 4.140 g/cm^3

Figure of merit

$F_{20} = 54.9(0.012, 31)$

Reference intensity

$I/I_{\text{corundum}} = 3.49(10)$

Additional patterns

1. PDF card 20-111, labeled $\text{Sb}_2\text{O}_5 \cdot 4\text{H}_2\text{O}$ [Baetsle and Huys, 1968]
2. PDF card 21-803, labeled $\text{Sb}_2\text{O}_5 \cdot 4\text{H}_2\text{O}$ [Abe and Ito, 1968]
3. Natta and Baccaredda [1936]
4. Hanawalt et al. [1938]

References

- Abe, M. and Ito, T. (1968). Bull. Chem. Soc. Jap. 41, 333.
 Baetsle, L. H. and Huys, D. (1968). J. Inorg. Nucl. Chem. 30, 639.
 Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Ed. 10, 457.
 Natta, G. and Baccaredda, M. (1936). Gazz. Chim. Ital. 66, 308.
 Stewart, D. J., Knop, O., Ayasse, C., and Woodhams, F. W. D. (1972). Can. J. Chem. 50, 690.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
$d(\text{Å})$	I	hkl	$2\theta(^\circ)$	
5.993	100	1 1 1	14.77	
3.123	70	3 1 1	28.56	
2.989	90	2 2 2	29.87	
2.590	20	4 0 0	34.61	
2.376	10	3 3 1	37.83	
2.115	3	4 2 2	42.72	
1.9928	17	5 1 1	45.48	
1.8302	35	4 4 0	49.78	
1.7503	20	5 3 1	52.22	
1.5789	10	5 3 3	58.40	
1.5607	25	6 2 2	59.15	
1.4950	6	4 4 4	62.03	
1.4506	12	7 1 1	64.15	
1.3479	10	7 3 1	69.71	
1.1877	7	6 6 2	80.87	
1.1576	6	8 4 0	83.43	
1.1366	4	9 1 1	85.33	
1.0856	2	9 3 1	90.40	
1.0569	3	8 4 4	93.58	
1.0408	4	7 7 1	95.48	

Antimony Oxide, Sb₆O₁₃

CAS registry no.
12165-47-8

Sample

The sample was prepared by heating antimonous acid (H₁₄Sb₁₄O₂₁(OH)₄₂) at 780 °C for 30 minutes.

Color

Colorless

Structure

Cubic, Fd3m (227), Z = 4. Defect pyrochlore structure [Stewart et al., 1972]. This material has been reported as Sb₂O₅ [Swanson et al., 1960] and as Sb₃O₆(OH) (stibiconite) [Dihlström and Westgren, 1937]. The composition of the mineral stibiconite is uncertain [Vitaliano and Mason, 1952].

Lattice constant of this sample

a = 10.3060(2) Å

Volume

1094.6 Å³

Density

(calculated) 5.696 g/cm³

Figure of merit

F₃₀ = 71.6(0.010,40)

Additional patterns

1. PDF card 11-690 [Swanson et al., 1960] called Sb₂O₅
2. PDF card 16-938 [Dihlström and Westgren, 1937] called Sb₃O₆(OH)
3. PDF card 21-51 [Ito et al., Tokyo Institute of Technology, 1966].
4. Natta and Baccaredda [1936]
5. Stewart et al. [1972]

References

- Dihlström, K. and Westgren, A. (1937). Z. Anorg. Allg. Chem. 235, 153.
Natta, G. and Baccaredda, M. (1936). Gazz. Chim. Ital. 66, 308.
Stewart, D. J., Krop, O., Ayasse, C., and Woodhams, F. W. D. (1972). Can. J. Chem. 50, 690.
Swanson, H. E., Cook, M. I., Evans, E. H., and de Groot, J. H. (1960). Nat. Bur. Stand. U.S. Circ. 539, 10, 10.
Vitaliano, C. J. and Mason, B. (1952). Amer. Mineral. 52, 982.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard W, a = 3.16524 Å				
c(Å)	I	hkl	2θ(°)	
5.949	25	1 1 1	14.88	
3.108	20	3 1 1	28.70	
2.976	100	2 2 2	30.00	
2.577	30	4 0 0	34.78	
2.365	4	3 3 1	38.02	
2.1022	2	4 2 2	42.99	
1.9833	6	5 1 1	45.71	
1.8213	25	4 4 0	50.04	
1.7416	8	5 3 1	52.50	
1.6293	1L	6 2 0	56.43	
1.5716	2	5 3 3	58.70	
1.5535	30	6 2 2	59.45	
1.4876	9	4 4 4	62.37	
1.4432	8	5 5 1	64.52	
1.3416	6	7 3 1	70.08	
1.2885	4	8 0 0	73.43	
1.2592	1	7 3 3	75.43	
1.1902	1	7 5 1	80.66	
1.1822	8	6 6 2	81.32	
1.1522	8	8 4 0	83.91	
1.1313	4	9 1 1	85.83	
1.0805	3	9 3 1	90.94	
1.0519	6	8 4 4	94.16	
1.0360	3	7 7 1	96.07	
.9965	2	9 5 1	101.25	
.9918	4	10 2 2	101.92	
.9611	3	9 5 3	106.54	
.9291	1	11 1 1	112.00	
.9109	2	8 8 0	115.49	
.9004	6	9 7 1	117.63	
.8742	6	9 7 3	123.57	
.8710	8	10 6 2	124.35	
.8588	6	12 0 0	127.51	
.8500	3	11 5 1	129.98	
.8277	2	11 5 3	137.06	
.8148	5	12 4 0	141.96	
.8072	2	9 9 1	145.20	

Antimony Tin, SbSn

CAS registry no.
28980-49-6

Sample

The sample was made by melting Sn and Sb together above 1100 °C in air. It was then quenched by pouring out onto a slab, and ground. This phase has a homogeneity range of 45-55 percent Sb [Hägg and Hybinette, 1935].

Color

Black

Structure

Hexagonal, $R\bar{3}m$, $Z = 3$. This phase was studied by Hägg and Hybinette [1935]. These authors reported a rhombohedral cell with both a and c doubled. No lines were found in the authors' pattern or the NBS pattern that required the larger cell. This phase has been considered cubic [Ôsawa, 1929] and [Bowen and Jones, 1931].

Lattice constants of this sample

$a = 4.3255(3)$ Å
 $c = 5.3465(8)$

$c/a = 1.2360$

Volume
86.6 Å³

Density

(calculated) 13.827 g/cm³

Figure of merit

$F_{14} = 67.4(0.013, 16)$

Reference intensity

$I/I_{\text{corundum}} = 2.34(12)$

Polymorphism

SbSn transforms to a different phase at 320 °C [Iwasê et al., 1931].

Additional patterns

1. PDF card 1-830 [Hanawalt et al., 1938]
2. Hägg and Hybinette [1935]

References

- Bowen, E. G. and Jones, W. M. (1931). Phil. Mag. 12, 441.
Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
Hägg, G. and Hybinette, A. G. (1935). Phil. Mag. Series 7, 20, 913.
Iwasê, K., Aoki, N., and Ôsawa, A. (1931). Sc. Rep. Tôhoku Imp. Univ. 20, 353.
Ôsawa, A. (1929). Nature 74, 14.

CuK α_1 $\lambda = 1.540598$ Å; temp. 25 ± 1 °C			
Internal standard W, $a = 3.16524$ Å			
$d(\text{Å})$	I	hkl	$2\theta(^{\circ})$
3.067	100	1 0 1	29.09
2.176	30	0 1 2	41.46
2.162	30	1 1 0	41.74
1.7837	8	0 0 3	51.17
1.7679	14	0 2 1	51.66
1.5343	8	2 0 2	60.27
1.3757	8	1 1 3	68.10
1.3683	10	2 1 1	68.52
1.2589	3	1 0 4	75.45
1.2512	7	1 2 2	76.00
1.0878	1	0 2 4	90.16
1.0814	1	2 2 0	90.85
1.0225	2	3 0 3	97.76
1.0200	3	1 3 1	98.09

Barium Bromide Hydrate, BaBr₂·2H₂O

CAS registry no.
7791-28-8

Sample

The sample was made by slow evaporation of an aqueous solution at room temperature.

Color

Colorless

Optical data

Biaxial (-), $N_\alpha = 1.720$, $N_\beta = 1.732$,
 $N_\gamma = 1.748$. 2V is large.

Structure

Monoclinic, C2/c (15), Z = 4. The structure was determined by Bang [1961].

Lattice constants of this sample

$a = 10.442(2) \text{ \AA}$
 $b = 7.207(1)$
 $c = 8.384(2)$
 $\beta = 113.61(2)^\circ$

$a/b = 1.4489$

$c/b = 1.1633$

Volume

$578.1 \text{ \AA}^3$

Density

(calculated) 3.828 g/cm^3

Figures of merit

$F_{30} = 82.2(0.011, 32)$

$M_{20} = 43.8$

Reference intensity

$I/I_{\text{corundum}} = 4.3(2)$

Reference

Bang, E. (1961). Mat. Fys. Medd. Dan. Vid. Selsk. 33, no. 4, 1.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
5.77	25	1 1 0	15.35	
5.264	20	-1 1 1	16.83	
4.790	2	2 0 0	18.51	
4.158	6	1 1 1	21.35	
3.842M	30	0 0 2	23.13	
3.842M		-2 0 2	23.13	
3.623	10	-1 1 2	24.55	
3.606	16	0 2 0	24.67	
3.265	7	0 2 1	27.29	
3.134	1	-3 1 1	28.46	
2.937	25	-2 2 1	30.41	
2.916	45	3 1 0	30.63	
2.890M	100	1 1 2	30.92	
2.890M		-3 1 2	30.92	
2.629M	11	0 2 2	34.08	
2.629M		-2 2 2	34.08	
2.582	11	-1 1 3	34.72	
2.539M	1	2 0 2	35.32	
2.539M		-4 0 2	35.32	
2.504	16	2 2 1	35.84	
2.446	3	3 1 1	36.71	
2.410	6	-3 1 3	37.28	
2.391	20	4 0 0	37.58	
2.329	3	1 3 0	38.62	
2.293	16	-1 3 1	39.26	
2.194	3	-2 2 3	41.11	
2.171	4	1 3 1	41.57	
2.155	2	1 1 3	41.89	
2.107	6	-4 2 1	42.89	
2.096	14	-2 0 4	43.13	
2.085	15	-1 3 2	43.36	
1.993	4	4 2 0	45.48	
1.981	3	-5 1 1	45.76	
1.977	3	-3 3 1	45.86	
1.970M	4	-1 1 4	46.03	
1.970M		-3 1 4	46.03	
1.911+	9	-4 2 3	47.53	
1.911+		1 3 2	47.53	
1.886	3	-5 1 3	48.22	
1.8125M	9	-1 3 3	50.30	
1.8125M		-2 2 4	50.30	
1.7896	1	4 2 1	50.99	
1.7641	2	3 3 1	51.78	
1.7407M	8	4 0 2	52.53	
1.7407M		-6 0 2	52.53	
1.7182	2	2 2 3	53.27	
1.7023M	9	1 1 4	53.81	
1.7023M		-5 1 4	53.81	
1.6858	5	2 4 0	54.38	
1.6579	1	5 1 1	55.37	

Barium Chlorate, Ba(ClO₃)₂

CAS registry no.
13477-00-4

Sample

The sample was prepared by heating
Ba(ClO₃)₂·H₂O at about 250 °C for 15 hours.

Color

Colorless

Structure

Orthorhombic. The crystal system aspect is
apparently F*** and Z is assumed to be 8. The
cell was determined from the Visser program
[1969].

Lattice constants of this sample

a = 11.782(3) Å
b = 13.264(3)
c = 7.727(2)

a/b = 0.8883
c/b = 0.5826

Volume

1207.5 Å³

Density

(calculated) 3.347 g/cm³ (assuming Z = 8)

Figure of merit

F₃₀ = 52.2(0.014,41)

Additional pattern

1. PDF card 1-530 [Hanawalt et al., 1938],
data appears to be for Ba(ClO₄)₂

References

Hanawalt, J. D., Rinn, H. W., and Frevel, L. K.
(1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
Visser, J. W. (1969). J. Appl. Crystallogr. 2,
89.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard Si, a = 5.43088 Å				
d(Å)	I	hkl	2θ(°)	
5.80	80	1 1 1	15.27	
4.401	8	2 2 0	20.16	
3.651	60	1 3 1	24.36	
3.385	95	3 1 1	26.31	
3.337	100	0 2 2	26.69	
3.318	45	0 4 0	26.85	
3.232	25	2 0 2	27.58	
2.945	20	4 0 0	30.33	
2.904	9	2 2 2	30.76	
2.889	7	2 4 0	30.93	
2.745	35	3 3 1	32.59	
2.473	20	1 1 3	36.30	
2.454	10	1 5 1	36.59	
2.314	30	2 4 2	38.88	
2.221	13	5 1 1	40.59	
2.210M	50	0 6 0	40.80	
2.210M		4 2 2	40.80	
2.188	14	1 3 3	41.22	
2.126	20	3 1 3	42.49	
2.114	25	3 5 1	42.73	
2.070	8	2 6 0	43.70	
2.007	3	5 3 1	45.14	
1.936	14	3 3 3	46.89	
1.919	12	0 6 2	47.34	
1.884	9	6 2 0	48.28	
1.8268	9	1 5 3	49.88	
1.8200	10	1 7 1	50.08	
1.7695	15	2 2 4	51.61	
1.7509	5	6 0 2	52.20	
1.7239	4	5 1 3	53.08	
1.7188	5	5 5 1	53.25	
1.6716	11	3 5 3	54.88	
1.6685	13	0 4 4	54.99	
1.6319	4	7 1 1	56.33	
1.6154	4	4 0 4	56.96	
1.6081	6	4 6 2	57.24	

Barium Iodide Hydrate, BaI₂·2H₂O

CAS registry no.
7787-33-9

Sample

The sample was made by slow evaporation of an aqueous solution of BaI₂ at about 60 °C.

Color

Strong yellowish brown

Structure

Monoclinic, I2/a (15), Z = 4, by analogy with the powder pattern for BaBr₂·2H₂O. The axial ratios confirmed those given by Groth [1906]. The equivalent C-centered cell is a = 11.090(2) Å, b = 7.634(1), c = 8.656(2), β = 112.98(2)°.

Lattice constants of this sample

a = 11.089(2) Å
b = 7.634(1)
c = 8.656(2)
β = 112.96(2)°

a/b = 1.4526
c/b = 1.1339

Volume

674.7 Å³

Density

(calculated) 4.206 g/cm³

Figure of merit

F₃₀ = 68.5(0.012,38)

Reference intensity

I/I_{corundum} = 3.4(2)

Reference

Groth, P. (1906). Chemische Krystallographie
I (Engelmann, Leipzig, Germany), p. 242.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard W, a = 3.16524 Å				
d(Å)	I	hkl	2θ(°)	
6.12	9	1 1 0	14.47	
5.518	16	0 1 1	16.05	
5.110	3	2 0 0	17.34	
4.386	3	-2 1 1	20.23	
3.980M	25	0 0 2	22.32	
3.980M		-2 0 2	22.32	
3.819	30	0 2 0	23.27	
3.765	19	-1 1 2	23.61	
3.443	2	-1 2 1	25.86	
3.108M	60	3 1 0	28.70	

d(Å)	I	hkl	2θ(°)
3.108M		1 2 1	28.70
3.058	30	2 2 0	29.18
3.031M	100	1 1 2	29.45
3.031M		-3 1 2	29.45
2.756M	14	0 2 2	32.46
2.756M		-2 2 2	32.46
2.676+	10	-2 1 3	33.46
2.676+		2 0 2	33.46
2.655	13	-3 2 1	33.73
2.599	2	-4 1 1	34.48
2.554	15	4 0 0	35.11
2.468	4	1 3 0	36.37
2.423	12	0 3 1	37.07
2.299	2	-2 3 1	39.16
2.239	3	3 2 1	40.25
2.193+	12	-1 3 2	41.13
2.193+		2 2 2	41.13
2.164	11	-2 0 4	41.71
2.122	5	4 2 0	42.56
2.110	2	4 1 1	42.82
2.039+	3	-1 1 4	44.39
2.039+		-3 1 4	44.39
2.016M	9	1 3 2	44.93
2.016M		-3 3 2	44.93
2.005	6	1 2 3	45.18
1.9735	3	5 1 0	45.95
1.9092	3	0 4 0	47.59
1.9017	5	-5 2 1	47.79
1.8828	7	-2 2 4	48.30
1.8722	2	-4 3 1	48.59
1.8466M	10	4 0 2	49.31
1.8466M		-6 0 2	49.31
1.8068	3	-5 2 3	50.47
1.7972	3	1 4 1	50.76
1.7876	6	2 4 0	51.05
1.7760M	10	1 1 4	51.41
1.7760M		-5 1 4	51.41
1.7657+	5	0 2 4	51.73
1.7657+		-4 2 4	51.73
1.7364	1	-6 1 3	52.67
1.7011	1	6 0 0	53.85
1.6953	4	-3 4 1	54.05
1.6621+	14	4 2 2	55.22
1.6621+		-6 2 2	55.22
1.6505M	4	2 0 4	55.64
1.6505M		-6 0 4	55.64
1.6389M	1	5 2 1	56.07
1.6389M		-4 1 5	56.07
1.6156	1L	3 2 3	56.95
1.5921	5	5 3 0	57.87
1.5706	1	3 4 1	58.74
1.5531+	6	6 2 0	59.47
1.5531+		2 4 2	59.47
1.5500+	5	5 1 2	59.60
1.5500+		-7 1 2	59.60

Barium Phosphate, Ba₂P₂O₇, (high form)

CAS registry no.
13466-21-2

Sample

The sample was prepared by heating BaCO₃ with H₄P₂O₇ at 950 °C for 1 hour, grinding and heating a few minutes at 1100 °C. Chemical analysis of material dried at 100 °C gave BaO as 68.25 percent and P₂O₅ as 31.12 percent. The theoretical composition for Ba₂P₂O₇ gives BaO = 68.4 percent and P₂O₅ = 31.6 percent.

Color

Colorless

Optical data

Uniaxial (+), N_o = 1.595, N_e = 1.600

Structure

Hexagonal. The crystal system aspect is apparently P6₃** and Z is assumed to be 3. The cell was determined from the Visser [1969] program. Ranby et al. [1955] proposed an orthorhombic cell for this phase. It did not fit our data. Mehdi et al. [1977] proposed a different orthorhombic cell which did not properly fit his data or ours.

Lattice constants of this sample

a = 9.4175(8) Å
c = 7.081(1)

c/a = 0.7519

Volume

543.85 Å³

Density

(calculated) 4.109 g/cm³, assuming Z = 3.

Figures of merit

F₃₀ = 54.8(0.012,46)
M₂₀ = 58.7

Reference intensity

I/I_{corundum} = 4.3(2)

Polymorphism

Below about 725 °C, Ba₂P₂O₇ forms an α phase, isostructural with α-Ca₂P₂O₇ [McCauley and Hummel, 1968; Ranby et al., 1955].

Additional patterns

1. PDF card 9-45 [Langguth et al., 1956]
2. Mehdi et al. [1977]
3. Ranby et al. [1955]

References

- Langguth, R. P., Osterheld, R. K., and Karl-Kroupa, E. (1956). J. Phys. Chem. 60, 1335.
McCauley, R. A. and Hummel, F. A. (1968). Trans. Brit. Ceram. Soc. 67, 624.
Mehdi, S., Hussain, M. R., and Rao, B. R. (1977). Indian J. Chem. 15A, 820.
Ranby, P. W., Mash, D. H., and Henderson, S. T. (1955). Brit. J. Appl. Phys. 6, Sup 4, S18.
Visser, J. W. (1969). J. Appl. Crystallogr. 2, 89.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard Si, a = 5.43088 Å				
d(Å)	I	hkl	2θ(°)	
5.346	4	1 0 1	16.57	
4.709	1	1 1 0	18.83	
3.923	100	1 1 1	22.65	
3.539	25	0 0 2	25.14	
3.084	7	2 1 0	28.93	
2.833	35	1 1 2	31.56	
2.719	25	3 0 0	32.91	
2.355	16	2 2 0	38.18	
2.325	20	2 1 2	38.69	
2.262	10	3 1 0	39.82	
2.235	13	2 2 1	40.33	
2.156M	18	3 0 2	41.87	
2.156M		3 1 1	41.87	
2.110	17	1 1 3	42.82	
2.043	40	2 0 3	44.30	
2.038	40	4 0 0	44.42	
1.960M	7	2 2 2	46.28	
1.960M		4 0 1	46.28	
1.907	3	3 1 2	47.66	
1.8711	4	3 2 0	48.62	
1.8092	7	3 2 1	50.40	
1.7705	5	0 0 4	51.58	
1.7258	3	4 1 1	53.02	
1.6671	2	2 2 3	55.04	
1.6338	4	3 1 3	56.26	
1.5896M	5	4 1 2	57.97	
1.5896M		5 0 1	57.97	
1.5694	1	3 3 0	58.79	
1.5415	5	4 2 0	59.96	
1.5327	3	3 3 1	60.34	
1.5055	1L	4 2 1	61.55	
1.4829	4	3 0 4	62.59	
1.4653	3	5 1 0	63.43	
1.4340	4	5 1 1	64.98	
1.4210	3	4 1 3	65.65	
1.4130	3	4 2 2	66.07	
1.3938	1	3 1 4	67.10	
1.3540	3	5 1 2	69.35	
1.3413M	1	5 0 3	70.10	
1.3413M		4 3 0	70.10	
1.3380	2	2 0 5	70.30	
1.3170	2	4 3 1	71.59	
1.2903	1	4 2 3	73.31	
1.2856	2	3 2 4	73.62	

Barium Thiosulfate Hydrate, $\text{BaS}_2\text{O}_3 \cdot \text{H}_2\text{O}$

CAS registry no.
13466-25-6

Sample

The sample was made by adding a concentrated solution of $\text{Na}_2\text{S}_2\text{O}_3$ to a similar hot solution of BaCl_2 . The solution was then cooled. This produced small plates. When the pure material was dissolved in water and the liquid allowed to evaporate at room temperature, small needles were formed. The intensities were determined on a mixture of the crystal types.

Color

Colorless

Structure

Orthorhombic, Pnca (60), $Z = 8$. The structure of $\text{BaS}_2\text{O}_3 \cdot \text{H}_2\text{O}$ was studied by Nardelli and Fava [1962].

Lattice constants of this sample

$a = 7.386(1) \text{ \AA}$
 $b = 20.050(3)$
 $c = 7.191(2)$

$a/b = 0.3684$
 $c/b = 0.3587$

Volume

$1064.9 \text{ \AA}^3$

Density

(calculated) 3.337 g/cm^3

Figure of merit

$F_{30} = 51.4 (0.015, 40)$

Additional pattern

1. PDF card 1-42 [Hanawalt et al., 1938]

References

Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
Nardelli, M. and Fava, G. (1962). Acta Crystallogr. 15, 477.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
10.04	9	0 2 0	8.80	
5.018	60	0 4 0	17.66	
4.900	7	0 3 1	18.09	
4.588	35	1 2 1	19.33	
4.085	5	1 3 1	21.74	
3.694	50	2 0 0	24.07	
3.630	50	2 1 0	24.50	
3.594M	100	0 0 2	24.75	
3.594M		1 4 1	24.75	
3.501	10	0 5 1	25.42	

$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
3.468	20	2 2 0	25.67
3.386	25	0 2 2	26.30
3.342	75	0 6 0	26.65
3.244	11	2 1 1	27.47
3.235M	16	1 0 2	27.55
3.235M		2 3 0	27.55
3.190	25	1 1 2	27.95
3.162	5	1 5 1	28.20
3.077	8	1 2 2	29.00
2.973	16	2 4 0	30.03
2.922	25	0 4 2	30.57
2.748	10	2 4 1	32.56
2.715M	12	1 4 2	32.97
2.715M		2 5 0	32.97
2.661	11	0 7 1	33.65
2.577	35	2 0 2	34.78
2.554	30	2 1 2	35.11
2.508	30	0 8 0	35.78
2.479	55	2 6 0	36.21
2.449	55	0 6 2	36.66
2.382	6	0 1 3	37.73
2.343	6	2 6 1	38.39
2.314	16	3 1 1	38.88
2.292	20	2 4 2	39.28
2.263	45	2 7 0	39.80
2.254M	55	1 8 1	39.96
2.254M		0 3 3	39.96
2.223	30	1 2 3	40.55
2.199	18	3 3 1	41.01
2.166	14	2 5 2	41.66
2.146	10	1 7 2	42.08
2.128	2	0 9 1	42.45
2.112	7	3 4 1	42.78
2.076	15	1 4 3	43.56
2.057M	10	0 5 3	43.99
2.057M		0 8 2	43.99
2.040	35	2 6 2	44.38
2.006	9	0 10 0	45.17
1.916	11	2 7 2	47.40
1.869	12	1 10 1	48.69
1.847	5	4 0 0	49.31
1.839M	8	4 1 0	49.54
1.839M		0 7 3	49.54
1.8071	7	3 7 1	50.46
1.7619	12	2 10 0	51.85
1.7512	11	0 10 2	52.19
1.7401	8	1 1 4	52.55
1.7355	7	3 6 2	52.70
1.6863	6	1 8 3	54.36
1.6707	12	0 12 0	54.91
1.6341M	18	2 11 0	56.25
1.6341M		4 5 1	56.25
1.6159M	10	2 0 4	56.94
1.6159M		4 6 0	56.94
1.6102	12	3 9 1	57.16

Barium Thiosulfate Hydrate, $\text{BaS}_2\text{O}_3 \cdot \text{H}_2\text{O}$ (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.6010	10	1 5 4	57.52
1.5824M	18	0 6 4	58.26
1.5824M		2 10 2	58.26
1.5514	7	4 7 0	59.54
1.5220	18	2 12 0	60.81
1.5146	17	0 12 2	61.14
1.4876	8	2 11 2	62.37
1.4229M	14	1 11 3	65.55
1.4229M		2 13 0	65.55

o-Bromobenzoic Acid, $C_7H_5BrO_2$

Synonym

1. 2-Bromobenzoic Acid

CAS registry no.

88-65-3

Sample

The sample was NBS Standard Reference Material 2142.

Color

Colorless

Structure

Monoclinic, $A2/a$ (15), $Z = 8$. The structure was determined by Ferguson and Sim [1962].

Lattice constants of this sample

$a = 23.016(4) \text{ \AA}$
 $b = 4.085(1)$
 $c = 14.871(3)$
 $\beta = 96.62(2)^\circ$

$a/b = 5.6343$
 $c/b = 3.6404$

Volume

$1389.0 \text{ \AA}^3$

Density

(calculated) 1.923 g/cm^3

Figure of merit

$F_{30} = 68.6(0.012, 37)$

Reference intensity

$I/I_{\text{corundum}} = 0.80(2)$

Additional pattern

1. PDF card 13-794 [Ferguson and Sim, 1959]

Reference

Ferguson, G. and Sim, G. A. (1962). Acta Crystallogr. 15, 346.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
11.41	13	2 0 0	7.74	
7.41	5	0 0 2	11.94	
6.56	55	-2 0 2	13.49	
5.905	80	2 0 2	14.99	
5.716	25	4 0 0	15.49	
4.805	4	-4 0 2	18.45	
4.290	40	4 0 2	20.69	
3.940	30	0 1 1	22.55	
3.862	60	1 1 1	23.01	
3.811	40	6 0 0	23.32	
3.756	25	-2 1 1	23.67	
3.691M	90	0 0 4	24.09	
3.691M		2 1 1	24.09	
3.641	45	-2 0 4	24.43	
3.558	65	-6 0 2	25.01	
3.454	19	3 1 1	25.77	
3.401	18	2 0 4	26.18	
3.288	100	-4 1 1	27.10	
3.237	14	6 0 2	27.53	
3.198	30	4 1 1	27.88	
3.144M	5	0 1 3	28.36	
3.144M		-1 1 3	28.36	
3.088M	17	-2 1 3	28.89	
3.088M		1 1 3	28.89	
3.033	6	-5 1 1	29.43	
2.982	20	-3 1 3	29.94	
2.974	17	2 1 3	30.02	
2.950	12	4 0 4	30.27	
2.856	40	8 0 0	31.29	
2.781	19	-6 1 1	32.16	
2.696	11	6 1 1	33.20	
2.673	25	4 1 3	33.50	
2.569	14	8 0 2	34.90	
2.511	30	6 0 4	35.73	
2.465	19	-2 0 6	36.42	
2.388	25	-2 1 5	37.63	
2.352M	9	2 0 6	38.23	
2.352M		-7 1 3	38.23	
2.347M	7	-8 1 1	38.32	
2.347M		-3 1 5	38.32	
2.300	6	2 1 5	39.13	
2.280	19	8 1 1	39.49	
2.259	4	-10 0 2	39.87	
2.226	4	3 1 5	40.49	
2.186M	8	7 1 3	41.26	
2.186M		-6 0 6	41.26	
2.139	9	4 1 5	42.22	
2.115	6	10 0 2	42.71	
2.106	6	9 1 1	42.91	
2.052M	8	-9 1 3	44.10	

o-Bromobenzoic Acid, $C_7H_5BrO_2$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
2.052M		-10 0 4	44.10
1.981	5	-8 0 6	45.76
1.967M	18	-1 2 2	46.12
1.967M		6 0 6	46.12
1.950M	11	-2 2 2	46.54
1.950M		10 1 1	46.54
1.9264	10	-8 1 5	47.14
1.9237	9	4 2 0	47.21
1.9047	4	12 0 0	47.71
1.8835	11	-1 1 7	48.28
1.8751	9	0 1 7	48.51
1.8568	5	-2 0 8	49.02
1.8497M	5	7 1 5	49.22
1.8497M		10 0 4	49.22
1.8385	5	-4 1 7	49.54
1.8282M	7	-5 2 2	49.84
1.8282M		-9 1 5	49.84
1.8200M	8	-4 0 8	50.08
1.8200M		2 1 7	50.08
1.8005M	6	6 2 0	50.66
1.8005M		-5 1 7	50.66
1.7955M	10	12 0 2	50.81
1.7955M		-11 1 3	50.81
1.7880+	12	10 1 3	51.04
1.7880+		5 2 2	51.04
1.7670	8	8 0 6	51.69
1.7559M	6	8 1 5	52.04
1.7559M		-6 1 7	52.04

Cadmium Borate, CdB_4O_7

Sample

The sample was prepared by heating CdO and B_2O_3 in a 1:2 molar mixture at 900 °C for 5 hours.

Color

Colorless

Structure

Orthorhombic, Pbca (61), $Z = 8$, [Hand and Krogh-Moe, 1962]. The structure of CdB_4O_7 has been determined by Ihara and Krogh-Moe [1966].

Lattice constants of this sample

$a = 8.704(1) \text{ \AA}$
 $b = 14.176(2)$
 $c = 8.229(1)$

$a/b = 0.6140$
 $c/b = 0.5805$

Volume

$1015.4 \text{ \AA}^3$

Density

(calculated) 3.501 g/cm^3

Figure of merit

$F_{30} = 50.8(0.013, 46)$

Reference intensity

$I/I_{\text{corundum}} = 0.82(6)$

Additional pattern

1. PDF card 14-162 [Hand and Krogh-Moe, 1962]

References

Hand, D. and Krogh-Moe, J. (1962). J. Amer. Ceram. Soc. 45, 197.
 Ihara, M. and Krogh-Moe, J. (1966). Acta Crystallogr. 20, 132.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}; \text{ temp. } 25 \pm 1 \text{ } ^\circ\text{C}$ Internal standard W, $a = 3.16524 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	
7.10	12	0 2 0	12.45	
5.504	70	1 1 1	16.09	
5.371	100	0 2 1	16.49	
4.574	11	1 2 1	19.39	
4.164	50	2 1 0	21.32	
4.113	30	0 0 2	21.59	
3.717M	80	1 0 2	23.92	
3.717M		2 1 1	23.92	
3.599	60	1 1 2	24.72	
3.555	45	0 2 2	25.03	

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
3.544	45	0 4 0	25.11
3.202	95	2 3 0	27.84
2.984	30	2 3 1	29.92
2.924M	70	2 1 2	30.55
2.924M		1 3 2	30.55
2.749	20	2 4 0	32.54
2.687M	19	3 1 1	33.32
2.687M		0 4 2	33.32
2.559	85	0 2 3	35.04
2.527	2	2 3 2	35.49
2.456	13	1 2 3	36.56
2.372	25	3 0 2	37.90
2.338	5	3 1 2	38.47
2.290M	40	2 1 3	39.32
2.290M		1 3 3	39.32
2.282	60	2 5 1	39.45
2.272	20	0 6 1	39.63
2.255	8	1 5 2	39.95
2.197	10	1 6 1	41.04
2.176	25	4 0 0	41.46
2.120	4	3 3 2	42.61
2.082M	6	2 3 3	43.42
2.082M		4 1 1	43.42
2.059M	16	2 5 2	43.94
2.059M		0 0 4	43.94
2.016	30	4 2 1	44.93
1.994	5	1 6 2	45.46
1.970M	55	3 4 2	46.03
1.970M		3 5 1	46.03
1.918M	14	3 2 3	47.35
1.918M		1 7 1	47.35
1.8540M	20	4 4 0	49.10
1.8540M		2 6 2	49.10
1.8438M	20	2 1 4	49.39
1.8438M		1 3 4	49.39
1.8361M	30	3 3 3	49.61
1.8361M		2 7 0	49.61
1.7958	30	2 5 3	50.80
1.7916	20	2 7 1	50.93
1.7785M	30	0 4 4	51.33
1.7785M		1 7 2	51.33
1.7718	20	0 8 0	51.54
1.7531	4	1 6 3	52.13
1.7435	2	1 4 4	52.44
1.7306	25	2 3 4	52.86
1.6988	4	1 8 1	53.93
1.6912M	8	5 1 1	54.19
1.6912M		4 4 2	54.19
1.6744	8	3 6 2	54.78
1.6577	18	4 2 3	55.38
1.6274M	3	3 7 1	56.50
1.6274M		0 8 2	56.50
1.6066	7	1 1 5	57.30
1.6023	9	5 3 1	57.47
1.6002M	11	4 6 0	57.55

Cadmium Borate, CdB_4O_7 - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.6002M		1 8 2	57.55
1.5926M	7	5 1 2	57.85
1.5926M		4 5 2	57.85
1.5765	5	1 2 5	58.50
1.5706	10	4 6 1	58.74
1.5552	5	2 5 4	59.38
1.5512	4	0 6 4	59.55
1.5399	4	3 7 2	60.03
1.5302M	6	2 1 5	60.45
1.5302M		1 3 5	60.45
1.5234M	11	3 6 3	60.75
1.5234M		1 9 1	60.75
1.5188	13	5 3 2	60.95
1.4943	5	4 0 4	62.06
1.4876M	7	0 8 3	62.37
1.4876M		3 8 1	62.37
1.4624M	11	4 2 4	63.57
1.4624M		5 1 3	63.57
1.4601M	15	5 4 2	63.68
1.4601M		5 5 1	63.68
1.4428	3	6 1 0	64.54
1.4208M	6	6 2 0	65.66
1.4208M		3 7 3	65.66
1.4176	7	0 10 0	65.83
1.4032M	10	5 3 3	66.59
1.4032M		3 2 5	66.59
1.3958	4	5 5 2	66.99
1.3869	5	6 3 0	67.48
1.3818M	7	4 6 3	67.76
1.3818M		5 6 1	67.76
1.3777	10	4 4 4	67.99
1.3740	9	4 8 0	68.20
1.3699M	14	3 3 5	68.43
1.3699M		2 7 4	68.43

Cadmium Phosphate, $\text{Cd}_2\text{P}_2\text{O}_7$

Sample

The sample was prepared by heating a 1:1 molar mixture of CdCO_3 and $(\text{NH}_4)_2\text{HPO}_4$ at 700 °C for several days, followed by heating at 800 °C for 2 hours.

Color

Colorless

Structure

Triclinic, $\text{P}\bar{1}$ (2), $Z = 2$. The structure of $\text{Cd}_2\text{P}_2\text{O}_7$ was determined by Calvo and Au [1969].

Lattice constants of this sample

$a = 6.602(2) \text{ \AA}$
 $b = 6.778(2)$
 $c = 6.631(2)$
 $\alpha = 95.79(2)^\circ$
 $\beta = 97.68(2)$
 $\gamma = 65.00(2)$

$a/b = 0.9740$
 $c/b = 0.9783$

Volume

$266.2 \text{ \AA}^3$

Density

(calculated) 4.975 g/cm^3

Figure of merit

$F_{30} = 51.3(0.012, 47)$

Reference intensity

$I/I_{\text{corundum}} = 1.58(3)$

Additional patterns

1. PDF card 17-635 [Brown and Hummel, 1964]
2. Ropp et al. [1961]

References

- Brown, J. J. and Hummel, F. A. (1964). J. Electrochem. Soc. 111, 1052.
 Calvo, C. and Au, P. K. L. (1969). Can. J. Chem. 47, 3409.
 Ropp, R. C., Mooney, R. W., and Hoffman, C. W. W. (1961). Anal. Chem. 33, 1687.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$	
6.15	12	0 1 0	14.40	
5.965	8	1 0 0	14.84	
4.645	11	-1 0 1	19.09	
4.586	18	-1 -1 1	19.34	
4.377	15	0 1 1	20.27	

d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$
4.207	40	1 0 1	21.10
3.987	14	1 1 1	22.28
3.353	30	1 2 0	26.56
3.279	25	0 0 2	27.17
3.262	35	2 1 0	27.32
3.194	35	-1 1 1	27.91
3.126	35	-1 -2 1	28.53
3.094	100	-2 -1 1	28.83
3.068	85	0 2 0	29.08
2.974	45	2 0 0	30.02
2.956	80	0 -1 2	30.21
2.835M	90	0 1 2	31.53
2.835M		0 -2 1	31.53
2.794	7	2 2 0	32.01
2.729	8	0 2 1	32.79
2.708	5	-2 -2 1	33.05
2.671	10	1 1 2	33.53
2.613	20	2 0 1	34.29
2.489	14	-2 -1 2	36.05
2.449	30	2 2 1	36.66
2.325M	30	-2 1 0	38.69
2.325M		-2 0 2	38.69
2.298	14	0 -2 2	39.17
2.240	4	1 3 0	40.23
2.218	20	1 -2 1	40.65
2.187M	6	0 2 2	41.25
2.187M		0 0 3	41.25
2.170M	30	3 1 0	41.58
2.170M		2 1 2	41.58
2.142	16	-1 -1 3	42.16
2.124	30	-1 0 3	42.52
2.114	17	3 2 0	42.73
2.101M	12	2 0 2	43.01
2.101M		-3 -2 1	43.01
1.993	6	2 2 2	45.47
1.974	4	2 3 1	45.93
1.9526	14	-2 1 2	46.47
1.9470	16	1 1 3	46.61
1.9256M	18	0 3 1	47.16
1.9256M		-3 -1 2	47.16
1.8961	4	-1 1 3	47.94
1.8526	18	-2 -2 3	49.14
1.7756M	14	0 -3 2	51.42
1.7756M		1 3 2	51.42
1.7264M	14	-1 3 0	53.00
1.7264M		-3 -3 2	53.00
1.7117M	14	2 1 3	53.49
1.7117M		3 1 2	53.49
1.6982	8	0 3 2	53.95

Cadmium Phosphate, $\text{Cd}_3(\text{PO}_4)_2$

Sample

The sample was prepared by heating a 3:2 molar mixture of CdO and $(\text{NH}_4)_2\text{HPO}_4$ at 800 °C overnight.

Color

Colorless

Structure

Monoclinic, $P2_1/c$ (14), $Z = 4$. The cell was found by use of the Visser program [1969] and by comparison with $\beta\text{-Zn}_3(\text{PO}_4)_2$ and $\text{Mn}_3(\text{PO}_4)_2$. The space group was assigned by consideration of the absences in the powder pattern.

Lattice constants of this sample

$a = 8.662(2) \text{ \AA}$
 $b = 10.333(3)$
 $c = 8.307(2)$
 $\beta = 114.48(2)^\circ$

$a/b = 0.8383$
 $c/b = 0.8039$

Volume

$676.7 \text{ \AA}^3$

Density

(calculated) 5.174 g/cm^3 (assuming $Z = 4$)

Figures of merit

$F_{30} = 72.4(0.011, 39)$
 $M_{20} = 35.5$

Reference intensity

$I/I_{\text{corundum}} = 1.16(6)$

Additional pattern

1. PDF card 14-443 [Ropp et al., 1962]

References

Ropp, R. C., Mooney, R. W., and Hoffman, C. W. W. (1961). *Anal. Chem.* **33**, 1687.
 Visser, J. W. (1969). *J. Appl. Crystallogr.* **2**, 89.

$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
3.562	30	-2 0 2	24.98
3.429	80	1 2 1	25.96
3.367	90	-2 1 2	26.45
3.305	100	-2 2 1	26.96
3.230	18	-1 2 2	27.59
3.154	60	1 3 0	28.27
3.101	25	-1 3 1	28.77
3.051	30	0 2 2	29.25
2.962	85	1 0 2	30.15
2.933	16	-2 2 2	30.45
2.898	35	2 1 1	30.83
2.848	18	1 1 2	31.38
2.775	3	-3 1 1	32.23
2.753	3	1 3 1	32.50
2.663M	45	-1 1 3	33.63
2.663M		-3 1 2	33.63
2.650	50	-1 3 2	33.80
2.627	30	3 0 0	34.10
2.594	45	2 3 0	34.55
2.546M	8	0 3 2	35.22
2.546M		3 1 0	35.22
2.516	18	-3 2 1	35.65
2.477	4	-2 3 2	36.24
2.449	25	0 1 3	36.66
2.431M	25	-1 2 3	36.94
2.431M		-3 2 2	36.94
2.385	2	-2 2 3	37.69
2.317	4	-3 1 3	38.84
2.270	4	2 3 1	39.67
2.265	3	0 2 3	39.76
2.251	1L	1 4 1	40.02
2.213	3	-2 4 1	40.74
2.152M	12	-1 3 3	41.95
2.152M		-4 0 2	41.95
2.106	12	-4 1 2	42.91
2.099	10	2 2 2	43.05
2.092M	12	-2 4 2	43.20
2.092M		-4 1 1	43.20
2.073	3	-2 0 4	43.63
2.034M	16	0 3 3	44.51
2.034M		3 2 1	44.51
1.994	15	0 5 1	45.45
1.987	16	-4 2 2	45.63
1.971M	25	-4 1 3	46.00
1.971M		4 0 0	46.00
1.936M	17	4 1 0	46.90
1.936M		-3 1 4	46.90
1.923M	13	-3 4 1	47.23
1.923M		-2 2 4	47.23
1.910	25	2 3 2	47.57
1.885M	15	1 5 1	48.24
1.885M		-1 4 3	48.24
1.8632M	8	-2 5 1	48.84
1.8632M		-2 4 3	48.84
1.8424M	12	3 4 0	49.43
1.8424M		4 2 0	49.43

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
7.87	2	1 0 0	11.23	
6.27	4	1 1 0	14.12	
6.10	6	0 1 1	14.50	
4.318	50	1 2 0	20.55	
4.263	25	0 2 1	20.82	
4.195	14	1 1 1	21.16	
3.969	25	-2 1 1	22.38	
3.942	9	2 0 0	22.54	
3.844	30	-1 1 2	23.12	
3.778	19	0 0 2	23.53	

Calcium Aluminum Iron Oxide (Brownmillerite), $\text{Ca}_4\text{Al}_2\text{Fe}_2\text{O}_{10}$

CAS registry no.
12068-35-8

Sample

The sample was prepared by the Portland Cement Association. This phase is a component of portland cement and is known as C_4AF .

Color

Deep brown

Structure

Orthorhombic, Pcmn (62), $Z = 2$. The structure was determined by Bertaut et al. [1959]. $\text{Ca}_4\text{Al}_2\text{Fe}_2\text{O}_{10}$ is isostructural and forms a series of solid solutions with $\text{Ca}_2\text{Fe}_2\text{O}_5$ [Bertaut et al., 1959].

Lattice constants of this sample

$a = 5.5672(9) \text{ \AA}$
 $b = 14.521(2)$
 $c = 5.349(1)$

$a/b = 0.3834$
 $c/b = 0.3684$

Volume $\text{\AA}^3$
432.4 $\text{\AA}^3$

Density

(calculated) 3.732 g/cm^3

Figure of merit

$F_{30} = 30.9(0.011, 85)$

Reference intensity

$I/I_{\text{corundum}} = 1.32(10)$

Additional patterns

1. PDF card 11-124 [Midgley, 1957]
2. Bertaut et al. [1959]
3. Hansen et al. [1928]

References

- Bertaut, E. F., Blum, P., and Sagnieres, A. (1959). *Acta Crystallogr.* **12**, 149.
Hansen, W. C. and Brownmiller, S. T. (1928). *Amer. J. Sci.* **15**, 224.
Midgley, H. G. (1957). *Mag. Concr. Res.* March 1957.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	
7.25	45	0 2 0	12.20	
5.193	4	1 1 0	17.06	
3.859	4	1 0 1	23.03	
3.654	16	1 3 0	24.34	
3.629	6	0 4 0	24.51	
3.406	4	1 2 1	26.14	
2.784	25	2 0 0	32.12	
2.673	35	0 0 2	33.50	
2.644	100	1 4 1	33.88	
2.576	17	1 5 0	34.80	
2.472	2	2 0 1	36.32	
2.434	4	2 1 1	36.90	
2.210	8	2 4 0	40.79	
2.155	9	0 4 2	41.89	
2.051	35	1 6 1	44.13	
1.9283	35	2 0 2	47.09	
1.8813	3	2 5 1	48.34	
1.8632	9	2 2 2	48.84	
1.8149	45	0 8 0	50.23	
1.7952	3	0 6 2	50.82	
1.7327	7	3 3 0	52.79	
1.5784	14	3 4 1	58.42	
1.5638	4	3 5 0	59.02	
1.5380	14	1 4 3	60.11	
1.5202	7	2 8 0	60.89	
1.5013+	8	2 0 3	61.74	
1.5013+		3 5 1	61.74	
1.4524	4	0 10 0	64.06	
1.4197	5	3 6 1	65.72	
1.3901	6	1 6 3	67.30	
1.3669	3	4 2 0	68.60	
1.3588	5	1 10 1	69.07	
1.3373	4	0 0 4	70.34	
1.3215	12	2 8 2	71.31	

Calcium Boride, CaB₆

CAS registry no.
12007-99-7

Sample

The sample was obtained from Alfa Products
(Ventron), Danvers, MA.

Color

Dark olive brown

Structure

Cubic, Pm3m (221), Z = 1. The structure was
determined by von Stackelberg and Neumann [1932].

Lattice constant of this sample

$a = 4.1535(1) \text{ \AA}$

Volume

$71.653 \text{ \AA}^3$

Density

(calculated) 2.432 g/cm^3

Figure of merit

$F_{21} = 74.2(0.012, 24)$

Reference intensity

$I/I_{\text{corundum}} = 1.92(10)$

Additional pattern

1. PDF card 3-654 [von Stackelberg and
Neumann, 1932].

Reference

von Stackelberg, M. and Neumann, F. (1932).
Z. Phys. Chem. 19, 314.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
4.151	6	1 0 0	21.39	
2.938	100	1 1 0	30.40	
2.398	45	1 1 1	37.48	
2.077	25	2 0 0	43.53	
1.8572	30	2 1 0	49.01	
1.6953	5	2 1 1	54.05	
1.4686	3	2 2 0	63.27	
1.3847	19	3 0 0	67.60	
1.3137	13	3 1 0	71.80	
1.2523	4	3 1 1	75.92	
1.1522	1	3 2 0	83.91	
1.1100	4	3 2 1	87.89	
1.0384	2	4 0 0	95.77	
1.0073	3	4 1 0	99.76	
.9791	4	4 1 1	103.76	
.9528	1L	3 3 1	107.89	
.9287	2	4 2 0	112.09	
.9064	4	4 2 1	116.38	
.8856	2	3 3 2	120.87	
.8146	4	5 1 0	142.05	
.7993	3	5 1 1	149.04	

m-Chlorobenzoic Acid, C₇H₅ClO₂

Synonym
1. 3-Chlorobenzoic Acid

CAS registry no.
535-80-8

Sample
The sample was NBS Standard Reference Material
2144.

Color
Colorless

Structure
Monoclinic, P2₁/a (14), Z = 4. The structure
was determined by Gougoutas and Lessinger [1975].

Lattice constants of this sample
a = 11.110(2) Å
b = 16.015(3)
c = 3.8455(8)
β = 95.00(2)°
a/b = 0.6937
c/b = 0.2401

Volume
681.6 Å³

Density
(calculated) 1.526 g/cm³

Figure of merit
F₃₀ = 53.8(0.011,52)

Reference intensity
I/I_{corundum} = 0.63(7)

Additional patterns
1. PDF card 24-1594 [Li, Polytechnic Institute
of Brooklyn, Brooklyn, NY.]
2. PDF card 20-1577 [Dept. of Physics, Univ.
Coll., Cardiff, Wales.]

Reference
Gougoutas, J. Z. and Lessinger, L. (1975). J.
Solid State Chem. 12, 51.

d(Å)	I	hkl	2θ(°)
4.005	18	0 4 0	22.18
3.842	45	2 3 0	23.13
3.622	45	-1 1 1	24.56
3.591	16	3 1 0	24.77
3.453	35	0 2 1	25.78
3.376	100	-1 2 1	26.38
3.351	14	3 2 0	26.58
3.287	75	-2 0 1	27.11
3.243	95	2 4 0	27.48
3.220	90	-2 1 1	27.68
3.114	9	0 3 1	28.64
3.077	12	1 5 0	29.00
3.041	5	-2 2 1	29.35
2.799	10	-2 3 1	31.95
2.771M	10	2 5 0	32.28
2.771M		0 4 1	32.28
2.727M	8	4 1 0	32.82
2.727M		-1 4 1	32.82
2.670	12	0 6 0	33.54
2.629	4	-3 2 1	34.07
2.615	4	4 2 0	34.26
2.516	8	3 1 1	35.65
2.456M	20	4 3 0	36.56
2.456M		0 5 1	36.56
2.416M	25	2 4 1	37.18
2.416M		3 5 0	37.18
2.342	2	-4 0 1	38.41
2.301	4	3 3 1	39.11
2.276	5	4 4 0	39.57
2.240	1	1 7 0	40.23
2.201	2	2 5 1	40.98
2.192	3	5 1 0	41.14
2.168	8	-1 6 1	41.63
2.162	9	3 6 0	41.74
2.156	8	4 0 1	41.87
2.134	7	5 2 0	42.31
2.113	3	2 7 0	42.75
2.044	4	5 3 0	44.27
2.002M	13	2 6 1	45.25
2.002M		0 8 0	45.25
1.971	2	1 8 0	46.02
1.9376	2	5 4 0	46.85
1.9214	2	4 6 0	47.27
1.8983	3	4 4 1	47.88
1.8788	6	-2 7 1	48.41
1.8326	2	6 1 0	49.71
1.7635+	9	2 0 2	51.80
1.7635+		4 7 0	51.80
1.7597ri	9	3 8 0	51.92
1.7597M		-4 6 1	51.92
1.7432	7	6 3 0	52.45
1.6930M	7	-5 5 1	54.13
1.6930M		2 9 0	54.13
1.6747+	4	-3 3 2	54.77
1.6747+		2 3 2	54.77

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C			
Internal standard Si, a = 5.43088 Å			
d(Å)	I	hkl	2θ(°)
9.07	6	1 1 0	9.74
6.48	85	1 2 0	13.65
5.538	7	2 0 0	15.99
4.808	55	1 3 0	18.44
4.549	16	2 2 0	19.50

Chromium Chloride Hydrate, $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$

Synonym

1. Dichlorotetraaquo chromium(III) chloride dihydrate, $[\text{Cr}(\text{H}_2\text{O})_4\text{Cl}_2]\text{Cl} \cdot 2\text{H}_2\text{O}$

CAS registry no.

10060-12-5

Sample

The sample was obtained from City Chemical Corp., New York, NY.

Color

Very dark yellowish green

Structure

Monoclinic, C2/c (15), $Z = 4$. The structure was determined by Dance and Freeman [1965]. Morosin [1966] had also independently determined the same structure. The synonym name and formula are those obtained as the results of crystal structure analysis.

Lattice constants of this sample

$a = 12.048(2) \text{ \AA}$
 $b = 6.8352(8)$
 $c = 11.643(1)$
 $\beta = 94.14(1)^\circ$

$a/b = 1.7626$

$c/b = 1.7032$

Volume

$956.27 \text{ \AA}^3$

Density

(calculated) 1.851 g/cm^3

Figure of merit

$F_{30} = 65.2(0.012, 39)$

Polymorphism

A hexagonal modification has been reported by Andress and Carpenter [1934].

Additional pattern

1. PDF card 12-446 [Shrier, Rutgers University]

References

- Andress, K. R. and Carpenter, C. (1934) Z. Kristallogr. Kristallgeometrie Kristallphys. Kristallchem. 87A, 446.
 Dance, I. G. and Freeman, H. C. (1965). J. Inorg. Chem. 4, 1555.
 Morosin, B. (1966). Acta Crystallogr. 21, 280.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
6.00	45	2 0 0	14.74	
5.805	30	0 0 2	15.25	
5.362	100	-1 1 1	16.52	
5.211	65	1 1 1	17.00	
4.333	30	-2 0 2	20.48	
4.079	18	1 1 2	21.77	
4.032	16	2 0 2	22.03	
3.456	30	3 1 0	25.76	
3.371	55	-3 1 1	26.42	
3.297	25	-1 1 3	27.02	
3.278	30	0 2 1	27.18	
3.054	40	-3 1 2	29.22	
3.006	6	4 0 0	29.70	
2.946	40	0 2 2	30.32	
2.902M	17	-2 2 1	30.79	
2.902M		0 0 4	30.79	
2.893	14	3 1 2	30.88	
2.853	13	2 2 1	31.33	
2.749	19	-4 0 2	32.54	
2.690	30	-2 0 4	33.28	
2.682	25	-2 2 2	33.38	
2.644	6	-1 1 4	33.87	
2.605	25	2 2 2	34.40	
2.592	30	4 0 2	34.58	
2.571	40	1 1 4	34.87	
2.543	9	2 0 4	35.27	
2.500	8	3 1 3	35.89	
2.398	8	-2 2 3	37.48	
2.294	2	-3 1 4	39.24	
2.268	3	5 1 0	39.71	
2.256M	6	4 2 0	39.93	
2.256M		-5 1 1	39.93	
2.238M	6	-4 2 1	40.27	
2.238M		1 3 0	40.27	
2.212	5	0 2 4	40.76	
2.204	5	-1 3 1	40.91	
2.194M	9	4 2 1	41.11	
2.194M		1 3 1	41.11	
2.189	8	-1 1 5	41.20	
2.167	8	-4 0 4	41.64	
2.138	15	1 1 5	42.24	
2.115	3	-2 2 4	42.71	
2.080	2	1 3 2	43.47	
2.066M	7	4 2 2	43.78	
2.066M		5 1 2	43.78	
2.040	20	2 2 4	44.36	
2.017M	10	-5 1 3	44.91	
2.017M		4 0 4	44.91	
1.997	4	-4 2 3	45.37	
1.980	3	3 3 0	45.78	

Chromium Chloride Hydrate, $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.949	8	-1 3 3	46.56
1.940	25	3 3 1	46.79
1.936M	30	-6 0 2	46.88
1.936M		0 0 6	46.88
1.9268	17	1 3 3	47.13
1.9047	6	4 2 3	47.71
1.9006	4	5 1 3	47.82
1.8824	8	-2 0 6	48.31
1.8748	7	3 1 5	48.52
1.8600	9	-1 1 6	48.93
1.8547	8	3 3 2	49.08
1.8299	2	-4 2 4	49.79
1.8048	10	2 0 6	50.53
1.7893	7	-3 3 3	51.00
1.7379M	5	3 3 3	52.62
1.7379M		4 2 4	52.62
1.7349	6	-3 1 6	52.72
1.7282	14	6 2 0	52.94
1.7084M	2	0 4 0	53.60
1.7084M		-6 0 4	53.60
1.6907	6	0 4 1	54.21
1.6843+	5	0 2 6	54.43
1.6843+		-6 2 2	54.43
1.6643+	5	-7 1 1	55.14
1.6643+		-4 2 5	55.14
1.6454	3	3 1 6	55.83
1.6394	4	0 4 2	56.05
1.6266	7	5 3 1	56.53
1.6235M	7	2 4 1	56.65
1.6235M		-1 3 5	56.65
1.6130	4	-1 1 7	57.05
1.5962M	3	2 2 6	57.71
1.5962M		6 0 4	57.71
1.5836	3	1 1 7	58.21
1.5762M	8	4 2 5	58.51
1.5762M		4 0 6	58.51
1.5711	12	7 1 2	58.72
1.5336M	3	-3 1 7	60.30
1.5336M		-3 3 5	60.30
1.5243M	6	-5 1 6	60.71
1.5243M		-2 4 3	60.71
1.5103	4	-4 2 6	61.33

Chromium Sulfate, $\text{Cr}_2(\text{SO}_4)_3$

CAS registry no.
10101-53-8

Sample

The sample was prepared by heating $\text{NH}_4\text{Cr}(\text{SO}_4)_2$ at 500 °C for 3 hours. The sample contained a very small percent of Cr_2O_3 .

Color

Reddish brown

Structure

Hexagonal, $R\bar{3}$ (148), $Z = 6$. [Kokkoros, 1965].

Lattice constants of this sample

$a = 8.132(1) \text{ \AA}$
 $c = 21.943(6)$

$c/a = 2.6983$

Volume

$1256.8 \text{ \AA}^3$

Density

(calculated) 3.109 g/cm^3

Figure of merit

$F_{30} = 40.0(0.014, 55)$

Reference intensity

$I/I_{\text{corundum}} = 1.55(5)$

Additional patterns

1. PDF card 18-393 [Kokkoros, 1965]
2. PDF card 18-394 [Wattelle-Marion and Thiard, 1965]

References

- Kokkoros, P. A. (1965). Mineral. Petrogr. Mitt. 10, 45.
Wattelle-Marion, G. and Thiard, R. (1965). C. R. Acad. Sci. 261, 4105.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{Å})$	I	hkl	$2\theta(^\circ)$	
5.93	50	0 1 2	14.93	
4.327	45	1 0 4	20.51	
4.070	15	1 1 0	21.82	
3.658	25	0 0 6	24.31	
3.555	100	1 1 3	25.03	
2.965	35	0 2 4	30.11	
2.721	40	1 1 6	32.89	
2.644	11	2 1 1	33.88	
2.395	9	2 1 4	37.52	
2.347	11	3 0 0	38.31	
2.274	3	1 2 5	39.59	
2.235	8	3 0 3	40.32	
2.163	9	2 0 8	41.72	
2.092	6	1 1 9	43.20	
2.029	3	2 1 7	44.61	
1.975	4	3 0 6	45.91	
1.923	5	3 1 2	47.23	
1.909	5	1 2 8	47.59	
1.8627	6	0 2 10	48.85	
1.8395	4	1 3 4	49.51	
1.7771	9	2 2 6	51.37	
1.7390	3	0 4 2	52.58	
1.6931	11	2 1 10	54.12	
1.6573	4	1 3 7	55.39	
1.6114	2	3 2 1	57.11	
1.5981	3	2 3 2	57.63	
1.5903	3	3 1 8	57.94	
1.5613	2	2 2 9	59.12	
1.5504	6	3 2 4	59.58	
1.5366	6	4 1 0	60.17	
1.5167	3	2 3 5	61.04	
1.4818	3	0 4 8	62.64	
1.4586	10	1 3 10	63.75	
1.4425	4	3 0 12	64.55	

Copper Lead Hydroxide Sulfate, Linarite, $\text{CuPb}(\text{OH})_2(\text{SO}_4)$

Sample

The hand separated sample is from U.S. National Museum (NMNH R8105) from Mammoth Mine, Pinal Co., AZ.

Major impurities

Approximately 10% PbSO_4 was present in this mineral as a second phase and was ignored.

Color

Deep blue

Structure

Monoclinic, $P2_1/m$ (11), $Z = 2$. The structure was determined by Bachmann and Zeeman [1961]. Araki [1962] re-examined his earlier work and confirmed the above structure.

Lattice constants of this sample

$a = 9.6913(9)\text{\AA}$
 $b = 5.6503(6)$
 $c = 4.6873(5)$
 $\beta = 102.66(1)^\circ$

$a/b = 1.7152$

$c/b = 0.8296$

Volume

$250.43\text{\AA}^3$

Density

(calculated) 5.315 g/cm^3

Figure of merit

$F_{30} = 76.6(0.011, 35)$

Additional patterns

1. PDF card 4-598 [Berry, 1951]

References

Araki, T. (1962). Mineral. J. Japan. 3, 282.
 Bachmann, H.-G. and Zeeman, J. (1961). Acta Crystallogr. 14, 747.
 Berry, L. G. (1951). Amer. Mineral. 36, 512.

CuK α_1 $\lambda = 1.540598\text{\AA}$; temp. $25 \pm 1^\circ\text{C}$				
Internal standard W, $a = 3.16524\text{\AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
9.46	11	1 0 0	9.34	
4.849	40	1 1 0	18.28	
4.731	3	2 0 0	18.74	
4.521	60	-1 0 1	19.62	
3.805	9	1 0 1	23.36	
3.717	3	-2 0 1	23.92	
3.625	30	2 1 0	24.54	
3.556	55	0 1 1	25.02	
3.151M	100	1 1 1	28.30	
3.151M		3 0 0	28.30	
3.106	40	-2 1 1	28.72	
2.978	19	2 0 1	29.98	
2.912	2	-3 0 1	30.68	
2.826	17	0 2 0	31.64	
2.754	6	3 1 0	32.49	
2.707	30	1 2 0	33.06	
2.587	25	-3 1 1	34.64	
2.424	8	2 2 0	37.05	
2.405	17	0 2 1	37.36	
2.365M	5	3 0 1	38.02	
2.365M		4 0 0	38.02	
2.344	4	-1 0 2	38.37	
2.317	20	-4 0 1	38.83	
2.267	20	1 2 1	39.72	
2.261	20	-2 0 2	39.83	
2.250	9	-2 2 1	40.05	
2.181M	17	3 1 1	41.36	
2.181M		4 1 0	41.36	
2.164	19	-1 1 2	41.71	
2.145	6	-4 1 1	42.09	
2.119M	20	0 1 2	42.63	
2.119M		1 0 2	42.63	
2.104	12	3 2 0	42.95	
2.081	4	-3 0 2	43.45	
2.049	8	2 2 1	44.16	
2.027	20	-3 2 1	44.67	
1.9021M	2	2 0 2	47.78	
1.9021M		-5 0 1	47.78	
1.8469	5	1 3 0	49.30	
1.8295	12	4 1 1	49.80	
1.8128M	20	3 2 1	50.29	
1.8128M		4 2 0	50.29	
1.8018M	17	2 1 2	50.62	
1.8018M		-5 1 1	50.62	
1.7932	14	5 1 0	50.88	
1.7769	7	0 2 2	51.38	
1.7660M	9	-4 1 2	51.72	
1.7660M		-2 2 2	51.72	
1.7497	5	2 3 0	52.24	
1.7416	8	0 3 1	52.50	

Copper Lead Hydroxide Sulfate, Linarite, $\text{CuPb}(\text{OH})_2(\text{SO}_4)$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.6883	5	1 3 1	54.29
1.6803	8	-2 3 1	54.57
1.6752	8	-3 2 2	54.75
1.6456	4	-5 0 2	55.82
1.6264	5	5 0 1	56.54
1.6130	5	3 1 2	57.05
1.5804M	8	-3 3 1	58.34
1.5804M		-5 1 2	58.34
1.5765M	13	-5 2 1	58.50
1.5765M		6 0 0	58.50
1.5718	9	5 2 0	58.69
1.5595	2	-1 0 3	59.20
1.5542M	2	-2 0 3	59.42
1.5542M		-4 2 2	59.42
1.5413	4	-6 1 1	59.97
1.5247	3	0 0 3	60.69
1.5079	4	-3 0 3	61.44
1.5033	4	-1 1 3	61.65
1.4891	6	4 0 2	62.30
1.4736M	4	3 3 1	63.03
1.4736M		4 3 0	63.03
1.4680	4	-1 3 2	63.30
1.4571	2	-3 1 3	63.83
1.4466	2	3 2 2	64.35
1.4216	2	-5 2 2	65.62
1.4124	6	0 4 0	66.10
1.4092+	6	5 2 1	66.27
1.4092+		-6 1 2	66.27
1.3878	2	-4 1 3	67.43
1.3802	3	-7 0 1	67.85
1.3763	4	6 2 0	68.07
1.3655M	3	2 0 3	68.68
1.3655M		-1 2 3	68.68
1.3576	2	6 1 1	69.14
1.3504	5	7 0 0	69.56
1.3490+	6	4 3 1	69.64
1.3490+		-1 4 1	69.64

p-Fluorobenzoic Acid, C₇H₅FO₂

CAS registry no.
456-22-4

Sample
The sample was NBS Standard Reference
Material 2143.

Color
Colorless

Structure
Monoclinic, P₂₁/n (14), Z = 4. The structure
was qualitatively determined by Toussaint [1952].

Lattice constants of this sample

a = 26.545(4) Å
b = 6.385(2)
c = 3.816(1)
β = 93.72(2)°

a/b = 4.1573
c/b = 0.5976

Volume
645.4 Å³

Density
(calculated) 1.442 g/cm³

Figure of merit
F₃₀ = 60.5(0.012,41)

Reference intensity
I/I_{corundum} = 1.10(4)

Additional pattern
1. PDF card 11-730 [Institute of Physics,
Cardiff, Wales]

Reference
Toussaint, J. (1952). Mem. Soc. Roy. Sci.
Liege, Collect. 8, 12, 1.

d(Å)	I	hkl	2θ(°)
3.580	75	-3 0 1	24.85
3.312	35	8 0 0	26.90
3.274M	70	0 1 1	27.22
3.274M		-1 1 1	27.22
3.226	65	1 1 1	27.63
3.194M	9	0 2 0	27.91
3.194M		-5 0 1	27.91
3.172	7	1 2 0	28.11
3.134	5	2 1 1	28.46
3.005+	4	3 2 0	29.71
3.005+		5 0 1	29.71
2.940	8	8 1 0	30.38
2.875	5	4 2 0	31.08
2.856	4	-5 1 1	31.29
2.715	4	5 1 1	32.97
2.672	5	9 1 0	33.51
2.649	2	10 0 0	33.81
2.586	5	6 2 0	34.66
2.560	3	6 1 1	35.02
2.446+	4	10 1 0	36.71
2.446+		0 2 1	36.71
2.423	5	-2 2 1	37.08
2.404	4	-9 0 1	37.37
2.395	4	-8 1 1	37.52
2.299	7	8 2 0	39.16
2.264M	7	8 1 1	39.79
2.264M		4 2 1	39.79
2.252M	5	11 1 0	40.00
2.252M		-9 1 1	40.00
2.208	1L	12 0 0	40.84
2.164	1	9 2 0	41.70
2.129	2	9 1 1	42.43
2.102M	4	6 2 1	43.00
2.102M		2 3 0	43.00
2.096M	3	-11 0 1	43.12
2.096M		-7 2 1	43.12
2.087	2	12 1 0	43.31
2.039	1	10 2 0	44.40
2.007	1L	-8 2 1	45.15
1.942	1	13 1 0	46.75
1.921M	1	11 2 0	47.28
1.921M		-9 2 1	47.28
1.892	1	14 0 0	48.06
1.847M	3	-2 3 1	49.31
1.847M		-13 0 1	49.31
1.844	3	9 2 1	49.38
1.825	6	0 1 2	49.93
1.815M	2	12 2 0	50.24
1.815M		14 1 0	50.24

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C			
Internal standard Ag, a = 4.08651 Å			
d(Å)	I	hkl	2θ(°)
13.26	85	2 0 0	6.66
6.62	20	4 0 0	13.37
6.21	6	1 1 0	14.26
5.76	20	2 1 0	15.38
5.178	100	3 1 0	17.11
4.600	30	4 1 0	19.28
4.412	2	6 0 0	20.11
4.077	3	5 1 0	21.78
3.805	5	-1 0 1	23.36
3.737	10	1 0 1	23.79

Gold Chloride, AuCl

CAS registry no.
10294-29-8

Sample

The sample was prepared by dissolving Au metal in aqua regia. The dark red intermediate crystals obtained were dried at 200 °C for one hour. The AuCl crystals were found to be metastable, disproportionately decomposing into Au metal and Au₂Cl₆ [Janssen et al., 1974]. Au₂Cl₆ was not detected in this sample; however, the Au metal present was used as the internal standard.

Color

Yellow

Structure

Tetragonal, I4₁/amd (141), Z = 8. The structure was studied by Janssen et al. [1974]. The structure had been reported to be orthorhombic by Capella and Schwab [1965].

Lattice constants of this sample

a = 6.7425(9) Å
c = 8.694(1)

c/a = 1.2894

Volume

395.2 Å³

Density

(calculated) 7.812 g/cm³

Figure of merit

F₁₆ = 81.8(0.010,20)

Additional patterns

1. PDF card 27-241 [Janssen et al., 1974]
2. Capella and Schwab [1965]

References

- Capella, L. and Schwab, C. (1965). C. R. Acad. Sci. 260, 4337.
Janssen, E. M. W., Folmer, J. C. W., and Wiegers, G. A. (1974). J. Less-Common Metals 38, 71.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C			
Internal standard Au, a = 4.0786 Å			
d(Å)	I	hkl	2θ(°)
5.327	100	1 0 1	16.63
3.371	4	2 0 0	26.42
3.213	5	1 1 2	27.74
2.849	60	2 1 1	31.37
2.664M	100	2 0 2	33.62
2.664M		1 0 3	33.62
2.384	25	2 2 0	37.71
2.173	18	0 0 4	41.52
2.089	30	2 1 3	43.27
1.8278M	14	3 2 1	49.85
1.8278M		2 0 4	49.85
1.7760	4	3 0 3	51.41
1.6846M	20	4 0 0	54.42
1.6846M		1 0 5	54.42
1.6063M	17	4 1 1	57.31
1.6063M		2 2 4	57.31
1.5711M	10	4 0 2	58.72
1.5711M		3 2 3	58.72
1.5061	4	2 1 5	61.52
1.4245M	20	4 2 2	65.47
1.4245M		4 1 3	65.47
1.3754	4	3 0 5	68.12

Iron Phosphate Hydrate (Vivianite), $\text{Fe}_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$

Sample

The sample was made by slow reaction of H_3PO_4 on FeSO_4 solution with some H_2SO_4 added. The flask was freed of air by flushing with natural gas and left with occasional shaking for two weeks.

Color

Grayish purplish blue

Structure

Monoclinic, I2/m (12), $Z = 2$ [Barth, 1937].

The structure was determined by Mori and Ito [1950]. It is isostructural with $\text{Fe}_3(\text{AsO}_4)_2 \cdot 8\text{H}_2\text{O}$ (parasymphesite) [Ritz et al., 1974].

Lattice constants of this sample

$a = 10.034(3) \text{ \AA}$

$b = 13.449(3)$

$c = 4.707(2)$

$\beta = 102.65(3)^\circ$

$a/b = 0.7461$

$c/b = 0.3500$

Volume

$619.7 \text{ \AA}^3$

Density

(calculated) 2.688 g/cm^3

Figure of merit

$F_{30} = 52.6 (0.015, 38)$

Polymorphism

A polymorph of $\text{Fe}_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$ occurs naturally, is triclinic and is called meta-vivianite [Ritz et al., 1974].

Additional pattern

1. PDF card 3-70 [Dow Chemical Co., Midland, MI]

References

Barth, T. F. W. (1937). *Amer. Mineral.* **22**, 325.

Mori, H. and Ito, T. (1950). *Acta Crystallogr.* **3**, 1.

Ritz, C., Essene, E. J., and Peacor, D. R. (1974). *Amer. Mineral.* **59**, 896.

$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
4.081	12	1 3 0	21.76
3.849	7	1 0 1	23.09
3.768	1L	-1 2 1	23.59
3.361	1	0 4 0	26.50
3.343	2	1 2 1	26.64
3.210	16	0 3 1	27.77
2.985	10	-3 0 1	29.91
2.960	8	2 1 1	30.17
2.770	4	2 4 0	32.29
2.728	9	-3 2 1	32.80
2.706	9	-1 4 1	33.08
2.637	6	3 3 0	33.97
2.593	4	1 5 0	34.57
2.530	8	1 4 1	35.45
2.514	3	2 3 1	35.68
2.448	1	4 0 0	36.68
2.421	6	3 0 1	37.11
2.321	7	0 5 1	38.77
2.296	1	0 0 2	39.20
2.279M	1	-2 0 2	39.51
2.279M		3 2 1	39.51
2.233	5	-3 4 1	40.35
2.194	5	-2 5 1	41.11
2.173	2	0 2 2	41.53
2.108M	1	1 1 2	42.86
2.108M		-4 3 1	42.86
2.075	4	3 5 0	43.59
2.039	1L	2 6 0	44.40
2.012M	2	2 5 1	45.03
2.012M		-1 6 1	45.03
1.964M	2	3 4 1	46.19
1.964M		-5 0 1	46.19
1.936M	2	5 1 0	46.89
1.936M		1 6 1	46.89
1.886M	2	1 7 0	48.22
1.886M		-5 2 1	48.22
1.816	2	4 3 1	50.20
1.793	1	-3 6 1	50.89
1.786	3	-4 5 1	51.10
1.772	2	0 7 1	51.52
1.6809	6	0 8 0	54.55
1.6599	2	-3 5 2	55.30
1.5974M	3	4 5 1	57.66
1.5974M		3 3 2	57.66
1.5834	4	5 5 0	58.22
1.5404	1	1 8 1	60.01

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}; \text{ temp. } 25 \pm 1^\circ \text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
7.93	13	1 1 0	11.15	
6.73	100	0 2 0	13.15	
4.900	12	2 0 0	18.09	
4.558	5	-1 0 1	19.46	
4.341	2	0 1 1	20.44	

Iron Sulfate, $\text{Fe}_2(\text{SO}_4)_3$

CAS registry no.
10028-22-5

Sample

The sample was made by heating $\text{Fe}_2(\text{SO}_4)_3 \cdot x\text{H}_2\text{O}$ at 200 °C for several hours, followed by heating at 500 °C in a sealed glass tube for 1 hour.

Color

Yellow white

Structure

Hexagonal, $R\bar{3}$ (148), $Z = 6$ [Kokkoros, 1965].

Lattice constants of this sample

$a = 8.236(1)\text{Å}$
 $c = 22.166(6)$

$c/a = 2.6914$

Volume

1302.1 Å^3

Density

(calculated) 3.060 g/cm^3

Figure of Merit

$F_{30} = 32.8(0.017, 53)$

Reference intensity

$I/I_{\text{corundum}} = 2.26(11)$

Additional pattern

1. PDF card 18-652 [Kokkoros, 1965]

Reference

Kokkoros, P. A. (1965). *Tschermak's Mineral. Petrogr. Mitt.* 10, 45.

CuK α_1 $\lambda = 1.540598\text{ Å}$; temp. $25 \pm 1\text{ °C}$				
Internal standard Si, $a = 5.43088\text{ Å}$				
$d(\text{Å})$	I	hkl	$2\theta(^{\circ})$	
6.01	50	0 1 2	14.72	
4.380	45	1 0 4	20.26	
4.124	13	1 1 0	21.53	
3.699	7	0 0 6	24.04	
3.599	100	1 1 3	24.72	
3.002	40	0 2 4	29.74	
2.751	45	1 1 6	32.52	
2.678	10	2 1 1	33.43	
2.581	1	0 1 8	34.73	
2.426	9	2 1 4	37.03	
2.378	12	3 0 0	37.80	
2.301	1	1 2 5	39.11	
2.263	7	3 0 3	39.80	
2.190	2	2 0 8	41.19	
2.114	7	1 1 9	42.74	
2.054	3	2 1 7	44.06	
1.999	4	3 0 6	45.33	
1.947	3	3 1 2	46.62	
1.931	4	1 2 8	47.01	
1.882	6	0 2 10	48.31	
1.863	6	1 3 4	48.85	
1.847	1	0 0 12	49.31	
1.799	11	2 2 6	50.71	
1.760	3	0 4 2	51.90	
1.7123	11	2 1 10	53.47	
1.6781	4	1 3 7	54.65	
1.6330	1	3 2 1	56.29	
1.6099	5	3 1 8	57.17	
1.5794	1	2 2 9	58.38	
1.5694	7	3 2 4	58.79	
1.5561	7	4 1 0	59.34	
1.5346	2	2 3 5	60.26	
1.5231	2	4 1 3	60.76	
1.4995	2	0 4 8	61.82	
1.4757	7	1 3 10	62.93	

Lead Bromide Hydroxide, PbBr(OH)

CAS registry no.
16651-91-5

Sample

The sample was prepared by making a saturated aqueous solution of fresh recrystallized PbBr₂. To this was added a 10% solution of NaOH. The precipitate was left for 80 hours in the liquid to promote growth of the crystals.

Color

Colorless

Structure

Orthorhombic, Pnam (62), Z = 4. The structure of PbBr(OH) was determined by Møller [1966]. PbBr(OH) is isostructural with SbBrS and PbCl(OH).

Lattice constants of this sample

a = 7.3850(8) Å
b = 10.013(1)
c = 4.0835(5)

a/b = 0.7375
c/b = 0.4078

Volume

301.96 Å³

Density

(calculated) 6.689 g/cm³

Figure of merit

F₃₀ = 78.7(0.012,31)

Reference Intensity

I/I_{corundum} = 5.9(3)

Additional patterns

1. PDF card 6-257 [Shell Petroleum Co., Ltd.]
2. Møller [1966]

Reference

Møller, C. K. (1966). Kgl. Dan. Vidensk. Sels. Mat. Fys. Medd. 35, 15.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard Si, a = 5.43088 Å				
d(Å)	I	hkl	2θ(°)	
5.93	9	1 1 0	14.93	
4.998	9	0 2 0	17.73	
4.139	55	1 2 0	21.45	
3.781	4	0 1 1	23.51	
3.693	10	2 0 0	24.08	
3.462	25	2 1 0	25.71	
3.363	100	1 1 1	26.48	
3.042	12	1 3 0	29.34	
2.970	20	2 2 0	30.06	
2.908	45	1 2 1	30.72	
2.737	4	2 0 1	32.69	
2.641	40	2 1 1	33.91	
2.584	50	0 3 1	34.69	
2.504	6	0 4 0	35.83	
2.475	10	2 3 0	36.26	
2.439	3	1 3 1	36.82	
2.403	18	2 2 1	37.40	
2.391	25	3 1 0	37.59	
2.371	20	1 4 0	37.92	
2.210	15	3 2 0	40.80	
2.118	19	2 3 1	42.65	
2.072	4	2 4 0	43.64	
2.064	6	3 1 1	43.83	
2.043	20	0 0 2	44.31	
1.982	2	3 3 0	45.75	
1.943	14	3 2 1	46.70	
1.933	8	1 5 0	46.97	
1.8901	2	0 2 2	48.10	
1.8483	4	2 4 1	49.26	
1.8313	12	1 2 2	49.75	
1.7975	8	0 5 1	50.75	
1.7860	6	2 0 2	51.10	
1.7824	5	3 3 1	51.21	
1.7597M	7	2 5 0	51.92	
1.7597M		2 1 2	51.92	
1.7475	13	1 5 1	52.31	
1.6959	4	1 3 2	54.03	
1.6823M	25	2 2 2	54.50	
1.6823M		4 0 1	54.50	
1.6688	3	0 6 0	54.98	
1.6151	19	4 3 0	56.97	
1.6120	20	3 4 1	57.09	
1.5944	2	4 2 1	57.78	
1.5824	4	0 4 2	58.26	
1.5757	5	2 3 2	58.53	
1.5531M	16	3 5 0	59.47	
1.5531M		3 1 2	59.47	
1.5476	14	1 4 2	59.70	
1.5211	7	2 6 0	60.85	
1.5123	1	1 6 1	61.24	

Lead Bromide Hydroxide, PbBr(OH) - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.4998	7	3 2 2	61.81
1.4610	4	5 1 0	63.64
1.4518	7	3 5 1	64.09
1.4251	7	2 6 1	65.44
1.4166	3	5 2 0	65.88
1.4036M	4	1 7 0	66.57
1.4036M		1 5 2	66.57
1.3967	3	4 4 1	66.94
1.3811	1	3 6 0	67.80
1.3692	1	4 0 2	68.47
1.3574M	2	4 5 0	69.15
1.3574M		4 1 2	69.15
1.3499	3	0 7 1	69.59
1.3385	5	5 2 1	70.27
1.3276	9	1 7 1	70.93
1.2929	4	1 2 3	73.14
1.2820	2	5 3 1	73.86
1.2669M	10	4 3 2	74.89
1.2669M		2 1 3	74.89
1.2603	6	0 3 3	75.35
1.2513	1	0 8 0	75.99
1.2426	1	1 3 3	76.62
1.2197	6	2 6 2	78.33
1.2146	5	5 4 1	78.72
1.1928	3	2 3 3	80.45
1.1885M	5	5 5 0	80.80
1.1885M		5 1 2	80.80

Lithium Calcium Aluminum Boron Hydroxy Silicate,
Liddicoatite, $\text{Ca}(\text{Li},\text{Al})_3\text{Al}_6\text{B}_3\text{Si}_6\text{O}_{27}(\text{O},\text{OH})_3(\text{OH},\text{F})$

Sample

The sample is holotype material from U.S. National Museum (NMNH #135815). The locality of this sample can be stated only in general terms. The crystals occur as detritus in the soils near Antsirabe in Madagascar, and a specific site for the occurrence of the type mineral is not known [Dunn et al., 1977].

Color

Dark olive brown

Optical data

Uniaxial(-), $N_o = 1.637$, $N_e = 1.621$ [Dunn et al., 1977].

Structure

Hexagonal, R3m (160), $Z = 3$, isostructural with tourmalines [Dunn et al., 1977].

Lattice constants of this sample

$a = 15.847(1) \text{ \AA}$
 $c = 7.1080(7)$

$c/a = 0.4485$

Volume

$1546.0 \text{ \AA}^3$

Density

(calculated) 3.06 g/cm^3 [based on $\text{Ca}(\text{Li}_{1.74}\text{Al}_{1.26})\text{Al}_6\text{B}_3\text{Si}_6\text{O}_{27.52}(\text{OH})_{2.48}(\text{F},\text{OH})$ according to empirical formula by Dunn et al. (1977)].

Figure of merit

$F_{30} = 62.0(0.015,32)$

Reference

Dunn, P. J., Appleman, D. E., and Nelen, J. E. (1977). Amer. Mineral. 62, 1121.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$	
7.94	5	1 1 0	11.14	
6.33	6	1 0 1	13.99	
4.943	30	0 2 1	17.93	
4.581	19	3 0 0	19.36	
4.197	50	2 1 1	21.15	
3.962	55	2 2 0	22.42	
3.445	50	0 1 2	25.84	
3.357	25	1 3 1	26.53	
3.093	9	4 0 1	28.84	
2.995	30	4 1 0	29.81	
2.933	100	1 2 2	30.45	
2.881	9	3 2 1	31.02	
2.641	2	3 3 0	33.92	
2.598	14	3 1 2	34.49	
2.559	85	0 5 1	35.04	
2.468	1	0 4 2	36.37	
2.437	4	2 4 1	36.85	
2.368	18	0 0 3	37.96	
2.356	15	2 3 2	38.17	
2.328	24	5 1 1	38.65	
2.288	5	6 0 0	39.34	
2.270	4	1 1 3	39.67	
2.173	7	5 0 2	41.53	
2.151	17	4 3 1	41.96	
2.105	19	3 0 3	42.94	
2.095	19	4 2 2	43.15	
2.033	30	2 2 3	44.53	
2.025	40	1 5 2	44.71	
2.008	6	1 6 1	45.12	
1.980	5	4 4 0	45.78	
1.9054	35	3 4 2	47.69	
1.8901	3	3 5 1	48.10	
1.8582	5	4 1 3	48.98	
1.8375	7	6 2 1	49.57	
1.8031	3	6 1 2	50.58	
1.7619	10	1 0 4	51.85	
1.7200	1	0 2 4	53.21	
1.7061	2	5 4 1	53.68	
1.6812	2	2 1 4	54.54	
1.6781	3	2 6 2	54.65	
1.6459	17	6 0 3	55.81	
1.6319	14	2 7 1	56.33	
1.6112	2	5 2 3	57.12	
1.5851	13	5 5 0	58.15	
1.5782	8	4 0 4	58.43	
1.5750	6	4 5 2	58.56	
1.5670	3	8 1 1	58.89	
1.5479	3	3 2 4	59.69	
1.5371	4	4 6 1	60.15	
1.5247	6	9 0 0	60.69	

Lithium Calcium Aluminum Boron Hydroxy Silicate,
Liddicoatite, $\text{Ca}(\text{Li},\text{Al})_3\text{Al}_6\text{B}_3\text{Si}_6\text{O}_{27}(\text{O},\text{OH})_3(\text{OH},\text{F})$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.5161	6	7 2 2	61.07
1.4974	4	8 2 0	61.92
1.4913	14	0 5 4	62.20
1.4655	6	2 4 4	63.42
1.4414	20	5 1 4	64.61
1.4226	3	7 4 0	65.57
1.4139	5	0 1 5	66.02
1.4102	7	1 9 1	66.22
1.3958M	17	6 3 3	66.99
1.3958M		4 3 4	66.99
1.3713	1	1 2 5	68.35
1.3475	8	10 0 1	69.73
1.3334	2	5 6 2	70.58
1.3208	4	6 6 0	71.35
1.3167M	8	5 5 3	71.61
1.3167M		3 5 4	71.61
1.3134	8	0 4 5	71.82
1.3022	10	10 1 0	72.53
1.2987	7	6 2 4	72.76
1.2926	2	5 7 1	73.16
1.2826	2	9 0 3	73.82
1.2760	2	8 4 1	74.27
1.2690	4	9 3 0	74.75
1.2656	5	8 2 3	74.98
1.2622	12	5 0 5	75.22
1.2496	5	5 4 4	76.11
1.2463	3	4 2 5	76.35
1.2316	3	1 5 5	77.43
1.2316	3	1 5 5	77.43
1.2289	4	0 11 1	77.63

Lithium Chromium Oxide Hydrate, $\text{Li}_2\text{CrO}_4 \cdot 2\text{H}_2\text{O}$

Sample

The sample was made by slow evaporation at room temperature of an aqueous solution of Li_2CrO_4 .

Color

Strong orange yellow

Structure

Orthorhombic, $\text{P2}_1\text{2}_1\text{2}_1$ (19), $Z = 4$. The cell was obtained from the axial ratios of Groth [1908] assuming a density near 2.1 and a $Z = 4$.

Lattice constants of this sample

$a = 7.746(1) \text{ \AA}$
 $b = 12.011(2)$
 $c = 5.5094(7)$

$a/b = 0.6449$
 $c/b = 0.4587$

Volume

$512.56 \text{ \AA}^3$

Density

(calculated) 2.150 g/cm^3

Figure of merit

$F_{30} = 74.6(0.012, 35)$

Additional pattern

1. PDF card 1-819 [Hanawalt et al., 1938]

Reference

Groth, P. (1908). *Chemische Krystallographie II*, (Wilhelm Engelmann, Leipzig, Germany) p. 365.
 Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). *Ind. Eng. Chem. Anal. Ed.* **10**, 457.

$\text{CuK}\alpha_1\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$			
Internal standard Si, $a = 5.43088 \text{ \AA}$			
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
6.52	25	1 1 0	13.57
5.012	25	0 1 1	17.68
4.751	90	1 2 0	18.66
4.489	85	1 0 1	19.76
4.205	75	1 1 1	21.11
4.061	85	0 2 1	21.87
3.687	60	2 1 0	24.12
3.593	25	1 2 1	24.76
3.558	60	1 3 0	25.01
3.239	4	0 3 1	27.52
3.170	70	2 0 1	28.13
3.062	100	2 1 1	29.14
3.002	75	0 4 0	29.74
2.993	75	1 3 1	29.83
2.802M	11	2 2 1	31.91

$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
2.802M		1 4 0	31.91
2.784	20	2 3 0	32.13
2.754	80	0 0 2	32.48
2.685	12	0 1 2	33.34
2.597	3	1 0 2	34.51
2.537	7	1 1 2	35.35
2.525	7	3 1 0	35.52
2.494	25	1 4 1	35.98
2.485	45	2 3 1	36.12
2.382	19	1 2 2	37.74
2.373M	40	2 4 0	37.89
2.373M		3 2 0	37.89
2.338	25	3 0 1	38.48
2.293M	5	1 5 0	39.25
2.293M		3 1 1	39.25
2.271	3	0 3 2	39.66
2.245	4	2 0 2	40.14
2.206	14	2 1 2	40.88
2.179M	45	2 4 1	41.40
2.179M		3 2 1	41.40
2.170	17	3 3 0	41.59
2.118	12	1 5 1	42.65
2.103	13	2 2 2	42.98
2.041	16	2 5 0	44.34
2.029	10	0 4 2	44.62
2.018	11	3 3 1	44.87
1.9586M	5	2 3 2	46.32
1.9586M		3 4 0	46.32
1.9365	8	4 0 0	46.88
1.9134	20	2 5 1	47.48
1.8839	9	3 0 2	48.27
1.8614	5	3 1 2	48.89
1.8424	4	4 2 0	49.43
1.8271M	4	4 0 1	49.87
1.8271M		1 6 1	49.87
1.8149	12	0 1 3	50.23
1.8061	10	4 1 1	50.49
1.7988	5	2 4 2	50.71
1.7863	7	1 0 3	51.09
1.7676	9	1 1 3	51.67
1.7481	2	4 2 1	52.29
1.7135	1	1 2 3	53.43
1.6755M	9	3 5 1	54.74
1.6755M		1 7 0	54.74
1.6591	25	2 0 3	55.33
1.6435	6	2 1 3	55.90
1.6272	20	4 4 0	56.51
1.6030	3	1 7 1	57.44
1.5962	7	3 4 2	57.71
1.5824	3	3 6 0	58.26
1.5708	4	4 1 2	58.73

Lithium Tin Oxide, Li_2SnO_3

CAS registry no.
12188-25-9

Sample

The sample was prepared by heating $\text{Li}_2\text{C}_2\text{O}_4$ and SnO_2 at 800 °C for 10 minutes followed by 950 °C for 20 minutes.

Color

Colorless

Structure

Monoclinic, A2/a (15), Z = 8, [Scheer et al., 1955; Lang, 1954]. The structure of Li_2SnO_3 has been studied by Kreuzburg et al. [1970].

Lattice constants of this sample

$a = 10.027(2) \text{ \AA}$
 $b = 9.181(2)$
 $c = 5.301(2)$
 $\beta = 100.26(2)^\circ$

$a/b = 1.0921$
 $c/b = 0.5774$

Volume

$480.1 \text{ \AA}^3$

Density

(calculated) 4.996 g/cm^3

Figure of merit

$F_{30} = 27.9(0.014, 80)$

Reference intensity

$I/I_{\text{corundum}} = 4.1(3)$

Polymorphism

There is a second form of Li_2SnO_3 which differs in its stacking [Lang, 1966].

References

Kreuzburg, G., Stewner, F., and Hoppe, R. (1970).
Z. Anorg. Allg. Chem. 379, 242.
Lang, G. (1954). Z. Anorg. Allg. Chem. 276, 77.
Lang, G. (1966). Z. Anorg. Allg. Chem. 348, 246.
Scheer, J. J., Van Arkel, A. E., and Heyding,
R. D. (1955). Can. J. Chem. 33, 683.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$	
4.932	100	2 0 0	17.97	
4.586	17	0 2 0	19.34	
4.539	10	0 1 1	19.54	
4.386	7	-1 1 1	20.23	
4.166	3	1 2 0	21.31	
3.899	2	1 1 1	22.79	
3.630	2	-2 1 1	24.50	
3.106	1	2 1 1	28.72	
2.886	1	-3 1 1	30.96	
2.673	2	3 2 0	33.50	
2.641	1	0 3 1	33.92	
2.608M	55	-1 3 1	34.36	
2.608M		0 0 2	34.36	
2.495M	25	-2 0 2	35.97	
2.495M		1 3 1	35.97	
2.466	9	4 0 0	36.40	
2.324	1	-4 1 1	38.72	
2.293	3	0 4 0	39.25	
2.288	2	-1 2 2	39.34	
2.154M	65	-3 3 1	41.91	
2.154M		2 0 2	41.91	
1.974	20	3 3 1	45.94	
1.7343	3	-1 1 3	52.74	
1.7321M	3	-1 4 2	52.81	
1.7321M		0 5 1	52.81	
1.7233M	2	-1 5 1	53.10	
1.7233M		0 4 2	53.10	
1.6527	12	-5 3 1	55.56	
1.6446	6	6 0 0	55.86	
1.6180	1	-5 2 2	56.86	
1.5300M	19	0 6 0	60.46	
1.5300M		-1 3 3	60.46	
1.5164	17	5 3 1	61.06	
1.4612M	15	2 6 0	63.63	
1.4612M		1 3 3	63.63	
1.3202M	6	-2 0 4	71.39	
1.3202M		0 6 2	71.39	
1.3041M	5	-6 1 3	72.41	
1.3041M		0 0 4	72.41	
1.3002	7	4 6 0	72.66	
1.2921	3	-7 3 1	73.19	
1.2723M	2	0 7 1	74.52	
1.2723M		-1 2 4	74.52	
1.2685M	1	-2 2 4	74.78	
1.2685M		-1 7 1	74.78	
1.2473	9	2 6 2	76.28	
1.2325	3	1 5 3	77.36	
1.2093	3	5 6 0	79.13	
1.2081M	3	2 0 4	79.23	
1.2081M		4 3 3	79.23	
1.1990	4	7 3 1	79.95	
1.1459M	1L	8 1 1	84.48	
1.1459M		-5 6 2	84.48	
1.1224	4	4 6 2	86.68	

Magnesium Sulfate Hydrate (Kieserite), $\text{MgSO}_4 \cdot \text{H}_2\text{O}$

CAS registry no.
14567-64-7

Sample

A sample of $\text{MgSO}_4 \cdot 7\text{H}_2\text{O}$ was obtained from Fisher Scientific Co. of Fairlawn, NJ. The material was heated first at 150 °C, then sealed in a tube and heated for 1 3/4 hours at 400 °C.

Color

Colorless

Structure

Monoclinic, $A2/a$ (15), $Z = 4$. The structure was determined by Leonhardt and Weiss [1957] and confirmed by Bregeault et al. [1972].

Lattice constants of this sample

$a = 7.5110(9) \text{ \AA}$
 $b = 7.611(1)$
 $c = 6.921(1)$
 $\beta = 116.17(1)^\circ$

$a/b = 0.9868$

$c/b = 0.9093$

Volume

$355.1 \text{ \AA}^3$

Density

(calculated) 2.589 g/cm^3

Figure of merit

$F_{30} = 60.5(0.011, 47)$

Reference intensity

$I/I_{\text{corundum}} = 1.02(4)$

Additional pattern

1. PDF card 13-102 [Kubisz, 1960] (natural mineral)

References

Bregeault, J.-M., Herpin, P., and Coing-Boyat, J. (1972). Bull. Soc. Chim. Fr. 1972, 2247.
Kubisz, J. (1960). Bull. Acad. Pol. Sci. Ser. Sci. Geol. Geogr. 8, 101.
Leonhardt, H. J. and Weiss, R. (1957). Naturwissenschaften 44, 338.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
4.815	75	0 1 1	18.41	
3.405	100	1 1 1	26.15	
3.351	70	-2 1 1	26.58	
3.313	70	1 2 0	26.89	
3.106	13	0 0 2	28.72	
3.051	40	-2 0 2	29.25	
2.560	35	-1 2 2	35.03	
2.523	30	2 2 0	35.55	
2.401	3	2 1 1	37.42	
2.380	3	-2 2 2	37.76	
2.342	4	-1 3 1	38.41	
2.185	7	-1 1 3	41.28	
2.099	9	-2 3 1	43.07	
2.054	20	1 2 2	44.05	
2.023	3	-3 2 2	44.77	
1.965	8	-3 1 3	46.16	
1.934	4	3 2 0	46.94	
1.9039M	5	2 0 2	47.73	
1.9039M		0 4 0	47.73	
1.8657	1	-4 0 2	48.77	
1.8125	3	3 1 1	50.30	
1.7919M	1	-4 1 1	50.92	
1.7919M		2 3 1	50.92	
1.7288M	1L	-2 0 4	52.92	
1.7288M		1 1 3	52.92	
1.7029	3	2 2 2	53.79	
1.6750	14	-4 2 2	54.76	
1.6577	5	2 4 0	55.38	
1.6227	8	0 4 2	56.68	
1.6043	3	0 3 3	57.39	
1.5866	7	-3 3 3	58.09	
1.5531	4	0 0 4	59.47	
1.5401M	2	4 2 0	60.02	
1.5401M		-1 2 4	60.02	
1.5265	2	-3 2 4	60.61	
1.5030	4	3 3 1	61.66	
1.4524M	3	1 3 3	64.06	
1.4524M		3 4 0	64.06	
1.4366	2	-5 1 3	64.85	
1.4160	2	-4 2 4	65.91	
1.3975	1	-5 2 2	66.90	

Manganese Phosphate, $\text{Mn}_3(\text{PO}_4)_2$

Sample

The sample was prepared by heating a 3:2 molar mixture of MnCO_3 and $(\text{NH}_4)_2\text{HPO}_4$ overnight at 850 °C.

Color

Pinkish white

Structure

Monoclinic, $P2_1/c$ (14), $Z = 4$. The cell was found by use of the Visser program [1969] and by comparison with $\beta\text{-Zn}_3(\text{PO}_4)_2$ and $\text{Cd}_3(\text{PO}_4)_2$. The space group was assigned by consideration of the absences in the powder pattern.

Lattice constants of this sample

$a = 8.446(2) \text{ \AA}$
 $b = 10.059(3)$
 $c = 8.047(2)$
 $\beta = 114.27(2)^\circ$

$a/b = 0.8396$

$c/b = 0.8000$

Volume

$623.2 \text{ \AA}^3$

Density

(calculated) 3.781 g/cm^3 (assuming $Z = 4$)

Figures of merit

$F_{30} = 54.0(0.013, 44)$

$M_{20} = 31.1$

Polymorphism

$\text{Mn}_3(\text{PO}_4)_2$ is also reported to crystallize in a graffonite structure [Calvo, 1968]. Stephens and Calvo [1969] also describe a second monoclinic form of $\text{Mn}_3(\text{PO}_4)_2$ which they call " β ".

Additional pattern

1. PDF card 3-0465 [Dow Chemical Co., Midland, MI]

References

Calvo, C. (1968). Amer. Mineral. 53, 742.
 Stephens, J. S. and Calvo, C. (1969). Can. Chem. 47, 2215.
 Visser, J. W. (1969). J. Appl. Crystallogr. 2, 89.

CuK α $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$			
Internal standard W, $a = 3.16524 \text{ \AA}$			
$d(\text{Å})$	I	hkl	$2\theta(^\circ)$
6.10	8	1 1 0	14.50
5.92	6	0 1 1	14.96
4.207	35	1 2 0	21.10
4.010	16	-1 0 2	22.15
3.852	7	2 0 0	23.07
3.726	55	-1 1 2	23.86
3.669	10	0 0 2	24.24
3.597	12	2 1 0	24.73
3.458	25	-2 0 2	25.74
3.446	13	0 1 2	25.83
3.341	35	1 2 1	26.66
3.269	90	-2 1 2	27.26
3.218	100	-2 2 1	27.70
3.135	30	-1 2 2	28.45
3.073	65	1 3 0	29.03
3.018	25	-1 3 1	29.58
2.963	45	0 2 2	30.14
2.882	60	1 0 2	31.01
2.849	20	-2 2 2	31.37
2.827	55	2 1 1	31.62
2.772	10	1 1 2	32.27
2.705	9	-3 1 1	33.09
2.681M	4	1 3 1	33.40
2.681M		-3 0 2	33.40
2.616	9	-2 3 1	34.25
2.593	25	-3 1 2	34.57
2.573	25	-1 3 2	34.84
2.528	60	2 3 0	35.48
2.489	2	3 1 0	36.06
2.453	14	-3 2 1	36.60
2.408	8	-2 3 2	37.31
2.375	20	0 1 3	37.85
2.368	18	-3 2 2	37.97
2.357	18	-1 2 3	38.15
2.315	9	-2 2 3	38.87
2.285	2	3 2 0	39.41
2.248	4	-3 1 3	40.08
2.215	5	2 3 1	40.71
2.184M	5	2 1 2	41.30
2.184M		1 3 2	41.30
2.157	6	-2 4 1	41.85
2.132	3	-1 4 2	42.37
2.095+	5	-4 0 2	43.15
2.095+		-3 3 2	43.15
2.089	8	-1 3 3	43.28
2.052M	15	-4 1 2	44.09
2.052M		1 1 3	44.09
2.034	11	-2 4 2	44.50
2.006	2	-2 0 4	45.16
1.986	2	3 2 1	45.64

Manganese Phosphate, $\text{Mn}_3(\text{PO}_4)_2$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.975M	7	0 3 3	45.92
1.975M		-1 0 4	45.92
1.968	11	-2 1 4	46.08
1.940M	13	-1 1 4	46.80
1.940M		0 5 1	46.80
1.933+	17	1 2 3	46.96
1.933+		-4 2 2	46.96
1.916	20	-4 1 3	47.40
1.891	6	4 1 0	48.09
1.874M	8	-3 4 1	48.53
1.874M		-3 1 4	48.53
1.860	16	2 3 2	48.93
1.835M	9	-3 4 2	49.64
1.835M		1 5 1	49.64

Manganese Sulfate Hydrate (Szmikite), $\text{MnSO}_4 \cdot \text{H}_2\text{O}$

Sample

A sample of MnSO_4 was obtained from J. T. Baker Co., Phillipsburg, NJ. Crystals were formed from a saturated solution of the material at room temperature. The crystals slowly changed to the monohydrate when left in open air and were finally heated at 250 °C for 2½ hours.

Color

Colorless

Structure

Monoclinic, $A2/a$ (15), $Z = 4$, isostructural with $\text{CoSO}_4 \cdot \text{H}_2\text{O}$. The structure was determined by Le Fur et al. [1966].

Lattice constants of this sample

$a = 7.766(1) \text{ \AA}$
 $b = 7.666(1)$
 $c = 7.120(1)$
 $\beta = 115.85(1)^\circ$

$a/b = 1.0130$
 $c/b = 0.9288$

Volume $\text{\AA}^3$
 381.5 $\text{\AA}^3$

Density

(calculated) 2.943 g/cm³

Figure of merit

$F_{30} = 77.8(0.010, 37)$

Reference intensity

$I/I_{\text{corundum}} = 1.91(7)$

Additional pattern

1. PDF card 14-166 [Pistorius, 1961]

References

Le Fur, Y., Coing-Boyat, J., and Bassi, G.
 (1966). C. R. Acad. Sci. Ser. C 262, 632.
 Pistorius, C. W. F. T. (1961). Z. Anorg. Allg. Chem. 302, 226.

CuK α_1 $\lambda = 1.540598 \overset{\circ}{\text{\AA}}$; temp. 25 $\pm$ 1 $^{\circ}\text{C}$				
Internal standard Ag, $a = 4.08651 \overset{\circ}{\text{\AA}}$				
$d(\overset{\circ}{\text{\AA}})$	I	hkl	$2\theta(^{\circ})$	
4.916	50	0 1 1	18.03	
4.855	30	-1 1 1	18.26	
3.834	8	0 2 0	23.18	
3.507	100	1 1 1	25.38	
3.445	20	-2 1 1	25.84	
3.361	30	1 2 0	26.50	
3.203	1L	0 0 2	27.83	
3.139	40	-2 0 2	28.41	
2.606	15	-1 2 2	34.38	
2.580	30	2 2 0	34.74	

^o d(Å)	I	hkl			2θ(°)
2.483	1	2	1	1	36.15
2.457	1	0	2	2	36.54
2.446	3	-3	1	1	36.71
2.366	7	-1	3	1	38.00
2.245	10	-1	1	3	40.13
2.145	6	1	3	1	42.09
2.131	2	-2	3	1	42.38
2.109	7	1	2	2	42.85
2.072	1	-3	2	2	43.65
2.0193	8	-3	1	3	44.85
1.9894	1	3	2	0	45.56
1.9722	4	2	0	2	45.98
1.9164	2	0	4	0	47.40
1.8762	4	3	1	1	48.48
1.8536	1L	-4	1	1	49.11
1.8316	1L	2	3	1	49.74
1.8159	1L	-3	3	1	50.20
1.7795	1	-2	0	4	51.30
1.7528	4	2	2	2	52.14
1.7472	2	4	0	0	52.32
1.7291	2	-1	3	3	52.91
1.7218M	8	-4	2	2	53.15
1.7218M		-2	3	3	53.15
1.6806	3	2	4	0	54.56
1.6443	5	0	4	2	55.87
1.6389	3	0	3	3	56.07
1.6193	5	-3	3	3	56.81
1.6149	4	-2	2	4	56.98
1.6015	3	0	0	4	57.50
1.5896	1L	4	2	0	57.97
1.5809	1	-1	2	4	58.32
1.5701	1	-4	0	4	58.76
1.5658	1L	-3	2	4	58.94
1.5432	3	3	3	1	59.89
1.5128	1L	-3	4	2	61.22
1.4961	1L	4	1	1	61.98
1.4887M	2	-1	5	1	62.32
1.4887M		1	3	3	62.32
1.4810M	3	-5	1	1	62.68
1.4810M		-5	1	3	62.68
1.4778	2	0	2	4	62.83
1.4643M	1L	-4	3	3	63.48
1.4643M		3	2	2	63.48
1.4526	1L	-4	2	4	64.05
1.4390	1L	-5	2	2	64.73
1.4290	1L	1	5	1	65.24

Mercury Sulfate, HgSO₄

Sample

The sample was obtained from Alfa Division,
Ventron Corp., Danvers, MA.

Color

Yellowish white

Structure

Orthorhombic, P2₁mn (31), Z = 2. The structure was determined by Bonefačić [1963] and Kokkoros and Rentzeperis [1963]. Aurivillius [1964] reports that the symmetry is monoclinic rather than orthorhombic.

Lattice constants of this sample

a = 4.8150(2) Å

b = 6.5752(3)

c = 4.7810(2)

a/b = 0.7323

c/b = 0.7271

Volume

151.36 Å³

Density

(calculated) 6.509 g/cm³

Figure of merit

F₃₀ = 118(0.008,31)

Additional patterns

1. PDF card 13-519 [Kokkoros and Rentzeperis, U. Thessaloniki, Greece]
2. Aurivillius and Malmros [1961]

References

- Aurivillius, K. (1964). Ark. Kemi 24, 151.
Aurivillius, K. and Malmros, B. (1961). Acta Chem. Scand. 15, 1932.
Bonefačić, A. (1963). Croat. Chem. Acta 35, 195.
Kokkoros, P. A. and Rentzeperis, P. J. (1963). Z. Kristallogr. Kristallgeometrie Kristallphys. Kristallchem. 119, 234.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard W, a = 3.16524 Å				
d(Å)	I	hkl	2θ(°)	
4.782	12	0 0 1	18.54	
3.884	85	1 1 0	22.88	
3.865	85	0 1 1	22.99	
3.392	100	1 0 1	26.25	
3.288	75	0 2 0	27.10	
3.014	45	1 1 1	29.62	
2.707	4	0 2 1	33.06	
2.408	25	2 0 0	37.32	
2.390	17	0 0 2	37.60	
2.361	60	1 2 1	38.09	
2.2457	20	0 1 2	40.12	
2.1509	10	2 0 1	41.97	
2.1412	20	1 0 2	42.17	
2.0431	35	2 1 1	44.30	
2.0361	25	1 1 2	44.46	
1.9936M	35	1 3 0	45.46	
1.9936M		0 3 1	45.46	
1.9423	25	2 2 0	46.73	
1.9333	16	0 2 2	46.96	
1.8406	12	1 3 1	49.48	
1.7988	8	2 2 1	50.71	
1.7939	14	1 2 2	50.86	
1.6967	7	2 0 2	54.00	
1.6440	17	0 4 0	55.88	
1.6154	7	0 3 2	56.96	
1.5936	3	0 0 3	57.81	
1.5593	5	3 1 0	59.21	
1.5545	4	0 4 1	59.41	
1.5353	9	2 3 1	60.23	
1.5313	8	1 3 2	60.40	
1.5215	6	3 0 1	60.83	
1.5128	1L	1 0 3	61.22	
1.5077	5	2 2 2	61.45	
1.4791	15	1 4 1	62.77	
1.4743	19	1 1 3	63.00	
1.4342	3	0 2 3	64.97	
1.3807	10	3 2 1	67.82	
1.3576	5	2 4 0	69.14	
1.3541	5	0 4 2	69.34	
1.3415	5	2 3 2	70.09	
1.3329	1	3 0 2	70.61	
1.3293	3	2 0 3	70.83	
1.3060M	4	3 1 2	72.29	
1.3060M		2 4 1	72.29	
1.3039	5	1 4 2	72.42	
1.2950	1	3 3 0	73.00	
1.2684M	4	1 5 0	74.79	
1.2684M		0 5 1	74.79	
1.2502	1	3 3 1	76.07	
1.2452	5	1 3 3	76.43	

Mercury Sulfate, HgSO_4 - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.2348	2	3 2 2	77.19
1.2320	4	2 2 3	77.40
1.2261	2	1 5 1	77.84
1.2035	1	4 0 0	79.59
1.1804	2	2 4 2	81.47
1.1758	3	0 1 4	81.86
1.1673	1L	4 0 1	82.58
1.1601	2	1 0 4	83.21
1.1522	2	0 5 2	83.91
1.1442	1	0 4 3	84.63
1.1387	1	3 3 2	85.14
1.1302	1	4 2 0	85.93
1.1218	2	2 5 1	86.73
1.1206	1	1 5 2	86.85
1.1166	4	3 4 1	87.24
1.1144	4	3 1 3	87.45
1.1002	1L	4 2 1	88.88
1.0960	2	0 6 0	89.31
1.0940	2	1 2 4	89.52
1.0751	1L	4 0 2	91.53
1.0681	1L	0 6 1	92.30
1.0611	1	4 1 2	93.09
1.0566	2	2 1 4	93.61
1.0493	2	0 3 4	94.46
1.0430	3	1 6 1	95.22
1.0394	3	2 5 2	95.65
1.0352	1	3 4 2	96.16
1.0335	2	2 4 3	96.37
1.0302	1	4 3 1	96.78
1.0254	1L	1 3 4	97.39
1.0218	2	4 2 2	97.85
1.0171	1L	3 5 0	98.46
1.0050	3	3 3 3	100.08
.9974	2	2 6 0	101.13
.9949	2	3 5 1	101.47
.9924	3	1 5 3	101.83

Mercury Sulfate, Hg_2SO_4

Sample

The sample was reagent material obtained from Kahlbaum, Berlin, Germany.

Color

Yellowish white

Structure

Monoclinic, $P2_1/a$ (13), $Z = 2$, isostructural with mercury selenate. The structure was determined by Dorm [1969].

Lattice constants of this sample

$a = 8.365(1) \text{ \AA}$
 $b = 4.4262(5)$
 $c = 6.2785(9)$
 $\beta = 91.77(1)^\circ$

$a/b = 1.8899$

$c/b = 1.4185$

Volume

$232.34 \text{ \AA}^3$

Density

(calculated) 7.108 g/cm^3

Figure of merit

$F_{30} = 76.4(0.013, 30)$

Reference intensity

$I/I_{\text{corundum}} = 3.4(3)$

Additional pattern

1. PDF card 1-0838 [Hanawalt et al., 1938]

References

Dorm, E. (1969). Acta Chem. Scand. 23, 1607.
 Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
6.28	4	0 0 1	14.08	
4.427	80	0 1 0	20.04	
4.182	75	2 0 0	21.23	
3.916	1	1 1 0	22.69	
3.619	25	0 1 1	24.58	
3.530	4	-2 0 1	25.21	
3.432	25	2 0 1	25.94	
3.342	7	-1 1 1	26.65	
3.296	13	1 1 1	27.03	
3.136	20	0 0 2	28.44	
3.039	100	2 1 0	29.37	
2.712	12	2 1 1	33.00	
2.560	25	0 1 2	35.02	
2.549	20	-2 0 2	35.18	
2.473	7	2 0 2	36.29	
2.468	7	-1 1 2	36.38	
2.433	1L	1 1 2	36.92	
2.359	2	3 1 0	38.12	
2.228	2	-3 1 1	40.46	
2.214	12	0 2 0	40.72	
2.209	20	-2 1 2	40.82	
2.189	2	3 1 1	41.21	
2.159	6	2 1 2	41.81	
2.139	1L	1 2 0	42.22	
2.090M	20	4 0 0	43.25	
2.090M		0 0 3	43.25	
2.087	14	0 2 1	43.32	
2.029	6	-1 2 1	44.63	
2.021	5	1 2 1	44.81	
2.002	1L	-4 0 1	45.27	
1.964	4	4 0 1	46.18	
1.956	7	2 2 0	46.38	
1.8909M	16	0 1 3	48.08	
1.8909M		4 1 0	48.08	
1.8759	1	-2 2 1	48.49	
1.8600	5	2 2 1	48.93	
1.8561	4	-1 1 3	49.04	
1.8487	6	2 0 3	49.25	
1.8085	4	0 2 2	50.42	
1.7958	6	4 1 1	50.80	
1.7747	1	-1 2 2	51.45	
1.7644	6	-4 0 2	51.77	
1.7613	5	1 2 2	51.87	
1.7413	5	-2 1 3	52.51	
1.7333	1	3 2 0	52.77	
1.7159	1	4 0 2	53.35	
1.7055	6	2 1 3	53.70	
1.6784	2	-3 2 1	54.64	
1.6705	4	-2 2 2	54.92	
1.6626	2	3 2 1	55.20	

Mercury Sulfate, Hg_2SO_4 - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.6492	2	2 2 2	55.69
1.6386	6	-4 1 2	56.08
1.5992	1L	4 1 2	57.59
1.5684	1L	0 0 4	58.83
1.5643	1L	5 1 0	59.00
1.5286	1	-5 1 1	60.52
1.5188	4	4 2 0	60.95
1.5044	1	3 2 2	61.60
1.4893	1L	1 2 3	62.29
1.4838M	1L	-2 0 4	62.55
1.4838M		-4 2 1	62.55
1.4753	1L	0 3 0	62.95
1.4692	1	4 2 1	63.24
1.4561	1	4 0 3	63.88
1.4390	1	-2 2 3	64.73
1.4358	1	0 3 1	64.89
1.4222	1	-4 1 3	65.59
1.4174	3	-1 3 1	65.84
1.4138	2	1 3 1	66.03
1.4070	1	-2 1 4	66.39
1.3910	1	2 3 0	67.25
1.3831	2	4 1 3	67.69
1.3798	2	-4 2 2	67.87

Nicotinic Acid, C₆H₅NO₂

Synonym

1. 3-Pyridinecarboxylic Acid

CAS registry no.

59-67-6

Sample

The sample was NBS Standard Reference Material 148. It is used for checking microdeterminations of carbon, hydrogen and nitrogen.

Color

Colorless

Optical data

Biaxial(-), $N_{\alpha} = 1.424(2)$, $N_{\beta} = 1.717$, $N_{\gamma} \sim 1.79$.
2V = 46° [Wright and King, 1950].

Structure

Monoclinic, P2₁/a (14), Z = 4, [Wright and King, 1950].

Lattice constants of this sample

a = 7.222(2) Å
b = 11.672(3)
c = 7.178(2)
 $\beta = 113.42(2)^{\circ}$

a/b = 0.6187
c/b = 0.6150

Volume
555.3 Å³

Density

(calculated) 1.473 g/cm³

Figure of merit

F₃₀ = 47.8(0.011,57)

Reference intensity

I/I_{corundum} = 0.95(3)

Additional pattern

1. PDF card 24-1843 [Wright and King, 1950]

Reference

Wright, W. B. and King, G. S. D. (1950).
Acta Crystallogr. 3, 31.

CuK α_1 $\lambda = 1.540598$ Å; temp. 25±1 °C					
Internal standard W, a = 3.16524 Å					
d(Å)	I	hkl			2 $\theta(^{\circ})$
5.73	100	0	1	1	15.45
4.362	40	0	2	1	20.34
4.185	25	-1	2	1	21.21
3.743	7	1	1	1	23.75
3.588	55	-2	0	1	24.79
3.429	70	-2	1	1	25.96
3.314	80	2	0	0	26.88
3.271M	20	1	2	1	27.24
3.271M		-1	3	1	27.24
3.188	50	2	1	0	27.96
3.053	7	-2	2	1	29.23
3.043	8	-1	2	2	29.32
2.916M	3	0	4	0	30.63
2.916M		-2	1	2	30.63
2.881	3	2	2	0	31.01
2.869	3	0	2	2	31.15
2.773	4	1	3	1	32.26
2.670M	4	1	4	0	33.54
2.670M		0	4	1	33.54
2.628M	11	-1	3	2	34.09
2.628M		-1	4	1	34.09
2.513	6	0	3	2	35.70
2.381	5	-2	3	2	37.75
2.347	12	1	4	1	38.31
2.298	5	-2	0	3	39.16
2.259	7	-1	4	2	39.87
2.196	11	0	0	3	41.07
2.178	10	-1	5	1	41.43
2.157	3	0	1	3	41.85
2.145M	3	-3	2	2	42.09
2.145M		1	3	2	42.09
2.009	3	1	5	1	45.08
1.984	2	-3	3	2	45.68
1.977M	2	-3	1	3	45.86
1.977M		2	0	2	45.86
1.956	2	-2	5	1	46.37
1.949	1	2	1	2	46.56
1.928	1	1	4	2	47.09
1.905	1	0	5	2	47.71
1.866M	1	1	6	0	48.77
1.866M		0	6	1	48.77
1.8496M	1	-1	6	1	49.22
1.8496M		1	1	3	49.22
1.8094	3	-3	4	2	50.39
1.8064	4	-2	4	3	50.48
1.7833+	7	1	2	3	51.18
1.7833+		-2	0	4	51.18
1.7628+	3	-4	1	1	51.82
1.7628+		2	3	2	51.82

Oxalic Acid Hydrate, $C_2H_2O_4 \cdot 2H_2O$

Synonym

1. Ethanedioic acid dihydrate
2. Hydrogen oxalate hydrate

CAS registry no.

6153-56-6

Sample

Oxalic acid hydrate, analytical reagent was obtained from Mallinkrodt, St. Louis, MO 63147. It was dissolved in distilled water at room temperature. The solution was allowed to evaporate partly at room temperature and the precipitate was filtered.

Color

Colorless

Structure

Monoclinic, $P2_1/a$ (14), $Z = 2$. The structure was last refined by Ahmed and Cruickshank [1953] who correlated various earlier data.

Lattice constants of this sample

$a = 11.890(3) \text{ \AA}$
 $b = 3.6070(7)$
 $c = 6.121(1)$
 $\beta = 103.31(3)^\circ$

$a/b = 3.2966$
 $c/b = 1.6971$

Volume

$255.4 \text{ \AA}^3$

Density

(calculated) 1.639 g/cm^3

Figure of merit

$F_{30} = 52.8(0.012, 47)$

Additional pattern

1. PDF card 14-832 [de Wolff, Techn. Phys. Dienst, Delft, Holland]

Reference intensity

$I/I_{\text{corundum}} = 1.63(6)$

Reference

Ahmed, F. R. and Cruickshank, D. W. J. (1953). Acta Crystallogr. 6, 385.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
5.94	25	0 0 1	14.89	
5.79	4	2 0 0	15.30	
4.729	30	-2 0 1	18.75	
3.737	1L	2 0 1	23.79	
3.443	16	1 1 0	25.86	
3.075	100	-1 1 1	29.01	
2.937	10	-2 0 2	30.41	
2.874	8	-4 0 1	31.09	
2.632	1	3 1 0	34.03	
2.595	4	2 1 1	34.53	
2.562	4	-3 1 1	34.99	
2.431	17	2 0 2	36.95	
2.396	6	4 0 1	37.51	
2.364	12	-4 0 2	38.03	
2.333	2	-1 1 2	38.56	
2.296	6	0 1 2	39.20	
2.279M	12	3 1 1	39.51	
2.279M		-2 1 2	39.51	
2.257	8	4 1 0	39.92	
2.178	1	1 1 2	41.42	
1.986	3	0 0 3	45.65	
1.978	3	-4 1 2	45.84	
1.947	1L	5 1 0	46.61	
1.929	2	6 0 0	47.08	
1.8354	2	3 1 2	49.63	
1.8210	1L	-6 0 2	50.05	
1.8035	1L	0 2 0	50.57	
1.7734	2	-1 1 3	51.49	
1.7679	1	-2 1 3	51.66	
1.7578	1L	2 0 3	51.98	
1.7395	1	0 1 3	52.57	
1.7236	2	-1 2 1	53.09	
1.7218+	2	6 0 1	53.15	
1.7218+		2 2 0	53.15	
1.7011	1L	6 1 0	53.85	
1.6915	1L	1 2 1	54.18	
1.6710	2	1 1 3	54.90	
1.6446	1	-4 1 3	55.86	
1.6169	1	-3 2 1	56.90	
1.5802	1	2 1 3	58.35	
1.5422	2	0 2 2	59.93	
1.5371M	3	3 2 1	60.15	
1.5371M		-2 2 2	60.15	
1.5307M	2	4 2 0	60.43	
1.5307M		-2 0 4	60.43	

Picric Acid, $C_6H_3N_3O_7$

Synonym

1. 2,4,6-Trinitrophenol

CAS registry no.

88-89-1

Sample

The sample was obtained from the General Chemical Division, Allied Chemical and Dye Corp., New York, NY. It was recrystallized from water.

Color

Light yellow

Structure

Orthorhombic, $P2_1ca$ (29), $Z = 8$ [Bredig and Möller, 1929].

Lattice constants of this sample

$a = 9.723(4) \text{ \AA}$

$b = 19.139(6)$

$c = 9.271(3)$

$a/b = 0.5080$

$c/b = 0.4844$

Volume

$1725.3 \text{ \AA}^3$

Density

(calculated) 1.764 g/cm^3

Figure of merit

$F_{30} = 42.5(0.017, 41)$

Additional pattern

1. PDF card 9-789 [Morse and Baun, Wright Air Development Center, Wright-Patterson AFB, Ohio]

Reference

Bredig, M. A. and Möller, H. (1929).
Z. Kristallogr. Kristallgeometrie
Kristallphys. Kristallchem. 71, 331.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
9.56	20	0 2 0	9.24	
6.65	3	0 2 1	13.31	
6.38	6	0 3 0	13.88	
6.34	6	1 1 1	13.96	
5.49	45	1 2 1	16.13	
5.245	1	0 3 1	16.89	
4.784	40	0 4 0	18.53	
4.706	15	2 1 0	18.84	
4.629M	25	0 0 2	19.16	
4.629M		1 3 1	19.16	
4.507	11	0 1 2	19.68	
4.327	16	2 2 0	20.51	
4.247	19	0 4 1	20.90	
4.184	20	1 0 2	21.22	
4.087	19	1 1 2	21.73	
3.901	90	1 4 1	22.78	
3.869	100	2 3 0	22.97	
3.831M	60	1 2 2	23.20	
3.831M		0 5 0	23.20	
3.750	70	0 3 2	23.71	
3.569	30	2 3 1	24.93	
3.500	45	1 3 2	25.43	
3.411	19	2 4 0	26.10	
3.351	14	2 0 2	26.58	
3.326M	12	0 4 2	26.78	
3.326M		1 5 1	26.78	
3.203	4	2 4 1	27.83	
3.191	5	0 6 0	27.94	
3.152	13	1 4 2	28.29	
3.015	90	0 6 1	29.61	
2.954	7	0 5 2	30.23	
2.944	9	0 2 3	30.34	
2.909	7	1 1 3	30.71	
2.879	25	1 6 1	31.04	
2.862	40	2 5 1	31.23	
2.822	9	1 5 2	31.68	
2.815	13	1 2 3	31.76	
2.780	6	0 3 3	32.17	
2.673	25	1 3 3	33.50	
2.667	27	2 6 0	33.57	
2.626	8	0 6 2	34.11	
2.597	9	0 4 3	34.51	
2.576	11	3 4 1	34.80	
2.564	11	2 6 1	34.96	
2.532	6	1 7 1	35.42	
2.523	5	2 5 2	35.56	
2.509	9	1 4 3	35.76	
2.411	3	4 1 0	37.27	
2.389	3	3 5 1	37.62	
2.355M	5	4 2 0	38.18	

Picric Acid, $C_6H_3N_3O_7$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
2.355M		0 7 2	38.18
2.313	8	2 6 2	38.90
2.290M	2	2 4 3	39.32
2.290M		1 7 2	39.32
2.273	2	4 3 0	39.62
2.255M	3	1 0 4	39.94
2.255M		1 8 1	39.94
2.208M	3	3 6 1	40.83
2.208M		4 3 1	40.83
2.180M	2	0 3 4	41.39
2.180M		3 2 3	41.39
2.153	3	4 0 2	41.93
2.126M	9	0 8 2	42.49
2.126M		1 3 4	42.49
2.094	3	2 0 4	43.17
2.085	4	0 4 4	43.36
2.076	5	1 8 2	43.56
2.041+	5	3 6 2	44.35
2.041+		4 3 2	44.35
2.021	4	2 6 3	44.82
2.004M	3	1 7 3	45.22
2.004M		4 5 1	45.22
1.948M	4	2 9 0	46.58
1.948M		2 8 2	46.58
1.931	3	3 5 3	47.02

Potassium Chromium Sulfate, $\text{KCr}(\text{SO}_4)_2$

CAS registry no.
10141-00-1

Sample

The sample was prepared by heating $\text{KCr}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$ at 300 °C for several days. The crystallinity was improved by heating at 700 °C. However some impurity lines developed at this temperature, and therefore there may be minor errors in the intensities.

Color

Medium yellow green

Structure

Hexagonal, P321 (150), $Z = 1$, isostructural with other dehydrated alums such as $\text{KAl}(\text{SO}_4)_2$ and $\text{NH}_4\text{Al}(\text{SO}_4)_2$. The structure of these compounds was studied by Vegard and Maurstad [1928].

Lattice constants of this sample

$a = 4.7547(6)\text{Å}$
 $c = 8.054(2)$

$c/a = 1.6939$

Volume

157.68 Å^3

Density

(calculated) 2.983 g/cm^3

Figure of merit

$F_{19} = 74.6(0.010, 25)$

Additional pattern

1. PDF card 3-325 [Dow Chemical Co.]

Reference

Vegard L. and Maurstad, A. (1928). Z. Kristallogr, Kristallgeometrie Kristallphys. Kristallchem. 69, 519.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$					
Internal standard Si, $a = 5.43088 \text{ \AA}$					
$d(\text{\AA})$	τ	hkl			$2\theta(^\circ)$
8.06	40	0	0	1	10.97
4.115	15	1	0	0	21.58
3.664	100	1	0	1	24.27
2.879	75	1	0	2	31.04
2.685	10	0	0	3	33.34
2.377	35	1	1	0	37.81
2.280	8	1	1	1	39.50
2.0466	10	1	1	2	44.22
1.9948	4	2	0	1	45.43
1.8333	19	2	0	2	49.69
1.8085	13	1	0	4	50.42
1.7795	1	1	1	3	51.30
1.6110	2	0	0	5	57.13
1.5566	3	2	1	0	59.32
1.5364	10	1	1	4	60.18
1.5288	8	2	1	1	60.51
1.4514	13	2	1	2	64.11
1.4398	4	2	0	4	64.69
1.3724	12	3	0	0	68.29

Potassium Iron Sulfate (Yavapaiite), $\text{KFe}(\text{SO}_4)_2$

CAS registry no.
13718-65-5

Sample

The sample was precipitated by adding ethyl alcohol to a concentrated solution of KOH and $\text{Fe}(\text{OH})_3$ in H_2SO_4 .

Color

Colorless

Structure

Monoclinic, C2/m (12), $Z = 2$, [Hutton, 1959].

Lattice constants of this sample

$a = 8.155(1)\text{\AA}$
 $b = 5.1539(6)$
 $c = 7.877(1)$
 $\beta = 94.85(1)^\circ$

$a/b = 1.5823$
 $c/b = 1.5284$

Volume $\text{\AA}^3$
329.9

Density

(calculated) 2.890 g/cm^3

Figure of merit

$F_{30} = 56.2(0.017, 32)$

Reference intensity

$I/I_{\text{corundum}} = 0.99(3)$

Additional patterns

1. PDF card 12-632 [Hutton, 1959]
2. Corey and Sidhu [1945]

References

- Hutton, C. O. (1959). Amer. Mineral. 44, 1105.
Corey, R. C. and Sidhu, S. S. (1945). J. Am. Chem. Soc. 67, 1490.

CuK α_1 $\lambda = 1.540598 \text{\AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard Si, $a = 5.43088 \text{\AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
7.87	70	0 0 1	11.23	
4.354	11	1 1 0	20.38	
4.066	50	2 0 0	21.84	
3.885	70	-1 1 1	22.87	
3.739M	65	-2 0 1	23.78	
3.739M		1 1 1	23.78	
3.494	55	2 0 1	25.47	
2.985	100	-1 1 2	29.91	
2.854	50	1 1 2	31.32	
2.711	6	2 0 2	33.02	
2.617	6	0 0 3	34.24	
2.578	30	0 2 0	34.77	
2.449	1	0 2 1	36.67	
2.399	55	3 1 0	37.46	
2.343	2	-3 1 1	38.39	
2.288M	10	-2 0 3	39.34	
2.288M		-1 1 3	39.34	
2.197	3	1 1 3	41.04	
2.176	1	2 2 0	41.46	
2.154	13	0 2 2	41.91	
2.120M	18	-2 2 1	42.61	
2.120M		2 0 3	42.61	
2.073	2	2 2 1	43.63	
2.031	7	4 0 0	44.57	
2.007	1	-4 0 1	45.13	
1.980	2	3 1 2	45.79	
1.963	3	0 0 4	46.22	
1.941	13	-2 2 2	46.77	
1.927	3	4 0 1	47.13	
1.869M	12	-4 0 2	48.69	
1.869M		2 2 2	48.69	
1.837M	10	-3 1 3	49.58	
1.837M		0 2 3	49.58	
1.829	14	-2 0 4	49.81	
1.821	6	-1 1 4	50.05	
1.7597	6	1 1 4	51.92	
1.7450	11	4 0 2	52.39	
1.7111M	4	-2 2 3	53.51	
1.7111M		2 0 4	53.51	
1.7055	3	3 1 3	53.70	
1.6801	2	1 3 0	54.58	
1.6492	5	-1 3 1	55.69	
1.5836	2	-4 2 1	58.21	
1.5691	4	0 0 5	58.80	
1.5609	4	0 2 4	59.14	
1.5552	8	-1 3 2	59.38	
1.5500	8	5 1 0	59.60	
1.5353	4	1 3 2	60.23	
1.5137	12	-4 2 2	61.18	
1.4974M	5	5 1 1	61.92	

Potassium Iron Sulfate (Yavapaiite), $\text{KFe}(\text{SO}_4)_2$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.4913	9	-2 2 4	62.20
1.4827	2	-5 1 2	62.60
1.4657	6	3 1 4	63.41
1.4510	9	3 3 0	64.13
1.4453	10	4 2 2	64.41
1.4251+	2	2 2 4	65.44
1.4251+		-1 3 3	65.44
1.4036M	5	-4 2 3	66.57
1.4036M		5 1 2	66.57
1.3538M	2	6 0 0	69.36
1.3538M		-6 0 1	69.36
1.3234	3	4 2 3	71.19
1.3078	2	0 0 6	72.17
1.2936	1	-3 3 3	73.09
1.2885M	6	5 1 3	73.43
1.2885M		0 4 0	73.43
1.2682	6	-1 1 6	74.80
1.2669	9	-5 1 4	74.89
1.2281	1	2 4 0	77.69
1.2184	1	-2 4 1	78.43
1.2157	4	2 0 6	78.64
1.2086	2	2 4 1	79.19
1.1990M	2	6 2 0	79.95
1.1990M		-6 2 1	79.95

Potassium Nitrosyl Ruthenium Chloride, $K_2NORuCl_5$

Sample

These data are essentially the same pattern reported by Swanson et al. [1963], with minor revisions. The pattern has been indexed using crystallographic data published since 1963. The very small sample used then was a special preparation and is no longer available. The original sample had been prepared from a mixture of a soluble ruthenium salt with KCl and concentrated HNO_3 .

Color

Very dark red

Optical data

Biaxial(+), $N_\alpha = 1.750$, $N_\beta = 1.762$, $N_\gamma = 1.777$, $2V \sim 90^\circ$

Structure

Orthorhombic, Pmnb (62), $Z = 4$ [Khodeshova and Bokii, 1964; de Wolff, 1968].

Lattice constants of this sample

$a = 10.369(4) \text{ \AA}$
 $b = 13.296(4)$
 $c = 6.894(3)$

$a/b = 0.7798$
 $c/b = 0.5185$

Volume

$950.4 \text{ \AA}^3$

Density

(calculated) 2.701 g/cm^3

Figure of merit

$F_{30} = 54.6(0.018, 31)$

Additional patterns

1. PDF card 24-886, revised by PDF editors [Swanson et al., 1963]
2. Powder Diffraction Data, [1976]. The data is very nearly the same as that given here.

References

- Khodeshova, T. S. and Bokii, G. B. (1964). J. Struct. Chem. 5, 130.
Powder Diffraction Data from the Joint Committee on Powder Diffraction Standards Associateship at the National Bureau of Standards (1976).
 (The Joint Committee on Powder Diffraction Standards, Swarthmore, PA, 19081), p. 387.
 Swanson, H. E., Morris, M. C., Stinchfield, R. P., and Evans, E. H. (1963). Nat. Bur. Stand. U.S. Monogr. 25, Sec. 2, 29.
 de Wolff, P. M. (1968). J. Appl. Crystallogr. 1, 108.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp $25 \pm 1 \text{ }^\circ\text{C}$					
Internal standard Ag, $a = 4.08651 \text{ \AA}$					
$d(\text{\AA})$	I	hk ℓ			$2\theta(^\circ)$
6.13	8	0	1	1	14.44
5.75	100	1	0	1	15.40
5.61	95	1	2	0	15.79
5.28	17	1	1	1	16.78
5.19	25	2	0	0	17.06
4.790	30	0	2	1	18.51
4.352	1L	1	2	1	20.39
4.085	6	2	2	0	21.74
3.962	10	2	1	1	22.42
3.731	4	0	3	1	23.83
3.520	25	2	2	1	25.28
3.509	25	1	3	1	25.36
3.450	25	0	0	2	25.80
3.335	16	0	1	2	26.71
3.325	16	0	4	0	26.79
3.176	1L	1	1	2	28.07
3.091	12	3	0	1	28.86
3.068	11	3	2	0	29.08
3.028	15	2	3	1	29.48
2.996	14	0	4	1	29.80
2.934	7	1	2	2	30.44
2.879	13	1	4	1	31.04
2.871	13	2	0	2	31.13
2.805	35	2	1	2	31.88
2.800M	35	3	2	1	31.94
2.800M		2	4	0	31.94
2.720	35	0	3	2	32.90
2.632M	8	2	2	2	34.03
2.632M		1	3	2	34.03
2.594M	50	2	4	1	34.55
2.594M		4	0	0	34.55
2.481	1L	0	5	1	36.18
2.409	7	2	3	2	37.29
2.393	10	0	4	2	37.56
2.277	15	4	2	1	39.54
2.262	10	3	4	1	39.82
2.238	4	2	5	1	40.26
2.211	10	1	1	3	40.78
2.167	1L	1	6	0	41.65
2.137	1L	3	3	2	42.26
2.105	7	0	5	2	42.93
2.072	14	4	0	2	43.66
2.063	16	1	5	2	43.84
2.047	6	4	1	2	44.22
2.037	7	2	6	0	44.44
2.000	4	1	3	3	45.30
1.980	10	5	2	0	45.78
1.959	4	4	4	1	46.32
1.954	4	2	6	1	46.44

Silver Thiocyanate, AgCNS

CAS registry no.
506-64-9

Sample

The sample was precipitated by adding AgNO₃ solution to one of KCNS.

Color

Colorless

Structure

Monoclinic, C2/c (15), Z = 8, [Lindqvist, 1957].

Lattice constants of this sample

a = 8.774(2) Å
b = 7.972(1)
c = 8.182(2)
β = 93.78(2)°

a/b = 1.1006

c/b = 1.0263

Volume

571.1 Å³

Density

(calculated) 3.860 g/cm³

Figure of merit

F₃₀ = 54.6(0.014,39)

Reference intensity

I/I_{corundum} = 2.95(9)

Additional pattern

1. PDF card 12-382 [Pistorius, University of California, Los Angeles, Calif.]

Reference

Lindqvist, J. (1957). Acta Crystallogr.
10, 29.

d(Å)	I	hkl	2θ(°)
3.089	55	-2 0 2	28.88
2.945	10	2 2 0	30.33
2.891	12	2 0 2	30.91
2.850	9	0 2 2	31.36
2.810	19	-2 2 1	31.82
2.732	80	2 2 1	32.75
2.648	10	-3 1 1	33.82
2.542	14	1 3 0	35.28
2.512	13	-1 1 3	35.71
2.430	4	1 1 3	36.97
2.415	4	1 3 1	37.20
2.341	17	2 2 2	38.42
2.247	25	0 2 3	40.09
2.214	13	3 1 2	40.72
2.188	6	4 0 0	41.22
2.177	13	-1 3 2	41.44
2.140	4	1 3 2	42.20
2.046	4	-2 2 3	44.23
2.041	13	0 0 4	44.35
1.993M	2	-3 1 3	45.47
1.993M		0 4 0	45.47
1.965	2	3 3 0	46.15
1.9361	4	0 4 1	46.89
1.9191	4	4 2 0	47.33
1.9036	11	1 1 4	47.74
1.8991	11	-2 0 4	47.86
1.8920M	12	-4 2 1	48.05
1.8920M		3 3 1	48.05
1.8777	12	4 0 2	48.44
1.8737	8	3 1 3	48.55
1.8145	3	2 4 0	50.24
1.8051	5	2 0 4	50.52
1.7916	4	0 4 2	50.93
1.7818	4	-2 4 1	51.23
1.7607	2	2 4 1	51.89
1.7401	6	3 3 2	52.55
1.7105	1	5 1 0	53.53
1.6747	2	-2 4 2	54.77
1.6527	3	5 1 1	55.56
1.6405	5	2 4 2	56.01
1.6125	2	-4 2 3	57.07
1.6084	3	0 4 3	57.23
1.5772	2	1 3 4	58.47
1.5441M	2	-4 0 4	59.85
1.5441M		-1 5 1	59.85
1.5373	3	1 5 1	60.14
1.5275	4	4 2 3	60.57
1.4736	3	4 4 0	63.03
1.4618M	4	5 3 0	63.60
1.4618M		-4 4 1	63.60

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard Si, A = 5.43088 Å				
d(Å)	I	hkl	2θ(°)	
5.890	65	1 1 0	15.03	
4.674	100	1 1 1	18.97	
4.079	5	0 0 2	21.77	
3.577	25	0 2 1	24.87	
3.426	3	-1 1 2	25.99	

Sodium Aluminum Fluoride (Chiolite), $\text{Na}_5\text{Al}_3\text{F}_{14}$

Sample

The sample was made by treating NaHCO_3 and Al powder with HF solution. The precipitate was dried and heated to 450 °C for 10 minutes.

Color

Colorless

Structure

Tetragonal, $P4/mnc$ (128), $Z = 2$. The structure of $\text{Na}_5\text{Al}_3\text{F}_{14}$ was studied by Clausen [1936], and refined by Brosset [1938].

Lattice constants of this sample

$a = 7.0142(8) \text{ \AA}$
 $c = 10.400(3)$

$c/a = 1.4826$

Volume

$511.6 \text{ \AA}^3$

Density

(calculated) 2.998 g/cm^3

Figure of merit

$F_{30} = 61.2(0.014, 35)$

Reference intensity

$I/I_{\text{corundum}} = 1.15(5)$

Additional pattern

1. PDF card 2-749 [Clausen, 1936] [Brosset, 1938]

References

Brosset, C., (1938). Z. Anorg. Allgem. Chem. 238, 201.

Clausen, H., (1936). Z. Kristallogr. Kristallgeometrie Kristallphys. Kristallchem. 95, 394.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
5.81	20	1 0 1	15.24	
5.202	30	0 0 2	17.03	
4.962	10	1 1 0	17.86	
3.589	6	1 1 2	24.79	
3.505	15	2 0 0	25.39	
3.107	3	1 0 3	28.71	
3.004	18	2 1 1	29.72	
2.909	100	2 0 2	30.71	
2.601	7	0 0 4	34.46	
2.481	8	2 2 0	36.18	
2.325	50	2 1 3	38.69	
2.303	6	1 1 4	39.08	
2.282	8	3 0 1	39.46	
2.239	8	2 2 2	40.24	
2.219	12	3 1 0	40.62	
2.170	20	3 1 1	41.58	
2.089	2	2 0 4	43.27	
2.040	2	3 1 2	44.38	
2.002	25	2 1 4	45.27	
1.996	20	1 0 5	45.39	
1.946	11	3 2 0	46.64	
1.940	7	3 0 3	46.80	
1.7939	25	2 2 4	50.86	
1.7537	23	4 0 0	52.11	
1.7340M	5	2 1 5	52.75	
1.7340M		0 0 6	52.75	
1.7020	2	4 1 0	53.82	
1.6970	2	3 2 3	53.99	
1.6875	6	3 1 4	54.32	
1.6786	6	4 1 1	54.63	
1.6615	3	4 0 2	55.24	
1.6538	3	3 3 0	55.52	
1.6167	6	4 1 2	56.91	
1.5684	3	4 2 0	58.83	
1.5538M	25	3 0 5	59.44	
1.5538M		2 0 6	59.44	
1.5013	19	4 2 2	61.74	
1.4532M	7	4 0 4	64.02	
1.4532M		1 0 7	64.02	
1.4284	1	4 2 3	65.27	
1.4208M	1	3 2 5	65.66	
1.4208M		2 2 6	65.66	
1.4023	2	4 3 0	66.64	
1.3945	4	3 3 4	67.06	

Sodium Borate, Na₂B₄O₇

CAS registry no.
1330-43-4

Sample

The sample was made by heating Na₂B₄O₇·10H₂O
at 500 °C for 72 hours.

Color

Colorless

Structure

Triclinic, P $\bar{1}$ (2), Z = 4. The structure was
refined by Krogh-Moe [1974].

Lattice constants of this sample

a = 8.646(4) Å
b = 10.506(4)
c = 6.572(2)
 α = 94.95(2)°
 β = 90.93(4)
 γ = 93.18(3)

a/b = 0.8229

c/b = 0.6255

Volume

593.7 Å³

Density

(calculated) 2.252 g/cm³

Figure of merit

F₃₀ = 44.4 (0.014,49)

Additional patterns

1. PDF card 9-14 [Dasgupta and Banerjee, 1955]
2. PDF card 27-656 [Smith et al., Annual Report
to the Joint Committee on Powder Diffraction
Standards, (1974)]

References

- Dasgupta, D. R. and Banerjee, B. K. (1955). J.
Chem. Phys. 23, 2189.
Krogh-Moe, J. (1974). Acta Crystallogr. B30,
578.

CuK α ₁ λ = 1.540598 Å; temp. 25±1 °C

Internal standard Si, a = 5.43088 Å

d(Å)	I	hkl	2 θ (°)
10.46	7	0 1 0	8.45
8.64	5	1 0 0	10.23
6.55	20	0 0 1	13.51
6.49	35	1 1 0	13.63
5.78	10	0 -1 1	15.32
5.35	25	0 1 1	16.57
5.23	50	0 2 0	16.93
5.17	17	1 0 1	17.13
4.83	4	1 -1 1	18.34
4.77	4	-1 -1 1	18.58

d(Å)	I	hkl	2 θ (°)
4.64	8	-1 1 1	19.12
4.360	30	1 2 0	20.35
4.321	20	2 0 0	20.54
4.072	25	-2 1 0	21.81
3.926	100	0 2 1	22.63
3.879	12	1 -2 1	22.91
3.779	2	-1 -2 1	23.52
3.647	6	-1 2 1	24.39
3.484M	19	0 3 0	25.55
3.484M		2 -1 1	25.55
3.431+	35	-2 -1 1	25.95
3.431+		-2 1 1	25.95
3.297	30	-1 3 0	27.02
3.235	16	2 2 0	27.55
3.205	10	0 -1 2	27.81
3.086M	16	2 -2 1	28.91
3.086M		-1 0 2	28.91
3.035M	10	1 -3 1	29.41
3.035M		1 0 2	29.41
2.998	8	1 -1 2	29.78
2.972	8	0 3 1	30.04
2.859	11	-1 3 1	31.26
2.841	17	1 1 2	31.46
2.815	35	-3 1 0	31.76
2.790	20	-2 3 0	32.05
2.753	16	1 -2 2	32.50
2.670	45	0 2 2	33.54
2.580M	16	2 0 2	34.74
2.580M		-3 2 0	34.74
2.541	9	-1 4 0	35.29
2.513	15	-2 3 1	35.70
2.459M	50	1 4 0	36.51
2.459M		3 2 0	36.51
2.412	8	1 -3 2	37.25
2.374	6	-1 -4 1	37.87
2.287	8	0 3 2	39.37
2.240M	6	-1 3 2	40.22
2.240M		1 4 1	40.22
2.176	13	0 -1 3	41.47
2.160M	11	3 3 0	41.79
2.160M		4 0 0	41.79
2.134	16	0 -4 2	42.32
2.121M	20	-2 -4 1	42.60
2.121M		-2 4 1	42.60
2.087M	6	4 1 0	43.31
2.087M		1 -4 2	43.31
2.052	30	3 -2 2	44.10
2.040M	16	0 -5 1	44.37
2.040M		4 0 1	44.37
2.034M	16	-4 1 1	44.50
2.034M		-4 2 0	44.50
2.022	25	1 -2 3	44.79
1.936+	30	-4 2 1	46.90
1.936+		-1 4 2	46.90
1.923	25	-1 2 3	47.24

Sodium Borate, $\text{Na}_2\text{B}_4\text{O}_7$ (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.882+	10	-4 3 0	48.33
1.882+		3 4 0	48.33
1.877	12	-3 4 1	48.45
1.870M	10	1 5 1	48.66
1.870M		-2 -2 3	48.66
1.865	10	2 1 3	48.80
1.837M	4	-3 3 2	49.59
1.837M		0 -5 2	49.59
1.821M	8	-4 0 2	50.05
1.821M		-2 4 2	50.05
1.807	13	-2 2 3	50.46
1.784	4	4 0 2	51.15
1.746	7	3 3 2	52.36
1.724	6	1 -4 3	53.09

Sodium Borate Hydroxide Hydrate (Borax), $\text{Na}_2\text{B}_4\text{O}_5(\text{OH})_2 \cdot 8\text{H}_2\text{O}$

Synonym

1. Tincal

CAS registry no.

1303-96-4

Sample

The sample from Fisher Scientific Co., Fairlawn, NJ was recrystallized from aqueous solution. It was somewhat unstable in dry air, losing H_2O to become the 5-hydrate. Because of this instability it was impossible to obtain consistent results with the intensity measurements.

Color

Colorless

Structure

Monoclinic, A2/a (15), $Z = 4$. The structure of borax was studied by Morimoto [1956], and refined by Levy and Lisensky [1978] using neutron diffraction.

Lattice constants of this sample

$a = 12.219(3) \text{ \AA}$
 $b = 10.665(3)$
 $c = 11.884(2)$
 $\beta = 106.64(2)^\circ$

$a/b = 1.1457$
 $c/b = 1.1143$

Volume

$1483.8 \text{ \AA}^3$

Density

(calculated) 1.709 g/cm^3

Figure of merit

$F_{30} = 44.2(0.014, 48)$

Additional patterns

1. PDF card 12-258 [Cipriani, 1958]
2. PDF card 24-1055 [Thomas and Soustelle, 1970]
3. Minder, W. [1935]

References

- Cipriani, C. (1958). Atti Soc. Toscana Sci. Natur. Pisa Mem. Processi Verb. Ser. A 65, 284.
 Levy, H. A. and Lisensky, G. C. (1978). Acta Crystallogr. B34, 3502.
 Minder, W. (1935). Z. Kristallogr. Kristallgeometrie Kristallphys. Kristallchem. 92, 301.
 Morimoto, N. (1956). Mineral J. Japan 2, 1.
 Thomas, G. and Soustelle, M. (1970). Bull. Soc. Chim. Fr. 1970, 4202.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$	
7.78	6	0 1 1	11.36	
7.17	11	-1 1 1	12.34	
5.97	16	1 1 1	14.83	
5.84	40	2 0 0	15.15	
5.69	50	0 0 2	15.56	
5.33	7	0 2 0	16.61	
5.20	20	-2 1 1	17.04	
4.860	80	1 2 0	18.24	
3.936M	45	-1 2 2	22.57	
3.936M		2 2 0	22.57	
3.889	1	0 2 2	22.85	
3.596	7	2 0 2	24.74	
3.577M	8	0 1 3	24.87	
3.577M		-2 2 2	24.87	
3.498M	5	-2 1 3	25.44	
3.498M		1 2 2	25.44	
3.391	2	0 3 1	26.26	
3.334	3	-1 3 1	26.72	
3.187M	8	1 3 1	27.97	
3.187M		1 1 3	27.97	
3.075	8	-3 2 2	29.01	
2.980	40	2 2 2	29.96	
2.929	10	4 0 0	30.50	
2.848	65	0 0 4	31.39	
2.833	60	2 3 1	31.55	
2.740	1	2 1 3	32.66	
2.676	4	-3 3 1	33.46	
2.665	9	0 4 0	33.60	
2.644M	5	-1 3 3	33.88	
2.644M		-4 1 3	33.88	
2.576	100	4 1 1	34.80	
2.565M	95	-2 3 3	34.95	
2.565M		4 2 0	34.95	
2.520	2	3 2 2	35.60	
2.459	11	3 3 1	36.51	
2.387	4	-3 3 3	37.66	
2.345	30	4 0 2	38.36	
2.341	25	3 1 3	38.43	
2.335	15	-2 4 2	38.53	
2.313	5	2 0 4	38.91	
2.258	1	-5 1 3	39.90	
2.218	9	2 3 3	40.65	
2.201M	8	3 4 0	40.97	
2.201M		-4 2 4	40.97	
2.174	5	-3 4 2	41.51	
2.162	6	-4 3 3	41.74	
2.146	8	4 2 2	42.07	
2.122	2	2 2 4	42.56	
2.098	4	0 5 1	43.09	
2.081	10	-1 5 1	43.46	

Sodium Borate Hydroxide Hydrate (Borax), $\text{Na}_2\text{B}_4\text{O}_5(\text{OH})_2 \cdot 8\text{H}_2\text{O}$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
2.076	7	-4 1 5	43.57
2.044	7	1 5 1	44.27
2.033	16	-6 0 2	44.52
2.015	8	4 1 3	44.96
1.989	2	3 3 3	45.58
1.983M	3	-1 4 4	45.71
1.983M		-4 4 2	45.71
1.969M	5	-1 3 5	46.05
1.969M		-2 3 5	46.05
1.950M	9	3 4 2	46.53
1.950M		6 0 0	46.53
1.913M	12	-3 3 5	47.50
1.913M		2 1 5	47.50
1.898	11	0 0 6	47.89
1.855M	9	5 3 1	49.08
1.855M		-2 2 6	49.08
1.833	12	6 2 0	49.71
1.790	4	-4 4 4	50.98
1.777M	5	4 3 3	51.39
1.777M		0 6 0	51.39
1.758M	10	-6 3 1	51.98
1.758M		1 6 0	51.98
1.748M	3	2 4 4	52.30
1.748M		-4 5 1	52.30
1.731	2	-6 3 3	52.84
1.705M	8	2 5 3	53.73
1.705M		2 3 5	53.73
1.701M	11	-7 1 3	53.84
1.701M		2 6 0	53.84
1.6613	2	-3 1 7	55.25
1.6585+	2	-7 2 2	55.35
1.6585+		1 6 2	55.35
1.6159M	2	-4 1 7	56.94
1.6159M		-6 4 2	56.94
1.5952	1	7 2 0	57.75
1.5841M	1	-1 5 5	58.19
1.5841M		-2 5 5	58.19
1.5740M	2	6 4 0	58.60
1.5740M		7 1 1	58.60
1.5457+	2	0 4 6	59.78
1.5457+		-5 1 7	59.78
1.5313M	2	-2 3 7	60.40
1.5313M		5 2 4	60.40
1.5197M	3	4 6 0	60.91
1.5197M		-3 3 7	60.91

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.5177M	3	-1 3 7	61.00
1.5177M		-2 6 4	61.00
1.5083	3	0 6 4	61.42
1.4853	2	-4 3 7	62.48
1.4538	1	-4 0 8	63.99
1.4303M	5	6 3 3	65.17
1.4303M		-5 3 7	65.17
1.4233	4	0 0 8	65.53
1.4153	3	2 4 6	65.95
1.3608M	2	-5 2 8	68.95
1.3608M		-6 3 7	68.95

Sodium Silicon Fluoride (Malladrite), Na₂SiF₆

Sample

The sample was from Fisher Scientific Co.,
Fairlawn, NJ.

Color

Colorless

Structure

Hexagonal, P321 (150), Z = 3, isostructural
with Na₂GeF₆ and other hexafluorides. The
structure is similar to that of K₂S₂O₆. The
structure of Na₂SiF₆ was determined by Zalkin
et al. [1964].

Lattice constants of this sample

a = 8.8659(7) Å
c = 5.0433(5)

c/a = 0.5688

Volume

343.3 Å³

Density

(calculated) 2.729 g/cm³

Figure of merit

F₃₀ = 76.6(0.012,34)

Reference intensity

I/I_{corundum} = 0.87(2)

Additional patterns

1. PDF card 8-36 [African Explosives and Chem.
Ind., Transvaal, South Africa]
2. PDF card 19-1193 [U.S. Bureau of Mines,
Albany, OR]
3. PDF card 25-1166 [Royal Ontario Museum,
Ontario, Canada], pattern is actually
sylvite (KCl)
4. Cox [1954]
5. Cipriani [1955]

References

- Cipriani, C. (1955). Rend. Soc. Mineral.
Ital. 10, 253.
Cox, B. (1954). J. Chem. Soc. 1954, 3251.
Zalkin, A., Forrester, J. D., and Templeton,
D. H. (1964). Acta Crystallogr. 17, 1408.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C			
Internal standard Si, a = 5.43088 Å			
d(Å)	I	hkl	2θ(°)
5.041	13	0 0 1	17.58
4.429	100	1 1 0	20.03
4.213	95	1 0 1	21.07
3.331	90	1 1 1	26.74
3.056	50	2 0 1	29.20
2.902	9	2 1 0	30.79
2.558	5	3 0 0	35.05
2.521	7	0 0 2	35.58
2.516	15	2 1 1	35.66
2.394	1	1 0 2	37.54
2.281	90	3 0 1	39.47
2.216	6	2 2 0	40.68
2.191	4	1 1 2	41.16
2.129	3	3 1 0	42.42
2.107	4	2 0 2	42.88
2.030	9	2 2 1	44.61
1.9626	6	3 1 1	46.22
1.9043	10	2 1 2	47.72
1.7962	55	3 0 2	50.79
1.7616	4	3 2 0	51.86
1.6806	2	0 0 3	54.56
1.6629	20	3 2 1	55.19
1.6419	4	1 0 3	55.96
1.6269	9	3 1 2	56.52
1.5904	20	4 1 1	57.94
1.5718	4	1 1 3	58.69
1.5404	3	2 0 3	60.01
1.5268	3	4 0 2	60.60
1.4776	11	3 3 0	62.84
1.4695	5	5 0 1	63.23
1.4548	8	2 1 3	63.94
1.4514	8	4 2 0	64.11
1.4049	3	3 0 3	66.50
1.3951M	8	4 1 2	67.03
1.3951M		4 2 1	67.03
1.3391	1	2 2 3	70.23
1.3302	3	5 1 1	70.77
1.3194	2	3 1 3	71.44
1.2751	1	3 3 2	74.33
1.2643	2	4 0 3	75.07
1.2609	2	0 0 4	75.31
1.2293	4	5 2 0	77.60
1.2160	3	3 2 3	78.61
1.2099	2	5 1 2	79.09
1.1869	1	4 1 3	80.93
1.1566	1	2 1 4	83.52
1.1411	2	6 0 2	84.92
1.1312	3	3 0 4	85.84

Sodium Titanium Oxide, Na₂Ti₃O₇

CAS registry no.
12034-36-5

Sample

The sample was prepared by dry heating Na₂CO₃ + TiO₂ (anatase) at 1250 °C. Since Na evaporated, NaOH plus moisture was added to make a paste. The sample was then heated for 45 minutes at 1000 °C and then reheated for 17 hours at 950 °C after correcting with TiO₂.

Color

Colorless

Structure

Monoclinic, P2₁/m (11), Z = 2. The structure was determined by Andersson and Wadsley [1961].

Lattice constants of this sample

a = 9.1279(7) Å
b = 3.8032(5)
c = 8.5621(7)
β = 101.60(1)°

a/b = 2.4001
c/b = 2.2513

Volume

291.17 Å³

Density

(calculated) 3.441 g/cm³

Figure of merit

F₃₀ = 115.3(0.008,32)

Additional pattern

1. PDF card 14-85 [Andersson and Wadsley, 1961]

Reference

Andersson, S. and Wadsley, A. D. (1961).
Acta Crystallogr. 14, 1245.

CuKα ₁ λ = 1.540598 Å; temp 25±1 °C				
Internal standard W, a = 3.16524 Å				
d(Å)	I	hkl	2θ(°)	
8.95	7	1 0 0	9.87	
8.40	100	0 0 1	10.52	
6.84	4	-1 0 1	12.93	
5.587	30	1 0 1	15.85	
4.469	7	2 0 0	19.85	
4.189	2	0 0 2	21.19	
4.130	5	-1 0 2	21.50	
3.652	2	2 0 1	24.35	
3.535	1	1 0 2	25.17	
3.464	35	0 1 1	25.70	
3.422	5	-2 0 2	26.02	
3.142	18	1 1 1	28.38	
3.005	7	-3 0 1	29.71	
2.982	20	3 0 0	29.94	
2.897	6	2 1 0	30.84	
2.856	7	-2 1 1	31.29	
2.817	8	0 1 2	31.74	
2.799M	12	-1 1 2	31.95	
2.799M		0 0 3	31.95	
2.791	7	2 0 2	32.04	
2.699	5	-3 0 2	33.16	
2.645	8	3 0 1	33.86	
2.635	9	2 1 1	34.00	
2.618	16	-2 0 3	34.22	
2.588	7	1 1 2	34.63	
2.543	6	-2 1 2	35.26	
2.527	6	1 0 3	35.49	
2.358	3	-3 1 1	38.13	
2.346	4	3 1 0	38.33	
2.282	1	-3 0 3	39.46	
2.274	1L	-1 1 3	39.60	
2.251M	1	0 1 3	40.02	
2.251M		2 1 2	40.02	
2.236	2	4 0 0	40.31	
2.172	2	3 1 1	41.54	
2.158	1	-2 1 3	41.82	
2.1050	3	1 1 3	42.93	
2.0967	4	0 0 4	43.11	
2.0643	35	-2 0 4	43.82	
2.0598	40	4 0 1	43.92	
1.9558M	6	-3 1 3	46.39	
1.9558M		1 0 4	46.39	
1.9271	2	4 1 0	47.12	
1.9221	1	3 1 2	47.25	
1.9009	20	0 2 0	47.81	
1.8607M	2	3 0 3	48.91	
1.8607M		1 2 0	48.91	
1.8547	3	0 2 1	49.08	
1.8261M	2	4 0 2	49.90	
1.8261M		-5 0 1	49.90	

Sodium Titanium Oxide, $\text{Na}_2\text{Ti}_3\text{O}_7$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.8149	10	-2 1 4	50.23
1.8105	7	4 1 1	50.36
1.7998	2	1 2 1	50.68
1.7670	1	2 0 4	51.69
1.7333	1	-4 1 3	52.77
1.7279	1L	-1 2 2	52.95
1.7120	1	-1 0 5	53.48
1.6815	1	5 0 1	54.53
1.6716	1	3 1 3	54.88
1.6663	3	-5 0 3	55.07
1.6459+	7	4 1 2	55.81
1.6459+		-5 1 1	55.81
1.6112	2	-5 1 2	57.12
1.6071M	3	-3 2 1	57.28
1.6071M		-3 0 5	57.28
1.6030M	5	3 2 0	57.44
1.6030M		2 1 4	57.44
1.5964	2	4 0 3	57.70
1.5797	1	-1 2 3	58.37
1.5612	5	-1 1 5	59.13
1.5413	6	-2 1 5	59.97
1.5378M	6	5 1 1	60.12
1.5378M		5 0 2	60.12
1.5195M	4	-5 0 4	60.92
1.5195M		1 2 3	60.92
1.5024	2	-6 0 2	61.69
1.4934	1	-4 0 5	62.10
1.4902	1	6 0 0	62.25
1.4759	4	2 0 5	62.92
1.4720	6	4 1 3	63.11
1.4410	6	-6 0 3	64.63
1.4257M	2	-1 0 6	65.41
1.4257M		5 1 2	65.41
1.4117M	5	-6 1 1	66.14
1.4117M		-5 1 4	66.14
1.3980M	14	-2 2 4	66.87
1.3980M		0 0 6	66.87
1.3969M	14	-6 1 2	66.93
1.3969M		4 2 1	66.93
1.3874	1	6 1 0	67.45
1.3759M	6	-3 0 6	68.09
1.3759M		2 1 5	68.09
1.3631	2	1 2 4	68.82
1.3507	1	3 0 5	69.54
1.3473	1L	-6 1 3	69.74
1.3347	1	-1 1 6	70.50

Strontium Chromium Oxide, Sr_2CrO_4

CAS registry no.
12206-20-1

Sample

The sample was made by heating Cr_2O_3 with SrCrO_4 and $\text{Sr}(\text{OH})_2$ under N_2 at about 1000 °C for about 1/2 hour.

Color

Black

Structure

Orthorhombic, $\text{P2}_1\text{nb}$ (33), $Z = 8$. The structure of Sr_2CrO_4 has been studied by Wilhelmi [1967].

Lattice constants of this sample

$a = 10.007(2) \text{ \AA}$
 $b = 14.194(3)$
 $c = 5.809(1)$

$a/b = 0.7050$

$c/b = 0.4093$

Volume

$825.1 \text{ \AA}^3$

Density

(calculated) 4.689 g/cm^3

Figure of merit

$F_{30} = 66.2(0.012, 38)$

Polymorphism

Kafalas and Longo [1972] report that Sr_2CrO_4 transforms to a K_2NiF_4 structure at 65 kbars and 1000 °C.

Additional pattern

1. PDF card 19-1206 [Wilhelmi, 1967]

References

Kafalas, J. A. and Longo, J. M. (1972).

J. Solid State Chem. 4, 55.

Wilhelmi, K.-A., (1967). Ark. Kemi 26, 157.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Si, $a = 5.43088 \text{ \AA}$				
d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$	
5.024	3	1 0 1	17.64	
5.007	2	2 0 0	17.70	
3.663M	4	0 3 1	24.28	
3.663M		2 1 1	24.28	
3.448	3	1 3 1	25.82	
3.343M	17	1 4 0	26.64	
3.343M		2 2 1	26.64	
3.029	19	0 4 1	29.47	
3.021	16	3 2 0	29.54	
2.901	90	1 4 1	30.80	
2.892M	100	2 4 0	30.89	
2.892M		3 0 1	30.89	
2.848	8	0 1 2	31.39	
2.738	2	1 1 2	32.68	
2.680	1	3 2 1	33.41	
2.592	5	2 4 1	34.58	
2.550	2	0 5 1	35.16	
2.512	3	2 0 2	35.72	
2.472M	4	2 1 2	36.31	
2.472M		1 5 1	36.31	
2.430	20	3 4 0	36.96	
2.403	2	1 3 2	37.39	
2.368M	5	2 2 2	37.97	
2.368M		0 6 0	37.97	
2.360	6	4 2 0	38.10	
2.303	7	1 6 0	39.09	
2.273	1	2 5 1	39.61	
2.267	1	4 1 1	39.72	
2.247	1	0 4 2	40.10	
2.243	1L	3 4 1	40.18	
2.219	6	2 3 2	40.63	
2.193M	5	1 4 2	41.13	
2.193M		0 6 1	41.13	
2.187	8	4 2 1	41.25	
2.165	3	3 1 2	41.69	
2.139	3	2 6 0	42.22	
2.092	6	3 2 2	43.20	
2.050	18	2 4 2	44.15	
1.9878	3	3 3 2	45.60	
1.9252	9	5 2 0	47.17	
1.8916	4	5 0 1	48.06	
1.8791	3	4 1 2	48.40	
1.8636	9	3 4 2	48.83	
1.8344	1	0 6 2	49.66	
1.8038	2	1 6 2	50.56	
1.7916M	3	0 3 3	50.93	
1.7916M		2 1 3	50.93	
1.7743	1	0 8 0	51.46	
1.7641	3	1 3 3	51.78	
1.7500	4	2 2 3	52.23	

Strontium Chromium Oxide, Sr_2CrO_4 - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.7438	5	5 4 0	52.43
1.7340	3	3 5 2	52.75
1.7221	1	2 6 2	53.14
1.6996	3	0 4 3	53.90
1.6872	1	2 3 3	54.33
1.6744	11	3 0 3	54.78
1.6716	13	4 4 2	54.88
1.6632M	6	3 1 3	55.18
1.6632M		0 7 2	55.18
1.6486	7	4 6 1	55.71
1.6368	2	5 1 2	56.15
1.6087	7	2 4 3	57.22
1.6058	4	5 2 2	57.33
1.5789M	2	1 5 3	58.40
1.5789M		3 3 3	58.40
1.5658	5	3 8 0	58.94
1.5636	2	6 2 1	59.03

Thallium, α -Tl

CAS registry no.
7440-28-0

Sample

The sample was obtained from the Fisher Scientific Co., Silver Spring, MD.

Color

Gray metallic

Structure

Hexagonal, $P6_3/mmc$ (194), $Z = 2$, isostructural with magnesium. The structure of thallium was studied by Sekito [1930].

Lattice constants of this sample

$$a = 3.4568(3) \text{ \AA}$$

$$c = 5.5259(5)$$

$$c/a = 1.5986$$

Volume

$$57.185 \text{ \AA}^3$$

Density

(calculated) 11.869 g/cm³

Figure of merit

$$F_{22} = 76.9(0.012, 24)$$

Polymorphism

Hexagonal thallium transposes to a body-centered cubic phase above 230 °C [Lipson and Stokes, 1941]. Becker and Ebert [1923] had reported a tetragonal phase which later was shown to be hexagonal.

Additional patterns

1. PDF 1-1084 [Hanawalt et al., 1938]
2. Barrett [1958]
3. Sekito [1930]
4. Suganuma [1960]

References

- Barrett, C. S. (1958). Phys. Rev. 110, 1071.
 Becker, K. and Ebert, F. (1923). Z. Phys. 16, 165.
 Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
 Lipson, H. and Stokes, A. R. (1941). Nature 148, 437.
 Sekito, S. (1930). Z. Kristallogr. Kristallgeometrie Kristallphys. Kristallchem. 74, 189.
 Suganuma, R. (1960). J. Phys. Soc. Japan. 15, 1395.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$			
Internal standard W, $a = 3.16524 \text{ \AA}$			
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
2.991	20	1 0 0	29.85
2.760	50	0 0 2	32.41
2.631	100	1 0 1	34.05
2.030	20	1 0 2	44.59
1.7285	18	1 1 0	52.93
1.5687	35	1 0 3	58.82
1.4965	3	2 0 0	61.96
1.4651	20	1 1 2	63.44
1.4447	14	2 0 1	64.44
1.3820	8	0 0 4	67.75
1.3159	3	2 0 2	71.66
1.2544	7	1 0 4	75.77
1.1617	9	2 0 3	83.07
1.1084	10	2 1 1	88.05
1.0792	11	1 1 4	91.09
1.0473	2	2 1 2	94.70
1.0368	16	1 0 5	95.97
1.0151	3	2 0 4	98.72
.9980	3	3 0 0	101.04
.9640	6	2 1 3	106.08
.9386	3	3 0 2	110.30
.9210	3	0 0 6	113.52

Thallium Fluoride, TlF

CAS registry no.
7789-27-7

Sample

The sample was obtained from the City Chemical Co., New York, NY.

Color

Colorless

Structure

Orthorhombic, $Z = 4$. Pca^* is consistent with the absences and has been used without any verifying data. Ketelaar [1935] determined that TlF belonged to the space group $Fmmm$ (69). However, data reported here, as well as data from another researcher, Harshaw (priv. comm.), have a number of weak extra lines which do not fit that space group. These extra lines were found to persist after the sample had been refluxed.

Lattice constants of this sample

$a = 5.4910(4) \text{ \AA}$
 $b = 6.0974(3)$
 $c = 5.1855(4)$

$a/b = 0.9006$
 $c/b = 0.8504$

Volume

$173.61 \text{ \AA}^3$

Density

(calculated) 8.546 g/cm^3

Figures of merit

$F_{30} = 44.6(0.010, 70)$
 $M_{20} = 71.0$

Reference intensity

$I/I_{\text{corundum}} = 3.2(3)$

Additional pattern

1. PDF 3-0483 [Ketelaar, 1935]

Reference

Ketelaar, J. A. A. (1935). Z. Kristallogr. Kristallgeometrie Kristallphys. Kristallchem. 92, 30.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
6.095	1	0 1 0	14.52	
3.205	100	1 1 1	27.81	
3.047	45	0 2 0	29.29	
2.748	16	2 0 0	32.56	
2.593	16	0 0 2	34.56	
2.426	1	2 0 1	37.02	
2.370	2	1 2 1	37.93	
2.0400	13	2 2 0	44.37	
1.9755	11	0 2 2	45.90	
1.8857	11	2 0 2	48.22	
1.7889	20	1 3 1	51.01	
1.6604	8	3 1 1	55.28	
1.6033	10	2 2 2	57.43	
1.5916	8	1 1 3	57.89	
1.5243	4	0 4 0	60.71	
1.4134	1L	1 4 1	66.05	
1.3727	1	4 0 0	68.27	
1.3327	3	2 4 0	70.62	
1.3143	5	0 4 2	71.76	
1.2965M	1	4 1 1	72.90	
1.2965M		0 0 4	72.90	
1.2807	4	1 3 3	73.95	
1.2517	1	4 2 0	75.96	
1.2307	3	3 1 3	77.50	
1.2194	1L	0 5 0	78.35	
1.2129	1	4 0 2	78.85	
1.1930	1	0 2 4	80.43	
1.1897	1	4 1 2	80.70	
1.1854	3	2 4 2	81.06	
1.1717	1	3 4 0	82.21	
1.1601	4	1 5 1	83.21	
1.1273	1	4 2 2	86.21	
1.1111	1L	4 3 1	87.78	
1.1037	1L	0 5 2	88.52	
1.0940	2	2 2 4	89.52	
1.0690	2	3 3 3	92.20	
1.0583	2	5 1 1	93.42	
1.0201	1	4 4 0	98.07	
1.0164	1	0 6 0	98.56	
.9959	1	3 5 1	101.33	
.9876	1L	0 4 4	102.52	
.9805	1	1 5 3	103.55	
.9719	1L	1 4 4	104.85	
.9530	1	2 6 0	107.85	
.9493	1	4 4 2	108.47	
.9461	1	0 6 2	109.01	
.9291	1	2 4 4	112.00	
.9111	1	1 3 5	115.45	
.9004	1	4 2 4	117.64	
.8945	1	2 6 2	118.89	
.8751	1	3 5 3	123.34	
.8486	1	1 7 1	130.38	

Thallium Hydrogen Phthalate, C₈H₅O₄Tl

Synonyms

1. Thallous acid phthalate
2. Thallium hydrogen-o-phthalate

CAS registry no.

29050-41-7

Sample

The sample was obtained as fragments of a single crystal, originally from Quartz Products, Plainfield, NJ.

Color

Colorless

Structure

Orthorhombic, Pca2₁ (29), Z = 4, by analogy with C₈H₅O₄Rb. The structure of C₈H₅O₄Rb was refined by Smith [1975].

Lattice constants of this sample

a = 10.050(2) Å
b = 12.882(2)
c = 6.622(1)

a/b = 0.7802

c/b = 0.5140

Volume

857.2 Å³

Density

(calculated) 2.863 g/cm³

Figure of merit

F₃₀ = 54.7(0.014,40)

Reference

Smith, R. A. (1975). Acta Crystallogr. **B31**, 2347.

CuK α_1 λ = 1.540598 Å; temp. 25 $\pm$ 1 °C				
Internal standard Si, a = 5.43088 Å				
d(Å)	I	hkl	2 θ (°)	
12.91	100	0 1 0	6.84	
7.91	1L	1 1 0	11.18	
6.44	11	0 2 0	13.73	
5.43	3	1 2 0	16.32	
5.084	4	1 1 1	17.43	
5.029	2	2 0 0	17.62	
4.684	1	2 1 0	18.93	
4.296	3	0 3 0	20.66	
4.197	4	1 2 1	21.15	
4.005	12	2 0 1	22.18	
3.952	9	1 3 0	22.48	
3.824	25	2 1 1	23.24	
3.397	25	2 2 1	26.21	
3.311	2	0 0 2	26.91	
3.220	10	0 4 0	27.68	
3.066	5	1 4 0	29.10	
2.972	4	3 2 0	30.04	
2.944	8	0 2 2	30.34	
2.930	7	2 3 1	30.48	
2.825	3	1 2 2	31.65	
2.783	6	1 4 1	32.14	
2.708M	2	3 2 1	33.05	
2.708M		2 4 0	33.05	
2.643	3	3 3 0	33.89	
2.624	2	0 3 2	34.14	
2.577	1L	0 5 0	34.78	
2.538	2	1 3 2	35.34	
2.510M	4	4 0 0	35.74	
2.510M		2 4 1	35.74	
2.496	2	1 5 0	35.95	
2.466	3	4 1 0	36.41	
2.336	7	1 5 1	38.51	
2.323M	4	2 3 2	38.73	
2.323M		3 4 0	38.73	
2.250	2	1 4 2	40.05	
2.210	3	3 2 2	40.79	
2.169	1L	4 3 0	41.61	
2.147	1L	0 6 0	42.05	
2.099	1L	1 6 0	43.05	
2.063	3	3 3 2	43.84	
2.060	2	4 3 1	43.91	
2.042	3	3 5 0	44.32	
2.021	2	2 0 3	44.80	
2.001	6	1 6 1	45.28	
1.997	6	2 1 3	45.38	
1.978	3	4 1 2	45.85	
1.952	1L	3 5 1	46.48	
1.927M	2	2 2 3	47.12	
1.927M		1 3 3	47.12	
1.911	2	4 2 2	47.54	

Thallium Hydrogen Phthalate, $C_8H_5O_4Tl$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.901M	3	5 1 1	47.80
1.901M		3 4 2	47.80
1.840	1L	0 7 0	49.49
1.829	1	2 3 3	49.82
1.809	2	1 7 0	50.40
1.792	1	1 4 3	50.93
1.773	1L	1 6 2	51.49
1.755	1	5 3 1	52.07
1.746	1	1 7 1	52.35
1.7392	2	3 5 2	52.58
1.6996	1L	4 4 2	53.90
1.6953	1L	2 6 2	54.05
1.6713	1L	2 7 1	54.89
1.6522M	2	1 5 3	55.58
1.6522M		5 4 1	55.58
1.6416	1	0 1 4	55.97
1.6198M	1L	6 2 0	56.79
1.6198M		1 1 4	56.79
1.6094M	1	0 8 0	57.19
1.6094M		0 7 2	57.19
1.5861	1	3 6 2	58.11
1.5455M	1	1 8 1	59.79
1.5455M		0 3 4	59.79
1.5415	1	5 5 1	59.96
1.5209	1L	1 6 3	60.86
1.4937	1L	2 8 1	62.09
1.4842M	1L	6 1 2	62.53
1.4842M		4 7 0	62.53

Thallium Oxide (Avicennite), Tl_2O_3

The experimental data reported here are the same as those reported earlier by Swanson and Fuyat [1953]. This pattern has not been re-measured. The space group has been changed and the corresponding indices were changed when necessary. Also other additional information has been added.

CAS registry no.
1314-12-1

Sample

The sample of thallium oxide from Johnson Matthey Co., Ltd., London, England, was annealed at 370 °C in a sealed tube for 2 hours to prevent volatilization of noxious fumes.

Major impurities

0.001 to 0.01% each: Ca, Mg, Li, and Na
less than 0.001% each: Al, Cu, Pb, and Si.

Color

Black

Structure

Cubic, $\text{Ia}\bar{3}$ (206), $Z = 16$, isostructural with Mn_2O_3 [Pauling and Shappell, 1930].
The space group used earlier was $\text{I}\bar{2}_13$.

Lattice constant of this sample

$a = 10.5434(7) \text{ \AA}$

Volume

$1172.0 \text{ \AA}^3$

Density

(calculated) 10.354 g/cm^3

Figure of merit

$F_{30} = 52.7(0.018, 31)$

Polymorphism

Prewitt et al. [1969] report the existence of a hexagonal modification.

Additional patterns

1. PDF card 5-584 [Swanson and Fuyat, 1953]
2. Hanawalt et al. [1938]
3. Kon'kova and Savel'ev [1960], natural mineral

References

- Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
Kon'kova, E. A. and Savel'ev, V. F. (1960). Zap. Vses. Mineral. Obshchest. 89, 316.
Pauling, L. and Shappell, M. D. (1930). Z. Kristallogr. Kristallgeometrie Kristallphys. Kristallchem. 75, 128.
Prewitt, C. T., Shannon, R. D., Rogers, D. B., and Sleight, A. W. (1969). Inorg. Chem. 8, 1985.
Swanson, H. E. and Fuyat, R. K. (1953). Nat. Bur. Stand. U.S. Circ. 539, 2, 28.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$					
Internal standard W, $a = 3.16524 \text{ \AA}$					
$d(\text{\AA})$	I	hkl			$2\theta(^{\circ})$
4.304	11	2	1	1	20.62
3.042	100	2	2	2	29.34
2.816	3	3	2	1	31.75
2.635	42	4	0	0	34.00
2.484	6	4	1	1	36.13
2.357	2	4	2	0	38.15
2.248	4	3	3	2	40.08
2.149	1	4	2	2	42.01
2.068	8	4	3	1	43.74
1.924	3	5	2	1	47.20
1.863	33	4	4	0	48.85
1.808	2	4	3	3	50.43
1.758	1	6	0	0	51.97
1.710	5	6	1	1	53.55
1.668	2	6	2	0	55.01
1.6280	4	5	4	1	56.48
1.5890	27	6	2	2	57.99
1.5540	6	6	3	1	59.43
1.5220	6	4	4	4	60.81
1.4910	3	5	4	3	62.21
1.4620	1	6	4	0	63.59
1.4340	3	6	3	3	64.98
1.4090	2	6	4	2	66.28
1.3390	3	6	5	1	70.24
1.3180	3	8	0	0	71.53
1.2980	4	7	4	1	72.80
1.2790	2	8	2	0	74.06
1.2597	2	6	5	3	75.40
1.2428	1	6	6	0	76.60
1.2261	3	8	3	1	77.84
1.2094	6	6	6	2	79.13
1.1789	4	8	4	0	81.60
1.1646	1	8	3	3	82.82
1.1371	2	9	2	1	85.29
1.1110	1	7	5	4	87.79
1.0874	1	9	3	2	90.21
1.0764	2	8	4	4	91.39
1.0649	1	9	4	1	92.66

Uric Acid (Phase 1), $C_5H_4N_4O_3$

Synonyms

1. 2,6,8-Trioxypurine
2. 8-Hydroxyxanthine

CAS registry no.

69-93-2

Sample

The sample was NBS Standard Reference Material 913.

Color

Colorless

Structure

Monoclinic, $P2_1/n$ (14), $Z = 4$. The structure was determined by Ringertz [1966].

Lattice constants of this sample

$a = 13.102(3) \text{ \AA}$
 $b = 7.416(2)$
 $c = 6.225(1)$
 $\beta = 90.37(3)^\circ$

$a/b = 1.7667$

$c/b = 0.8394$

Volume

$604.9 \text{ \AA}^3$

Density

(calculated) 1.846 g/cm^3

Figure of merit

$F_{30} = 36.3(0.012, 68)$

Reference intensity

$I/I_{\text{corundum}} = 0.94(1)$

Polymorphism

Shirley and Sutor [1968] report a second phase with a monoclinic cell of similar size.

Additional patterns

1. PDF card 21-1959 [Shirley and Sutor, 1968]
2. PDF card 22-2000 [Swanson et al., 1970]

References

- Ringertz, H. (1966). *Acta Crystallogr.* **20**, 397.
 Shirley, R. and Sutor, D. J. (1968). *Science* **159**, 544.
 Swanson, H. E., McMurdie, H. F., Morris, M. C., and Evans, E. H. (1970). *Nat. Bur. Std. U.S. Monogr.* **25**, Sec. 8, 154.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp $25 \pm 1^\circ \text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
6.54	45	2 0 0	13.53	
5.633	18	-1 0 1	15.72	
4.913	50	2 1 0	18.04	
4.769	7	0 1 1	18.59	
4.485	2	-1 1 1	19.78	
3.860	55	-2 1 1	23.02	
3.706	7	0 2 0	23.99	
3.587	4	-3 0 1	24.80	
3.276	17	4 0 0	27.20	
3.185	50	0 2 1	27.99	
3.098	100	-1 2 1	28.79	
2.994	4	4 1 0	29.82	
2.868M	25	0 1 2	31.16	
2.868M		-2 2 1	31.16	
2.801	11	1 1 2	31.93	
2.623	3	2 1 2	34.15	
2.570	16	3 2 1	34.88	
2.456	3	4 2 0	36.56	
2.421	4	-5 0 1	37.11	
2.312	4	2 3 0	38.92	
2.280	5	4 2 1	39.50	
2.245	11	-2 2 2	40.14	
2.184	6	6 0 0	41.31	
2.151M	2	4 1 2	41.96	
2.151M		3 3 0	41.96	
2.096M	2	-3 2 2	43.12	
2.096M		6 1 0	43.12	
2.032	3	3 3 1	44.56	
2.027	3	-5 2 1	44.67	
1.997	1L	0 1 3	45.37	
1.989	1L	-6 1 1	45.56	
1.978	1L	-1 1 3	45.84	
1.9306M	1	-4 2 2	47.03	
1.9306M		5 1 2	47.03	
1.9149+	1	-2 1 3	47.44	
1.9149+		1 3 2	47.44	
1.8821M	2	-4 3 1	48.32	
1.8821M		6 2 0	48.32	
1.8788M	2	-3 0 3	48.41	
1.8788M		4 3 1	48.41	
1.8697	1	3 0 3	48.66	
1.7988M	6	6 2 1	50.71	
1.7988M		5 3 0	50.71	
1.7955M	5	-7 0 1	50.81	
1.7955M		-1 2 3	50.81	

Zinc Chlorate Hydrate, $\text{Zn}(\text{ClO}_4)_2 \cdot 6\text{H}_2\text{O}$

CAS registry no.
13637-61-1

Sample

The sample was prepared by evaporation at room temperature of an aqueous solution.

Color

Colorless

Structure

Hexagonal, $P6/mmm$ (191), $Z = 4$, isostructural with Ni and other divalent metal perchlorate hexahydrates. The structure of this group of compounds was studied by West [1935].

Lattice constants of this sample

$a = 15.629(4) \text{ \AA}$
 $c = 5.215(1)$

$c/a = 0.3337$

Volume

$1103.1 \text{ \AA}^3$

Density

(calculated) 2.242 g/cm^3

Figure of merit

$F_{30} = 32.3(0.012, 77)$

Additional pattern

1. PDF card 6-197 [Dow Chemical Co.]

Reference

West, C. D. (1935). Z. Kristallogr.
Kristallgeometrie Kristallphys.
Kristallchem. 91, 480.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$			
Internal standard Ag, $a = 4.08651 \text{ \AA}$			
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
6.77	6	2 0 0	13.06
4.868	14	1 0 1	18.21
4.341	6	1 1 1	20.44
4.132	85	2 0 1	21.49
3.909	100	2 2 0	22.73
3.655	6	2 1 1	24.33
3.386	3	4 0 0	26.30
3.045	2	3 1 1	29.31
2.841	75	4 0 1	31.46
2.670	3	3 2 1	33.54
2.608	12	0 0 2	34.36
2.560M	3	1 0 2	35.03
2.560M		4 2 0	35.03
2.433M	10	2 0 2	36.91
2.433M		5 1 0	36.91
2.296	11	4 2 1	39.21
2.258M	6	3 0 2	39.90
2.258M		6 0 0	39.90
2.168M	4	2 2 2	41.62
2.168M		5 2 0	41.62
2.072	8	6 0 1	43.66
2.066M	18	4 0 2	43.79
2.066M		6 1 0	43.79
1.955M	12	4 1 2	46.42
1.955M		4 4 0	46.42
1.878M	6	5 0 2	48.42
1.878M		6 2 0	48.42
1.826	22	4 2 2	49.91
1.7657	9	6 2 1	51.73
1.7058M	5	6 0 2	53.69
1.7058M		6 3 0	53.69
1.6950	2	7 1 1	54.06
1.6838	4	2 0 3	54.45
1.6089	2	8 0 1	57.21
1.5462	5	4 0 3	59.76
1.5236M	4	6 2 2	60.74
1.5236M		7 3 0	60.74
1.4768M	7	7 1 2	62.88
1.4768M		8 2 0	62.88
1.4626	1L	5 0 3	63.56
1.4372	1	4 2 3	64.82
1.4193M	4	8 0 2	65.74
1.4193M		6 5 0	65.74

Zinc Phosphate, α - $\text{Zn}_3(\text{PO}_4)_2$

CAS registry no.
7779-90-0

Sample

The sample was prepared by heating ZnCO_3 and P_2O_5 at 900 °C for several days with intermittent grindings.

Color

Colorless

Structure

Monoclinic, $A2/a$ (15), $Z = 4$. The structure was determined by Calvo [1965].

Lattice constants of this sample

$a = 15.006(3) \text{ \AA}$
 $b = 5.635(1)$
 $c = 8.183(1)$
 $\beta = 104.99(2)^\circ$

$a/b = 2.6629$
 $c/b = 1.4521$

Volume $\text{\AA}^3$
668.5

Density
3.836 g/cm³

Figure of merit
 $F_{30} = 37.4(0.016, 51)$

Reference intensity
 $I/I_{\text{corundum}} = 1.40(9)$

Polymorphism

Above 942 °C, α - $\text{Zn}_3(\text{PO}_4)_2$ transforms to β - $\text{Zn}_3(\text{PO}_4)_2$. A small percentage of Mn^{++} substituting for the Zn^{++} stabilizes a γ form [Calvo, 1965].

Additional patterns

1. PDF card 1-524 [New Jersey Zinc Co.]
2. PDF card 11-35 [Katnack and Hummel, 1958]

References

Calvo, C. (1965). Can. J. Chem. 43, 436.
Katnack, F. L. and Hummel, F. A. (1958).
J. Electrochem. Soc. 105, 125.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard Ag, $a = 4.08651 \text{ \AA}$				
d($\text{\AA}$)	I	hkl	$2\theta(^\circ)$	
7.25	3	2 0 0	12.20	
4.583M	35	0 1 1	19.35	
4.583M		-1 1 1	19.35	
4.193	30	1 1 1	21.17	
3.947	35	0 0 2	22.51	
3.928	25	-2 0 2	22.62	
3.607	90	-3 1 1	24.66	
3.146	70	2 0 2	28.35	
3.079	100	-4 1 1	28.98	
2.815	13	0 2 0	31.76	
2.764	9	1 2 0	32.36	
2.657	9	4 1 1	33.70	
2.627	20	2 2 0	34.10	
2.448	40	-1 1 3	36.68	
2.415	20	6 0 0	37.20	
2.385	6	0 1 3	37.68	
2.320	5	-1 2 2	38.78	
2.294	35	0 2 2	39.24	
2.287	16	-2 2 2	39.36	
2.250	25	-4 1 3	40.04	
2.225	18	4 2 0	40.51	
2.216	16	1 2 2	40.68	
2.125	12	2 1 3	42.50	
2.086	12	-4 2 2	43.34	
2.018	5	6 1 1	44.89	
1.975	11	0 0 4	45.90	
1.963M	11	3 2 2	46.21	
1.963M		-4 0 4	46.21	
1.941	5	-6 1 3	46.76	
1.859	5	6 0 2	48.97	
1.837	13	-8 0 2	49.59	
1.827M	16	-1 3 1	49.87	
1.827M		0 3 1	49.87	
1.805	10	-6 2 2	50.52	
1.789	9	7 1 1	51.00	
1.785	12	-7 1 3	51.14	
1.745	1	-3 3 1	52.39	
1.6761	11	3 3 1	54.72	
1.6727	9	-4 3 1	54.84	
1.6552	7	-2 2 4	55.47	
1.6175	2	0 2 4	56.88	
1.5957	5	-9 1 1	57.73	
1.5677	3	-3 1 5	58.86	
1.5502	17	-8 0 4	59.59	
1.5479	16	-4 1 5	59.69	
1.5281	7	6 1 3	60.54	
1.5229	10	0 1 5	60.77	
1.5115M	11	-5 1 5	61.28	
1.5115M		2 2 4	61.28	
1.5072+	10	5 3 1	61.47	
1.5072+		8 0 2	61.47	
1.4980	6	1 3 3	61.89	
1.4759	5	1 1 5	62.92	

Zinc Phosphate, β - $\text{Zn}_3(\text{PO}_4)_2$

CAS registry no.
7779-90-0

Sample

The sample was prepared by heating ZnCO_3 and H_3PO_4 together at 1000 °C for several days, and cooling rapidly.

Color

Colorless

Structure

Monoclinic, $\text{P2}_1/\text{a}$ (14), $Z = 4$. The structure of β - $\text{Zn}_3(\text{PO}_4)_2$ was determined by Stephens and Calvo [1967].

Lattice constants of this sample

$a = 8.685(2) \text{ \AA}$
 $b = 9.179(1)$
 $c = 8.265(1)$
 $\beta = 112.80(1)^\circ$

$a/b = 0.9462$

$c/b = 0.9004$

Volume

$607.5 \text{ \AA}^3$

Density

(calculated) 4.221 g/cm^3

Figure of merit

$F_{30} = 88.4(0.009, 36)$

Polymorphism

$\text{Zn}_3(\text{PO}_4)_2$ has an inversion from α to β form at 942 °C. This is sluggish so that the β (high) form exists metastably at room temperature. [Stephens and Calvo, 1967] [Katnack and Hummel, 1958].

Additional pattern

1. PDF card 11-27 [Katnack and Hummel, 1958]

References

Katnack, F. L. and Hummel, F. A. (1958). J. Electrochem. Soc. 105, 125.
Stephens, J. S. and Calvo, C. (1967). Can. J. Chem. 45, 2303.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
d(Å)	I	hkl	$2\theta(^\circ)$	
7.61	3	0 0 1	11.62	
6.04	2	1 1 0	14.66	
5.590	2	-1 1 1	15.84	
4.296	5	-2 0 1	20.66	
4.178	12	1 1 1	21.25	

d(Å)	I	hkl	$2\theta(^\circ)$
4.008	9	2 0 0	22.16
3.931	35	0 2 1	22.60
3.890	25	-2 1 1	22.84
3.810	3	0 0 2	23.33
3.753	2	-1 1 2	23.69
3.669	14	2 1 0	24.24
3.526	9	-2 0 2	25.24
3.290	100	-2 1 2	27.08
3.135	35	-2 2 1	28.45
3.084	45	2 0 1	28.93
3.064	55	-1 2 2	29.12
3.018	30	2 2 0	29.58
2.931	10	0 2 2	30.47
2.927	7	2 1 1	30.52
2.866	80	1 1 2	31.18
2.839	50	0 3 1	31.49
2.808	11	-1 3 1	31.84
2.759	2	-3 1 1	32.43
2.661	4	-2 0 3	33.65
2.626	4	-3 1 2	34.12
2.561+	15	1 3 1	35.01
2.561+		2 2 1	35.01
2.557	14	-2 1 3	35.06
2.539	11	0 0 3	35.32
2.491	35	-2 3 1	36.02
2.455	6	-1 3 2	36.58
2.449M	8	0 1 3	36.67
2.449M		-3 2 1	36.67
2.431	3	2 3 0	36.95
2.387	25	0 3 2	37.65
2.357	10	-1 2 3	38.15
2.352	8	-3 2 2	38.23
2.343	3	2 0 2	38.38
2.306	9	3 2 0	39.02
2.300	9	-2 2 3	39.13
2.296	11	0 4 0	39.20
2.269	3	2 1 2	39.69
2.206	6	1 4 0	40.88
2.197	14	0 4 1	41.04
2.182	5	-1 4 1	41.34
2.173	3	2 3 1	41.53
2.148M	14	1 3 2	42.02
2.148M		-4 0 2	42.02
2.128	3	1 1 3	42.44
2.103	8	-3 3 1	42.97
2.091M	18	-3 2 3	43.24
2.091M		-4 1 2	43.24
2.087	16	2 2 2	43.33
2.061	1	1 4 1	43.89
2.043M	3	-1 3 3	44.30
2.043M		-3 3 2	44.30
2.028	9	3 2 1	44.64
2.024	10	-2 4 1	44.74
2.007M	11	-2 3 3	45.14
2.007M		-2 1 4	45.14

Zinc Phosphate, β - $\text{Zn}_3(\text{PO}_4)_2$ - (continued)

d(Å)	I	hkl	2 θ (°)
1.992M	8	-4 0 3	45.51
1.992M		-1 1 4	45.51
1.976	1	1 2 3	45.89
1.965	2	0 4 2	46.15
1.954M	4	4 1 0	46.43
1.954M		0 3 3	46.43
1.945M	7	-4 1 3	46.66
1.945M		-4 2 2	46.66
1.923	6	-2 4 2	47.22
1.9054M	14	-3 1 4	47.69
1.9054M		0 0 4	47.69
1.8766	7	-2 2 4	48.47
1.8657	9	0 1 4	48.77
1.8632M	25	-1 2 4	48.84
1.8632M		-3 3 3	48.84
1.8597	20	2 3 2	48.94
1.8455	3	2 0 3	49.34
1.8344M	4	4 2 0	49.66
1.8344M		3 1 2	49.66
1.8268M	5	-4 2 3	49.88
1.8268M		1 4 2	49.88
1.8098	5	2 1 3	50.38
1.7899	6	1 5 0	50.98
1.7750	9	4 0 1	51.44
1.7613+	3	-1 4 3	51.87
1.7613+		-4 3 1	51.87
1.7395	2	3 4 0	52.57
1.7096	12	1 5 1	53.56
1.7034	10	0 4 3	53.77
1.6872	10	-2 5 1	54.33
1.6772M	13	-5 1 1	54.68
1.6772M		-1 5 2	54.68
1.6699M	7	-4 3 3	54.94
1.6699M		2 5 0	54.94
1.6525M	8	-2 0 5	55.57
1.6525M		-5 1 3	55.57
1.6427M	13	-3 3 4	55.93
1.6427M		-3 4 3	55.93
1.6280	5	-2 5 2	56.48
1.6240	6	-5 2 2	56.63
1.6105	2	3 4 1	57.15
1.6023	9	1 2 4	57.47
1.5972M	6	3 3 2	57.67
1.5972M		-3 1 5	57.67
1.5924	3	-1 1 5	57.86
1.5679M	12	1 5 2	58.85
1.5679M		-4 4 2	58.85
1.5557	2	-2 2 5	59.36
1.5502	4	-3 5 1	59.59
1.5399	5	3 1 3	60.03

d(Å)	I	hkl	2 θ (°)
1.5313M	7	-4 0 5	60.40
1.5313M		-2 4 4	60.40
1.5245+	6	-1 2 5	60.70
1.5245+		-1 4 4	60.70
1.5117+	7	5 2 0	61.27
1.5117+		-2 5 3	61.27
1.5083M	9	4 4 0	61.42
1.5083M		2 0 4	61.42
1.5041M	10	-4 4 3	61.61
1.5041M		0 1 5	61.61

Zinc Phosphate, γ -Zn₃(PO₄)₂

Sample

This sample was prepared by heating stoichiometric amounts of ZnCO₃ and H₃PO₄ with 3% of the ZnCO₃ replaced by MnCO₃, at 900 °C for several days. This phase has useful luminescence properties, and is only stabilized by the addition of low percents of certain other bivalent cations [Calvo, 1965].

Color

Colorless

Structure

Monoclinic, P2₁/n (14), Z = 2. The structure of γ -Zn₃(PO₄)₂ was determined by Calvo [1963].

Lattice constants of this sample

a = 7.549(1) Å
b = 8.499(1)
c = 5.0491(8)
β = 95.03(1)°

a/b = 0.8882
c/b = 0.5941

Volume

322.7 Å³

Density

(calculated) 3.973 g/cm³

Figure of merit

F₃₀ = 85.9 (0.009,37)

Reference intensity

I/I_{corundum} = 1.6(2)

Polymorphism

Without the addition of other bivalent ions Zn₃(PO₄)₂ exists in an α form below 942 °C and in a β form above. Both are monoclinic [Calvo, 1965].

Additional pattern

1. Hummel and Katnack [1958]

References

Calvo, C. (1963). J. Phys. Chem. Solids. 24, 141.
Calvo, C. (1965). Can. J. Chem. 43, 436.
Hummel, F. A. and Katnack, F. L. (1958). J. Electrochem. Soc. 105, 528.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C				
Internal standard Si, a = 5.43088 Å				
d(Å)	I	h	k	l
2θ(°)				
5.626	6	1	1	0
4.363	80	-1	0	1
4.331	25	0	1	1
4.249	3	0	2	0
4.023	40	1	0	1
3.880	25	-1	1	1
3.700	6	1	2	0
3.435	100	2	1	0
3.244	20	0	2	1
3.042	19	-1	2	1
2.919	8	1	2	1
2.817	25	2	2	0
2.738	13	2	1	1
2.651	10	1	3	0
2.530	35	-2	2	1
2.515	30	0	0	2
2.468	45	0	3	1
2.404	20	3	1	0
2.391	8	2	2	1
2.376	2	-1	3	1
2.355	2	-1	1	2
2.327	2	-3	0	1
2.316	8	1	3	1
2.245	10	-3	1	1
2.181	2	-2	0	2
2.168	4	3	0	1
2.164	2	0	2	2
2.124M	13	0	4	0
2.124M		-1	2	2
2.105	20	-2	3	1
2.101	20	3	1	1
2.040M	18	-3	2	1
2.040M		1	2	2
2.012	3	2	0	2
1.9570M	2	0	4	1
1.9570M		2	1	2
1.9392	4	-2	2	2
1.9322	2	3	2	1
1.9103	4	-1	4	1
1.8799+	5	0	3	2
1.8799+		4	0	0
1.8766	4	3	3	0
1.8536	14	-1	3	2
1.8497	8	2	4	0
1.8176	7	2	2	2
1.8149	4	-3	1	2
1.7975M	4	-3	3	1
1.7975M		1	3	2
1.7743	14	-4	1	1
1.7613	4	-2	4	1

Zinc Phosphate, γ - $\text{Zn}_3(\text{PO}_4)_2$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.7197	2	4 2 0	53.22
1.7029	6	-3 2 2	53.79
1.6792	6	4 1 1	54.61
1.6691M	12	3 1 2	54.97
1.6691M		-4 2 1	54.97
1.6579	6	1 5 0	55.37
1.6368	5	-1 1 3	56.15
1.6063M	2	1 0 3	57.31
1.6063M		-1 4 2	57.31
1.5881	1	4 2 1	58.03
1.5667M	5	4 3 0	58.90
1.5667M		1 5 1	58.90
1.5595	10	0 2 3	59.20
1.5545	12	-3 3 2	59.41
1.5493	10	2 5 0	59.63

Zinc Phosphate Hydrate (Hopeite), $\text{Zn}_3(\text{PO}_4)_2 \cdot 4\text{H}_2\text{O}$

CAS registry no.
7543-51-3

Sample

The sample was a reagent from the Chicago Apparatus Co., recrystallized from aqueous solution.

Color

Colorless

Structure

Orthorhombic, Pnma (62), $Z = 4$. The structure of hopeite has been determined by Mamedov et al. [1961] and Liebau [1965].

Lattice constants of this sample

$a = 10.611(1) \text{ \AA}$
 $b = 18.312(2)$
 $c = 5.0309(6)$

$a/b = 0.5795$

$c/b = 0.2747$

Volume

$977.55 \text{ \AA}^3$

Density

(calculated) 3.113 g/cm^3

Figure of merit

$F_{30} = 73.8(0.010, 40)$

Polymorphism

A polymorph of $\text{Zn}_3(\text{PO}_4)_2 \cdot 4\text{H}_2\text{O}$ is called parahopeite [Chao, 1969]. The pattern for parahopeite is on card 24-1461.

Additional patterns

1. PDF card 1-964 [Hanawalt et al., 1938]
2. PDF card 9-497 [Murdoch, Univ. of Cal., Los Angeles, Calif.], natural mineral.
3. PDF card 23-747 [Komrska and Satava 1969]
4. PDF card 26-1397 [Whitaker, 1973], natural mineral

References

- Chao, G. Y. (1969). Z. Kristallogr, Kristallgeometrie Kristallphys. Kristallchem. 130, 261.
- Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
- Komrska, J. and Satava, V. (1969). Silikaty 13, 135.
- Liebau, F. (1965). Acta Crystallogr. 18, 352.
- Mamedov, C. S., Gamidov, R., and Belov, N. W. (1961). Kristallographia 6, 114.
- Whitaker, A., (1973). J. Appl. Crystallogr. 6, 495.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$				
Internal standard W, $a = 3.16524 \text{ \AA}$				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	
9.16	55	0 2 0	9.65	
5.311	17	2 0 0	16.68	
5.095	25	2 1 0	17.39	
4.855	30	0 1 1	18.26	
4.576	55	0 4 0	19.38	
4.414	35	1 1 1	20.10	
4.072	7	1 2 1	21.81	
4.005	20	2 3 0	22.18	
3.880	14	0 3 1	22.90	
3.648M	9	2 0 1	24.38	
3.648M		1 3 1	24.38	
3.468	30	2 4 0	25.67	
3.391	40	2 2 1	26.26	
3.225	1	1 4 1	27.64	
3.134	9	2 3 1	28.46	
3.053	1	0 6 0	29.23	
3.015	4	2 5 0	29.61	
2.963	8	0 5 1	30.14	
2.855+	100	3 1 1	31.30	
2.855+		2 4 1	31.30	
2.760	3	3 2 1	32.41	
2.652	19	4 0 0	33.77	
2.614	25	3 3 1	34.28	
2.585	3	2 5 1	34.67	
2.548	15	4 2 0	35.19	
2.535	11	1 6 1	35.38	
2.515	15	0 0 2	35.67	
2.445M	3	1 0 2	36.72	
2.445M		3 4 1	36.72	
2.426M	10	1 1 2	37.02	
2.426M		0 2 2	37.02	
2.342	7	2 6 1	38.40	
2.321	1	0 7 1	38.77	
2.288	7	0 8 0	39.35	
2.271M	15	1 3 2	39.66	
2.271M		3 5 1	39.66	
2.268	13	1 7 1	39.71	
2.206M	4	2 2 2	40.88	
2.206M		0 4 2	40.88	
2.190	2	4 3 1	41.18	
2.158	7	1 4 2	41.83	
2.148	3	4 5 0	42.02	
2.130	1	2 3 2	42.41	
2.100M	11	2 8 0	43.03	
2.100M		3 6 1	43.03	
2.038M	3	3 1 2	44.42	
2.038M		2 4 2	44.42	
2.002M	16	4 6 0	45.26	
2.002M		3 2 2	45.26	
1.977	2	4 5 1	45.87	

Zinc Phosphate Hydrate (Hopeite), $\text{Zn}_3(\text{PO}_4)_2 \cdot 4\text{H}_2\text{O}$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
1.940+	25	3 7 1	46.79
1.940+		2 8 1	46.79
1.9111	2	5 2 1	47.54
1.8994	1	2 9 0	47.85
1.8715	1	3 4 2	48.61
1.8618M	2	4 7 0	48.88
1.8618M		5 3 1	48.88
1.8247	15	4 0 2	49.94
1.7985	1	5 4 1	50.72
1.7896M	1	4 2 2	50.99
1.7896M		3 5 2	50.99
1.7772	3	2 9 1	51.37
1.7361	5	6 2 0	52.68
1.7306	4	2 10 0	52.86
1.7252	3	5 5 1	53.04
1.7014	2	3 6 2	53.84
1.6953	6	4 4 2	54.05
1.6719	6	1 8 2	54.87
1.6646	5	3 9 1	55.13
1.6370	5	2 10 1	56.14
1.6298	3	1 2 3	56.41
1.6169	3	0 3 3	56.90
1.6143M	4	4 9 0	57.00
1.6143M		3 7 2	57.00
1.5974	4	5 2 2	57.66
1.5931M	4	2 1 3	57.83
1.5931M		6 5 0	57.83
1.5755M	1	2 2 3	58.54
1.5672+	10	5 3 2	58.88
1.5672+		6 4 1	58.88
1.5633	9	1 11 1	59.04
1.5295M	9	6 6 0	60.48
1.5295M		5 4 2	60.48
1.5254M	10	0 12 0	60.66
1.5254M		0 5 3	60.66
1.5161M	3	2 9 2	61.07
1.5161M		3 0 3	61.07
1.5092M	10	2 4 3	61.38
1.5092M		1 5 3	61.38
1.5068	7	4 10 0	61.49

Aluminum Iron Antimony Oxide, Bahianite, $\text{Al}_{5.66}\text{Fe}_{0.09}\text{Sb}_{2.95}\text{O}_{16}$

References

- Cromer, D. T. and Mann, J. B. (1968). Acta Crystallogr. A24, 321.
 Cromer, D. T. and Liberman, D. J. (1970). J. Chem. Phys. 53, 1891.
 Moore, P. B. and Araki, T. (1976). Neues Jahrb. Mineral. Abh. 126, 113.

Structure

Monoclinic, C2/m (12), Z = 2. The structure was determined by Moore and Araki [1976], for a sample from Serra de Mangabeira, Bahia, Brazil.

Atom positions

2(a) 1.8 antimony and 0.2 iron
 4(g) 4 antimony
 2(d) 2 aluminum
 8(j) 7.52 aluminum and 0.48 iron
 8(j) 8 oxygen in each of 3 different sites
 4(i) 4 oxygen in each of 2 different sites
 The single crystal analysis did not refine positions for the Al atoms in the tetrahedral sites and they were omitted also from calculation of this powder pattern. Minor amounts of W^{+6} in the octahedral sites were not determined either but their contribution was absorbed into the site distribution refinement [Moore and Araki, 1976].

Lattice constants

a = 9.407(6) Å
 b = 11.542(8)
 c = 4.410(3)
 $\beta = 90.94(3)^\circ$

a/b = 0.8150
 c/b = 0.3821

(published values: a = 9.406(6) Å,
 b = 11.541(8), c = 4.410(3), $\beta = 90.94(3)^\circ$
 [Moore and Araki, 1976]).

Volume
 478.75 Å³

Density

(calculated) 5.362 g/cm³
 This is the value calculated from the formula above, based on a chemical analysis by Moore and Araki in their table 1 part A [1976]. Due to the problems in the site distribution, mentioned above, a density is different if calculated from the multiplicities given in the atom positions.

Thermal parameters

Isotropic [Moore and Araki, 1976]

Scattering factors

Al^{3+} , Fe^{3+} , O^{1-} , Sb^{5+} [Cromer and Mann, 1968].
 Dispersion corrections were applied to Al, Fe, and O [Cromer and Liberman, 1970].

Scale factors (integrated intensities)

$\gamma = 0.1911 \times 10^{-3}$
 I/I_{corundum} (calculated) = 1.74 for reflection
 with hkl = 201

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2 θ (°)	$\lambda = 1.540598\text{Å}$
7.28	27	1 1 0	12.14	
5.76	18	0 2 0	15.36	
4.70	84	2 0 0	18.86	
4.41	40	0 0 1	20.14	
3.792	21	-1 1 1	23.44	
3.751	18	1 1 1	23.70	
3.645	10	2 2 0	24.40	
3.559	30	1 3 0	25.00	
3.504	25	0 2 1	25.40	
3.243	100	-2 0 1	27.48	
3.191	99	2 0 1	27.94	
3.026	2	3 1 0	29.50	
2.884	21	0 4 0	30.98	
2.827	17	-2 2 1	31.62	
2.778	37	-1 3 1	32.20	
2.763	33	1 3 1	32.38	
2.513	10	-3 1 1	35.70	
2.4755	10	3 1 1	36.26	
2.4597	53	2 4 0	36.50	
2.4302	19	3 3 0	36.96	
2.4138	57	0 4 1	37.22	
2.3517	21	4 0 0	38.24	
2.2047	11	0 0 2	40.90	
2.1772	5	4 2 0	41.44	
2.1553	49	-2 4 1	41.88	
2.1397	19	-3 3 1	42.20	
2.1168	10	3 3 1	42.68	
2.1027	3	1 1 2	42.98	
2.0607	24	4 0 1	43.90	
2.0087	5	-2 0 2	45.10	
1.9837	13	2 0 2	45.70	
1.9642	4	-4 2 1	46.18	
1.9404	4	4 2 1	46.78	
1.8968	2	-2 2 2	47.92	
1.8799	7	-1 3 2	48.38	
1.8755	6	2 2 2	48.50	
1.8697	5	1 3 2	48.66	
1.8568	2	5 1 0	49.02	
1.8227	11	4 4 0	50.00	
1.7802	1	2 6 0	51.28	
1.7629	2	0 6 1	51.82	
1.7515	9	0 4 2	52.18	
1.7209	1	-5 1 1	53.18	
1.6921	24	-4 4 1	54.16	
1.6772	23	4 4 1	54.68	

Aluminum Iron Antimony Oxide, Bahianite, $\text{Al}_{5.66}\text{Fe}_{0.09}\text{Sb}_{2.95}\text{O}_{16}$ - (continued)

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
1.6489	34	-2 4 2	55.70	
1.6349	37	2 4 2	56.22	
1.6216	31	-4 0 2+	56.72	
1.5954	17	4 0 2	57.74	
1.5859	8	-5 3 1	58.12	
1.5701	9	5 3 1	58.76	
1.5672	8	6 0 0	58.88	
1.5378	1	4 2 2	60.12	
1.5254	10	-1 7 1	60.66	
1.5222	13	1 7 1	60.80	
1.5132	1	6 2 0	61.20	
1.4848	7	-6 0 1	62.50	
1.4697	8	6 0 1+	63.22	
1.4593	5	3 7 0+	63.72	
1.4428	12	0 8 0	64.54	

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
7.29	23	1 1 0	12.13	
5.77	16	0 2 0	15.34	
4.70	78	2 0 0	18.85	
4.41	38	0 0 1	20.12	
3.795	20	-1 1 1	23.43	
3.752	16	1 1 1	23.69	
3.646	9	2 2 0	24.40	
3.561	29	1 3 0	24.99	
3.504	24	0 2 1	25.40	
3.243	100	-2 0 1	27.48	
3.191	100	2 0 1	27.94	
3.026	2	3 1 0	29.50	
2.885	21	0 4 0	30.97	
2.827	17	-2 2 1	31.62	
2.792	14	2 2 1	32.03	
2.779	33	-1 3 1	32.19	
2.762	29	1 3 1	32.39	
2.513	10	-3 1 1	35.69	
2.4765	7	3 1 1	36.24	
2.4595	57	2 4 0	36.50	
2.4304	15	3 3 0	36.96	
2.4145	61	0 4 1	37.21	
2.3514	23	4 0 0	38.24	
2.2047	12	0 0 2	40.90	
2.1776	3	4 2 0	41.43	
2.1558	54	-2 4 1	41.87	
2.1401	1	2 4 1	42.19	
2.1400	17	-3 3 1	42.19	
2.1178	1	-1 1 2	42.66	
2.1172	10	3 3 1	42.67	

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
2.1029	2	1 1 2	42.97	
2.0609	24	4 0 1	43.90	
2.0595	3	0 2 2	43.93	
2.0089	5	-2 0 2	45.09	
1.9838	14	2 0 2	45.70	
1.9644	5	-4 2 1	46.17	
1.9408	4	4 2 1	46.77	
1.8973	2	-2 2 2	47.91	
1.8797	7	-1 3 2	48.38	
1.8760	1	2 2 2	48.49	
1.8693	5	1 3 2	48.67	
1.8566	1	5 1 0	49.02	
1.8228	13	4 4 0	50.00	
1.7805	1	2 6 0	51.27	
1.7632	2	0 6 1	51.81	
1.7519	10	0 4 2	52.17	
1.7211	1	-5 1 1	53.17	
1.7013	1	5 1 1	53.84	
1.6922	26	-4 4 1	54.16	
1.6900	3	5 3 0	54.23	
1.6770	26	4 4 1	54.69	
1.6487	38	-2 4 2	55.71	
1.6474	1	2 6 1	55.75	
1.6434	5	-3 3 2	55.90	
1.6347	42	2 4 2	56.23	
1.6241	12	1 7 0	56.63	
1.6227	5	3 3 2	56.68	
1.6217	25	-4 0 2	56.72	
1.5953	20	4 0 2	57.74	
1.5859	8	-5 3 1	58.12	
1.5703	9	5 3 1	58.75	
1.5689	1	1 5 2	58.81	
1.5676	5	6 0 0	58.86	
1.5612	1	-4 2 2	59.13	
1.5377	1	4 2 2	60.13	
1.5254	10	-1 7 1	60.66	
1.5226	10	1 7 1	60.78	
1.5128	1	6 2 0	61.22	
1.4848	8	-6 0 1	62.50	
1.4698	3	0 0 3	63.21	
1.4695	6	6 0 1	63.23	
1.4593	5	3 7 0	63.72	
1.4583	1	5 5 0	63.77	
1.4444	1	-1 1 3	64.46	
1.4427	14	0 8 0	64.54	
1.4379	2	-6 2 1	64.78	

Antimony Iron Titanium Oxide Hydroxide, Derbylite, $\text{SbFe}_4\text{Ti}_3\text{O}_{13}(\text{OH})$

Structure

Monoclinic, $\text{P2}_1/\text{m}$ (11), $Z = 2$. The structure was determined by Moore and Araki [1976] using data from sample #C4430, U.S. National Museum. The original location was Diamantina, Minas Gerais, Brazil.

Atom positions

Moore and Araki [1976]

2(e) 2 antimony
2(e) 2 titanium
4(f) 1.72 iron and 2.28 titanium
4(f) 1.72 titanium and 2.28 iron
2(e) 2 oxygen
2(e) 2 hydroxyl
4(f) 4 oxygen in each of 6 different sites
4(f) 4 iron

Lattice constants

$a = 7.160(1) \text{ \AA}$
 $b = 14.348(3)$
 $c = 4.970(1)$
 $\beta = 104.61(2)^\circ$

$a/b = 0.4990$
 $c/b = 0.3464$

(published values: $a = 7.160(1) \text{ \AA}$,
 $b = 14.347(3)$, $c = 4.970(1)$, $\beta = 104.61(2)^\circ$
[Moore and Araki, 1976]).

Volume $\text{\AA}^3$
494.1 $\text{\AA}^3$

Density

(calculated) 4.798 g/cm^3

Thermal parameters

Isotropic [Moore and Araki, 1976]

Scattering factors

Sb^{3+} , Fe^{3+} , Ti^{4+} , O^- [Cromer and Mann, 1968].
Antimony, iron and titanium factors were corrected for dispersion [Cromer and Liberman, 1970].

Scale factors (integrated intensities)

$\gamma = 0.1340 \times 10^{-3}$
 I/I_{corundum} (calculated) = 1.58 for reflection
with $hkl = 131$.

References

Cromer, D. T. and Mann, J. B. (1968). Acta Crystallogr. A24, 321.
Cromer, D. T. and Liberman, D. (1970). J. Chem. Phys. 53, 1891.
Moore, P. B. and Araki, T. (1976). Neues Jahrb. Mineral. Abh. 126, 292.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$ $\lambda = 1.540598 \text{\AA}$
6.23	21	1 1 0	14.20
4.98	5	1 2 0	17.80
4.81	21	0 0 1	18.44
4.52	18	-1 0 1	19.64
4.31	5	-1 1 1	20.60
3.994	26	0 2 1	22.24
3.935	7	1 3 0	22.58
3.824	25	-1 2 1	23.24
3.584	3	0 4 0	24.82
3.553	5	1 0 1	25.04
3.461	4	2 0 0	25.72
3.453	4	1 1 1	25.78
3.366	16	2 1 0	26.46
3.222	8	-2 0 1	27.66
3.184	37	1 4 0+	28.00
3.119	50	2 2 0	28.60
2.940	10	-2 2 1	30.38
2.852	100	1 3 1	31.34
2.808	19	-1 4 1+	31.84
2.673	90	-2 3 1	33.50
2.524	4	1 4 1	35.54
2.486	13	2 1 1	36.10
2.473	34	-1 0 2	36.30
2.468	29	0 5 1	36.38
2.423	5	-1 5 1	37.08
2.391	16	0 6 0	37.58
2.372	4	0 1 2	37.90
2.338	2	-1 2 2	38.48
2.309	3	3 0 0	38.98
2.293	8	-3 1 1	39.26
2.280	8	3 1 0+	39.50
2.260	6	1 6 0	39.86
2.232	21	1 5 1	40.38
2.210	5	2 5 0+	40.80
2.199	3	3 2 0	41.02
2.143	13	-2 5 1+	42.14
2.113	7	1 0 2+	42.76
2.090	7	1 1 2+	43.26
2.080	5	3 3 0	43.48
2.027	15	1 2 2	44.68
1.997	8	0 4 2	45.38
1.984	2	1 6 1	45.70
1.966	2	1 7 0	46.14
1.942	2	3 4 0	46.74
1.932	3	1 3 2	47.00
1.926	8	-3 0 2	47.16
1.921	7	-2 6 1	47.28
1.913	9	-2 4 2+	47.50
1.8953	3	2 5 1	47.96
1.8865	6	3 1 1+	48.20

Antimony Iron Titanium Oxide Hydroxide, Derbylite, $\text{SbFe}_4\text{Ti}_3\text{O}_{13}(\text{OH})$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.8604	9	-3 2 2	48.92
1.8427	2	0 5 2	49.42
1.8051	5	-3 5 1	50.52
1.7998	6	3 5 0	50.68
1.7763	15	2 0 2+	51.40
1.7641	8	-4 1 1+	51.78
1.7361	3	1 8 0	52.68
1.7294	5	-2 7 1	52.90
1.7246	5	2 2 2	53.06
1.7191	16	-1 6 2+	53.24
1.7014	2	1 5 2	53.84
1.6967	2	0 6 2	54.00
1.6806	2	0 8 1	54.56
1.6665	6	2 3 2+	55.06
1.6615	7	3 6 0	55.24
1.6571	4	-1 0 3	55.40
1.6424	6	-2 6 2	55.94
1.6285	2	4 3 0	56.46
1.6112	10	-4 0 2	57.12
1.6010	4	-4 1 2+	57.52
1.5924	17	2 8 0	57.86
1.5859	28	3 5 1	58.12
1.5721	3	-4 2 2	58.68
1.5672	3	-2 8 1	58.88
1.5648	4	-1 3 3+	58.98
1.5600	4	4 4 0+	59.18
1.5369	4	-3 7 1	60.16
1.5332	5	-2 3 3+	60.32
1.5272	3	-4 3 2	60.58
1.5200	12	0 3 3	60.90
1.5119	20	-4 5 1+	61.26
1.5039	6	4 1 1+	61.62
1.5004	4	-3 6 2+	61.78
1.4887	3	3 0 2	62.32
1.4831	2	4 5 0	62.58
1.4802	2	4 2 1+	62.72
1.4743	6	1 1 3+	63.00
1.4709	5	1 7 2+	63.16
1.4544	2	1 9 1	63.96
1.4420	3	4 3 1	64.58
1.4344	24	-1 5 3+	64.96
1.4239	5	-5 1 1	65.50
1.4208	3	3 3 2	65.66
1.4098	2	-2 5 3	66.24
1.4049	5	-2 8 2+	66.50
1.4015	3	0 5 3	66.68

Calculated Pattern (Integrated)			
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
6.24	18	1 1 0	14.18
4.98	4	1 2 0	17.78
4.81	18	0 0 1	18.43
4.52	16	-1 0 1	19.62
4.31	4	-1 1 1	20.58
3.995	24	0 2 1	22.24
3.936	6	1 3 0	22.57
3.825	24	-1 2 1	23.24
3.587	3	0 4 0	24.80
3.553	4	1 0 1	25.04
3.464	3	2 0 0	25.70
3.449	2	1 1 1	25.81
3.391	3	0 3 1	26.26
3.367	15	2 1 0	26.45
3.223	6	-2 0 1	27.66
3.185	26	1 4 0	27.99
3.184	10	1 2 1	28.00
3.120	49	2 2 0	28.59
2.940	10	-2 2 1	30.38
2.875	11	0 4 1	31.08
2.852	100	1 3 1	31.34
2.810	14	-1 4 1	31.82
2.806	4	2 3 0	31.87
2.673	94	-2 3 1	33.50
2.651	2	1 5 0	33.78
2.524	4	1 4 1	35.53
2.487	10	2 1 1	36.09
2.473	32	-1 0 2	36.30
2.464	11	0 5 1	36.43
2.423	5	-1 5 1	37.08
2.397	4	-2 4 1	37.49
2.391	14	0 6 0	37.58
2.372	3	0 1 2	37.91
2.338	2	-1 2 2	38.47
2.309	3	3 0 0	38.97
2.293	8	-3 1 1	39.26
2.280	6	3 1 0	39.49
2.280	2	0 2 2	39.49
2.260	5	1 6 0	39.85
2.260	1	-2 0 2	39.85
2.232	22	1 5 1	40.37
2.210	1	-3 2 1	40.80
2.210	3	2 5 0	40.80
2.198	2	3 2 0	41.02
2.148	2	0 3 2	42.02
2.143	10	-2 5 1	42.13
2.141	3	0 6 1	42.17
2.114	3	-1 6 1	42.74
2.113	4	1 0 2	42.77
2.090	4	1 1 2	43.25

Antimony Iron Titanium Oxide Hydroxide, Derbylite, $\text{SbFe}_4\text{Ti}_3\text{O}_{13}(\text{OH})$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.090	3	-3 3 1	43.26
2.080	4	3 3 0	43.48
2.036	1	-1 4 2	44.46
2.027	17	1 2 2	44.68
1.997	8	0 4 2	45.37
1.984	2	1 6 1	45.69
1.966	2	1 7 0	46.15
1.942	1	3 4 0	46.74
1.932	2	1 3 2	46.98
1.926	8	-3 0 2	47.15
1.920	2	-2 6 1	47.30
1.912	8	-2 4 2	47.51
1.909	3	-3 1 2	47.60
1.8957	2	2 5 1	47.95
1.8865	5	3 1 1	48.20
1.8856	2	0 7 1	48.22
1.8668	1	-1 7 1	48.74
1.8601	9	-3 2 2	48.93
1.8431	1	0 5 2	49.41
1.8056	5	-3 5 1	50.51
1.7992	5	3 5 0	50.70
1.7766	14	2 0 2	51.39
1.7755	3	1 7 1	51.42
1.7682	1	3 3 1	51.65
1.7655	4	-4 1 1	51.74
1.7641	2	2 7 0	51.78
1.7631	3	2 1 2	51.81
1.7363	3	1 8 0	52.67
1.7321	1	4 0 0	52.81
1.7295	4	-2 7 1	52.90
1.7245	1	2 2 2	53.06
1.7196	2	4 1 0	53.22
1.7191	15	-1 6 2	53.24
1.7013	2	1 5 2	53.84
1.6956	1	0 6 2	54.04
1.6805	2	0 8 1	54.57
1.6674	2	-4 3 1	55.03
1.6671	2	-1 8 1	55.04
1.6654	2	2 3 2	55.10
1.6612	5	3 6 0	55.25
1.6563	1	-1 0 3	55.43
1.6427	7	-2 6 2	55.93
1.6286	1	4 3 0	56.46
1.6138	1	-1 2 3	57.02
1.6114	10	-4 0 2	57.11
1.6013	2	-4 1 2	57.51
1.6011	1	1 8 1	57.52
1.5927	17	2 8 0	57.85
1.5914	1	2 7 1	57.90
1.5859	29	3 5 1	58.12

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.5791	2	-2 2 3	58.39
1.5722	2	-4 2 2	58.67
1.5672	2	-2 8 1	58.88
1.5651	2	-1 3 3	58.97
1.5599	1	0 7 2	59.18
1.5598	1	4 4 0	59.19
1.5370	4	-3 7 1	60.16
1.5333	2	-2 3 3	60.31
1.5330	1	3 7 0	60.33
1.5270	1	-4 3 2	60.59
1.5200	13	0 3 3	60.90
1.5132	2	0 9 1	61.20
1.5120	20	-4 5 1	61.26
1.5105	2	2 5 2	61.32
1.5042	2	4 1 1	61.61
1.5037	1	-1 4 3	61.63
1.5035	1	-1 9 1	61.64
1.4886	3	3 0 2	62.32
1.4829	1	4 5 0	62.59
1.4800	1	4 2 1	62.73
1.4755	3	-2 4 3	62.94
1.4748	1	-3 2 3	62.98
1.4741	4	1 1 3	63.01
1.4711	1	1 7 2	63.15
1.4699	1	-4 4 2	63.21
1.4545	1	1 9 1	63.96
1.4519	1	-1 8 2	64.08
1.4421	2	4 3 1	64.57
1.4373	9	-3 3 3	64.81
1.4348	11	0 10 0	64.94
1.4345	14	-1 5 3	64.96
1.4261	1	2 6 2	65.39
1.4240	4	-5 1 1	65.50
1.4214	1	3 3 2	65.63
1.4099	2	-2 5 3	66.23
1.4050	2	-4 5 2	66.49
1.4050	2	-2 8 2	66.50
1.4036	1	-3 7 2	66.57
1.3995	1	0 5 3	66.79

Benactyzine Hydrochloride, $C_{20}H_{26}ClNO_3$

Synonym

1. 2-Diethylaminoethyl benzilate hydrochloride

Structure

Triclinic, $P\bar{1}$ (2), $Z = 2$. The structure was refined by Petcher et al. [1974].

Atom positions

All atoms were in general positions 2(i).

Lattice constants

$a = 8.792(4) \text{ \AA}$
 $b = 15.949(8)$
 $c = 7.091(6)$
 $\alpha = 95.73(1)^\circ$
 $\beta = 94.10(1)$
 $\gamma = 87.57(1)$

$a/b = 0.5513$
 $c/b = 0.4446$

(published values: $a = 879.1(4) \text{ pm}$,
 $b = 1594.8(8)$, $c = 709.1(6)$, $\alpha = 95.73(1)^\circ$,
 $\beta = 94.10(1)$, $\gamma = 87.57(1)$ [Petcher et al., 1974])

Volume $\text{\AA}^3$
 $986.2 \text{ \AA}^3$

Density

(calculated) 1.225 g/cm^3

Thermal parameters

Isotropic. For hydrogen atoms, overall
 $B = 5.5$. For all other atoms, isotropic B_i
were estimated from β_{ij} for individual atoms.

Scattering factors

Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)

$\gamma = 0.3987 \times 10^{-3}$
 I/I_{corundum} (calculated) = 0.380 for reflection
with $hkl = 100$.

Additional pattern

1. Folen [1975]

References

Folen, V. A. (1975). J. Forensic Sci. 20,
348.
International Tables for X-ray Crystallography
III (1962). (The Kynoch Press, Birmingham,
Eng.) p. 202.
Petcher, T. J., Ramsay, W., and Forster, R.
(1974). J. Chem. Soc. Perkin II, 1151.

Calculated Pattern (Peak heights)				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	$\lambda - 1.540598\text{\AA}$
15.83	40	0 1 0	5.58	
8.75	60	1 0 0	10.10	
7.91	4	0 2 0	11.18	
7.78	13	1 1 0	11.36	
7.56	14	-1 1 0	11.70	
7.03	8	0 0 1	12.58	
6.67	39	0 -1 1	13.26	
6.21	3	0 1 1	14.26	
5.77	48	-1 2 0	15.34	
5.53	100	0 -2 1+	16.02	
5.29	14	0 3 0	16.76	
5.02	2	0 2 1	17.64	
4.96	1	1 1 1	17.86	
4.85	4	-1 -2 1	18.26	
4.52	2	1 -2 1	19.62	
4.454	7	-1 3 0	19.92	
4.410	7	-1 2 1	20.12	
4.312	24	1 2 1	20.58	
4.263	10	2 1 0	20.82	
4.184	2	-2 1 0	21.22	
4.081	4	-1 -3 1	21.76	
4.044	1	0 3 1	21.96	
3.962	3	0 4 0	22.42	
3.890	3	2 2 0	22.84	
3.844	8	1 -3 1	23.12	
3.776	43	-2 2 0	23.54	
3.657	37	1 4 0+	24.32	
3.610	6	2 0 1+	24.64	
3.573	6	-2 -2 1	24.90	
3.509	26	0 -1 2+	25.36	
3.432	6	2 3 0	25.94	
3.341	21	-2 2 1+	26.66	
3.314	19	0 4 1+	26.88	
3.262	3	2 2 1	27.32	
3.236	3	-2 -3 1	27.54	
3.204	9	-1 -2 2+	27.82	
3.175	4	1 -1 2	28.08	
3.102	11	1 4 1+	28.76	
3.010	8	2 -3 1	29.66	
3.006	8	0 -5 1	29.70	
2.974	1	-1 -3 2+	30.02	
2.921	1	3 0 0	30.58	
2.888	4	3 1 0+	30.94	
2.854	4	-3 1 0	31.32	
2.807	2	0 3 2	31.86	
2.764	4	-3 0 1+	32.36	
2.746	12	-2 1 2	32.58	
2.701	2	-1 -4 2+	33.14	
2.670	3	-3 -2 1	33.54	
2.665	3	1 5 1+	33.60	

Benactyzine Hydrochloride, $C_{20}H_{26}ClNO_3$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.644	3	2 4 1+	33.88
2.614	3	2 5 0	34.28
2.598	3	2 1 2+	34.50
2.583	6	1 -4 2	34.70
2.553	3	-3 2 1+	35.12
2.527	2	-2 5 0	35.50
2.505	3	-1 6 0+	35.82
2.481	2	2 2 2+	36.18
2.433	1	-1 -5 2+	36.92
2.399	3	0 6 1+	37.46
2.393	3	3 4 0	37.56
2.362	3	3 -3 1	38.06
2.355	3	0 -1 3+	38.18
2.349	3	-2 5 1+	38.28
2.340	2	1 -5 2	38.44
2.326	2	2 3 2+	38.68
2.312	3	-3 4 0	38.92
2.300	2	2 6 0	39.14
2.263	1	2 -4 2+	39.80
2.229	1	1 0 3+	40.44
2.221	1	0 -7 1+	40.58
2.213	1	1 7 0	40.74
2.190	3	4 0 0+	41.18
2.181	4	-1 -7 1+	41.36
2.170	3	1 5 2	41.58
2.154	1	2 -6 1+	41.90
2.140	1	-2 -1 3	42.20
2.132	2	4 2 0+	42.36
2.112	2	-3 5 0+	42.78
2.101	1	1 2 3+	43.02
2.094	1	-4 2 0+	43.16
2.060	2	-3 3 2	43.92
2.041	2	2 7 0+	44.34
2.037	2	3 -3 2+	44.44
2.033	2	3 -5 1	44.54
2.023	2	3 5 1+	44.76
2.017	2	1 -4 3+	44.90
2.014	1	2 -1 3+	44.98
1.995	1	1 3 3+	45.42
1.987	2	2 5 2+	45.62
1.975	1	-1 -7 2+	45.90
1.965	2	-3 -5 2+	46.16
1.924	1	2 -3 3+	47.20
1.919	1	1 -7 2+	47.34
1.901	3	2 7 1+	47.80
1.830	2	-4 4 1+	49.78
1.826	2	1 8 1+	49.90
1.820	1	4 -4 1	50.08
1.804	2	0 5 3+	50.56
1.800	2	-3 2 3	50.66

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.768	1	2 -7 2+	51.66
1.760	2	0 0 4+	51.92
1.757	2	-4 3 2+	52.00
1.750	2	0 -9 1+	52.22
1.723	1	2 8 1+	53.10
1.714	1	-4 -6 1+	53.40
1.709	1	3 -6 2+	53.58
1.699	1	1 -9 1+	53.92
1.655	1	-4 -2 3+	55.48
1.619	1	-3 -6 3+	56.84
1.584	1	4 -5 2+	58.20

Calculated Pattern (Integrated)				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$	
15.86	66	0 1 0	5.57	
8.76	100	1 0 0	10.08	
7.93	4	0 2 0	11.15	
7.79	20	1 1 0	11.35	
7.56	23	-1 1 0	11.70	
7.04	13	0 0 1	12.56	
6.68	66	0 -1 1	13.25	
6.21	5	0 1 1	14.24	
5.78	83	-1 2 0	15.32	
5.68	1	-1 0 1	15.59	
5.54	94	0 -2 1	15.99	
5.53	87	-1 -1 1	16.02	
5.29	24	0 3 0	16.76	
5.03	3	0 2 1	17.63	
4.96	1	1 1 1	17.86	
4.86	6	-1 -2 1	18.25	
4.52	2	1 -2 1	19.60	
4.457	11	-1 3 0	19.90	
4.410	11	-1 2 1	20.12	
4.313	43	1 2 1	20.58	
4.263	14	2 1 0	20.82	
4.186	2	-2 1 0	21.21	
4.081	7	-1 -3 1	21.76	
4.043	1	0 3 1	21.97	
3.965	5	0 4 0	22.41	
3.894	4	2 2 0	22.82	
3.849	11	1 -3 1	23.09	
3.838	3	-2 0 1	23.15	
3.805	6	-2 -1 1	23.36	
3.779	80	-2 2 0	23.52	
3.687	21	-1 3 1	24.12	
3.662	36	1 4 0	24.29	
3.661	9	-2 1 1	24.29	
3.655	27	1 3 1	24.33	
3.612	4	2 0 1	24.63	

Benactyzine Hydrochloride, $C_{20}H_{26}ClNO_3$ - (continued)

d(Å)	I	hkl	2 θ (°) λ - 1.540598Å
3.608	4	0 -4 1	24.66
3.575	8	-2 -2 1	24.89
3.565	1	-1 4 0	24.96
3.520	21	0 0 2	25.28
3.509	33	0 -1 2	25.36
3.434	9	2 3 0	25.92
3.418	1	-1 -4 1	26.05
3.368	15	0 1 2	26.45
3.346	20	-2 2 1	26.62
3.346	6	-1 -1 2	26.62
3.340	13	0 -2 2	26.67
3.319	16	0 4 1	26.84
3.316	5	-2 3 0	26.86
3.313	14	2 -2 1	26.89
3.262	3	2 2 1	27.32
3.238	4	-2 -3 1	27.52
3.206	9	-1 -2 2	27.80
3.205	7	-1 1 2	27.81
3.192	1	1 0 2	27.93
3.176	5	1 -1 2	28.07
3.107	2	0 2 2	28.71
3.106	4	-1 4 1	28.71
3.102	16	1 4 1	28.76
3.011	13	2 -3 1	29.64
3.003	6	0 -5 1	29.72
2.993	1	2 4 0	29.82
2.973	1	-1 -3 2	30.04
2.921	1	3 0 0	30.58
2.891	4	3 1 0	30.90
2.887	3	1 2 2	30.95
2.882	1	-2 -4 1	31.01
2.855	8	-3 1 0	31.31
2.846	2	-2 -1 2	31.41
2.807	3	0 3 2	31.86
2.792	1	0 5 1	32.03
2.769	2	0 -4 2	32.30
2.765	4	-3 0 1	32.35
2.747	24	-2 1 2	32.57
2.702	2	-1 -4 2	33.13
2.698	1	2 -4 1	33.18
2.671	4	-3 -2 1	33.52
2.664	2	1 5 1	33.62
2.658	1	2 0 2	33.70
2.649	1	-2 4 1	33.81
2.643	2	2 4 1	33.89
2.636	2	3 0 1	33.98
2.614	5	2 5 0	34.28
2.599	2	2 1 2	34.48
2.598	1	3 1 1	34.49
2.596	1	3 3 0	34.52

d(Å)	I	hkl	2 θ (°) λ - 1.540598Å
2.583	11	1 -4 2	34.70
2.556	1	1 6 0	35.08
2.555	2	-3 2 1	35.10
2.553	2	-2 -5 1	35.13
2.527	3	-2 5 0	35.49
2.506	5	-1 6 0	35.80
2.504	1	3 -2 1	35.83
2.498	1	3 2 1	35.92
2.482	2	2 2 2	36.17
2.479	1	0 -5 2	36.21
2.434	1	-1 -5 2	36.90
2.433	1	-1 4 2	36.92
2.408	2	2 -5 1	37.31
2.400	2	1 4 2	37.44
2.399	2	0 6 1	37.46
2.393	4	3 4 0	37.56
2.381	1	-3 3 1	37.75
2.363	4	3 -3 1	38.05
2.355	1	3 3 1	38.19
2.355	2	0 -1 3	38.19
2.350	2	-2 5 1	38.27
2.346	1	0 0 3	38.33
2.340	2	1 -5 2	38.44
2.327	2	2 3 2	38.67
2.327	1	-3 0 2	38.67
2.313	5	-3 4 0	38.91
2.300	3	2 6 0	39.14
2.262	1	2 -4 2	39.81
2.229	2	1 0 3	40.43
2.220	1	0 -7 1	40.60
2.213	2	1 7 0	40.75
2.193	2	0 2 3	41.13
2.191	2	4 0 0	41.17
2.189	2	-1 5 2	41.21
2.182	3	-1 -7 1	41.35
2.181	2	4 1 0	41.37
2.179	1	-3 2 2	41.41
2.175	1	-1 7 0	41.49
2.170	4	1 5 2	41.58
2.166	1	3 -1 2	41.66
2.154	1	2 -6 1	41.90
2.140	1	-2 -1 3	42.19
2.133	2	-4 0 1	42.33
2.131	2	4 2 0	42.37
2.113	1	-2 -2 3	42.76
2.112	1	-3 5 0	42.79
2.101	1	1 2 3	43.02
2.060	3	-3 3 2	43.91
2.046	1	1 7 1	44.23
2.042	2	2 7 0	44.32

Benactyzine Hydrochloride, C₂₀H₂₆ClNO₃ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.037	2	3 -3 2	44.44
2.035	1	4 -1 1	44.49
2.032	1	3 -5 1	44.56
2.023	2	3 5 1	44.76
2.014	1	2 -1 3	44.98
2.013	1	2 0 3	45.01
2.004	1	-2 2 3	45.20
1.995	1	1 3 3	45.41
1.989	1	3 3 2	45.56
1.987	3	2 5 2	45.62
1.976	1	-1 -7 2	45.90
1.965	2	-3 -5 2	46.17
1.965	1	1 6 2	46.17
1.924	1	2 -3 3	47.19
1.919	1	-1 8 0	47.33
1.917	1	1 -7 2	47.39
1.907	1	-2 3 3	47.66
1.902	1	-4 -2 2	47.77
1.902	4	2 7 1	47.79
1.900	2	1 -5 3	47.84
1.830	3	-4 4 1	49.77
1.819	1	4 -4 1	50.10
1.806	1	4 0 2	50.49
1.804	1	0 5 3	50.54
1.804	1	0 -8 2	50.56
1.800	2	-3 2 3	50.66
1.770	1	2 -7 2	51.59
1.768	1	0 -1 4	51.66
1.760	2	0 0 4	51.92
1.757	1	-4 3 2	52.00
1.750	1	0 -9 1	52.23
1.735	1	-5 1 0	52.70
1.699	1	1 -9 1	53.92
1.619	1	-3 -6 3	56.83
1.588	1	-1 -8 3	58.04
1.584	1	4 -5 2	58.22

Beryllium Calcium Iron Magnesium Aluminum Phosphate Hydroxide Hydrate,
Roscherite, $\text{Be}_2\text{Ca}(\text{Fe}_{0.3}\text{Mg}_{0.7})_2\text{Al}_{0.67}(\text{PO}_4)_3(\text{OH})_3 \cdot 2\text{H}_2\text{O}$

Structure

Monoclinic, C2/c (15), Z = 4. The structure was refined by Fanfani et al. [1975] using material from the U.S. National Museum of Natural History (NMNH #R17847) from Lavra da Ilha, Taquaral (Minas Gerais), Brazil.

Atom positions

Fanfani et al. [1975]

4(a) 2.68 aluminum with 1.32 positions void
4(e) 4 calcium
8(f) 5.6 magnesium plus 2.4 iron
8(f) 8 beryllium
8(f) 8 phosphorus
4(e) 4 phosphorus
8(f) 8 oxygen in each of 6 different sites
8(f) 8 hydroxyl
4(e) 4 hydroxyl
8(f) 8 water

Polymorphism

A triclinic roscherite exists and has a very similar atomic arrangement. Its chemical composition is somewhat different including the replacement of most of the magnesium by manganese [Fanfani et al., 1977].

Lattice constants

a = 15.875(4) Å
b = 11.855(3)
c = 6.605(1)
β = 95.35(3)°

a/b = 1.3391
c/b = 0.5571

(published values: a = 15.874(4) Å,
b = 11.854(3), c = 6.605(1), β = 95°21'(2')
[Fanfani et al., 1975]).

Volume
1237.6 Å³

Density

(calculated) 2.768 g/cm³
(measured) 2.766(7) [Fanfani et al., 1975]

Thermal parameters

Isotropic [Fanfani et al., 1975]

Scattering factors

Zero ionization [International Tables, 1962].

Scale factors (integrated intensities)

γ = 0.1851 × 10⁻³
I/I_{corundum} (calculated) = 0.654 for reflection
with hkl = 110.

Additional patterns

1. PDF card 11-355 [Lindberg, 1958]. The data may represent a mixture of the monoclinic and triclinic forms.

References

- Fanfani, L., Nunzi, A., Zanazzi, P. F., and Zanzari, A. R. (1975). Tschermak's Mineral. Petrogr. Mitt. 22, 266.
Fanfani, L., Zanazzi, P. F., and Zanzari, A. R. (1977). Tschermak's Mineral. Petrogr. Mitt. 24, 169.
International Tables for X-ray Crystallography III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.
Lindberg, M. L. (1958). Amer. Mineral. 43, 824.

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
9.48	100	1 1 0	9.32	
7.89	3	2 0 0	11.20	
5.925	83	0 2 0	14.94	
5.549	2	-1 1 1	15.96	
4.813	31	3 1 0	18.42	
4.741	7	2 2 0	18.70	
4.401	12	0 2 1	20.16	
3.948	3	4 0 0+	22.50	
3.831	1	1 3 0	23.20	
3.736	4	3 1 1	23.80	
3.343	29	-1 3 1	26.64	
3.285	15	4 2 0+	27.12	
3.160	51	3 3 0	28.22	
3.142	46	-2 0 2	28.38	
3.054	48	1 1 2+	29.22	
2.940	37	2 0 2	30.38	
2.915	6	-3 3 1	30.64	
2.873	16	0 2 2	31.10	
2.854	10	4 2 1	31.32	
2.829	16	-3 1 2	31.60	
2.774	58	2 4 0	32.24	
2.701	3	0 4 1	33.14	
2.679	4	5 1 1	33.42	
2.633	41	6 0 0	34.02	
2.587	3	-2 4 1	34.64	
2.527	4	2 4 1+	35.50	
2.468	3	1 3 2+	36.38	
2.420	6	-4 2 2+	37.12	
2.408	12	6 2 0	37.32	
2.371	6	4 4 0	37.92	
2.345	9	1 5 0+	38.36	
2.326	1	-6 2 1	38.68	
2.271	6	-4 4 1	39.66	
2.258	2	5 3 1	39.90	
2.239	2	4 2 2	40.24	
2.218	25	7 1 0+	40.64	
2.202	13	0 4 2	40.96	
2.162	17	-1 1 3+	41.74	
2.157	12	-6 0 2+	41.84	
2.087	2	2 4 2	43.32	

Beryllium Calcium Iron Magnesium Aluminum Phosphate Hydroxide Hydrate,
Roscherite, $\text{Be}_2\text{Ca}(\text{Fe}_{0.7}\text{Mg}_{0.7})_2\text{Al}_{0.67}(\text{PO}_4)_3(\text{OH})_3 \cdot 2\text{H}_2\text{O}$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.062	2	-3 1 3	43.88
2.056	3	0 2 3	44.00
2.046	8	7 1 1	44.24
2.033	8	-2 2 3+	44.52
2.027	10	-6 2 2	44.68
1.976	14	-4 4 2+	45.88
1.971	10	6 4 0	46.00
1.922	8	-1 5 2+	47.26
1.917	8	2 6 0	47.38
1.909	5	5 3 2	47.60
1.892	2	-4 2 3+	48.04
1.885	3	1 3 3	48.24
1.874	2	4 4 2+	48.54
1.868	4	6 2 2	48.70
1.863	3	-5 1 3	48.84
1.846	1	-8 2 1	49.32
1.839	2	7 3 1+	49.54
1.796	2	5 5 1	50.80
1.776	5	3 5 2	51.42
1.767	11	-8 0 2+	51.68
1.763	8	0 4 3+	51.80
1.748	3	-2 4 3	52.30
1.743	7	-6 4 2	52.44
1.739	4	9 1 0	52.58
1.710	2	5 1 3	53.56
1.694	9	0 6 2+	54.10
1.684	2	1 7 0+	54.44
1.673	1	-2 6 2	54.84
1.657	4	-4 4 3	55.42
1.644	21	8 4 0+	55.88
1.640	18	6 4 2+	56.04
1.635	12	-1 7 1+	56.20
1.628	5	1 7 1+	56.48
1.624	3	-8 4 1	56.62
1.612	2	-1 5 3+	57.08
1.605	6	9 3 0+	57.38
1.5904	3	1 5 3+	57.94
1.5804	5	6 6 0+	58.34
1.5765	3	-3 7 1	58.50
1.5696	3	8 2 2	58.78
1.5662	5	8 4 1+	58.92
1.5629	3	7 5 1	59.06
1.5561	2	6 2 3+	59.34
1.5236	1	-7 3 3	60.74
1.5173	4	3 1 4+	61.02
1.5052	2	-7 5 2+	61.56
1.4930	6	-9 3 2+	62.12
1.4802	1	9 1 2+	62.72
1.4676	2	0 6 3	63.32
1.4643	3	-3 7 2	63.48

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.4601	2	-2 6 3	63.68
1.4569	4	-6 6 2+	63.84
1.4420	1	5 7 1	64.58
1.4352	6	-2 4 4+	64.92

Calculated Pattern (Integrated)			
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
9.48	100	1 1 0	9.32
7.90	3	2 0 0	11.19
5.927	87	0 2 0	14.93
5.552	2	-1 1 1	15.95
4.815	33	3 1 0	18.41
4.742	5	2 2 0	18.70
4.403	13	0 2 1	20.15
3.953	1	-2 2 1	22.48
3.951	3	4 0 0	22.48
3.834	1	1 3 0	23.18
3.736	5	3 1 1	23.80
3.345	33	-1 3 1	26.63
3.288	5	0 0 2	27.10
3.288	9	4 2 0	27.10
3.280	4	1 3 1	27.17
3.162	8	-1 1 2	28.20
3.161	46	3 3 0	28.21
3.141	46	-2 0 2	28.39
3.054	22	5 1 0	29.21
3.054	34	1 1 2	29.22
3.037	3	-4 2 1	29.39
2.964	5	0 4 0	30.13
2.940	44	2 0 2	30.38
2.914	3	-3 3 1	30.66
2.875	16	0 2 2	31.08
2.871	3	-5 1 1	31.13
2.854	9	4 2 1	31.32
2.830	17	-3 1 2	31.59
2.789	1	3 3 1	32.07
2.776	8	-2 2 2	32.22
2.775	63	2 4 0	32.23
2.702	3	0 4 1	33.13
2.680	4	5 1 1	33.41
2.634	49	6 0 0	34.00
2.634	2	2 2 2	34.01
2.614	2	3 1 2	34.28
2.587	2	-2 4 1	34.64
2.527	4	2 4 1	35.49
2.524	1	-1 3 2	35.54
2.469	1	5 3 0	36.37

Beryllium Calcium Iron Magnesium Aluminum Phosphate Hydroxide Hydrate,
Roscherite, $\text{Be}_2\text{Ca}(\text{Fe}_{0.3}\text{Mg}_{0.7})_2\text{Al}_{0.67}(\text{PO}_4)_3(\text{OH})_3 \cdot 2\text{H}_2\text{O}$ - (continued)

d(Å)	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.468	3	1 3 2	36.37
2.421	4	-4 2 2	37.11
2.419	2	4 0 2	37.14
2.407	14	6 2 0	37.32
2.371	7	4 4 0	37.92
2.345	3	-3 3 2	38.35
2.345	7	1 5 0	38.36
2.325	1	-6 2 1	38.69
2.271	7	-4 4 1	39.65
2.258	2	5 3 1	39.90
2.240	1	4 2 2	40.23
2.218	11	-1 5 1	40.64
2.218	16	7 1 0	40.64
2.218	4	3 3 2	40.65
2.201	13	0 4 2	40.96
2.199	1	1 5 1	41.01
2.192	2	4 4 1	41.15
2.162	18	-1 1 3	41.74
2.162	2	3 5 0	41.74
2.156	1	-6 0 2	41.86
2.156	1	-2 4 2	41.87
2.144	1	5 1 2	42.12
2.087	2	2 4 2	43.31
2.062	1	-3 1 3	43.86
2.056	2	0 2 3	44.01
2.047	1	-5 3 2	44.21
2.046	8	7 1 1	44.24
2.034	7	-2 2 3	44.52
2.031	2	3 5 1	44.58
2.026	8	-6 2 2	44.68
1.976	13	-4 4 2	45.88
1.976	4	0 6 0	45.89
1.976	2	8 0 0	45.89
1.969	2	6 4 0	46.06
1.968	1	6 0 2	46.08
1.923	1	-6 4 1	47.22
1.922	4	-1 3 3	47.26
1.922	4	-1 5 2	47.26
1.917	4	2 6 0	47.39
1.909	4	5 3 2	47.61
1.897	1	5 5 0	47.92
1.893	1	-4 2 3	48.03
1.885	3	1 3 3	48.25
1.874	1	4 4 2	48.54
1.868	4	6 2 2	48.71
1.862	1	-5 1 3	48.87
1.846	1	-8 2 1	49.32
1.838	2	7 3 1	49.54
1.796	2	5 5 1	50.80
1.776	6	3 5 2	51.42

d(Å)	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.768	8	-8 0 2	51.66
1.767	5	4 6 0	51.68
1.762	2	0 4 3	51.83
1.762	1	8 2 1	51.85
1.748	3	-2 4 3	52.29
1.744	7	-6 4 2	52.43
1.737	2	9 1 0	52.64
1.709	2	5 1 3	53.57
1.694	5	-8 2 2	54.09
1.694	6	0 6 2	54.11
1.684	2	1 7 0	54.44
1.673	1	-2 6 2	54.85
1.656	5	-4 4 3	55.43
1.644	10	0 0 4	55.88
1.644	16	8 4 0	55.88
1.643	2	9 1 1	55.93
1.640	1	-2 0 4	56.01
1.640	2	2 6 2	56.03
1.640	4	6 4 2	56.04
1.636	1	-7 1 3	56.18
1.635	7	-1 7 1	56.21
1.628	2	8 0 2	56.48
1.627	2	1 7 1	56.50
1.625	1	-8 4 1	56.60
1.612	1	-1 5 3	57.07
1.605	2	1 1 4	57.37
1.605	6	9 3 0	57.37
1.605	1	5 5 2	57.38
1.5981	1	-9 1 2	57.63
1.5904	3	1 5 3	57.94
1.5806	3	6 6 0	58.33
1.5806	1	10 0 0	58.33
1.5805	1	2 0 4	58.34
1.5764	1	-3 7 1	58.50
1.5697	3	8 2 2	58.78
1.5665	2	8 4 1	58.91
1.5665	2	4 4 3	58.91
1.5623	1	7 5 1	59.08
1.5561	1	6 2 3	59.34
1.5239	1	-7 3 3	60.73
1.5183	1	-4 2 4	60.97
1.5183	1	-8 4 2	60.98
1.5177	1	6 6 1	61.00
1.5168	3	3 1 4	61.04
1.5107	1	3 5 3	61.31
1.5054	1	-5 1 4	61.55
1.5052	1	-7 5 2	61.56
1.4933	3	-9 3 2	62.11
1.4932	2	-3 3 4	62.11
1.4928	1	5 7 0	62.13

Beryllium Calcium Iron Magnesium Aluminum Phosphate Hydroxide Hydrate,
Roscherite, $\text{Be}_2\text{Ca}(\text{Fe}_{0.3}\text{Mg}_{0.7})_2\text{Al}_{0.67}(\text{PO}_4)_3(\text{OH})_3 \cdot 2\text{H}_2\text{O}$ - (continued)

$d(\text{\AA})$	I	hkl			$2\theta(^{\circ})$
					$\lambda - 1.540598\text{\AA}$
1.4923	2	7	1	3	62.15
1.4912	2	-8	2	3	62.20
1.4807	1	9	1	2	62.70
1.4676	2	0	6	3	63.32
1.4643	3	-3	7	2	63.48
1.4594	1	-2	6	3	63.72
1.4571	2	-6	0	4	63.83
1.4568	2	-6	6	2	63.85
1.4422	1	5	7	1	64.57
1.4354	1	-10	2	2	64.91
1.4352	7	-2	4	4	64.92

Beryllium Calcium Manganese Aluminum Iron Phosphate Hydroxide Hydrate,
Roscherite, $\text{Be}_4\text{Ca}_2(\text{Mn}_{3.91}\text{Mg}_{0.04}\text{Ca}_{0.05})(\text{Al}_{1.13}\text{Fe}_{0.42}\text{Mn}_{1.2})(\text{PO}_4)_6(\text{OH})_4 \cdot 6\text{H}_2\text{O}$

Structure

Triclinic, $\text{C}\bar{1}$ (2), $Z = 2$. The structure was refined by Fanfani et al. [1977]. The material used in the structure determination was from Foote Mine, NC.

Atom positions

The trivalent cations Fe, Mn and Al filled only 2/3 of the special positions at 0, 0, $\frac{1}{2}$, the rest being void. All other atoms were in the 4 general positions of the C-centered arrangement [ibid.]. The z coordinate for O(4B) was taken as + 0.1754 and the z coordinate for O(5A) was taken as + 0.9195.

Polymorphism

A monoclinic roscherite exists and has a very similar atomic arrangement with partial disorder of the trivalent cations over the sites (0, 0, 0) and (0, 0, $\frac{1}{2}$). Its chemical composition is somewhat different, including the replacement of most of the manganese by magnesium [Fanfani et al., 1977].

Lattice constants

$a = 15.922(5) \text{ \AA}$
 $b = 11.966(4)$
 $c = 6.741(1)$
 $\alpha = 91.07(8)^\circ$
 $\beta = 94.35(8)$
 $\gamma = 89.99(8)$

(published values: $a = 15.921(5) \text{ \AA}$,
 $b = 11.965(4)$, $c = 6.741(1)$, $\alpha = 91^\circ 4(5)'$,
 $\beta = 94^\circ 21(5)'$, $\gamma = 89^\circ 59.5(5.0)'$ [Fanfani et al., 1977]).

CD cell: $a = 9.959 \text{ \AA}$, $b = 9.957$, $c = 6.741$,
 $\alpha = 92.83^\circ$, $\beta = 94.12$, $\gamma = 73.85$, sp. gp. Pl;
 $a/b = 1.0002$, $c/b = 0.6770$

Volume
 $1280.4 \text{ \AA}^3$

Density
 (calculated) 2.888 g/cm^3

Thermal parameters
 Isotropic [Fanfani et al., 1977]

Scattering factors
 Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)
 $\gamma = 0.1244 \times 10^{-3}$
 I/I_{corundum} (calculated) = 0.728 for
 reflection with $hkl = 020$.

References

Fanfani, L., Zanazzi, P. F., and Zanzari, A. R.
 (1977). Tschermak's Mineral. Petrogr. Mitt.
 24, 169.
International Tables for X-ray Crystallography
 III (1962). (The Kynoch Press, Birmingham,
 Eng.) p. 202.

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598 Å
9.54	100	-1 1 0+	9.26	
7.94	11	2 0 0	11.14	
6.71	2	0 0 1	13.18	
5.981	90	0 2 0	14.80	
5.654	11	-1 -1 1	15.66	
5.576	4	-1 1 1	15.88	
5.342	6	1 1 1+	16.58	
4.935	2	2 0 1	17.96	
4.839	40	3 1 0+	18.32	
4.507	3	0 -2 1	19.68	
4.423	10	0 2 1	20.06	
4.008	5	-2 -2 1	22.16	
3.952	2	-2 2 1	22.48	
3.786	5	3 1 1+	23.48	
3.404	8	-1 -3 1	26.16	
3.353	21	-1 3 1+	26.56	
3.307	6	4 2 0+	26.94	
3.229	8	-1 -1 2	27.60	
3.182	94	-2 0 2+	28.02	
3.140	20	1 -1 2	28.40	
3.110	18	1 1 2	28.68	
3.068	18	-5 1 0+	29.08	
3.014	36	2 0 2	29.62	
2.992	11	0 4 0	29.84	
2.951	5	0 -2 2+	30.26	
2.906	5	0 2 2	30.74	
2.864	9	-3 -1 2	31.20	
2.843	11	-3 1 2	31.44	
2.831	9	-2 -2 2	31.58	
2.798	48	2 4 0+	31.96	
2.751	3	0 -4 1	32.52	
2.722	6	5 -1 1	32.88	
2.714	6	5 1 1+	32.98	
2.682	3	3 -1 2	33.38	
2.645	43	6 0 0	33.86	
2.593	3	-2 4 1	34.56	
2.585	3	-1 -3 2	34.68	
2.576	5	2 -4 1	34.80	
2.536	6	1 -3 2+	35.36	
2.485	4	1 3 2+	36.12	
2.474	4	4 0 2	36.28	
2.448	2	-4 -2 2	36.68	
2.420	14	-6 2 0+	37.12	
2.384	9	-3 -3 2+	37.70	
2.366	6	-1 5 0+	38.00	
2.348	4	-3 3 2	38.30	
2.295	2	5 -3 1+	39.22	
2.274	4	-4 4 1+	39.60	
2.253	11	0 -4 2+	39.98	
2.228	22	-1 5 1+	40.46	

Beryllium Calcium Manganese Aluminum Iron Phosphate Hydroxide Hydrate, Roscherite,
 $\text{Be}_4\text{Ca}_2(\text{Mn}_{3.91}\text{Mg}_{0.04}\text{Ca}_{0.05})(\text{Al}_{1.13}\text{Fe}_{0.42}\text{Mn}_{1.2})(\text{PO}_4)_6(\text{OH})_4 \cdot 6\text{H}_2\text{O}$ - (continued)

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
2.211	20	-1 -1 3+	40.78	
2.196	10	-1 1 3+	41.06	
2.180	4	3 5 0+	41.38	
2.160	4	-6 0 2+	41.78	
2.154	3	1 1 3	41.90	
2.142	2	2 -4 2	42.16	
2.105	2	2 4 2+	42.94	
2.095	2	-3 -1 3	43.14	
2.076	7	-2 -2 3	43.56	
2.072	9	7 -1 1	43.66	
2.067	11	7 1 1+	43.76	
2.053	4	-2 2 3	44.08	
2.046	4	3 5 1+	44.24	
2.040	3	-6 -2 2	44.38	
2.025	2	-6 2 2	44.72	
2.004	6	-4 -4 2+	45.20	
1.994	5	0 6 0	45.44	
1.984	3	8 0 0	45.68	
1.976	4	-4 4 2+	45.88	
1.962	2	-1 -5 2	46.24	
1.955	3	5 -3 2	46.42	
1.933	8	5 3 2+	46.96	
1.929	7	-1 5 2+	47.08	
1.909	2	6 -2 2+	47.60	
1.903	2	-4 2 3	47.76	
1.898	2	6 2 2	47.90	
1.883	1	8 2 0+	48.30	
1.871	1	-5 1 3	48.62	
1.867	2	-5 -5 1+	48.74	
1.851	1	-8 -2 1+	49.18	
1.824	2	5 -5 1	49.96	
1.818	2	3 -5 2	50.14	
1.808	3	5 5 1+	50.42	
1.789	4	3 5 2+	51.02	
1.782	6	-4 6 0+	51.22	
1.778	5	0 4 3+	51.36	
1.769	7	-8 0 2	51.64	
1.760	5	-6 -4 2	51.90	
1.757	5	-2 4 3	52.02	
1.753	5	5 -1 3	52.12	
1.742	7	-6 4 2+	52.50	
1.729	4	0 -6 2	52.92	
1.700	7	0 6 2+	53.88	
1.692	3	-8 2 2	54.16	
1.685	5	-4 -4 3	54.40	
1.680	10	0 0 4	54.58	
1.676	8	6 -4 2	54.72	
1.654	15	-8 4 0+	55.52	
1.640	4	1 1 4+	56.04	
1.638	4	1 7 1	56.12	

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
1.633	4	1 -5 3+	56.30	
1.627	3	-8 4 1+	56.52	
1.622	2	-1 5 3	56.70	

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
9.56	57	-1 1 0	9.24	
9.55	49	1 1 0	9.25	
7.94	11	2 0 0	11.14	
6.72	2	0 0 1	13.16	
5.982	100	0 2 0	14.80	
5.659	12	-1 -1 1	15.65	
5.579	3	-1 1 1	15.87	
5.346	5	1 1 1	16.57	
5.332	1	-2 0 1	16.61	
4.947	1	2 0 1	17.91	
4.842	21	-3 1 0	18.31	
4.837	25	3 1 0	18.33	
4.780	1	-2 2 0	18.55	
4.774	1	2 2 0	18.57	
4.510	3	0 -2 1	19.67	
4.427	12	0 2 1	20.04	
4.049	1	-3 1 1	21.93	
4.009	5	-2 -2 1	22.16	
3.953	1	-2 2 1	22.47	
3.818	1	3 -1 1	23.28	
3.790	4	3 1 1	23.45	
3.785	2	2 2 1	23.48	
3.406	8	-1 -3 1	26.14	
3.360	12	0 0 2	26.50	
3.353	13	-1 3 1	26.56	
3.353	2	1 -3 1	26.57	
3.309	3	-4 2 0	26.92	
3.305	3	4 2 0	26.95	
3.232	7	-1 -1 2	27.58	
3.201	6	-1 1 2	27.85	
3.187	33	-3 3 0	27.98	
3.183	36	3 3 0	28.01	
3.182	51	-2 0 2	28.02	
3.140	20	1 -1 2	28.40	
3.111	18	1 1 2	28.67	
3.070	12	-5 1 0	29.06	
3.068	9	5 1 0	29.08	
3.013	44	2 0 2	29.62	
2.991	8	0 4 0	29.85	
2.953	4	0 -2 2	30.24	
2.947	2	-3 -3 1	30.31	
2.907	5	0 2 2	30.74	
2.883	2	4 2 1	30.99	
2.877	1	-5 -1 1	31.06	
2.865	9	-3 -1 2	31.19	

Beryllium Calcium Manganese Aluminum Iron Phosphate Hydroxide Hydrate, Roshcherite,
 $\text{Be}_4\text{Ca}_2(\text{Mn}_{3.91}\text{Mg}_{0.04}\text{Ca}_{0.05})(\text{Al}_{13}\text{Fe}_{42}\text{Mn}_{12})(\text{PO}_4)_6(\text{OH})_4 \cdot 6\text{H}_2\text{O}$ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.844	12	-3 1 2	31.43
2.830	6	-2 -2 2	31.59
2.812	1	3 3 1	31.80
2.800	30	-2 4 0	31.94
2.798	31	2 4 0	31.96
2.790	3	-2 2 2	32.06
2.752	2	0 -4 1	32.51
2.723	6	5 -1 1	32.87
2.712	3	5 1 1	33.00
2.710	2	2 -2 2	33.03
2.684	2	3 -1 2	33.36
2.666	1	-4 0 2	33.59
2.665	4	3 1 2	33.60
2.646	55	6 0 0	33.85
2.624	1	-2 -4 1	34.14
2.593	3	-2 4 1	34.56
2.584	1	-1 -3 2	34.69
2.576	4	2 -4 1	34.80
2.543	2	2 4 1	35.26
2.537	2	-1 3 2	35.35
2.537	4	1 -3 2	35.36
2.492	3	1 3 2	36.02
2.486	2	-5 3 0	36.11
2.483	1	5 3 0	36.15
2.474	3	4 0 2	36.29
2.448	3	-4 -2 2	36.68
2.423	2	-4 2 2	37.08
2.421	9	-6 2 0	37.11
2.419	8	6 2 0	37.14
2.390	4	-4 4 0	37.60
2.387	4	4 4 0	37.65
2.384	5	-3 -3 2	37.70
2.366	4	-1 5 0	37.99
2.366	3	1 5 0	38.01
2.349	4	-3 3 2	38.29
2.298	1	4 -2 2	39.17
2.296	1	5 -3 1	39.21
2.294	1	-4 -4 1	39.24
2.274	3	-4 4 1	39.60
2.255	8	0 -4 2	39.95
2.253	7	-1 -5 1	39.99
2.230	1	4 -4 1	40.41
2.229	9	-7 1 0	40.44
2.228	8	7 1 0	40.46
2.227	12	-1 5 1	40.47
2.214	10	0 4 2	40.73
2.211	16	-1 -1 3	40.78
2.208	3	4 4 1	40.84
2.200	1	-2 0 3	40.99
2.198	2	-2 -4 2	41.02

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.196	8	-1 1 3	41.07
2.181	2	-3 5 0	41.36
2.179	2	3 5 0	41.40
2.161	1	-2 4 2	41.77
2.160	4	-6 0 2	41.79
2.152	2	1 1 3	41.95
2.141	2	2 -4 2	42.17
2.105	1	2 4 2	42.94
2.095	1	-3 -1 3	43.14
2.085	2	0 2 3	43.36
2.077	6	-2 -2 3	43.54
2.072	5	7 -1 1	43.65
2.068	2	-5 -3 2	43.74
2.067	8	7 1 1	43.76
2.053	4	-2 2 3	44.08
2.045	2	-5 3 2	44.24
2.044	2	3 5 1	44.27
2.039	2	-6 -2 2	44.40
2.025	2	-6 2 2	44.73
2.006	3	6 0 2	45.16
2.004	5	-4 -4 2	45.20
1.994	6	0 6 0	45.45
1.985	2	8 0 0	45.68
1.977	4	-4 4 2	45.87
1.970	1	-1 -3 3	46.04
1.962	2	-1 -5 2	46.23
1.954	3	5 -3 2	46.43
1.939	2	-1 3 3	46.82
1.938	2	1 -3 3	46.83
1.934	2	-2 6 0	46.93
1.933	3	2 6 0	46.96
1.932	4	5 3 2	46.99
1.928	2	-1 5 2	47.09
1.927	1	-7 -1 2	47.12
1.925	1	-6 4 1	47.17
1.921	1	-4 -2 3	47.28
1.909	1	6 -2 2	47.59
1.902	2	-4 2 3	47.77
1.895	1	6 2 2	47.96
1.872	1	-5 1 3	48.60
1.867	1	-5 -5 1	48.73
1.864	1	7 -3 1	48.81
1.851	1	-8 -2 1	49.19
1.824	2	5 -5 1	49.95
1.818	2	3 -5 2	50.14
1.811	2	4 -2 3	50.34
1.808	3	5 5 1	50.42
1.789	3	3 5 2	51.00
1.788	2	-2 -4 3	51.05
1.783	3	-4 6 0	51.20

Beryllium Calcium Manganese Aluminum Iron Phosphate Hydroxide Hydrate, Roshcherite,
 $\text{Be}_4\text{Ca}_2(\text{Mn}_{3.91}\text{Mg}_{.04}\text{Ca}_{.05})(\text{Al}_{.13}\text{Fe}_{.42}\text{Mn}_{.12})(\text{PO}_4)_6(\text{OH})_4 \cdot 6\text{H}_2\text{O}$ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.782	1	3 3 3	51.23
1.781	3	4 6 0	51.26
1.777	1	8 2 1	51.36
1.777	2	0 4 3	51.37
1.769	9	-8 0 2	51.64
1.760	5	-6 -4 2	51.90
1.757	3	-2 4 3	52.00
1.753	3	5 -1 3	52.12
1.745	1	-9 1 0	52.38
1.745	1	5 1 3	52.38
1.745	1	9 1 0	52.40
1.742	5	-6 4 2	52.49
1.741	2	2 -4 3	52.51
1.729	6	0 -6 2	52.91
1.705	1	-5 -5 2	53.71
1.701	4	0 6 2	53.86
1.700	3	-8 -2 2	53.89
1.700	1	-1 7 0	53.90
1.699	1	1 7 0	53.92
1.692	2	-8 2 2	54.17
1.685	4	-4 -4 3	54.40
1.680	12	0 0 4	54.58
1.676	3	6 -4 2	54.74
1.670	1	-2 0 4	54.95
1.660	2	-4 4 3	55.29
1.658	4	-1 -7 1	55.37
1.658	1	9 1 1	55.38
1.657	3	6 4 2	55.41
1.655	2	8 0 2	55.49
1.655	9	-8 4 0	55.49
1.653	8	8 4 0	55.56
1.645	2	-7 -1 3	55.84
1.644	3	-1 7 1	55.90
1.638	1	1 1 4	56.11
1.637	2	1 7 1	56.14
1.633	3	1 -5 3	56.30
1.627	1	-3 7 0	56.52
1.627	2	-8 4 1	56.53
1.621	1	-1 5 3	56.74

Calcium Borate Hydrate, Hexahydroborite, $\text{Ca}[\text{B}(\text{OH})_4]_2 \cdot 2\text{H}_2\text{O}$

Structure

Monoclinic, P2/a (13), $Z = 2$. The structure was determined by Simonov et al. [1976], for material from the Solongo deposits in the Urals.

Atom positions

Calcium atoms were in special positions (3/4, 0, z). All other atoms were in general positions [ibid.].

Lattice constants

Simonov et al. [1976]

$a = 8.006(2) \text{ \AA}$
 $b = 8.012(2)$
 $c = 6.649(2)$
 $\gamma = 104.21(2)^\circ$

CD cell: $a = 8.012 \text{ \AA}$, $b = 6.649$, $c = 8.006$,
 $\beta = 104.21^\circ$ sp. gp. P2/c; $a/b = 1.2050$,
 $c/b = 1.2041$

Volume

$413.4 \text{ \AA}^3$

Density

(calculated) 1.878 g/cm^3

Thermal parameters

Isotropic [Simonov et al., 1976]

Scattering factors

B^0 , Ca^0 , O^- [Cromer and Mann, 1968].
 H^0 [International Tables, 1962]

Scale factors (integrated intensities)

$\gamma = 0.4656 \times 10^{-3}$
 I/I_{corundum} (calculated) = 1.05 for reflection
 with $hkl = 010$.

Additional pattern

1. PDF card 23-866 [Gode and Kuka, 1970]

References

Cromer, D. T. and Mann, J. B. (1968). Acta Crystallogr. A24, 321.
 Gode, G. K. and Kuka, P. Ya. (1970). Russ. J. Inorg. Chem. 15, 603.
 International Tables for X-ray Crystallography III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.
 Simonov, M. A., Yamanova, N. A., Kazanskaya, E. V., Egorov - Tismenko, Yu. K., and Belov, N. V. (1976). Sov. Phys. Dokl. 21, 314.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$
$\lambda = 1.540598\text{\AA}$			
7.76	100	0 1 0	11.40
6.64	38	0 0 1	13.32
5.046	12	0 1 1	17.56
4.576	13	-1 1 1	19.38
3.952	20	1 1 1	22.48
3.877	6	0 2 0+	22.92
3.346	76	-1 2 1+	26.62
3.173	14	2 1 0	28.10
3.056	4	0 1 2	29.20
2.855	7	-2 2 1+	31.30
2.754	1	1 1 2	32.48
2.589	2	0 3 0	34.62
2.524	43	2 0 2	35.54
2.468	35	-3 1 1+	36.38
2.413	13	0 3 1	37.24
2.295	23	2 1 2+	39.22
2.216	2	0 0 3	40.68
2.167	7	1 3 1	41.64
2.131	3	0 1 3+	42.38
2.092	1	-1 1 3	43.22
2.076	4	-3 1 2	43.56
2.042	1	0 3 2+	44.32
2.021	2	1 1 3	44.82
1.971	16	-2 3 2	46.00
1.941	10	0 4 0	46.76
1.936	12	-4 2 0+	46.88
1.924	11	-2 1 3+	47.20
1.863	10	4 0 1+	48.86
1.817	8	1 2 3+	50.16
1.782	3	4 1 0	51.22
1.776	8	-4 3 0	51.42
1.722	3	4 1 1	53.16
1.716	3	-4 3 1	53.34
1.703	2	-1 3 3	53.80
1.683	1	3 0 3+	54.48
1.678	3	3 2 2+	54.66
1.674	4	-2 4 2+	54.80
1.662	3	0 0 4	55.22
1.646	3	2 2 3	55.80
1.625	2	0 1 4+	56.58
1.608	1	-1 1 4	57.26
1.587	3	4 2 0	58.08
1.571	1	4 1 2+	58.72
1.553	4	0 5 0+	59.46
1.544	2	2 4 1	59.86
1.537	2	-4 4 1	60.14
1.528	2	2 0 4+	60.56
1.4853	1	-4 1 3	62.48
1.4709	1	1 2 4+	63.16
1.4676	1	-3 5 1	63.32

Calcium Borate Hydrate, Hexahydroborite, $\text{Ca}[\text{B}(\text{OH})_4]_2 \cdot 2\text{H}_2\text{O}$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.4618	2	2 3 3+	63.60
1.4325	1	2 4 2	65.06
1.4286	2	-2 5 2+	65.26
1.4094	1	-1 3 4	66.26

Calculated Pattern (Integrated)			
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
7.77	100	0 1 0	11.38
6.65	38	0 0 1	13.31
5.051	13	0 1 1	17.54
4.581	14	-1 1 1	19.36
3.955	21	1 1 1	22.46
3.883	3	0 2 0	22.88
3.881	2	2 0 0	22.90
3.872	3	-2 1 0	22.95
3.353	27	0 2 1	26.56
3.351	16	2 0 1	26.58
3.347	27	-1 2 1	26.61
3.346	24	-2 1 1	26.62
3.324	7	0 0 2	26.79
3.174	16	2 1 0	28.09
3.056	4	0 1 2	29.20
2.865	3	1 2 1	31.19
2.864	2	2 1 1	31.20
2.854	6	-2 2 1	31.32
2.754	2	1 1 2	32.48
2.589	3	0 3 0	34.62
2.525	46	2 0 2	35.53
2.523	6	-1 2 2	35.55
2.469	19	-1 3 1	36.35
2.468	25	-3 1 1	36.37
2.460	1	2 2 0	36.50
2.449	2	-2 3 0	36.67
2.413	15	0 3 1	37.24
2.411	2	3 0 1	37.27
2.298	2	-2 3 1	39.17
2.297	2	-3 2 1	39.18
2.296	3	1 2 2	39.20
2.296	22	2 1 2	39.21
2.290	3	-2 2 2	39.30
2.216	2	0 0 3	40.68
2.168	8	1 3 1	41.63
2.131	3	0 1 3	42.38
2.131	1	1 0 3	42.38
2.091	1	-1 1 3	43.22
2.076	5	-3 1 2	43.56
2.043	1	0 3 2	44.31

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.021	3	1 1 3	44.82
1.977	8	2 2 2	45.86
1.972	16	-2 3 2	45.99
1.971	1	-3 2 2	46.00
1.942	10	0 4 0	46.75
1.937	3	-2 4 0	46.86
1.936	6	-4 2 0	46.89
1.925	3	0 2 3	47.18
1.925	2	2 0 3	47.19
1.924	2	-1 2 3	47.21
1.924	6	-2 1 3	47.21
1.917	1	-4 1 1	47.40
1.866	4	2 3 1	48.75
1.866	3	3 2 1	48.76
1.864	2	0 4 1	48.82
1.863	6	4 0 1	48.86
1.860	1	-2 4 1	48.94
1.817	9	1 2 3	50.16
1.815	5	-2 2 3	50.24
1.782	2	4 1 0	51.21
1.776	10	-4 3 0	51.41
1.722	3	4 1 1	53.16
1.716	2	-4 3 1	53.35
1.703	3	-1 3 3	53.80
1.683	1	3 0 3	54.47
1.678	2	3 2 2	54.65
1.674	4	-2 4 2	54.80
1.662	4	0 0 4	55.21
1.646	4	2 2 3	55.79
1.625	2	0 1 4	56.58
1.608	1	-1 1 4	57.26
1.587	4	4 2 0	58.08
1.571	1	4 1 2	58.73
1.555	2	-5 1 1	59.39
1.553	4	0 5 0	59.46
1.544	3	2 4 1	59.85
1.537	1	-4 4 1	60.14
1.4854	1	-4 1 3	62.47
1.4726	1	1 2 4	63.08
1.4676	1	-3 5 1	63.32
1.4617	2	2 3 3	63.60
1.4326	1	2 4 2	65.06
1.4288	1	-2 5 2	65.25
1.4271	1	-4 4 2	65.34
1.4096	1	-1 3 4	66.25

Calcium Chromium Iron Titanium Oxide, Loveringite,
 $\text{Ca}_{.72}\text{RE}_{.33}(\text{Y}, \text{Th}, \text{U}, \text{Pb})_{.05}\text{Ti}_{12.48}\text{Fe}_{3.38}\text{Cr}_{2.24}\text{Mg}_{.92}\text{Zr}_{.58}\text{Al}_{.39}\text{V}_{.21}\text{Mn}_{.04}\text{O}_{38}$

Structure

Hexagonal, $R\bar{3}$ (148), $Z = 3$, isostructural with senaite. The structure was refined by Gatehouse et al. [1978] using rhombohedral positions. Those were used to calculate the powder pattern which was transformed to the hexagonal setting given here. The sample used for the structure work came from the Jimberlana Intrusion near Norseman, Western Australia.

Atom positions

- M(0) in 1(a) .72 calcium +.23 RE (as .1284 lanthanum and .1016 cerium) +.017 lead +.014 yttrium +.011 uranium +.006 thorium
- M(1) in 1(b) .58 zirconium +.32 magnesium +.1 RE (as .0285 hafnium, .0259 cerium, .0245 neodymium and .0236 holmium)
- M(2) in 2(c) partially vacant, with 1.23 iron and 0.6 magnesium
- M(3) in 6(f) partially vacant, with 2.24 chromium +2.19 iron +.86 titanium +.21 vanadium
- M(4) in 6(f) 5.81 titanium and .19 aluminum
- M(5) in 6(f) 5.81 titanium and .19 aluminum
- 6(f) 6 oxygen in each of 6 different sites
- 2(c) 2 oxygen

Electron microprobe analysis results gave weight percents of the elements as oxides, and the unit cell composition was normalized to 38 oxygen. Distribution of the cations in sites M(0) to M(5) inclusive was guided by the results for senaite and crichtonite which showed ordering sequences based on the size of the cations [Gatehouse et al., 1978]. The Mn was combined with the Fe in sites M(2) and M(3).

Lattice constants

$$a = 10.337 \text{ \AA}$$

$$c = 20.676$$

$$c/a = 2.0002$$

$$(\text{published values: } a = 9.117(4) \text{ \AA},$$

$$\alpha = 69.07(1)^\circ \text{ [Gatehouse et al., 1978]})$$

Volume

$$1913.4 \text{ \AA}^3$$

Density

$$(\text{calculated}) 4.415 \text{ g/cm}^3$$

Thermal parameters

Isotropic [Gatehouse et al., 1978]

Scattering factors

Al^{3+} , Ce^{4+} , Cr^{3+} , Fe^{3+} , Hf^{4+} , Ho^{3+} , La^{3+} ,
 Mg^{2+} , Nd^{3+} , O^{1-} , Pb^{2+} , Th^{4+} , Ti^{4+} , U^{4+} ,
 V^{5+} , Y^{3+} , Zr^{4+} [International Tables, 1974]
 Ca^{2+} [Cromer and Mann, 1968]

The factors for cerium, lanthanum and zirconium were corrected for dispersion [Cromer and Liberman, 1970]

Scale factors (integrated intensities)

$$\gamma = 0.06676 \times 10^{-3}$$

$$I/I_{\text{corundum}} = 0.624, \text{ for reflection with hexagonal } hkl = 024.$$

References

- Cromer, D. R. and Mann, J. B. (1968). Acta Crystallogr. A24, 321.
- Cromer, D. T. and Liberman, D. (1970). J. Chem. Phys. 53, 1891.
- Gatehouse, B. M., Grey, I. E., Campbell, I. H., and Kelly, P. (1978). Amer. Mineral. 63, 28.
- International Tables for X-ray Crystallography, IV (1974). (The Kynoch Press, Birmingham, Eng.) p. 99.

Calculated Pattern (Peak heights)					
d(Å)	I	hkl	2θ(°)	λ	1.540598 Å
6.89	1	0 0 3	12.84		
5.16	1	1 1 0	17.16		
4.476	9	1 0 4	19.82		
4.371	3	0 2 1	20.30		
4.134	23	1 1 -3+	21.48		
3.751	13	0 1 5	23.70		
3.443	3	0 0 6	25.86		
3.383	75	0 2 4	26.32		
3.339	7	2 1 1	26.68		
3.216	5	1 2 2	27.72		
3.038	71	2 0 5	29.38		
2.984	31	3 0 0	29.92		
2.866	100	1 1 -6+	31.18		
2.831	72	1 2 -4+	31.58		
2.807	12	1 0 7	31.86		
2.738	31	0 3 3+	32.68		
2.618	40	1 2 5+	34.22		
2.585	9	2 2 0	34.68		
2.465	53	3 1 -1	36.42		
2.414	28	3 1 2+	37.22		
2.297	2	0 0 9	39.18		
2.238	57	3 1 -4+	40.26		
2.128	59	3 1 5+	42.44		
2.099	5	1 1 -9+	43.06		
2.054	3	1 2 8+	44.06		
2.015	4	1 0 10+	44.96		
1.968	1	0 4 5	46.08		
1.954	7	1 4 0+	46.44		
1.909	12	2 3 -4	47.60		
1.901	16	3 1 -7	47.82		
1.878	6	0 2 10+	48.42		
1.839	17	2 3 5	49.52		
1.791	50	3 1 8	50.96		
1.764	10	2 1 10	51.78		
1.723	4	0 0 12	53.12		

Calcium Chromium Iron Titanium Oxide, Loveringite,
 $\text{Ca}_{.72}\text{RE}_{.33}(\text{Y,Th,U,Pb})_{.05}\text{Ti}_{12.48}\text{Fe}_{3.38}\text{Cr}_{2.24}\text{Mg}_{.92}\text{Zr}_{.58}\text{Al}_{.39}\text{V}_{.21}\text{Mn}_{.04}\text{O}_{38}$ - (continued)

d(Å)	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.700	25	1 4 6+	53.90
1.686	8	2 4 1+	54.36
1.643	11	5 0 5	55.92
1.635	4	1 1 -12+	56.22
1.608	10	4 2 -4+	57.26
1.589	61	3 1 -10	58.00
1.566	9	4 2 5+	58.94
1.541	10	3 3 -6+	59.98
1.535	9	5 1 4+	60.22
1.519	2	4 0 10	60.96
1.4987	28	3 1 11+	61.86
1.4883	3	4 1 9+	62.34
1.4717	1	5 0 8	63.12
1.4680	2	2 4 7+	63.30
1.4573	6	6 0 3+	63.82
1.4392	8	2 1 13+	64.72
1.4336	61	2 5 0	65.00
1.4155	6	4 3 4	65.94
1.4030	7	2 0 14+	66.60
1.3865	6	4 3 -5+	67.50
1.3782	2	3 3 -9+	67.96
1.3690	10	0 6 6+	68.48
1.3535	5	1 2 14+	69.38
1.3393	6	3 1 -13+	70.22
1.3317	5	1 1 -15	70.68
1.3236	2	5 2 -6+	71.18
1.3200	2	6 1 -4	71.40
1.3172	2	3 4 -7+	71.58
1.3093	2	2 4 10	72.08
1.2962	2	6 1 5+	72.92
1.2923	3	1 4 12+	73.18
1.2694	2	1 3 -14+	74.72
1.2574	1	2 4 -11+	75.56
1.2515	1	3 0 15+	75.98
1.2415	3	0 2 16+	76.70
1.2390	6	6 2 1	76.88
1.2325	2	6 2 -2	77.36
1.2216	3	0 7 5+	78.18
1.2185	3	3 3 -12+	78.42
1.2162	5	2 5 -9+	78.60
1.2097	3	4 4 6+	79.10
1.2072	6	1 2 -16+	79.30
1.1991	4	2 3 14+	79.94
1.1890	2	6 2 -5	80.76
1.1861	2	7 1 0	81.00

Calculated Pattern (Integrated)				
d(Å)	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$	
6.80	1	0 0 3	12.83	
5.17	1	1 1 0	17.14	
4.476	11	1 0 4	19.82	
4.375	3	0 2 1	20.28	
4.135	11	1 1 3	21.47	
4.135	16	1 1 -3	21.47	
4.108	9	2 0 2	21.62	
3.754	16	0 1 5	23.68	
3.446	2	0 0 6	25.83	
3.384	100	0 2 4	26.32	
3.339	6	2 1 1	26.67	
3.216	6	1 2 2	27.72	
3.037	97	2 0 5	29.38	
2.984	40	3 0 0	29.92	
2.867	56	1 1 6	31.17	
2.867	80	1 1 -6	31.17	
2.831	16	2 1 4	31.58	
2.831	80	1 2 -4	31.58	
2.805	8	1 0 7	31.88	
2.738	22	3 0 3	32.68	
2.738	20	0 3 3	32.68	
2.619	47	1 2 5	34.21	
2.619	10	2 1 -5	34.21	
2.584	12	2 2 0	34.68	
2.465	1	0 2 7	36.41	
2.465	3	1 3 1	36.42	
2.465	72	3 1 -1	36.42	
2.420	12	2 2 3	37.12	
2.420	11	2 2 -3	37.12	
2.414	23	3 1 2	37.21	
2.297	3	0 0 9	39.18	
2.238	29	1 3 4	40.26	
2.238	55	3 1 -4	40.26	
2.225	2	2 1 7	40.51	
2.225	2	1 2 -7	40.51	
2.129	73	3 1 5	42.43	
2.129	15	1 3 -5	42.43	
2.099	3	1 1 9	43.05	
2.099	4	1 1 -9	43.05	
2.054	3	1 2 8	44.05	
2.054	1	2 1 -8	44.05	
2.015	3	1 0 10	44.96	
2.014	2	2 3 2	44.96	
1.968	1	0 4 5	46.08	
1.954	8	1 4 0	46.45	
1.954	4	4 1 0	46.45	
1.909	1	3 2 4	47.61	
1.909	16	2 3 -4	47.61	
1.901	20	3 1 -7	47.82	
1.879	2	1 4 3	48.39	

Calcium Chromium Iron Titanium Oxide, Loveringite,
 $\text{Ca}_{.72}\text{RE}_{.33}(\text{Y, Th, U, Pb})_{.05}\text{Ti}_{12.48}\text{Fe}_{3.38}\text{Cr}_{2.24}\text{Mg}_{.92}\text{Zr}_{.58}\text{Al}_{.39}\text{V}_{.21}\text{Mn}_{.04}\text{O}_{38}$ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.879	3	4 1 3	48.39
1.879	2	4 1 -3	48.39
1.877	5	0 2 10	48.46
1.840	1	0 1 11	49.51
1.839	25	2 3 5	49.51
1.791	1	1 3 -8	50.96
1.791	76	3 1 8	50.96
1.784	1	4 0 7	51.17
1.784	1	5 0 -1	51.17
1.764	13	2 1 10	51.77
1.723	5	0 0 12	53.11
1.699	3	4 1 6	53.91
1.699	18	1 4 6	53.91
1.699	17	1 4 -6	53.91
1.699	1	4 1 -6	53.91
1.692	7	0 5 4	54.17
1.686	2	2 3 -7	54.36
1.686	1	3 2 7	54.36
1.686	4	2 4 1	54.37
1.643	1	1 2 11	55.91
1.643	17	5 0 5	55.92
1.635	2	1 1 12	56.23
1.635	2	1 1 -12	56.23
1.608	1	3 2 -8	57.25
1.608	5	2 4 4	57.25
1.608	8	4 2 -4	57.25
1.603	1	1 5 -1	57.44
1.589	1	1 3 10	58.00
1.589	95	3 1 -10	58.00
1.589	1	5 1 -2	58.00
1.566	2	1 0 13	58.93
1.566	7	4 2 5	58.94
1.566	5	2 4 -5	58.94
1.541	6	3 3 6	59.98
1.541	9	3 3 -6	59.98
1.535	3	1 5 -4	60.23
1.535	8	5 1 4	60.23
1.519	3	4 0 10	60.96
1.4986	39	3 1 11	61.86
1.4986	2	1 5 5	61.86
1.4986	3	5 1 -5	61.86
1.4920	1	6 0 0	62.17
1.4882	1	4 1 9	62.34
1.4718	1	5 0 8	63.12
1.4680	2	2 4 7	63.30
1.4582	4	6 0 3	63.77
1.4571	2	3 2 10	63.83
1.4571	1	2 3 -10	63.83
1.4570	4	4 3 -2	63.83
1.4394	4	1 2 -13	64.71

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.4394	4	2 1 13	64.71
1.4335	96	2 5 0	65.01
1.4335	5	5 2 0	65.01
1.4155	8	4 3 4	65.94
1.4122	1	1 5 -7	66.11
1.4035	3	5 2 -3	66.58
1.4035	3	5 2 3	66.58
1.4025	6	2 0 14	66.63
1.3865	1	3 4 5	67.50
1.3865	7	4 3 -5	67.50
1.3783	1	3 3 -9	67.95
1.3692	9	6 0 6	68.47
1.3692	7	0 6 6	68.47
1.3536	4	2 1 -14	69.37
1.3536	3	1 2 14	69.37
1.3393	7	1 3 13	70.22
1.3393	2	3 1 -13	70.22
1.3319	7	1 1 15	70.67
1.3319	1	1 1 -15	70.67
1.3235	1	5 2 -6	71.18
1.3199	1	6 1 -4	71.41
1.3173	1	4 3 7	71.57
1.3173	1	3 4 -7	71.57
1.3093	2	2 4 10	72.07
1.2965	1	4 0 13	72.91
1.2964	1	6 1 5	72.91
1.2922	2	1 4 12	73.18
1.2922	2	2 4 -12	73.18
1.2693	1	3 1 14	74.73
1.2693	1	1 3 -14	74.73
1.2693	1	1 5 -10	74.73
1.2514	1	3 0 15	75.99
1.2514	1	0 3 15	75.99
1.2416	2	0 2 16	76.69
1.2414	2	7 0 4	76.70
1.2392	7	6 2 1	76.87
1.2326	2	6 2 -2	77.36
1.2218	5	0 7 5	78.17
1.2162	1	5 2 9	78.60
1.2162	1	2 5 -9	78.60
1.2162	2	2 5 9	78.60
1.2162	2	5 2 -9	78.60
1.2099	2	4 4 6	79.09
1.2099	3	4 4 -6	79.09
1.2072	5	1 2 -16	79.30
1.2071	3	6 2 4	79.31
1.1990	3	2 3 14	79.95
1.1990	1	3 4 -10	79.95
1.1990	1	4 3 10	79.95
1.1890	4	6 2 -5	80.76

Calcium Hydrogen Phosphate Sulfate Hydrate, $\text{Ca}_2\text{HPO}_4\text{SO}_4 \cdot 4\text{H}_2\text{O}$

Structure

Monoclinic, Cc (9), Z = 4. The structure was determined by Sakae et al. [1978].

Atom positions

4(a) 2 phosphorus(1) and 2 sulfur(1)

4(a) 2 phosphorus(2) and 2 sulfur(2)

Four hydrogen atoms were not located in the structure determination. All other atoms are in general positions 4(a) and the "x" and "z" parameters were given to only 3 significant figures [ibid.].

Lattice constants

a = 5.721(5) Å

b = 30.994(5)

c = 6.250(4)

$\beta = 117.26(6)^\circ$

(published values: a = 5.721(5) Å, b = 30.992(5), c = 6.250(4), $\beta = 117.26(6)^\circ$ [Sakae et al., 1978]).

CD cell: a = 6.248(4) Å, b = 30.994(5), c = 5.721(5), $\beta = 117.22(6)^\circ$, sp. gp. Aa(9); a/b = 0.2016, c/b = 0.1846.

Volume

985.15 Å³

Density

(calculated) 2.321 g/cm³

Thermal parameters

Isotropic [Sakae et al., 1978]

Scattering factors

Zero ionization [International Tables, 1962]

Scale factor (integrated intensities)

$\gamma = 0.3683 \times 10^{-3}$

References

International Tables for X-ray Crystallography III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.

Sakae, T., Nagate, H., and Sudo, T. (1978). Amer. Mineral. 63, 520.

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2 θ (°)	$\lambda - 1.540598\text{Å}$
7.74	100	0 4 0	11.42	
5.02	5	-1 1 1+	17.66	
4.56	40	1 3 0+	19.44	
3.931	50	-1 5 1+	22.60	
3.874	15	0 8 0	22.94	
3.783	1	0 6 1	23.50	
3.339	45	1 7 0+	26.68	
3.093	10	-1 1 2+	28.84	
2.976	15	-1 3 2+	30.00	
2.852	35	-1 9 1+	31.34	
2.812	10	-2 2 1	31.80	
2.779	15	1 5 1+	32.18	
2.733	15	0 2 2	32.74	
2.707	1	0 10 1	33.06	
2.615	5	0 4 2	34.26	
2.543	15	2 0 0+	35.26	
2.509	5	2 2 0+	35.76	
2.447	20	0 6 2	36.70	
2.416	5	-2 4 2+	37.18	
2.308	5	-1 9 2+	39.00	
2.282	5	2 6 0+	39.46	
2.158	1	-1 13 1+	41.82	
2.126	5	2 8 0+	42.48	
2.102	10	-2 10 1	43.00	
2.088	5	-1 11 2+	43.30	
2.068	5	0 10 2+	43.74	
2.031	5	-1 3 3+	44.58	
1.976	5	-2 2 3+	45.88	
1.966	10	-2 10 2+	46.14	
1.936	1	0 16 0	46.88	
1.930	5	2 4 1+	47.04	
1.892	5	0 12 2+	48.06	
1.876	5	1 7 2+	48.48	
1.849	1	-3 3 2+	49.24	
1.829	1	0 16 1	49.82	
1.812	15	-2 12 2+	50.32	
1.798	5	-3 5 1+	50.72	
1.775	5	1 9 2+	51.44	
1.731	10	0 14 2+	52.86	
1.716	5	-1 17 1+	53.34	
1.669	5	-1 11 3+	54.96	
1.650	1	-3 9 1+	55.66	
1.646	1	0 18 1	55.82	
1.635	1	-3 5 3+	56.20	
1.583	1	-3 7 3+	58.22	
1.573	1	-1 17 2+	58.66	
1.564	1	-1 13 3+	59.02	
1.554	1	-2 0 4+	59.44	
1.547	5	-2 2 4+	59.74	
1.541	5	-2 16 2+	59.98	

Calcium Hydrogen Phosphate Sulfate Hydrate, $\text{Ca}_2\text{HPO}_4\text{SO}_4 \cdot 4\text{H}_2\text{O}$ - (continued)

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2 θ (°)	$\lambda - 1.540598\text{Å}$
7.75	100	0 4 0	11.41	
5.02	1	-1 1 1	17.65	
5.02	1	1 1 0	17.66	
4.56	20	-1 3 1	19.43	
4.56	20	1 3 0	19.44	
4.52	1	0 4 1	19.65	
3.932	30	-1 5 1	22.59	
3.932	30	1 5 0	22.60	
3.874	15	0 8 0	22.94	
3.783	1	0 6 1	23.50	
3.340	25	-1 7 1	26.67	
3.339	25	1 7 0	26.67	
3.094	5	-1 1 2	28.83	
3.093	5	1 1 1	28.84	
2.978	10	-1 3 2	29.98	
2.977	10	1 3 1	29.99	
2.852	20	-1 9 1	31.34	
2.852	20	1 9 0	31.34	
2.813	10	-2 2 1	31.79	
2.780	10	-1 5 2	32.18	
2.779	10	1 5 1	32.19	
2.734	15	0 2 2	32.72	
2.707	1	0 10 1	33.07	
2.615	10	0 4 2	34.26	
2.545	5	-1 7 2	35.24	
2.544	5	1 7 1	35.25	
2.544	5	-2 0 2	35.26	
2.543	5	2 0 0	35.27	
2.510	5	-2 2 2	35.74	
2.509	5	2 2 0	35.76	
2.502	1	-2 6 1	35.86	
2.447	25	0 6 2	36.70	
2.417	1	-2 4 2	37.17	
2.416	1	2 4 0	37.18	
2.308	5	-1 9 2	38.99	
2.308	5	1 9 1	39.00	
2.282	1	-2 6 2	39.46	
2.281	5	2 6 0	39.47	
2.159	1	-1 13 1	41.81	
2.159	1	1 13 0	41.81	
2.126	5	-2 8 2	42.48	
2.126	5	2 8 0	42.49	
2.102	10	-2 10 1	42.99	
2.088	1	-1 11 2	43.30	
2.088	1	1 11 1	43.30	
2.069	5	0 10 2	43.72	
2.031	5	-1 3 3	44.57	
2.031	5	1 3 2	44.58	
1.977	1	-2 2 3	45.86	
1.976	1	2 2 1	45.88	

d(Å)	I	hkl	2 θ (°)	$\lambda - 1.540598\text{Å}$
1.966	5	-2 10 2	46.13	
1.966	5	2 10 0	46.14	
1.965	1	-1 5 3	46.16	
1.964	1	1 5 2	46.17	
1.937	1	0 16 0	46.86	
1.930	5	-2 4 3	47.04	
1.930	5	2 4 1	47.05	
1.892	5	0 12 2	48.06	
1.877	1	-1 7 3	48.47	
1.876	1	-3 1 2	48.48	
1.876	5	1 7 2	48.48	
1.876	1	-3 1 1	48.49	
1.829	1	0 16 1	49.81	
1.812	10	-2 12 2	50.31	
1.812	10	2 12 0	50.31	
1.799	5	-3 5 2	50.71	
1.799	5	-3 5 1	50.72	
1.775	5	-1 9 3	51.43	
1.775	5	1 9 2	51.44	
1.731	5	0 14 2	52.84	
1.730	1	-3 7 2	52.87	
1.730	1	-3 7 1	52.88	
1.716	1	-1 17 1	53.34	
1.716	1	1 17 0	53.34	
1.670	1	-2 14 2	54.94	
1.670	1	2 14 0	54.95	
1.669	1	-1 11 3	54.97	
1.669	1	1 11 2	54.98	
1.650	1	-3 9 2	55.66	
1.650	1	-3 9 1	55.67	
1.645	1	0 18 1	55.85	
1.584	1	-3 7 3	58.21	
1.573	1	-1 17 2	58.65	
1.573	1	1 17 1	58.66	
1.547	5	-2 2 4	59.72	
1.547	1	2 2 2	59.75	
1.541	1	-2 16 2	59.98	
1.541	1	2 16 0	59.99	

Cannabidiol, C₂₁H₃₀O₂

Synonym

1. (1R-trans)-2-[3-Methyl-6-(1-methylethenyl)-2-cyclohexen-1-yl]-5-pentyl-1,3-benzenediol

CAS registry no.

13956-29-1

Structure

Monoclinic, P₂₁ (4), Z = 4. The structure was refined by Jones et al. [1977].

Atom positions

All atoms were in general positions 2(a).
Sixty-eight hydrogen positions were not located.

Lattice constants

a = 10.618(4) Å
b = 10.650(5)
c = 17.267(6)
β = 95.30(4)°

(published values: a = 10.617(4) Å,
b = 10.649(5), c = 17.266(6), β = 95.30(4)°
[Jones et al., 1977])

CD cell: a = 17.267(6) Å, b = 10.650(5),
c = 10.618(4), β = 95.30(4)°; sp. gp. P₂₁;
a/b = 1.6213; c/b = 0.9970

Volume

1944.2 Å³

Density

(calculated) 1.074 g/cm³ [Jones et al., 1977]

Thermal parameters

Isotropic. For hydrogen atoms, overall
B = 0.125. For other atoms, B_i were
estimated from U_{ij} for individual atoms.

Scattering factors

Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)

γ = 2.067 × 10⁻³
I/I_{corundum} (calculated) = 0.668 for reflections
with hkl = 011.

References

International Tables for X-ray Crystallography,
III (1962). (The Kynoch Press, Birmingham,
Eng.) p. 202.
Jones, P. G., Falvello, L., Kennard, O.,
Sheldrick, G. M., and Mechoulam, R. (1977).
Acta. Crystallogr. B33, 3211.

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
17.18	4	0 0 1	5.14	
10.57	5	1 0 0	8.36	
9.40	32	-1 0 1	9.40	
9.05	100	0 1 1	9.76	
8.60	33	0 0 2	10.28	
7.494	33	1 1 0	11.80	
7.042	19	-1 1 1	12.56	
6.702	30	1 1 1+	13.20	
6.384	20	1 0 2	13.86	
5.840	20	-1 1 2	15.16	
5.727	4	0 0 3	15.46	
5.474	3	1 1 2	16.18	
5.323	5	0 2 0	16.64	
5.187	6	-2 0 1	17.08	
5.081	34	0 2 1	17.44	
4.924	10	2 0 1	18.00	
4.701	28	-1 1 3+	18.86	
4.662	22	-2 1 1	19.02	
4.530	11	1 2 1+	19.58	
4.471	5	2 1 1	19.84	
4.296	20	-2 1 2+	20.66	
4.235	10	-1 2 2	20.96	
4.085	23	1 2 2	21.74	
4.005	24	2 1 2	22.18	
3.987	26	0 1 4	22.28	
3.901	15	0 2 3	22.78	
3.860	3	1 0 4	23.02	
3.841	3	-1 1 4	23.14	
3.808	2	-2 1 3	23.34	
3.736	7	-1 2 3+	23.80	
3.717	8	2 0 3+	23.92	
3.628	7	1 1 4	24.52	
3.587	4	1 2 3	24.80	
3.498	6	-2 0 4+	25.44	
3.477	4	0 3 1	25.60	
3.388	1	3 0 1	26.28	
3.358	3	2 2 2+	26.52	
3.341	3	-3 1 1+	26.66	
3.321	3	-2 1 4+	26.82	
3.283	3	1 3 1	27.14	
3.257	2	-1 2 4	27.36	
3.232	4	3 1 1+	27.58	
3.213	5	-3 1 2+	27.74	
3.160	2	3 0 2+	28.22	
3.123	2	1 2 4	28.56	
3.102	4	1 3 2	28.76	
3.052	7	2 1 4+	29.24	
3.010	1	-3 1 3+	29.66	
2.923	1	-2 2 4+	30.56	
2.897	1	-2 1 5	30.84	

Cannabidiol, C₂₁H₃₀O₂ - (continued)

d(Å)	I	hkl	2θ(°)
			λ - 1.540598Å
2.859	3	1 3 3+	31.26
2.735	2	1 2 5+	32.72
2.717	1	3 2 2	32.94
2.677	2	2 1 5+	33.44
2.662	1	0 4 0	33.64
2.621	3	1 1 6+	34.18
2.593	2	-4 0 2	34.56
2.582	3	1 4 0+	34.72
2.562	2	-1 4 1+	35.00
2.535	3	3 1 4+	35.38
2.499	1	-3 3 1+	35.90
2.452	1	3 3 1+	36.62
2.445	1	-3 3 2+	36.72
2.424	1	-4 1 3+	37.06
2.410	1	1 2 6	37.28
2.373	1	-1 4 3+	37.88
2.349	1	-3 3 3+	38.28
2.277	1	-3 1 6	39.54
2.235	1	3 3 3+	40.32
2.219	1	-1 2 7	40.62
2.214	2	-1 3 6	40.72
2.147	1	1 2 7+	42.06
2.119	1	-2 2 7+	42.64
2.088	1	-1 4 5+	43.30
2.004	1	-4 1 6+	45.22
1.997	1	0 5 3+	45.38
1.971	1	-2 5 1+	46.00
1.936	1	-2 3 7+	46.88
1.748	1	5 3 2+	52.28

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2θ(°)	
			λ - 1.540598Å	
17.19	3	0 0 1	5.14	
10.57	5	1 0 0	8.36	
9.40	29	-1 0 1	9.40	
9.05	100	0 1 1	9.76	
8.66	4	1 0 1	10.21	
8.60	30	0 0 2	10.28	
7.503	34	1 1 0	11.79	
7.048	19	-1 1 1	12.55	
6.717	21	1 1 1	13.17	
6.689	14	0 1 2	13.23	
6.387	20	1 0 2	13.85	
5.846	20	-1 1 2	15.14	
5.731	3	0 0 3	15.45	
5.478	3	1 1 2	16.17	
5.325	5	0 2 0	16.63	

d(Å)	I	hkl	2θ(°)
			λ - 1.540598Å
5.189	5	-2 0 1	17.07
5.087	35	0 2 1	17.42
5.047	4	0 1 3	17.56
4.927	10	2 0 1	17.99
4.735	4	2 1 0	18.72
4.706	14	-1 1 3	18.84
4.701	13	-2 0 2	18.86
4.665	18	-2 1 1	19.01
4.633	6	-1 2 1	19.14
4.536	8	1 2 1	19.56
4.527	3	0 2 2	19.59
4.471	5	2 1 1	19.84
4.328	1	2 0 2	20.50
4.301	14	-2 1 2	20.64
4.298	7	0 0 4	20.65
4.237	10	-1 2 2	20.95
4.090	21	1 2 2	21.71
4.078	6	-2 0 3	21.78
4.010	22	2 1 2	22.15
3.986	23	0 1 4	22.29
3.901	16	0 2 3	22.78
3.859	2	1 0 4	23.03
3.840	2	-1 1 4	23.15
3.808	1	-2 1 3	23.34
3.752	3	2 2 0	23.70
3.737	5	-1 2 3	23.79
3.718	5	2 0 3	23.91
3.716	2	-2 2 1	23.92
3.628	7	1 1 4	24.51
3.616	1	2 2 1	24.60
3.587	3	1 2 3	24.80
3.524	2	-2 2 2	25.25
3.511	3	2 1 3	25.35
3.497	4	-2 0 4	25.45
3.477	3	0 3 1	25.60
3.391	1	3 0 1	26.26
3.363	1	-1 0 5	26.49
3.359	2	2 2 2	26.52
3.345	1	0 2 4	26.63
3.340	1	-3 1 1	26.67
3.322	2	-2 1 4	26.81
3.285	2	1 3 1	27.13
3.257	1	-1 2 4	27.36
3.238	2	-2 2 3	27.53
3.231	2	3 1 1	27.58
3.215	4	-3 1 2	27.73
3.207	2	-1 1 5	27.80
3.194	1	2 0 4	27.91
3.160	1	3 0 2	28.22
3.125	2	1 2 4	28.54

Cannabidiol, C₂₁H₃₀O₂ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
3.103	4	1 3 2	28.75
3.059	6	2 1 4	29.17
3.051	3	1 1 5	29.25
3.049	1	2 2 3	29.27
3.029	1	3 1 2	29.46
2.923	1	-2 2 4	30.56
2.899	1	-2 1 5	30.82
2.865	2	1 3 3	31.19
2.860	2	3 2 1	31.24
2.858	1	-3 0 4	31.27
2.849	1	-3 2 2	31.38
2.733	1	1 2 5	32.74
2.718	1	3 2 2	32.93
2.679	2	2 1 5	33.42
2.662	1	0 4 0	33.63
2.631	1	0 4 1	34.05
2.623	1	-2 0 6	34.16
2.620	1	1 1 6	34.19
2.613	1	1 3 4	34.29
2.595	2	-4 0 2	34.54
2.582	3	1 4 0	34.72
2.562	2	-1 4 1	35.00
2.537	1	3 2 3	35.35
2.535	2	3 1 4	35.38
2.445	1	-3 3 2	36.73
2.424	1	-4 1 3	37.06
2.411	1	1 2 6	37.27
2.374	1	-1 4 3	37.86
2.277	1	-3 1 6	39.54
2.220	1	-1 2 7	40.60
2.214	1	-1 3 6	40.72
2.120	1	-2 2 7	42.62

L-Cocaine Hydrochloride, $C_{17}H_{22}ClNO_4$

Synonyms

1. L-3-Tropanylbenzoate-2-carboxylic acid methyl ester hydrochloride
2. Cocaine muriate

CAS registry no.

53-21-4

Structure

Orthorhombic, $P2_12_12_1$ (19), $Z = 4$. The structure was refined by Gabe and Barnes [1963].

Atom positions

All atoms were in general positions 4(a). A position was not located for the hydrogen associated with the chlorine in the hydrochloride.

Lattice constants

$a = 7.633(1) \text{ \AA}$
 $b = 10.301(1)$
 $c = 21.460(3)$

(published values: $a = 7.633(1) \text{ \AA}$,
 $b = 10.300(1)$, $c = 21.459(3)$ [Gabe and Barnes, 1963])

CD cell: $a = 10.301(1) \text{ \AA}$, $b = 21.460(3)$,
 $c = 7.633(1)$; sp. gp. $P2_12_12_1$; $a/b = 0.4800$,
 $c/b = 0.3557$.

Volume

$1687.3 \text{ \AA}^3$

Density

(calculated) 1.338 g/cm^3
(measured) 1.342 g/cm^3 [Gabe and Barnes, 1963]

Thermal parameters

Isotropic [Gabe and Barnes, 1963]

Scattering factors

Cl^- , C^0 , H^0 , N^0 , O^0 [International Tables, 1962]

Scale factors (integrated intensities)

$\gamma = 0.4587 \times 10^{-3}$
 I/I_{corundum} (calculated) = 0.470 for reflection
with $hkl = 002$.

Additional patterns

1. PDF card 28-1609 [Owen et al., 1972]

References

- Gabe, E. J. and Barnes, W. H. (1963). *Acta Crystallogr.* **16**, 796.
International Tables for X-ray Crystallography
III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.
Owen, J. T. R., Sithiraks, R., and Underwood, F. A. (1972). *J. Ass. Off. Anal. Chem.* **55**, 1171.

Calculated Pattern (Peak heights)				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598\text{\AA}$
10.72	100	0 0 2	8.24	
9.28	53	0 1 1	9.52	
7.43	20	0 1 2	11.90	
7.19	30	1 0 1	12.30	
6.206	3	1 0 2	14.26	
6.129	8	1 1 0	14.44	
5.878	83	0 1 3+	15.06	
5.323	35	1 1 2	16.64	
5.218	8	1 0 3	16.98	
5.145	24	0 2 0	17.22	
5.007	9	0 2 1	17.70	
4.756	64	0 1 4	18.64	
4.648	55	1 1 3+	19.08	
4.388	25	1 0 4	20.22	
4.267	32	1 2 0	20.80	
4.184	20	1 2 1	21.22	
4.037	21	1 1 4	22.00	
3.966	32	1 2 2	22.40	
3.815	3	2 0 0	23.30	
3.739	6	1 0 5	23.78	
3.714	5	0 2 4	23.94	
3.666	10	1 2 3	24.26	
3.579	38	2 1 0	24.86	
3.515	38	1 1 5	25.32	
3.394	18	2 1 2	26.24	
3.339	17	1 2 4	26.68	
3.297	3	0 2 5	27.02	
3.269	6	0 3 2	27.26	
3.239	15	1 0 6	27.52	
3.200	5	2 1 3	27.86	
3.129	13	1 3 0	28.50	
3.089	41	1 1 6	28.88	
3.066	17	2 2 0	29.10	
3.028	15	1 2 5+	29.48	
3.006	13	1 3 2	29.70	
2.976	12	2 1 4	30.00	
2.947	14	2 2 2	30.30	
2.868	1	1 3 3	31.16	
2.819	5	2 2 3	31.72	
2.741	9	1 2 6+	32.64	
2.704	2	1 3 4	33.10	
2.681	3	0 3 5	33.40	
2.662	3	2 2 4	33.64	
2.635	1	0 2 7	34.00	
2.5962	2	0 1 8	34.52	
2.5532	7	0 4 1+	35.12	
2.5295	11	1 3 5+	35.46	
2.4901	7	1 2 7+	36.04	
2.4768	6	0 3 6+	36.24	
2.4558	2	1 1 8+	36.56	

L-Cocaine Hydrochloride, $C_{17}H_{22}ClNO_4$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.4238	1	1 4 1	37.06
2.4063	2	3 1 2	37.34
2.3553	1	1 3 6	38.18
2.3283	9	2 1 7+	38.64
2.3088	6	1 4 3	38.98
2.3053	6	2 3 4+	39.04
2.2707	3	1 2 8	39.66
2.2436	2	3 1 4	40.16
2.2224	2	1 1 9+	40.56
2.1904	9	2 0 8+	41.18
2.1732	6	3 2 3	41.52
2.1682	6	2 2 7	41.62
2.1407	1	3 1 5	42.18
2.1349	1	2 4 0	42.30
2.0999	2	0 1 10+	43.04
2.0733	1	3 0 6+	43.62
2.0661	2	1 0 10	43.78
2.0439	3	3 3 0+	44.28
2.0326	5	3 1 6+	44.54
2.0188	4	2 2 8+	44.86
1.9804	4	1 5 1+	45.78
1.9618	7	2 3 7+	46.24
1.9233	3	3 2 6+	47.22
1.9172	4	0 1 11+	47.38
1.9111	4	2 4 5+	47.54
1.8968	2	1 3 9	47.92
1.8575	2	0 5 5+	49.00
1.8455	4	3 3 5+	49.34
1.8413	3	2 1 10	49.46
1.8330	2	2 4 6	49.70
1.8145	1	4 1 3+	50.24
1.8045	3	1 4 8+	50.54
1.7847	2	0 5 6+	51.14
1.7750	2	3 3 6	51.44
1.7705	2	4 1 4+	51.58
1.7572	2	2 5 3+	52.00
1.7540	2	3 4 3+	52.10
1.7379	1	2 0 11+	52.62
1.7132	3	2 1 11+	53.44
1.6973	1	4 2 4	53.98

Calculated Pattern (Integrated)			
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
10.73	100	0 0 2	8.23
9.29	54	0 1 1	9.52
7.43	20	0 1 2	11.90
7.19	31	1 0 1	12.30
6.220	2	1 0 2	14.23

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
6.133	7	1 1 0	14.43
5.897	50	1 1 1	15.01
5.876	51	0 1 3	15.07
5.324	37	1 1 2	16.64
5.220	5	1 0 3	16.97
5.150	25	0 2 0	17.20
5.008	9	0 2 1	17.70
4.758	69	0 1 4	18.63
4.656	35	1 1 3	19.05
4.643	30	0 2 2	19.10
4.389	27	1 0 4	20.22
4.269	34	1 2 0	20.79
4.187	20	1 2 1	21.20
4.180	1	0 2 3	21.24
4.038	22	1 1 4	21.99
3.967	36	1 2 2	22.39
3.817	2	2 0 0	23.29
3.758	1	2 0 1	23.66
3.741	5	1 0 5	23.76
3.715	4	0 2 4	23.93
3.666	11	1 2 3	24.26
3.596	4	2 0 2	24.74
3.579	40	2 1 0	24.86
3.577	1	0 0 6	24.87
3.530	3	2 1 1	25.21
3.516	42	1 1 5	25.31
3.395	20	2 1 2	26.23
3.367	1	2 0 3	26.45
3.341	19	1 2 4	26.66
3.297	2	0 2 5	27.02
3.270	5	0 3 2	27.25
3.239	17	1 0 6	27.52
3.201	5	2 1 3	27.85
3.131	14	1 3 0	28.48
3.110	2	2 0 4	28.68
3.099	12	1 3 1	28.79
3.090	40	1 1 6	28.87
3.066	15	2 2 0	29.10
3.036	7	2 2 1	29.40
3.027	11	1 2 5	29.49
3.006	13	1 3 2	29.70
2.977	12	2 1 4	29.99
2.948	14	2 2 2	30.29
2.938	6	0 2 6	30.40
2.869	1	1 3 3	31.15
2.818	7	2 2 3	31.72
2.749	4	2 1 5	32.55
2.742	1	1 1 7	32.63
2.742	8	1 2 6	32.63
2.704	2	1 3 4	33.10

L-Cocaine Hydrochloride, C₁₇H₂₂ClNO₄ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.681	3	0 3 5	33.39
2.662	3	2 2 4	33.64
2.634	1	0 2 7	34.00
2.5959	2	0 1 8	34.52
2.5752	1	0 4 0	34.81
2.5569	6	0 4 1	35.07
2.5526	3	2 3 0	35.13
2.5347	1	2 3 1	35.38
2.5298	6	2 1 6	35.45
2.5297	7	1 3 5	35.46
2.4950	3	2 2 5	35.97
2.4902	5	1 2 7	36.04
2.4833	1	2 3 2	36.14
2.4770	3	0 3 6	36.24
2.4757	2	3 0 2	36.26
2.4701	1	3 1 0	36.34
2.4577	1	1 1 8	36.53
2.4539	1	3 1 1	36.59
2.4245	1	1 4 1	37.05
2.4071	2	3 1 2	37.33
2.3560	1	1 3 6	38.17
2.3348	2	3 1 3	38.53
2.3282	5	2 1 7	38.64
2.3280	5	2 2 6	38.65
2.3216	1	0 4 4	38.76
2.3094	5	1 4 3	38.97
2.3050	3	2 3 4	39.05
2.2989	2	3 0 4	39.15
2.2714	4	1 2 8	39.65
2.2437	2	3 1 4	40.16
2.2224	2	1 1 9	40.56
2.2212	1	1 4 4	40.58
2.1946	6	2 0 8	41.10
2.1939	1	2 3 5	41.11
2.1906	5	1 3 7	41.17
2.1887	1	3 0 5	41.21
2.1733	6	3 2 3	41.52
2.1680	3	2 2 7	41.62
2.1409	1	3 1 5	42.18
2.1347	1	2 4 0	42.30
2.1009	2	0 1 10	43.02
2.0733	1	3 0 6	43.62
2.0659	2	1 0 10	43.78
2.0443	2	3 3 0	44.27
2.0372	3	1 3 8	44.43
2.0351	2	3 3 1	44.48
2.0325	3	3 1 6	44.54
2.0190	4	2 2 8	44.86
2.0081	1	3 3 2	45.11
1.9843	1	2 1 9	45.68

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.9809	1	0 2 10	45.77
1.9805	2	1 5 1	45.78
1.9797	2	0 5 3	45.80
1.9656	5	3 3 3	46.14
1.9616	6	2 3 7	46.24
1.9233	2	3 2 6	47.22
1.9174	1	1 2 10	47.37
1.9168	1	0 1 11	47.39
1.9163	1	1 5 3	47.40
1.9114	2	2 4 5	47.53
1.8971	2	1 3 9	47.91
1.8591	1	1 1 11	48.96
1.8573	1	0 5 5	49.01
1.8483	2	4 1 2	49.26
1.8456	3	3 3 5	49.34
1.8405	1	2 1 10	49.48
1.8331	2	2 4 6	49.70
1.8171	1	3 1 8	50.16
1.8149	1	4 1 3	50.23
1.8050	3	1 4 8	50.52
1.8035	2	3 4 1	50.57
1.7894	1	4 2 0	51.00
1.7852	1	0 5 6	51.12
1.7832	1	4 2 1	51.19
1.7748	1	3 3 6	51.45
1.7711	1	4 1 4	51.56
1.7574	1	2 5 3	51.99
1.7547	2	3 4 3	52.08
1.7519	1	2 4 7	52.17
1.7129	2	2 1 11	53.45
1.6975	1	4 2 4	53.97

Codeine Hydrobromide Hydrate, $C_{18}H_{22}BrNO_3 \cdot 2H_2O$

Synonyms

1. 7,8-Didehydro-4,5- α -epoxy-3-methoxy-17-methyl-morphinan-6- α -ol hydrobromide hydrate
2. Methyl morphine hydrobromide hydrate

Structure

Orthorhombic, $P2_12_12_1$ (19), $Z = 4$ [Lindsey and Barnes, 1955]. The structure was refined by Kartha et al. [1962]. The final R was 0.126. Intensities have been rounded to the nearer multiple of 10.

Atom positions

C, O, and N atoms were all in general positions 4(a). The Br atom was represented by 2 isotropic half-atoms separated slightly along "x". The H atom positions were not determined [Kartha et al. 1962].

Lattice constants

$a = 13.090(10) \text{ \AA}$
 $b = 20.826(15)$
 $c = 6.808(5)$

$a/b = 0.6285$

$c/b = 0.3269$

(published values: $a = 13.089(10) \text{ \AA}$,
 $b = 20.825(15)$, $c = 6.808(5)$ [Kartha et al.])

Volume $\text{\AA}^3$
 1856. $\text{\AA}^3$

Density

(calculated) 1.490 g/cm^3

(measured) 1.489 [Lindsey and Barnes, 1955]

Thermal parameters

Isotropic [Kartha et al., 1962]

Scattering factors

Zero ionization [International Tables, 1962]

Scale factor (integrated intensities)

$\gamma = 0.4209 \times 10^{-3}$

Additional pattern

1. PDF card 10-801 [Barnes and Lindsey, 1955]

References

Barnes, W. H. and Lindsey, J. M. (1955). Can. J. Chem. **33**, 5674.

International Tables for X-ray Crystallography **III** (1962). (The Kynoch Press, Birmingham, Eng.) pp. 202, 211.

Kartha, G., Ahmed, F. R. and Barnes, W. H. (1962). Acta Crystallogr. **15**, 326.

Lindsey, J. M. and Barnes, W. H. (1955). Acta Crystallogr. **8**, 227.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
10.39	20	0 2 0	8.50
8.14	20	1 2 0	10.86
6.47	10	0 1 1	13.68
6.24	20	2 1 0	14.18
6.13	20	1 3 0	14.44
6.04	50	1 0 1	14.66
5.79	40	1 1 1	15.28
5.70	50	0 2 1	15.54
5.22	90	1 2 1+	16.98
4.83	30	1 4 0	18.34
4.72	60	2 0 1	18.80
4.60	10	2 1 1	19.28
4.55	10	1 3 1	19.48
4.27	1	3 1 0	20.78
4.13	10	0 4 1	21.48
4.02	10	3 2 0	22.08
3.942	100	1 4 1	22.54
3.904	20	2 3 1	22.76
3.616	20	3 1 1	24.60
3.551	1	0 5 1	25.06
3.496	30	2 4 1	25.46
3.466	10	3 2 1+	25.68
3.427	10	1 5 1	25.98
3.404	10	0 0 2	26.16
3.358	40	0 1 2+	26.52
3.271	10	4 0 0	27.24
3.234	10	0 2 2+	27.56
3.140	20	1 2 2	28.40
3.123	40	2 5 1+	28.56
3.056	1	0 3 2	29.20
3.002	20	3 4 1+	29.74
2.976	10	1 3 2	30.00
2.951	1	4 0 1	30.26
2.919	10	4 1 1	30.60
2.901	10	2 2 2	30.80
2.848	10	0 4 2	31.38
2.795	20	2 6 1	32.00
2.769	30	2 3 2+	32.30
2.714	20	4 3 1+	32.98
2.684	1	3 0 2	33.36
2.668	10	1 7 1	33.56
2.635	1	0 5 2	34.00
2.598	20	3 2 2+	34.50
2.566	1	4 4 1	34.94
2.553	1	1 8 0	35.12
2.517	1	2 7 1+	35.64
2.504	1	3 3 2	35.84
2.457	1	3 7 0	36.54
2.445	1	2 5 2	36.72
2.430	10	0 6 2+	36.96

Codeine Hydrobromide Hydrate, $C_{18}H_{22}BrNO_3 \cdot 2H_2O$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.406	1	4 5 1	37.34
2.379	10	5 2 1+	37.78
2.359	1	4 0 2	38.12
2.343	10	4 1 2	38.38
2.304	1	5 3 1	39.06
2.278	1	2 6 2+	39.52
2.255	1	3 5 2	39.94
2.235	10	3 8 0	40.32
2.208	10	1 7 2+	40.84
2.186	1	1 2 3+	41.26
2.156	1	0 3 3	41.86
2.144	1	2 0 3+	42.12
2.128	10	1 3 3+	42.44
2.123	10	3 6 2+	42.54
2.108	1	5 5 1	42.86
2.094	1	4 7 1	43.16
2.077	10	6 0 1+	43.54
2.048	1	2 3 3+	44.18
2.044	1	1 8 2+	44.28
2.038	1	5 2 2+	44.42
2.004	1	3 1 3	45.22
1.998	10	5 6 1	45.36
1.993	10	3 7 2+	45.48
1.978	1	3 2 3	45.84
1.966	1	5 7 0	46.14
1.951	1	4 6 2	46.50
1.929	1	6 4 1+	47.06
1.913	1	0 9 2	47.48
1.905	10	2 10 1+	47.70
1.894	1	1 9 2	48.00
1.889	1	5 7 1	48.14
1.878	1	1 6 3+	48.42
1.874	1	1 11 0	48.54
1.869	1	3 8 2	48.68
1.858	10	5 5 2	49.00
1.841	1	7 2 0	49.48
1.836	1	4 2 3+	49.62
1.830	1	6 1 2	49.78
1.824	1	2 6 3	49.96

Calculated Pattern (Integrated)			
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
10.41	20	0 2 0	8.48
8.15	20	1 2 0	10.85
6.55	1	2 0 0	13.52
6.47	10	0 1 1	13.67
6.24	20	2 1 0	14.17

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
6.13	10	1 3 0	14.43
6.04	50	1 0 1	14.65
5.80	40	1 1 1	15.26
5.70	40	0 2 1	15.54
5.22	70	1 2 1	16.96
5.21	30	0 4 0	17.02
4.84	30	1 4 0	18.32
4.76	20	2 3 0	18.62
4.72	60	2 0 1	18.79
4.60	1	2 1 1	19.27
4.56	10	1 3 1	19.47
4.30	1	2 2 1	20.65
4.27	1	3 1 0	20.78
4.14	10	0 4 1	21.47
4.07	1	2 4 0	21.79
4.02	10	3 2 0	22.07
3.969	20	1 5 0	22.38
3.944	100	1 4 1	22.53
3.902	20	2 3 1	22.77
3.618	20	3 1 1	24.59
3.553	1	0 5 1	25.04
3.514	1	2 5 0	25.33
3.496	30	2 4 1	25.46
3.471	1	0 6 0	25.64
3.464	10	3 2 1	25.69
3.429	1	1 5 1	25.96
3.404	10	0 0 2	26.16
3.359	40	0 1 2	26.51
3.355	10	1 6 0	26.55
3.344	10	3 4 0	26.63
3.273	10	4 0 0	27.23
3.254	1	1 1 2	27.39
3.247	1	3 3 1	27.45
3.236	1	0 2 2	27.55
3.233	1	4 1 0	27.57
3.141	20	1 2 2	28.39
3.123	30	2 5 1	28.56
3.122	10	4 2 0	28.57
3.056	1	0 3 2	29.20
3.009	10	1 6 1	29.66
3.002	10	3 4 1	29.74
2.989	1	2 1 2	29.87
2.976	10	1 3 2	30.00
2.960	1	4 3 0	30.17
2.949	1	4 0 1	30.28
2.920	10	4 1 1	30.59
2.900	10	2 2 2	30.80
2.849	10	0 4 2	31.37
2.838	1	4 2 1	31.50
2.796	30	2 6 1	31.98

Codeine Hydrobromide Hydrate, $C_{18}H_{22}BrNO_3 \cdot 2H_2O$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.784	1	1 4 2	32.13
2.771	10	4 4 0	32.28
2.769	20	2 3 2	32.30
2.755	10	3 5 1	32.47
2.726	1	0 7 1	32.83
2.716	10	3 6 0	32.95
2.715	10	4 3 1	32.97
2.708	10	2 7 0	33.05
2.684	1	3 0 2	33.36
2.669	1	1 7 1	33.55
2.662	1	3 1 2	33.64
2.636	1	0 5 2	33.99
2.612	1	2 4 2	34.30
2.599	10	3 2 2	34.48
2.598	10	5 1 0	34.50
2.584	1	1 5 2	34.69
2.566	1	4 4 1	34.93
2.553	1	1 8 0	35.12
2.539	1	5 2 0	35.32
2.523	1	3 6 1	35.55
2.517	1	2 7 1	35.65
2.503	1	3 3 2	35.84
2.458	1	3 7 0	36.52
2.445	1	2 5 2	36.73
2.430	1	0 6 2	36.96
2.427	1	5 1 1	37.01
2.407	1	4 5 1	37.33
2.391	1	1 8 1	37.59
2.389	1	1 6 2	37.61
2.386	1	3 4 2	37.68
2.381	1	4 6 0	37.75
2.379	10	5 2 1	37.79
2.359	1	4 0 2	38.12
2.344	10	4 1 2	38.37
2.305	1	5 3 1	39.05
2.278	1	2 6 2	39.52
2.256	1	3 5 2	39.93
2.236	10	3 8 0	40.31
2.217	1	0 2 3	40.66
2.217	1	5 5 0	40.67
2.212	1	5 4 1	40.76
2.208	1	1 7 2	40.84
2.191	1	0 9 1	41.17
2.186	1	1 2 3	41.26
2.182	1	2 9 0	41.35
2.157	1	0 3 3	41.85
2.149	1	4 4 2	42.01
2.144	1	2 0 3	42.11
2.133	10	2 1 3	42.34
2.128	10	1 3 3	42.44

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.124	1	3 8 1	42.53
2.123	1	3 6 2	42.54
2.119	1	2 7 2	42.62
2.108	1	5 5 1	42.87
2.100	1	2 2 3	43.04
2.095	1	4 7 1	43.15
2.083	1	0 10 0	43.42
2.081	1	6 3 0	43.44
2.078	1	6 0 1	43.53
2.078	1	2 9 1	43.53
2.075	1	5 0 2	43.58
2.067	1	6 1 1	43.75
2.065	1	5 1 2	43.80
2.057	1	1 10 0	43.99
2.055	1	1 4 3	44.04
2.053	1	4 5 2	44.08
2.049	1	2 3 3	44.17
2.044	1	3 9 0	44.27
2.043	1	1 8 2	44.31
2.037	1	6 2 1	44.43
2.035	1	5 2 2	44.48
2.004	1	3 1 3	45.21
1.998	1	5 6 1	45.35
1.993	10	3 7 2	45.48
1.990	1	6 3 1	45.54
1.983	1	2 4 3	45.73
1.977	1	3 2 3	45.87
1.965	1	5 7 0	46.15
1.951	1	4 6 2	46.51
1.934	1	3 3 3	46.95
1.930	1	6 4 1	47.06
1.914	1	0 9 2	47.47
1.906	1	2 5 3	47.67
1.905	10	2 10 1	47.69
1.894	1	1 9 2	48.01
1.888	1	5 7 1	48.15
1.880	1	1 6 3	48.38
1.878	1	3 4 3	48.44
1.874	1	1 11 0	48.55
1.869	1	3 8 2	48.69
1.857	10	5 5 2	49.00
1.841	1	7 2 0	49.48
1.836	1	4 2 3	49.62
1.830	1	6 1 2	49.80
1.824	1	2 6 3	49.96

Copper Arsenate (Trippkeite), CuAs_2O_4

Structure

Tetragonal, $P4mbc$ (135), $Z = 4$. The structure was determined by Pertlik [1975].

Atom positions

[Pertlik, 1975]

4(d) 4 copper
8(g) 8 oxygen(1)
8(h) 8 oxygen(2)
8(h) 8 arsenic

Lattice constants

$a = 8.592(4) \text{ \AA}$
 $c = 5.573(4)$ [ibid.]

$a/c = 0.6486$

Volume

$411.4 \text{ \AA}^3$

Density

(calculated) 4.478 g/cm^3

Thermal parameters

Isotropic, in table 3 [Pertlik, 1975]

Scattering factors

Zero ionization [International Tables, 1962]

Scale factor (integrated intensities)

$\gamma = 1.112 \times 10^{-3}$
 I/I_{corundum} (calculated) = 4.16 for reflection
with $hkl = 211$.

References

International Tables for X-ray Crystallography
III (1962). (The Kynoch Press, Birmingham,
Eng.) pp. 202, 204, 211.
Pertlik, F. (1975). *Tschermak's Mineral.*
Petrogr. Mitt. 22, 211.

Calculated Pattern (Peak heights)				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598\text{\AA}$
6.07	67	1 1 0	14.58	
4.30	15	2 0 0	20.66	
3.841	8	2 1 0	23.14	
3.401	3	2 0 1	26.18	
3.162	100	2 1 1	28.20	
3.038	48	2 2 0	29.38	
2.786	6	0 0 2	32.10	
2.717	34	3 1 0	32.94	
2.532	15	1 1 2	35.42	
2.4416	1	3 1 1	36.78	
2.3376	33	2 0 2	38.48	
2.2554	14	2 1 2	39.94	
2.1914	3	3 2 1	41.16	
2.1475	1	4 0 0	42.04	
2.0833	2	4 1 0	43.40	
2.0536	2	2 2 2	44.06	
2.0044	6	4 0 1	45.20	
1.9514	30	4 1 1	46.50	
1.9210	7	4 2 0	47.28	
1.8159	3	4 2 1	50.20	
1.8118	3	3 2 2	50.32	
1.7185	1	4 3 0	53.26	
1.7014	10	4 0 2	53.84	
1.6721	11	2 1 3	54.86	
1.6381	21	3 3 2	56.10	
1.6128	1	5 1 1	57.06	
1.5819	1	4 2 2	58.28	
1.5336	1	5 2 1+	60.30	
1.5186	1	4 4 0	60.96	
1.4734	8	5 3 0	63.04	
1.4626	3	4 3 2	63.56	
1.4420	12	5 1 2	64.58	
1.4321	4	6 0 0	65.08	
1.4247	3	5 3 1	65.46	
1.4124	4	6 1 0	66.10	
1.4053	2	4 0 3	66.48	
1.3931	5	0 0 4	67.14	
1.3869	9	4 1 3	67.48	
1.3694	1	6 1 1	68.46	
1.3579	1	1 1 4	69.12	
1.3420	1	5 4 0	70.06	
1.3337	2	4 4 2+	70.56	
1.3197	1	6 2 1	71.42	
1.3046	2	5 4 1	72.38	
1.3027	2	5 3 2	72.50	
1.2665	3	2 2 4	74.92	
1.2599	2	6 1 2	75.38	
1.2398	4	3 1 4	76.82	
1.2211	5	6 2 2	78.22	
1.2151	2	7 1 0+	78.68	

Copper Arsenate (Trippkeite), CuAs₂O₄ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.2090	2	5 4 2	79.16
1.1914	1	6 4 0	80.56
1.1546	2	7 2 1+	83.70
1.1280	2	4 2 4+	86.14
1.1137	2	5 5 2+	87.52
1.1057	2	7 3 1	88.32
1.0877	1	5 4 3	90.18
1.0792	1	6 5 1	91.08
1.0705	2	2 1 5	92.04
1.0656	1	8 1 0	92.58
1.0466	2	7 4 1+	94.78
1.0458	2	7 3 2	94.88
1.0420	2	8 2 0	95.34
1.0233	1	6 5 2	97.66

Calculated Pattern (Integrated)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
6.08	58	1 1 0	14.57
4.30	14	2 0 0	20.66
3.842	8	2 1 0	23.13
3.402	3	2 0 1	26.17
3.163	100	2 1 1	28.19
3.038	48	2 2 0	29.38
2.787	6	0 0 2	32.10
2.717	35	3 1 0	32.94
2.533	15	1 1 2	35.41
2.4422	1	3 1 1	36.77
2.3378	35	2 0 2	38.48
2.2558	15	2 1 2	39.93
2.1911	3	3 2 1	41.17
2.1480	1	4 0 0	42.03
2.0839	2	4 1 0	43.39
2.0534	2	2 2 2	44.06
2.0043	7	4 0 1	45.20
1.9519	34	4 1 1	46.49
1.9453	1	3 1 2	46.65
1.9212	7	4 2 0	47.27
1.8163	3	4 2 1	50.19
1.8110	2	3 2 2	50.34
1.7184	1	4 3 0	53.26
1.7012	11	4 0 2	53.85
1.6725	13	2 1 3	54.85
1.6382	24	3 3 2	56.10
1.6129	1	5 1 1	57.06
1.5817	2	4 2 2	58.29
1.5339	1	5 2 1	60.29
1.5189	1	4 4 0	60.95

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.4735	10	5 3 0	63.04
1.4651	1	3 2 3	63.44
1.4626	3	4 3 2	63.56
1.4419	14	5 1 2	64.58
1.4320	4	6 0 0	65.08
1.4246	3	5 3 1	65.47
1.4125	4	6 1 0	66.10
1.4051	2	4 0 3	66.49
1.3933	6	0 0 4	67.13
1.3869	1	6 0 1	67.48
1.3867	9	4 1 3	67.49
1.3846	1	5 2 2	67.61
1.3692	1	6 1 1	68.47
1.3580	1	1 1 4	69.11
1.3418	1	5 4 0	70.07
1.3355	1	4 2 3	70.45
1.3336	2	4 4 2	70.56
1.3199	1	6 2 1	71.41
1.3046	2	5 4 1	72.38
1.3026	2	5 3 2	72.51
1.2664	4	2 2 4	74.93
1.2599	2	6 1 2	75.38
1.2398	5	3 1 4	76.83
1.2211	7	6 2 2	78.22
1.2151	1	7 1 0	78.68
1.2090	2	5 4 2	79.16
1.1915	1	6 4 0	80.56
1.1546	1	7 2 1	83.70
1.1544	1	5 3 3	83.71
1.1279	2	4 2 4	86.15
1.1138	2	5 5 2	87.51
1.1058	3	7 3 1	88.31
1.0878	1	5 4 3	90.17
1.0793	1	6 5 1	91.08
1.0705	2	2 1 5	92.04
1.0657	2	8 1 0	92.57
1.0467	1	7 4 1	94.77
1.0457	2	7 3 2	94.89
1.0419	2	8 2 0	95.34
1.0232	1	6 5 2	97.67

α -Dihydrophyllocladene, Hartite (or Bombiccite), $C_{20}H_{34}$

Synonyms

The name hartite was designated in 1841 and material called bombiccite was described later. Because of uncertainty in the chemistry, the two were not identified as the same phase until 1955 [Pellizer, 1955].

Structure

Triclinic, P1 (1), Z = 4. The structure was determined by Serantoni et al. [1978]. The natural mineral used for the determination was repeatedly dissolved and recrystallized from benzene.

Atom positions

1(a) 80 carbon

Hydrogen positions were not specified.

Lattice constants

a = 11.39(7) Å
b = 21.29(5)
c = 7.45(1)
 α = 94.6(1)°
 β = 101.8(2)
 γ = 81.5(1)

a/b = 0.5350

c/b = 0.3499

Volume

1747. Å³

Density

(calculated) 1.044 g/cm³

(measured) 1.08 [Serantoni et al., 1978]

Thermal parameters

Isotropic B_i calculated from U_i given in

Serantoni et al. [1978]

Scattering factors

C^0 [Cromer and Mann, 1968]

Scale factor (integrated intensities)

$\gamma = 3.162 \times 10^{-3}$

References

Cromer, D. T. and Mann, J. B. (1968). Acta Crystallogr. A24, 321.
Pellizer, R. (1955). Atti Accad. Naz. Lincei Cl. Sci. Fis. Mat. Natur. Rend. 19, 150.
Serantoni, E. F., Krajewski, A., Mongiorgi, R., Riva di Sanseverino, L. and Sheldrick, G. M. (1978). Acta Crystallogr. B34, 1311.

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598\text{Å}$
21.02	5	0 1 0	4.20	
10.52	35	0 2 0	8.40	
8.19	3	1 2 0	10.80	
7.14	7	-1 2 0	12.38	
6.99	14	0 -1 1	12.66	
6.64	40	-1 -1 1	13.32	
6.16	40	-1 1 1	14.36	
6.02	4	-1 -2 1	14.70	
5.84	3	0 2 1	15.16	
5.52	100	2 0 0	16.04	
5.45	50	1 1 1	16.26	
5.37	45	1 -1 1	16.50	
5.25	9	0 4 0	16.86	
5.18	13	2 2 0+	17.10	
5.01	9	1 4 0+	17.70	
4.92	5	-2 -1 1	18.00	
4.89	3	1 -2 1+	18.14	
4.64	5	-2 2 0	19.12	
4.56	6	-1 3 1	19.46	
4.52	6	-1 4 0	19.64	
4.43	3	1 3 1+	20.04	
4.33	1	-2 -3 1	20.50	
4.16	3	0 4 1	21.34	
4.09	3	2 4 0	21.72	
4.04	1	2 0 1+	22.00	
3.91	3	2 -1 1	22.72	
3.89	2	-2 -4 1+	22.84	
3.78	1	1 -4 1+	23.54	
3.75	1	-2 3 1	23.72	
3.68	2	2 -2 1+	24.16	
3.61	1	2 3 1+	24.64	
3.58	2	-2 4 0+	24.88	
3.55	1	-3 1 0	25.08	
3.48	2	1 6 0	25.60	
3.39	1	0 2 2+	26.30	
3.37	1	-1 5 1+	26.40	
3.36	1	-2 0 2	26.54	
3.33	2	-3 2 0+	26.78	
3.22	1	3 4 0+	27.68	
3.16	2	-1 -4 2+	28.22	
3.13	1	-1 3 2+	28.48	
3.06	4	3 1 1	29.14	
3.01	2	-2 -4 2+	29.68	
2.98	1	3 -1 1	29.92	
2.92	1	0 4 2+	30.56	
2.88	3	-1 4 2+	30.98	
2.76	2	4 0 0+	32.38	
2.72	1	-4 -3 1+	32.88	
2.64	1	1 8 0	33.96	
2.60	1	-2 -6 2	34.50	

α -Dihydrophyllocladene, Hartite (or Bombiccite), $C_{20}H_{34}$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
			$\lambda - 1.540598\text{\AA}$
2.54	1	3 -4 1	35.26
2.426	1	4 0 1+	37.02
2.387	2	4 -1 1+	37.66
2.353	1	-4 -4 2+	38.22
2.301	1	-1 -9 1+	39.12
2.281	1	-2 6 2+	39.48
2.259	1	0 -9 1+	39.88
2.214	1	-1 -5 3+	40.72
2.200	1	-2 3 3+	41.00
2.162	1	-4 -6 2+	41.74
2.119	1	1 10 0+	42.64
2.091	2	-3 -5 3+	43.24

Calculated Pattern (Integrated)			
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
			$\lambda - 1.540598\text{\AA}$
21.03	5	0 1 0	4.20
10.51	35	0 2 0	8.40
8.19	3	1 2 0	10.80
7.15	6	-1 2 0	12.37
6.99	14	0 -1 1	12.65
6.77	1	0 1 1	13.06
6.65	45	-1 -1 1	13.30
6.17	45	-1 1 1	14.35
6.14	2	0 -2 1	14.42
6.02	3	-1 -2 1	14.70
5.85	2	0 2 1	15.14
5.60	5	1 0 1	15.82
5.53	5	2 1 0	16.02
5.52	100	2 0 0	16.03
5.45	45	1 1 1	16.25
5.37	45	1 -1 1	16.49
5.35	1	-1 2 1	16.55
5.26	6	0 4 0	16.85
5.20	2	-1 -3 1	17.05
5.19	6	2 2 0	17.08
5.19	2	0 -3 1	17.08
5.17	3	-2 1 0	17.12
5.02	5	1 4 0	17.67
5.00	5	1 2 1	17.72
4.93	4	-2 -1 1	17.99
4.88	1	-2 0 1	18.15
4.88	2	1 -2 1	18.15
4.65	1	2 3 0	19.05
4.64	5	-2 2 0	19.11
4.60	1	-2 1 1	19.26

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
			$\lambda - 1.540598\text{\AA}$
4.56	6	-1 3 1	19.44
4.52	6	-1 4 0	19.64
4.44	2	1 3 1	20.00
4.43	1	-1 -4 1	20.04
4.33	1	-2 -3 1	20.48
4.16	3	0 4 1	21.33
4.09	3	2 4 0	21.69
4.08	1	-2 3 0	21.77
4.04	1	2 0 1	22.00
3.91	3	2 -1 1	22.70
3.89	1	-2 -4 1	22.85
3.78	1	1 -4 1	23.52
3.75	1	-2 3 1	23.73
3.68	1	2 -2 1	24.14
3.64	1	0 0 2	24.43
3.61	1	2 3 1	24.65
3.58	2	-2 4 0	24.88
3.55	1	-3 1 0	25.08
3.48	3	1 6 0	25.59
3.36	1	-2 0 2	26.53
3.34	1	-3 2 0	26.68
3.32	1	-2 -2 2	26.79
3.16	1	-1 -4 2	28.20
3.13	1	-1 3 2	28.45
3.08	1	-2 2 2	28.93
3.06	5	3 1 1	29.14
3.05	1	3 0 1	29.21
3.01	1	-2 -4 2	29.64
2.98	1	3 -1 1	29.91
2.92	1	0 4 2	30.55
2.90	1	3 3 1	30.83
2.89	3	-1 4 2	30.97
2.76	1	-3 4 1	32.35
2.76	1	4 0 0	32.39
2.64	1	1 8 0	33.95
2.60	1	-2 -6 2	34.50
2.54	1	3 -4 1	35.26
2.387	1	-3 4 2	37.65
2.386	1	4 -1 1	37.66
2.317	1	4 -2 1	38.84
2.281	1	-2 6 2	39.47
2.214	1	-1 -5 3	40.71
2.200	1	-2 3 3	41.00
2.091	1	-3 -5 3	43.24

(-)-Ephedrine Hydrochloride, C₁₀H₁₆ClNO

Synonyms

1. Biophedrin
2. Ephedral
3. Sanedrine

CAS registry no.
877-36-1

Structure

Monoclinic, P₂₁ (4), Z = 2. The structure was determined by Phillips [1954]. Bergin [1971] refined the structure using 3-dimensional data.

Atom positions

All atoms were in general positions 2(a) [Bergin, 1971].

Lattice constants

Bergin [1971]
a = 12.671(3) Å
b = 6.090(4)
c = 7.301(2)
β = 102.11(8)°

a/b = 2.0806
c/b = 1.1989

Volume
550.9 Å³

Density

(calculated) 1.216 g/cm³

Thermal parameters

Anisotropic [Bergin, 1971]

Scattering factors

Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)

γ = 0.6728 × 10⁻³
I/I_{corundum} (calculated) = 0.962 for reflection with hkl = 011.

Additional patterns

1. PDF card 5-0263 [E. Lilly and Co., Indianapolis, IN]
2. PDF card 24-1735 [Institute of Physics, University College, Cardiff, Wales]

References

- Bergin, R. (1971). Acta Crystallogr. **B27**, 381.
International Tables for X-ray Crystallography **III** (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.
Phillips, D. C. (1954). Acta Crystallogr. **7**, 159.

Calculated Pattern (Peak heights)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
12.37	9	1 0 0	7.14
7.13	17	0 0 1	12.40
6.84	45	-1 0 1	12.94
6.19	4	2 0 0	14.30
5.68	9	1 0 1	15.58
5.46	15	1 1 0	16.22
4.629	100	0 1 1	19.16
4.544	21	-1 1 1	19.52
4.341	18	2 1 0	20.44
4.130	25	3 0 0	21.50
3.976	4	-2 1 1	22.34
3.952	4	-3 0 1	22.48
3.636	2	-1 0 2	24.46
3.567	27	0 0 2	24.94
3.488	10	2 1 1	25.52
3.417	35	3 1 0+	26.06
3.314	9	-3 1 1	26.88
3.123	5	-1 1 2	28.56
3.079	20	0 1 2	28.98
3.046	3	0 2 0	29.30
2.980	18	-2 1 2	29.96
2.957	6	1 2 0	30.20
2.893	9	3 1 1	30.88
2.868	13	1 1 2	31.16
2.781	5	-1 2 1	32.16
2.754	9	-4 1 1+	32.48
2.733	3	2 2 0	32.74
2.715	6	-3 1 2	32.96
2.684	4	1 2 1	33.36
2.635	5	-2 2 1	34.00
2.577	2	2 1 2	34.78
2.477	4	2 2 1	36.24
2.426	4	4 1 1	37.02
2.413	5	-3 2 1+	37.24
2.396	1	-2 0 3	37.50
2.379	4	0 0 3	37.78
2.335	1	-1 2 2	38.52
2.317	1	-5 1 1+	38.84
2.295	1	5 1 0	39.22
2.273	6	-2 2 2	39.62
2.260	3	-1 1 3	39.86
2.252	2	1 0 3	40.00
2.230	5	-2 1 3+	40.42
2.171	2	4 2 0	41.56
2.148	3	-3 2 2	42.02
2.134	3	-3 1 3	42.32
2.129	3	4 0 2+	42.42
2.105	3	-6 0 1	42.94
2.079	2	2 2 2	43.50
2.009	1	4 1 2	45.10

(-)-Ephedrine Hydrochloride, C₁₀H₁₆ClNO - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.004	2	1 3 0	45.22
1.998	2	4 2 1+	45.36
1.990	1	-6 1 1+	45.54
1.975	1	-6 0 2	45.90
1.955	2	6 1 0	46.40
1.947	1	-1 3 1	46.62
1.929	1	2 3 0	47.08
1.912	1	3 2 2+	47.52
1.901	1	-1 2 3	47.82
1.881	4	6 0 1+	48.36
1.876	3	0 2 3	48.48
1.840	1	-5 1 3	49.50
1.832	1	2 3 1	49.72
1.821	2	3 3 0+	50.06
1.810	1	1 2 3+	50.38
1.744	2	-2 1 4+	52.42
1.731	1	-6 2 1	52.84
1.721	2	4 0 3+	53.18
1.713	2	0 1 4	53.46
1.696	1	-4 3 1+	54.02
1.683	1	-6 1 3	54.46
1.652	1	1 1 4+	55.58
1.578	1	-5 3 1	58.42
1.562	2	-2 2 4+	59.10

Calculated Pattern (Integrated)			
d(Å)	I	hkl	2θ(°) λ - 1.540598Å
12.39	8	1 0 0	7.13
7.14	15	0 0 1	12.39
6.84	43	-1 0 1	12.94
6.19	3	2 0 0	14.29
5.69	8	1 0 1	15.56
5.47	14	1 1 0	16.20
4.633	100	0 1 1	19.14
4.547	18	-1 1 1	19.50
4.343	18	2 1 0	20.43
4.158	8	1 1 1	21.35
4.130	24	3 0 0	21.50
3.979	3	-2 1 1	22.32
3.952	3	-3 0 1	22.48
3.639	1	-1 0 2	24.44
3.569	28	0 0 2	24.93
3.489	10	2 1 1	25.51
3.418	14	-2 0 2	26.05
3.418	23	3 1 0	26.05
3.315	9	-3 1 1	26.87
3.124	4	-1 1 2	28.55

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
3.097	4	4 0 0	28.80
3.088	1	-4 0 1	28.89
3.079	20	0 1 2	28.97
3.045	2	0 2 0	29.31
2.981	20	-2 1 2	29.95
2.957	5	1 2 0	30.20
2.893	9	3 1 1	30.88
2.869	14	1 1 2	31.15
2.782	5	-1 2 1	32.15
2.761	3	4 1 0	32.40
2.754	7	-4 1 1	32.49
2.733	2	2 2 0	32.75
2.715	6	-3 1 2	32.96
2.685	4	1 2 1	33.35
2.646	2	4 0 1	33.85
2.635	5	-2 2 1	34.00
2.578	2	2 1 2	34.77
2.477	4	2 2 1	36.24
2.433	1	-1 0 3	36.91
2.427	4	4 1 1	37.01
2.413	1	-4 1 2	37.23
2.412	5	-3 2 1	37.25
2.396	1	-2 0 3	37.51
2.380	4	0 0 3	37.78
2.335	1	-1 2 2	38.52
2.295	1	5 1 0	39.22
2.279	1	-3 0 3	39.51
2.274	6	-2 2 2	39.61
2.260	2	-1 1 3	39.86
2.251	1	1 0 3	40.02
2.234	3	3 2 1	40.34
2.230	3	-2 1 3	40.42
2.171	2	4 2 0	41.56
2.149	3	-3 2 2	42.01
2.134	2	-3 1 3	42.31
2.129	1	4 0 2	42.43
2.105	3	-6 0 1	42.93
2.079	3	2 2 2	43.50
2.009	1	4 1 2	45.08
2.003	1	1 3 0	45.23
1.997	1	4 2 1	45.37
1.989	1	-6 1 1	45.56
1.976	1	-6 0 2	45.89
1.955	3	6 1 0	46.40
1.946	1	-1 3 1	46.64
1.929	1	2 3 0	47.07
1.901	1	-1 2 3	47.81
1.883	2	-2 2 3	48.30
1.881	2	6 0 1	48.35
1.880	1	-6 1 2	48.39

(-)-Ephedrine Hydrochloride, $C_{10}H_{16}ClNO$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.875	2	0 2 3	48.52
1.840	1	-5 1 3	49.49
1.832	1	2 3 1	49.72
1.825	1	-3 2 3	49.95
1.822	1	3 3 0	50.03
1.820	1	-5 2 2	50.07
1.810	1	1 2 3	50.37
1.745	1	-2 3 2	52.38
1.743	1	-2 1 4	52.45
1.731	1	-6 2 1	52.83
1.722	1	1 3 2	53.14
1.721	1	4 0 3	53.19
1.713	2	0 1 4	53.46
1.696	1	-4 3 1	54.02
1.684	2	-6 1 3	54.45
1.578	1	-5 3 1	58.43
1.564	1	-5 1 4	59.02
1.562	2	-2 2 4	59.10

Haloperidol, C₂₁H₂₃ClFNO₂

Synonyms

1. Haldol
2. Serenase
3. 4-(4-hydroxy-4-p-chlorphenylpiperidino)4'-fluorobutyrophenone

CAS registry no.

52-86-8

Structure

Monoclinic, P₂₁/c (14), Z = 4. The structure was refined by Reed and Schaefer [1973].

Atom positions

All atoms were in general positions 4(e). The "x" parameter for carbon(7) was used as 0.0838. No hydrogen positions were listed in the reference.

Lattice constants

a = 7.816(5) Å
b = 8.996(6)
c = 28.346(20)
β = 106.34°

(published values: a = 7.816(5) Å,
b = 8.995(6), c = 28.344(20),
β = 106.34(4)° [Reed and Schaefer, 1973])

CD cell: a = 27.202, b = 8.996, c = 7.816,
β = 90.33°, space group P₂₁/n; a/b = 3.0237,
c/b = 0.8688

Volume

1912.6 Å³

Density

(calculated) 1.305 g/cm³
(measured) 1.23 g/cm³ [Reed and Schaefer, 1973]

Thermal parameters

Anisotropic [Reed and Schaefer, 1973]

Scattering factors

Zero ionization [International Tables, 1962]

Scale factor (integrated intensities)

γ = 1.271 × 10⁻³
I/I_{corundum} (calculated) = 1.29 for reflection
with hkl = $\bar{1}15$.

References

International Tables for X-ray Crystallography
III (1962). (The Kynoch Press, Birmingham,
Eng.) p. 202.
Reed, L. L. and Schaefer, J. P. (1973). Acta
Crystallogr. B29, 1886.

Calculated Pattern (Peak heights)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
8.53	2	0 1 1	10.36
7.49	10	1 0 0+	11.80
6.79	1	0 0 4	13.02
6.38	3	0 1 3	13.86
5.93	19	-1 0 4+	14.94
5.76	5	-1 1 2+	15.36
5.41	6	1 1 1+	16.36
4.946	2	-1 1 4+	17.92
4.653	3	0 1 5	19.06
4.467	100	-1 1 5	19.86
4.044	1	0 1 6	21.96
3.897	13	-1 2 1	22.80
3.751	3	0 2 4+	23.70
3.584	11	-1 2 4+	24.82
3.464	1	2 1 0+	25.70
3.396	7	-2 0 6+	26.22
3.339	2	-2 1 5	26.68
3.177	6	-2 1 6	28.06
3.000	6	-2 1 7	29.76
2.986	5	2 1 3+	29.90
2.951	2	-1 1 9+	30.26
2.934	3	-2 2 3+	30.44
2.881	3	2 2 0+	31.02
2.808	4	-2 2 5+	31.84
2.784	3	1 3 0+	32.12
2.745	2	1 2 6+	32.60
2.711	2	-2 2 6	33.02
2.641	1	-2 1 9	33.92
2.592	1	-2 2 7+	34.58
2.508	1	0 2 9	35.78
2.491	1	-1 3 6+	36.02
2.474	2	-1 1 11+	36.28
2.464	3	-3 1 5+	36.44
2.370	1	-2 3 1+	37.94
2.354	1	-2 2 9+	38.20
2.345	2	-2 3 4+	38.36
2.248	1	-2 3 6+	40.08
2.226	1	2 0 8+	40.50
2.129	1	0 3 9	42.42
2.119	1	-1 1 13	42.64
2.113	1	1 1 11+	42.76
2.103	1	-1 4 4+	42.98
2.010	3	3 1 5+	45.08
1.955	1	2 0 10+	46.40
1.947	2	-3 3 5+	46.62
1.907	1	-2 4 5	47.66
1.873	1	-2 3 11+	48.58

Haloperidol, C₂₁H₂₃ClFNO₂ - (continued)

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
8.54	2	0 1 1	10.35	
7.52	1	-1 0 2	11.75	
7.50	3	0 1 2	11.79	
7.50	6	1 0 0	11.79	
6.80	1	0 0 4	13.01	
6.39	3	0 1 3	13.86	
5.94	15	-1 0 4	14.91	
5.90	5	1 0 2	15.00	
5.90	9	-1 1 1	15.00	
5.77	3	-1 1 2	15.34	
5.76	2	1 1 0	15.37	
5.42	3	0 1 4	16.33	
5.42	2	-1 1 3	16.34	
5.40	3	1 1 1	16.39	
4.955	1	-1 1 4	17.89	
4.935	1	1 1 2	17.96	
4.655	2	0 1 5	19.05	
4.534	2	0 0 6	19.57	
4.498	55	0 2 0	19.72	
4.477	2	-1 0 6	19.81	
4.466	100	-1 1 5	19.86	
4.048	1	0 1 6	21.94	
3.908	1	-2 0 2	22.74	
3.899	13	-1 2 1	22.79	
3.762	1	-2 0 4	23.63	
3.752	2	0 2 4	23.70	
3.603	4	-1 1 7	24.69	
3.585	9	-1 2 4	24.81	
3.578	3	1 2 2	24.87	
3.400	1	0 0 8	26.19	
3.397	6	-2 0 6	26.21	
3.386	2	-1 2 5	26.30	
3.378	1	1 2 3	26.36	
3.339	2	-2 1 5	26.67	
3.178	6	-2 1 6	28.06	
3.165	2	1 2 4	28.18	
3.000	7	-2 1 7	29.75	
2.986	3	2 1 3	29.90	
2.981	2	0 3 1	29.95	
2.969	2	-2 0 8	30.08	
2.941	1	0 2 7	30.37	
2.934	2	-2 2 3	30.44	
2.886	1	-2 2 4	30.96	
2.880	2	2 2 0	31.02	
2.813	2	1 0 8	31.78	
2.809	2	-2 2 5	31.83	
2.786	1	-1 3 2	32.11	
2.784	3	1 3 0	32.12	
2.756	1	-1 2 8	32.46	
2.748	1	1 2 6	32.56	

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
2.711	2	-2 2 6	33.02	
2.642	1	-2 1 9	33.91	
2.598	1	-2 2 7	34.49	
2.509	1	0 2 9	35.76	
2.474	2	-1 1 11	36.28	
2.464	2	-3 1 5	36.44	
2.369	1	-2 3 1	37.95	
2.345	2	-2 3 4	38.36	
2.248	1	-2 3 6	40.08	
2.226	1	2 0 8	40.48	
2.129	1	0 3 9	42.43	
2.119	1	-1 1 13	42.63	
2.103	1	-1 4 4	42.97	
2.010	2	3 1 5	45.07	
2.007	1	1 4 4	45.13	
1.956	1	2 0 10	46.39	
1.948	1	-3 3 5	46.59	
1.945	1	-2 4 3	46.67	
1.907	1	-2 4 5	47.65	

Imipramine Hydrochloride, C₁₉H₂₅ClN₂

Synonyms

1. 5-(3-Dimethylaminopropyl)-10,11-dihydro-5H-dibenz[b,f]azepine hydrochloride
2. Berkomin
3. Tofranil
4. Deprinol

Structure

Monoclinic, P₂₁ (14), Z = 8. The structure was refined by Post et al. [1975].

Atom positions

All atoms were in general positions 4(e).

Lattice constants

a = 11.304(3) Å
b = 29.229(8)
c = 14.283(3)
β = 130.91(1)°

(published values: a = 11.303(3) Å,
b = 29.227(8), c = 14.282(3), β = 130.91(1)°
[Post et al., 1975])

CD cell: a = 11.304(1), b = 29.229(8),
c = 10.969(3), β = 100.24(1)°; sp. gp. P₂₁/n;
a/b = 0.3867, c/b = 0.3753

Volume
3566.5 Å³

Density

(calculated) 1.180 g/cm³
(measured) 1.18 g/cm³ [Post et al., 1975]

Thermal parameters

For hydrogen atoms, overall isotropic B = 7.26,
converted from U_{iso} = 0.092 Å². For all other
atoms, isotropic B_i were estimated from U_{ij}
for individual atoms.

Scattering factors

Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)

γ = 0.2872 × 10⁻³
I/I_{corundum} (calculated) = 0.285 for
reflection with hkl = 060.

Additional pattern

1. PDF card 27-1765 [de Leenheer and Heyndrickx, 1971]. The primary reference indicates that the powder data are for the HCl derivative; apparently the name and formula on the card are in error.

References

- International Tables for X-ray Crystallography
III (1962). (The Kynoch Press, Birmingham,
Eng.) p. 202.
de Leenheer, A. and Heyndrickx, A. (1971). J.
Ass. Off. Anal. Chem. 54, 625.
Post, M. L., Kennard, O. and Horn, A. S.
(1975). Acta Crystallogr. B31, 1008.

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598 Å
14.62	8	0 2 0	6.04	
10.11	78	0 1 1	8.74	
8.53	86	1 0 0	10.36	
8.20	14	1 1 0	10.78	
7.36	30	1 2 0+	12.02	
7.23	77	0 3 1	12.24	
7.13	46	-1 0 2	12.40	
6.932	13	-1 1 2	12.76	
6.104	2	-1 4 1	14.50	
5.757	8	-1 3 2	15.38	
5.549	47	1 4 0	15.96	
5.460	97	-2 1 2	16.22	
5.304	6	0 1 2	16.70	
5.187	21	-2 2 2+	17.08	
5.018	71	-2 2 1	17.66	
4.870	100	0 6 0	18.20	
4.721	7	0 3 2	18.78	
4.609	10	1 3 1	19.24	
4.562	11	-2 1 3	19.44	
4.432	40	-2 4 2+	20.02	
4.267	56	2 0 0+	20.80	
4.172	35	-2 3 3	21.28	
4.100	56	2 2 0+	21.66	
4.030	7	-2 5 2	22.04	
3.942	10	-2 5 1	22.54	
3.907	17	2 3 0+	22.74	
3.751	50	1 7 0	23.70	
3.714	36	-3 0 2	23.94	
3.684	39	2 4 0+	24.14	
3.666	39	-2 6 2	24.26	
3.613	24	0 6 2+	24.62	
3.567	53	-2 0 4	24.94	
3.545	24	-2 1 4	25.10	
3.466	54	-2 2 4+	25.68	
3.388	5	1 3 2	26.28	
3.324	30	-1 6 3+	26.80	
3.290	10	-2 7 1+	27.08	
3.250	30	-1 8 2+	27.42	
3.207	27	-2 4 4	27.80	
3.164	10	-3 3 1	28.18	
3.129	10	-3 5 3+	28.50	
3.089	5	-1 3 4	28.88	
3.074	6	1 5 2+	29.02	
3.054	9	-2 8 2	29.22	
3.028	5	0 8 2	29.48	
2.974	5	-1 4 4	30.02	
2.955	8	-1 9 2+	30.22	
2.923	4	0 10 0	30.56	
2.904	3	-3 5 1+	30.76	
2.895	3	-3 5 4+	30.86	

Imipramine Hydrochloride, C₁₉H₂₅ClN₂ - (continued)

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
2.866	5	-2 8 3	31.18	
2.847	7	3 0 0+	31.40	
2.826	4	-1 10 1	31.64	
2.819	5	-3 1 5	31.72	
2.776	7	2 8 0+	32.22	
2.731	12	-4 2 4+	32.76	
2.727	12	0 7 3+	32.82	
2.704	11	-4 3 3+	33.10	
2.699	11	0 0 4	33.16	
2.673	3	-4 3 4	33.50	
2.653	12	0 2 4+	33.76	
2.630	5	-4 2 2	34.06	
2.617	5	2 0 2+	34.24	
2.602	8	-3 7 4+	34.44	
2.579	4	0 11 1+	34.76	
2.552	3	1 10 1+	35.14	
2.548	3	-3 5 5	35.20	
2.531	5	0 4 4+	35.44	
2.512	2	-4 5 4	35.72	
2.498	2	-4 3 5	35.92	
2.491	2	-1 11 2	36.02	
2.478	1	1 5 3	36.22	
2.458	2	3 6 0	36.52	
2.431	3	-4 5 2+	36.94	
2.411	2	1 9 2+	37.26	
2.379	8	-2 11 1+	37.78	
2.360	6	0 6 4	38.10	
2.354	6	3 7 0	38.20	
2.345	4	-4 6 2	38.36	
2.325	4	3 3 1+	38.70	
2.300	4	-1 9 4+	39.14	
2.296	4	-4 4 1	39.20	
2.283	2	-4 6 5+	39.44	
2.274	2	1 10 2+	39.60	
2.261	3	-5 0 4+	39.84	
2.247	3	3 8 0+	40.10	
2.233	3	-5 2 4+	40.36	
2.215	4	3 5 1+	40.70	
2.203	6	-1 13 1+	40.94	
2.175	4	-5 2 3+	41.48	
2.170	4	1 2 4+	41.58	
2.158	2	-4 8 2+	41.82	
2.135	6	4 0 0+	42.30	
2.121	6	-2 9 5+	42.60	
2.107	3	-5 0 6+	42.88	
2.084	7	-2 13 2+	43.38	
2.079	6	-3 11 4+	43.50	
2.072	5	-2 13 1	43.64	
2.059	3	-5 1 2	43.94	
2.050	4	-5 6 4+	44.14	

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
2.044	4	-5 2 2	44.28	
2.039	3	2 9 2+	44.40	
2.021	4	-4 9 5+	44.80	
2.013	4	-4 2 7+	45.00	
1.999	2	1 6 4+	45.32	
1.987	2	3 3 2+	45.62	
1.955	3	4 6 0+	46.40	
1.945	3	-5 7 3+	46.66	
1.938	3	-3 11 5+	46.84	
1.922	3	-3 13 2+	47.26	
1.918	4	0 15 1+	47.36	
1.907	3	0 13 3+	47.64	
1.902	2	-2 14 3+	47.78	
1.898	2	-1 14 3	47.88	

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
14.61	7	0 2 0	6.04	
10.40	3	-1 1 1	8.50	
10.13	73	0 1 1	8.73	
8.54	81	1 0 0	10.35	
8.20	12	1 1 0	10.78	
7.38	19	1 2 0	11.99	
7.33	10	-1 3 1	12.07	
7.23	66	0 3 1	12.23	
7.14	34	-1 0 2	12.39	
6.934	10	-1 1 2	12.76	
6.107	1	-1 4 1	14.49	
5.758	7	-1 3 2	15.38	
5.553	40	1 4 0	15.95	
5.464	93	-2 1 2	16.21	
5.397	6	0 0 2	16.41	
5.307	2	0 1 2	16.69	
5.198	15	-2 2 2	17.04	
5.175	8	-1 5 1	17.12	
5.140	2	0 5 1	17.24	
5.106	4	-1 4 2	17.35	
5.063	13	0 2 2	17.50	
5.021	67	-2 2 1	17.65	
4.872	100	0 6 0	18.20	
4.824	5	1 5 0	18.38	
4.721	5	0 3 2	18.78	
4.612	8	1 3 1	19.23	
4.564	9	-2 1 3	19.43	
4.523	1	-1 5 2	19.61	
4.494	5	-1 1 3	19.74	
4.462	25	-1 6 1	19.88	

Imipramine Hydrochloride, C₁₉H₂₅ClN₂ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
4.440	20	0 6 1	19.98
4.426	21	-2 4 2	20.05
4.406	2	-2 2 3	20.14
4.315	9	-2 4 1	20.57
4.271	44	2 0 0	20.78
4.256	20	1 4 1	20.86
4.232	15	1 6 0	20.98
4.227	6	2 1 0	21.00
4.175	32	-2 3 3	21.26
4.121	23	-1 3 3	21.54
4.100	49	2 2 0	21.66
4.029	4	-2 5 2	22.04
3.945	7	-2 5 1	22.52
3.912	13	2 3 0	22.71
3.909	1	-1 7 1	22.73
3.900	2	1 5 1	22.78
3.894	4	0 7 1	22.82
3.751	50	1 7 0	23.70
3.716	30	-3 0 2	23.93
3.688	15	2 4 0	24.11
3.686	14	-3 1 2	24.12
3.678	5	-3 1 3	24.18
3.665	30	-2 6 2	24.27
3.625	5	-2 5 3	24.54
3.616	14	0 6 2	24.60
3.604	6	-1 7 2	24.68
3.601	2	-2 6 1	24.70
3.594	1	-3 2 3	24.75
3.590	5	-1 5 3	24.78
3.590	2	1 1 2	24.78
3.569	51	-2 0 4	24.93
3.543	16	-2 1 4	25.12
3.511	1	1 2 2	25.35
3.471	9	-1 8 1	25.64
3.467	32	-2 2 4	25.67
3.465	13	-3 3 3	25.69
3.461	8	0 8 1	25.72
3.449	1	2 5 0	25.81
3.391	4	1 3 2	26.26
3.375	1	0 3 3	26.38
3.339	10	-2 7 2	26.67
3.330	3	-3 0 4	26.75
3.325	6	-3 1 1	26.79
3.325	20	-1 6 3	26.79
3.308	3	-3 1 4	26.93
3.307	1	-3 4 3	26.94
3.291	5	-2 7 1	27.07
3.280	2	2 1 1	27.17
3.262	3	-3 2 1	27.32
3.258	8	-1 0 4	27.35

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
3.252	14	-1 8 2	27.40
3.246	12	-3 2 4	27.45
3.212	3	2 6 0	27.75
3.207	24	-2 4 4	27.80
3.180	1	-1 2 4	28.04
3.165	9	-3 3 1	28.17
3.136	3	-3 5 2	28.44
3.131	6	-3 5 3	28.48
3.126	1	2 3 1	28.53
3.118	3	-1 9 1	28.61
3.110	2	0 9 1	28.68
3.098	1	-2 7 3	28.79
3.090	2	-1 3 4	28.87
3.076	1	-1 7 3	29.01
3.076	4	1 5 2	29.01
3.064	1	0 5 3	29.12
3.054	8	-2 8 2	29.22
3.043	2	-3 4 1	29.33
3.030	1	-3 4 4	29.46
3.026	2	0 8 2	29.50
3.017	1	-2 8 1	29.59
2.976	5	-1 4 4	30.01
2.956	5	-1 9 2	30.21
2.954	3	-3 6 2	30.23
2.923	4	0 10 0	30.56
2.904	2	-3 5 1	30.76
2.894	1	0 6 3	30.87
2.893	1	-3 5 4	30.88
2.866	4	-2 8 3	31.18
2.848	4	3 0 0	31.39
2.846	3	-1 5 4	31.41
2.834	1	3 1 0	31.54
2.827	2	-1 10 1	31.62
2.817	3	-3 1 5	31.74
2.795	2	3 2 0	31.99
2.779	1	-3 2 5	32.19
2.776	2	2 8 0	32.21
2.776	2	-3 7 2	32.22
2.776	1	-2 9 1	32.22
2.752	1	-2 2 5	32.51
2.749	1	-3 6 4	32.55
2.734	4	1 7 2	32.73
2.732	6	-4 2 4	32.75
2.726	4	0 7 3	32.83
2.718	2	-3 3 5	32.93
2.713	1	-2 7 4	32.99
2.706	6	-4 3 3	33.08
2.705	2	-1 10 2	33.09
2.699	6	0 0 4	33.17
2.674	1	-4 3 4	33.48

Imipramine Hydrochloride, C₁₉H₂₅ClN₂ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.657	4	-2 9 3	33.70
2.654	9	0 2 4	33.75
2.653	1	3 4 0	33.75
2.639	1	-3 4 5	33.94
2.630	3	-4 2 2	34.07
2.618	3	2 0 2	34.23
2.617	1	-2 4 5	34.24
2.603	3	-3 7 4	34.42
2.602	2	-3 8 3	34.43
2.601	1	0 3 4	34.46
2.599	2	-4 4 4	34.48
2.580	2	0 11 1	34.74
2.577	1	2 2 2	34.79
2.552	1	1 10 1	35.14
2.547	1	-3 5 5	35.20
2.537	2	1 11 0	35.35
2.531	3	0 4 4	35.43
2.527	1	-2 5 5	35.50
2.511	2	-4 5 4	35.73
2.498	1	-4 3 5	35.92
2.490	1	-1 11 2	36.04
2.478	1	1 5 3	36.22
2.458	1	3 6 0	36.52
2.438	1	-4 6 3	36.83
2.431	2	-4 5 2	36.95
2.416	1	1 9 2	37.18
2.411	1	0 9 3	37.27
2.386	2	1 6 3	37.67
2.384	1	-1 4 5	37.71
2.379	5	-2 11 1	37.78
2.361	6	0 6 4	38.09
2.353	3	3 7 0	38.22
2.344	2	-4 6 2	38.38
2.325	2	-3 9 4	38.70
2.325	2	3 3 1	38.70
2.315	1	2 9 1	38.87
2.311	1	-3 3 6	38.93
2.306	1	2 6 2	39.03
2.300	2	-1 9 4	39.13
2.296	1	-4 4 1	39.21
2.283	1	-4 6 5	39.44
2.273	1	1 10 2	39.61
2.262	1	-3 4 6	39.81
2.260	2	-5 0 4	39.86
2.248	1	-4 3 6	40.08
2.246	1	3 8 0	40.11
2.233	2	-5 2 4	40.35
2.215	2	3 5 1	40.70
2.204	4	-1 13 1	40.92
2.201	2	0 13 1	40.97

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.199	1	-5 2 5	41.00
2.176	2	-1 10 4	41.47
2.175	2	-5 2 3	41.49
2.169	1	1 2 4	41.60
2.140	1	1 3 4	42.20
2.138	1	-3 6 6	42.24
2.136	3	4 0 0	42.28
2.134	2	-3 9 5	42.32
2.122	3	-2 9 5	42.58
2.120	3	-2 5 6	42.62
2.106	1	-5 0 6	42.91
2.093	2	-4 7 1	43.20
2.088	1	0 14 0	43.30
2.085	2	-5 2 6	43.37
2.085	5	-2 13 2	43.37
2.077	2	-3 11 4	43.54
2.077	1	3 7 1	43.54
2.073	3	-2 13 1	43.64
2.064	2	-4 9 2	43.83
2.058	1	-5 1 2	43.95
2.050	3	-5 6 4	44.14
2.043	2	-5 2 2	44.30
2.022	2	-4 9 5	44.78
2.022	1	-4 7 6	44.80
2.013	2	-4 2 7	45.00
2.012	1	-2 12 4	45.02
1.987	1	3 3 2	45.63
1.956	2	4 6 0	46.38
1.955	1	-2 14 2	46.42
1.946	1	-5 7 3	46.64
1.945	1	-3 4 7	46.66
1.943	1	3 11 0	46.72
1.937	1	-3 11 5	46.86
1.924	1	-3 13 2	47.21
1.922	1	-5 2 7	47.25
1.918	1	0 15 1	47.37
1.907	1	0 13 3	47.66
1.897	1	-1 14 3	47.90

Morphine Hydrochloride Hydrate, $C_{17}H_{20}ClNO_3 \cdot 3H_2O$

Synonyms

1. (-)-7,8-Didehydro-4,5- α -epoxy-17-methylmorphinan-3,6- α -diol hydrochloride hydrate
2. Morphine Chlorhydrate
3. Morphine Chloride Hydrate

Structure

Orthorhombic, $P2_12_12_1$ (19), $Z = 4$. The structure was determined by Gylbert [1973].

Atom positions

All atoms were in general positions 4(a). Bond lengths were calculated and indicated that the "z" coordinate of atom C3 should be 0.0935. That value was used in these calculations.

Lattice constants

$a = 13.020(7) \text{ \AA}$
 $b = 20.751(10)$
 $c = 6.941(4)$

$a/b = 0.6274$

$c/b = 0.3345$

(published values: $a = 13.019(7) \text{ \AA}$,
 $b = 20.750(10)$, $c = 6.941(4)$ [Gylbert, 1973])

Volume

$1875.3 \text{ \AA}^3$

Density

(calculated) 1.331 g/cm^3

(measured) 1.310 g/cm^3 [Gylbert, 1973]

Thermal parameters

Isotropic. For the hydrogen atoms, overall $B = 3.0$ [Gylbert, 1973]. For other atoms, isotropic B_i were estimated from β_{ij} for individual atoms.

Scattering factors

C^0 , H^0 , Cl^0 , N^0 , O^0 [International Tables, 1962]

Scale factors (integrated intensities)

$\gamma = 0.4275 \times 10^{-3}$

I/I_{corundum} (calculated) = 0.421, for reflection with $hkl = 020$.

Additional patterns

1. PDF card 10-798 [Barnes and Lindsey, 1955]

References

- Barnes, W. H. and Lindsey, J. M. (1955). Can. J. Chem. **33**, 565.
 Gylbert, L. (1973). Acta Crystallogr. **B29**, 1630.
 International Tables for X-ray Crystallography, **III** (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda = 1.540598\text{\AA}$
11.02	6	1 1 0	8.02
10.37	89	0 2 0	8.52
8.11	40	1 2 0	10.90
6.11	100	1 0 1+	14.48
5.870	29	1 1 1	15.08
5.764	84	0 2 1	15.36
5.273	24	1 2 1	16.80
5.187	17	0 4 0	17.08
4.897	20	0 3 1	18.10
4.818	18	1 4 0	18.40
4.746	35	2 0 1+	18.68
4.624	11	2 1 1	19.18
4.586	6	1 3 1	19.34
4.316	15	2 2 1	20.56
4.153	15	0 4 1	21.38
4.055	9	2 4 0	21.90
3.955	82	1 4 1	22.46
3.914	26	2 3 1	22.70
3.675	6	3 3 0	24.20
3.622	12	3 1 1	24.56
3.559	2	0 5 1	25.00
3.501	32	2 4 1+	25.42
3.469	16	0 0 2+	25.66
3.422	29	0 1 2	26.02
3.351	7	1 0 2	26.58
3.329	7	3 4 0	26.76
3.293	3	0 2 2	27.06
3.191	14	1 2 2	27.94
3.123	33	2 5 1	28.56
3.104	15	0 3 2+	28.74
3.054	3	2 6 0	29.22
3.012	16	1 3 2+	29.64
3.002	15	3 5 0	29.74
2.938	13	2 2 2+	30.40
2.884	5	0 4 2	30.98
2.833	1	4 2 1	31.56
2.800	9	2 3 2	31.94
2.753	9	3 5 1	32.50
2.727	2	0 7 1	32.82
2.711	2	3 0 2	33.02
2.688	3	3 1 2	33.30
2.668	4	1 7 1+	33.56
2.636	2	2 4 2	33.98
2.623	2	3 2 2	34.16
2.608	3	1 5 2	34.36
2.560	2	4 5 0	35.02
2.514	12	2 7 1+	35.68
2.464	4	2 5 2	36.44
2.448	5	3 7 0+	36.68
2.421	6	5 1 1	37.10

Morphine Hydrochloride Hydrate, $C_{17}H_{20}ClNO_2 \cdot 3H_2O$ - (continued)

d(Å)	I	hkl	2 θ (°) $\lambda = 1.540598\text{Å}$
2.403	7	3 4 2+	37.40
2.389	3	1 8 1	37.62
2.373	4	5 2 1	37.88
2.359	4	4 1 2	38.12
2.314	2	4 2 2	38.88
2.299	3	5 3 1	39.16
2.293	4	2 6 2	39.26
2.270	8	3 5 2	39.68
2.244	6	4 6 1+	40.16
2.226	7	3 8 0	40.50
2.221	6	1 7 2	40.58
2.207	2	5 4 1	40.86
2.193	2	0 3 3	41.12
2.188	2	0 9 1	41.22
2.163	8	1 3 3+	41.72
2.133	3	3 6 2+	42.34
2.121	1	3 8 1	42.60
2.102	2	5 5 1	43.00
2.085	4	1 4 3+	43.36
2.080	4	2 3 3+	43.48
2.074	4	2 9 1+	43.60
2.061	5	6 1 1	43.90
2.041	1	3 0 3	44.34
2.032	4	3 1 3+	44.56
2.010	2	2 4 3	45.08
2.000	6	3 7 2+	45.30
1.996	4	5 6 1	45.40
1.965	1	1 10 1	46.16
1.958	3	4 6 2+	46.34
1.947	1	4 8 1	46.60
1.933	3	5 4 2+	46.98
1.923	2	6 4 1+	47.22
1.902	2	1 6 3+	47.78
1.883	1	5 7 1+	48.30
1.873	2	3 8 2	48.56
1.867	4	1 11 0	48.74
1.862	5	5 5 2	48.88
1.853	2	4 7 2+	49.12
1.844	1	2 6 3	49.38
1.838	2	5 8 0+	49.56
1.832	2	3 5 3+	49.72
1.807	2	3 10 1+	50.46
1.803	2	1 11 1	50.58
1.790	1	7 1 1	50.98
1.785	1	5 6 2	51.14
1.777	2	5 8 1+	51.38
1.765	1	1 10 2	51.76
1.757	1	3 9 2+	52.02
1.729	2	5 0 3+	52.90
1.726	2	0 8 3	53.00

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2 θ (°) $\lambda = 1.540598\text{Å}$	
11.03	5	1 1 0	8.01	
10.38	100	0 2 0	8.52	
8.11	46	1 2 0	10.89	
6.21	4	2 1 0	14.25	
6.12	66	1 0 1	14.45	
6.11	59	1 3 0	14.49	
5.874	28	1 1 1	15.07	
5.769	98	0 2 1	15.35	
5.275	28	1 2 1	16.80	
5.188	18	0 4 0	17.08	
4.900	23	0 3 1	18.09	
4.819	19	1 4 0	18.39	
4.748	33	2 0 1	18.67	
4.741	9	2 3 0	18.70	
4.629	12	2 1 1	19.16	
4.586	5	1 3 1	19.34	
4.318	18	2 2 1	20.55	
4.155	18	0 4 1	21.37	
4.057	10	2 4 0	21.89	
3.959	86	1 4 1	22.44	
3.954	18	1 5 0	22.47	
3.915	26	2 3 1	22.70	
3.680	1	3 0 1	24.17	
3.676	7	3 3 0	24.19	
3.623	15	3 1 1	24.55	
3.562	1	0 5 1	24.98	
3.503	30	2 4 1	25.41	
3.500	11	2 5 0	25.43	
3.470	10	0 0 2	25.65	
3.468	6	3 2 1	25.67	
3.458	1	0 6 0	25.74	
3.436	7	1 5 1	25.91	
3.423	34	0 1 2	26.01	
3.353	7	1 0 2	26.56	
3.343	2	1 6 0	26.65	
3.329	6	3 4 0	26.76	
3.310	2	1 1 2	26.91	
3.291	3	0 2 2	27.07	
3.216	3	4 1 0	27.72	
3.191	18	1 2 2	27.94	
3.125	43	2 5 1	28.54	
3.106	5	4 2 0	28.72	
3.102	10	0 3 2	28.76	
3.054	2	2 6 0	29.22	
3.030	5	2 1 2	29.46	
3.017	13	1 3 2	29.58	
3.012	7	1 6 1	29.64	
3.001	2	3 4 1	29.74	
2.999	12	3 5 0	29.76	
2.947	5	4 0 1	30.30	

Morphine Hydrochloride Hydrate, $C_{17}H_{20}ClNO_3 \cdot 3H_2O$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.945	3	4 3 0	30.32
2.937	12	2 2 2	30.41
2.918	2	4 1 1	30.62
2.890	1	1 7 0	30.91
2.885	6	0 4 2	30.98
2.835	1	4 2 1	31.53
2.816	3	1 4 2	31.75
2.800	11	2 3 2	31.93
2.757	1	4 4 0	32.45
2.753	11	3 5 1	32.49
2.726	2	0 7 1	32.83
2.710	2	3 0 2	33.02
2.698	1	2 7 0	33.18
2.688	3	3 1 2	33.31
2.668	5	1 7 1	33.56
2.662	1	0 5 2	33.64
2.637	2	2 4 2	33.97
2.622	3	3 2 2	34.16
2.608	3	1 5 2	34.35
2.561	3	4 5 0	35.01
2.524	5	3 3 2	35.54
2.520	6	3 6 1	35.60
2.515	10	2 7 1	35.68
2.464	5	2 5 2	36.43
2.450	2	0 6 2	36.65
2.448	5	3 7 0	36.68
2.421	7	5 1 1	37.10
2.403	3	4 5 1	37.40
2.402	6	3 4 2	37.40
2.389	3	1 8 1	37.63
2.373	5	5 2 1	37.88
2.359	5	4 1 2	38.12
2.314	3	4 2 2	38.88
2.299	3	5 3 1	39.14
2.293	3	2 6 2	39.26
2.276	1	2 8 1	39.56
2.269	11	3 5 2	39.68
2.246	3	4 3 2	40.12
2.243	6	4 6 1	40.17
2.227	7	3 8 0	40.48
2.225	1	1 2 3	40.51
2.221	3	1 7 2	40.59
2.207	2	5 4 1	40.86
2.194	1	0 3 3	41.11
2.188	1	0 9 1	41.22
2.173	1	2 9 0	41.52
2.168	5	2 1 3	41.62
2.164	8	1 3 3	41.71
2.133	1	2 2 3	42.33
2.133	3	3 6 2	42.33

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.120	1	3 8 1	42.61
2.102	3	5 5 1	42.99
2.090	1	4 7 1	43.25
2.086	3	1 4 3	43.35
2.083	1	5 0 2	43.41
2.079	1	2 3 3	43.49
2.074	2	2 9 1	43.60
2.061	6	6 1 1	43.90
2.061	1	4 5 2	43.90
2.042	1	3 0 3	44.33
2.032	3	3 1 3	44.56
2.031	2	6 2 1	44.58
2.029	1	4 8 0	44.63
2.021	1	0 5 3	44.81
2.010	2	2 4 3	45.07
2.003	1	3 2 3	45.23
2.000	6	3 7 2	45.30
1.993	1	5 6 1	45.48
1.965	1	1 10 1	46.15
1.958	1	3 3 3	46.33
1.957	2	4 6 2	46.35
1.947	1	4 8 1	46.61
1.933	3	5 4 2	46.97
1.930	1	2 5 3	47.05
1.924	1	6 4 1	47.21
1.923	1	0 6 3	47.23
1.902	2	1 6 3	47.77
1.883	1	5 7 1	48.29
1.874	2	3 8 2	48.54
1.867	4	1 11 0	48.74
1.862	4	5 5 2	48.89
1.853	1	4 7 2	49.12
1.844	1	2 6 3	49.38
1.838	1	5 8 0	49.56
1.832	1	3 5 3	49.73
1.812	1	2 11 0	50.32
1.808	2	3 10 1	50.45
1.803	1	1 11 1	50.59
1.790	1	7 1 1	50.98
1.784	1	5 6 2	51.15
1.777	1	5 8 1	51.39
1.765	1	1 10 2	51.77
1.756	1	3 9 2	52.03
1.730	1	5 0 3	52.89
1.727	2	0 8 3	52.99

Naloxone Hydrochloride Hydrate, $C_{19}H_{22}ClNO_4 \cdot 2H_2O$

Synonyms

- 17-Allyl-4,5-epoxy-3,14-dihydroxy-morphinan-6-one hydrochloride hydrate
- (-)-N-Allyl-7,8-dihydro-14-hydroxy-morphinone hydrochloride hydrate

Structure

Orthorhombic, $P2_12_12_1$ (19), $Z = 4$. The structure was refined in 1975 by Sime et al., and in 1974 by Karle.

Atom positions

All atoms were in the general positions 4(a) given by Sime et al. [1975]. The "x" parameter for C(15) appeared to be in error, and the value 0.1908 was used instead, in these calculations.

Lattice constants

$a = 7.833(3) \text{ \AA}$
 $b = 13.186(5)$
 $c = 18.570(5)$

(published values: $a = 7.833(3) \text{ \AA}$,
 $b = 13.185(5)$, $c = 18.569(5)$ [Sime et al., 1975])

CD cell: $a = 13.185(5)$, $b = 18.570(5)$,
 $c = 7.833(3)$; sp. gp. = $P2_12_12_1$; $a/b = 0.7101$,
 $c/b = 0.4218$

Volume

$1918.0 \text{ \AA}^3$

Density

(calculated) 1.385 g/cm^3
(measured) 1.35 g/cm^3 [Sime et al.]

Thermal parameters

Isotropic. For hydrogen: overall $B = 4.0$
and for other atoms, B_i was estimated from
 B_{ij} for individual atoms.

Scattering factors

H^0 [International Tables, 1962]
All other atoms, zero ionization, from Cromer
and Mann [1968]. The chlorine atoms were cor-
rected for dispersion [Cromer and Liberman, 1970].

Scale factors (integrated intensities)

$\gamma = 1.196 \times 10^{-3}$
 I/I_{corundum} (calculated) = 1.13 for the
reflection with $hkl = 101$.

References

- Cromer, D. T. and Mann, J. B. (1968). Acta
Crystallogr. **A24**, 321.
Cromer, D. T. and Liberman, D. (1970). J.
Chem. Phys. **53**, 1891.
International Tables for X-ray Crystallography,
III (1962). (The Kynoch Press, Birmingham,
Eng.), p. 202.
Karle, I. L. (1974). Acta Crystallogr. **B30**,
1682.
Sime, R. L., Forehand, R. and Sime, R. J. (1975).
Acta Crystallogr. **B31**, 2326.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda = 1.540598\text{\AA}$
10.75	6	0 1 1	8.22
9.28	2	0 0 2	9.52
7.58	13	0 1 2	11.66
7.21	100	1 0 1	12.26
6.73	11	1 1 0	13.14
6.59	27	0 2 0	13.42
6.33	26	1 1 1	13.98
5.45	27	1 1 2	16.26
5.37	6	0 2 2	16.48
4.87	12	1 2 1	18.22
4.55	5	1 1 3	19.48
4.51	2	0 2 3	19.66
4.43	11	1 2 2	20.02
4.28	2	0 3 1	20.76
3.911	5	1 2 3+	22.72
3.831	11	1 3 0	23.20
3.751	23	1 3 1+	23.70
3.678	3	2 1 1	24.18
3.607	6	2 0 2	24.66
3.542	11	1 3 2	25.12
3.480	4	2 1 2	25.58
3.414	2	1 2 4	26.08
3.356	7	1 0 5+	26.54
3.312	18	2 2 1	26.90
3.252	5	1 3 3+	27.40
3.209	2	2 1 3	27.78
3.164	1	2 2 2	28.18
3.038	10	1 4 0	29.38
2.992	9	1 2 5+	29.84
2.955	6	1 3 4+	30.22
2.917	3	2 1 4+	30.62
2.912	3	0 4 3	30.68
2.888	3	1 4 2	30.94
2.790	6	2 3 2	32.06
2.727	4	2 2 4+	32.82
2.687	2	0 4 4	33.32
2.667	1	1 3 5	33.58
2.638	6	1 2 6+	33.96
2.560	2	3 1 0	35.02
2.542	1	1 4 4+	35.28
2.521	1	2 4 0	35.58
2.498	4	2 4 1	33.92
2.468	5	3 1 2+	36.38
2.426	2	0 5 3+	37.02
2.408	2	1 3 6+	37.32
2.348	4	1 2 7+	38.30
2.278	2	2 2 6	39.52
2.257	2	0 4 6+	39.92
2.226	1	1 0 8	40.50
2.201	2	1 5 4	40.98

Naloxone Hydrochloride Hydrate, $C_{19}H_{22}ClNO_4 \cdot 2H_2O$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598\text{\AA}$
2.182	2	3 3 2+	41.34	
2.173	1	2 5 1	41.52	
2.151	1	3 2 4	41.96	
2.129	2	2 5 2	42.42	
2.110	2	3 3 3+	42.82	
2.086	1	2 4 5+	43.34	
2.063	2	1 6 2+	43.86	
2.047	1	3 4 0	44.22	
1.999	3	3 4 2+	45.34	
1.973	1	3 1 6+	45.96	
1.944	1	1 5 6+	46.68	
1.921	1	3 3 5+	47.28	
1.910	2	1 2 9+	47.58	
1.896	1	4 1 2	47.94	
1.892	1	0 6 5	48.06	
1.868	1	0 3 9+	48.72	
1.855	1	3 5 0	49.06	
1.839	2	4 2 2+	49.52	

Calculated Pattern (Integrated)				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598\text{\AA}$
10.75	6	0 1 1	8.22	
10.75	6	0 -1 -1	8.22	
9.28	2	0 0 2	9.52	
9.28	2	0 0 -2	9.52	
7.59	12	0 1 2	11.65	
7.59	12	0 -1 -2	11.65	
7.22	100	1 0 1	12.25	
7.22	100	-1 0 -1	12.25	
6.73	9	1 1 0	13.14	
6.73	9	-1 -1 0	13.14	
6.59	27	0 2 0	13.42	
6.59	27	0 -2 0	13.42	
6.33	26	1 1 1	13.98	
6.33	27	-1 -1 -1	13.98	
5.45	28	1 1 2	16.25	
5.45	28	-1 -1 -2	16.25	
5.38	4	0 2 2	16.48	
5.38	4	0 -2 -2	16.48	
4.87	13	1 2 1	18.21	
4.87	12	-1 -2 -1	18.21	
4.56	5	1 1 3	19.46	
4.56	6	-1 -1 -3	19.46	
4.51	1	0 2 3	19.66	
4.51	1	0 -2 -3	19.66	
4.43	12	1 2 2	20.02	

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598\text{\AA}$
4.43	11	-1 -2 -2	20.02	
4.28	2	0 3 1	20.75	
4.28	2	0 -3 -1	20.75	
3.916	3	2 0 0	22.69	
3.916	3	-2 0 0	22.69	
3.910	3	1 2 3	22.72	
3.910	3	-1 -2 -3	22.72	
3.833	11	1 3 0	23.19	
3.833	11	-1 -3 0	23.19	
3.822	2	1 1 4	23.25	
3.822	1	-1 -1 -4	23.25	
3.754	11	2 1 0	23.68	
3.754	11	-2 -1 0	23.68	
3.754	14	1 3 1	23.68	
3.754	15	-1 -3 -1	23.68	
3.680	3	2 1 1	24.17	
3.680	3	-2 -1 -1	24.17	
3.609	6	2 0 2	24.65	
3.609	6	-2 0 -2	24.65	
3.543	12	1 3 2	25.11	
3.543	12	-1 -3 -2	25.11	
3.481	4	2 1 2	25.57	
3.481	4	-2 -1 -2	25.57	
3.416	2	1 2 4	26.07	
3.416	2	-1 -2 -4	26.07	
3.367	3	2 2 0	26.45	
3.367	3	-2 -2 0	26.45	
3.356	5	1 0 5	26.54	
3.356	5	-1 0 -5	26.54	
3.313	19	2 2 1	26.89	
3.313	18	-2 -2 -1	26.89	
3.310	2	2 0 3	26.92	
3.310	2	-2 0 -3	26.92	
3.259	3	1 3 3	27.34	
3.259	3	-1 -3 -3	27.34	
3.252	3	1 1 5	27.40	
3.252	3	-1 -1 -5	27.40	
3.246	1	0 4 1	27.46	
3.246	1	0 -4 -1	27.46	
3.236	1	0 2 5	27.54	
3.236	1	0 -2 -5	27.54	
3.210	2	2 1 3	27.77	
3.210	2	-2 -1 -3	27.77	
3.165	1	2 2 2	28.17	
3.165	1	-2 -2 -2	28.17	
3.038	12	1 4 0	29.37	
3.038	12	-1 -4 0	29.37	
2.994	4	2 0 4	29.82	
2.994	4	-2 0 -4	29.82	
2.991	6	1 2 5	29.85	

Naloxone Hydrochloride Hydrate, $C_{19}H_{22}ClNO_4 \cdot 2H_2O$ - (continued)

d(A)	I	hkl	2 θ (°) λ - 1.540598Å
2.991	6	-1 -2 -5	29.85
2.958	3	2 2 3	30.19
2.958	3	-2 -2 -3	30.19
2.956	4	1 3 4	30.21
2.956	4	-1 -3 -4	30.21
2.924	1	2 3 0	30.55
2.924	1	-2 -3 0	30.55
2.919	2	2 1 4	30.60
2.919	2	-2 -1 -4	30.60
2.910	2	0 4 3	30.70
2.910	2	0 -4 -3	30.70
2.888	2	1 4 2	30.94
2.888	2	-1 -4 -2	30.94
2.812	1	1 1 6	31.79
2.812	1	-1 -1 -6	31.79
2.802	2	0 2 6	31.92
2.802	2	0 -2 -6	31.92
2.789	7	2 3 2	32.07
2.789	7	-2 -3 -2	32.07
2.728	2	1 4 3	32.81
2.728	2	-1 -4 -3	32.81
2.726	3	2 2 4	32.83
2.726	3	-2 -2 -4	32.83
2.688	2	0 4 4	33.31
2.688	2	0 -4 -4	33.31
2.667	1	1 3 5	33.57
2.667	1	-1 -3 -5	33.57
2.644	1	2 3 3	33.88
2.644	1	-2 -3 -3	33.88
2.640	1	2 1 5	33.92
2.640	1	-2 -1 -5	33.92
2.638	6	1 2 6	33.96
2.638	6	-1 -2 -6	33.96
2.561	2	3 1 0	35.01
2.561	2	-3 -1 0	35.01
2.542	1	1 4 4	35.27
2.542	1	-1 -4 -4	35.27
2.522	1	2 4 0	35.57
2.522	1	-2 -4 0	35.57
2.499	4	2 4 1	35.91
2.499	4	-2 -4 -1	35.91
2.474	1	2 3 4	36.28
2.474	1	-2 -3 -4	36.28
2.469	3	3 1 2	36.36
2.469	3	-3 -1 -2	36.36
2.465	2	0 4 5	36.41
2.465	2	0 -4 -5	36.41
2.428	1	3 2 0	37.00
2.428	1	-3 -2 0	37.00
2.426	1	0 5 3	37.02

d(A)	I	hkl	2 θ (°) λ - 1.540598Å
2.426	1	0 -5 -3	37.02
2.408	1	1 3 6	37.31
2.408	1	-1 -3 -6	37.31
2.349	2	3 2 2	38.29
2.349	2	-3 -2 -2	38.29
2.348	3	1 2 7	38.30
2.348	3	-1 -2 -7	38.30
2.279	2	2 2 6	39.52
2.279	2	-2 -2 -6	39.52
2.256	2	0 4 6	39.92
2.256	2	0 -4 -6	39.92
2.226	1	1 0 8	40.50
2.226	1	-1 0 -8	40.50
2.201	2	1 5 4	40.98
2.201	2	-1 -5 -4	40.98
2.182	1	3 3 2	41.35
2.182	1	-3 -3 -2	41.35
2.172	1	2 5 1	41.53
2.172	1	-2 -5 -1	41.53
2.151	1	3 2 4	41.96
2.151	1	-3 -2 -4	41.96
2.129	2	2 5 2	42.42
2.129	2	-2 -5 -2	42.42
2.110	2	3 3 3	42.82
2.110	2	-3 -3 -3	42.82
2.086	1	2 4 5	43.33
2.086	1	-2 -4 -5	43.33
2.063	1	1 6 2	43.85
2.063	1	-1 -6 -2	43.85
2.047	1	3 4 0	44.22
2.047	1	-3 -4 0	44.22
1.999	2	3 4 2	45.34
1.999	2	-3 -4 -2	45.34
1.944	1	1 5 6	46.67
1.944	1	-1 -5 -6	46.67
1.910	1	1 2 9	47.58
1.910	1	-1 -2 -9	47.58
1.896	1	4 1 2	47.94
1.896	1	-4 -1 -2	47.94
1.891	1	0 6 5	48.07
1.891	1	0 -6 -5	48.07
1.840	1	4 2 2	49.50
1.840	1	-4 -2 -2	49.50
1.839	1	0 1 10	49.53
1.839	1	0 -1 -10	49.53

Palladium Selenium (Palladseite), Pd₁₇Se₁₅

Structure

Cubic, $Z = 2$. The space group Pm3m was used for the structure determination by Geller [1962] and for the powder pattern here. The x-ray data did not eliminate uncertainty about the space group which could also be P43m or P432 [Geller, 1962].

Atom positions

24(m) 24 palladium
12(j) 12 selenium
12(i) 12 selenium
6(f) 6 selenium
6(e) 6 palladium
3(d) 3 palladium
1(b) 1 palladium

Lattice constants

$a = 10.607(3) \text{ \AA}$

(published value: $a = 10.606(3) \text{ \AA}$ [Geller, 1962]).

Volume

$1193.4 \text{ \AA}^3$

Density

(calculated) 8.330 g/cm^3

Thermal parameters

Isotropic, Table 2 [Geller, 1962]

Scattering factors

Pd⁰, Se⁰ [Thomas and Umeda, 1957], corrected for dispersion [Cromer and Liberman, 1970]

Scale factor (integrated intensities)

$\gamma = 0.4090 \times 10^{-3}$

I/I_{corundum} (calculated) = 4.11 for reflection with $hkl = 440$.

References

Cromer, D. T. and Liberman, D. (1970). J. Chem. Phys. 53, 1891.
Geller, S. (1962). Acta Crystallogr. 15, 713.
Thomas, L. H. and Umeda, K. (1957). J. Chem. Phys. 26, 293.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda = 1.540598\text{\AA}$
5.30	5	2 0 0	16.72
4.741	3	2 1 0	18.70
4.329	1	2 1 1	20.50
3.748	4	2 2 0	23.72
3.534	4	2 2 1	25.18
3.353	44	3 1 0	26.56
3.198	91	3 1 1	27.88
3.062	3	2 2 2	29.14
2.942	18	3 2 0	30.36
2.834	52	3 2 1	31.54
2.572	64	4 1 0+	34.86
2.499	32	4 1 1	35.90
2.4327	26	3 3 1	36.92
2.3720	25	4 2 0	37.90
2.3145	20	4 2 1	38.88
2.1215	11	4 3 0+	42.58
2.0797	12	4 3 1+	43.48
2.0413	79	3 3 3	44.34
1.9365	1	5 2 1	46.88
1.8748	100	4 4 0	48.52
1.8462	3	5 2 2	49.32
1.8193	9	4 3 3+	50.10
1.7925	1	5 3 1	50.90
1.7679	36	6 0 0	51.66
1.7435	4	6 1 0	52.44
1.7203	16	5 3 2+	53.20
1.6772	6	6 2 0	54.68
1.6566	17	5 4 0+	55.42
1.6365	15	5 4 1	56.16
1.6175	3	5 3 3	56.88
1.5814	5	5 4 2+	58.30
1.5309	2	4 4 4	60.42
1.5155	2	7 0 0	61.10
1.5000	5	7 1 0+	61.80
1.4853	1	5 5 1	62.48
1.4709	5	6 4 0	63.16
1.4569	2	6 4 1	63.84
1.4049	2	5 4 4+	66.50
1.3927	3	7 3 0	67.16
1.3807	25	7 3 1	67.82
1.3579	5	6 4 3	69.12
1.3470	6	7 3 2+	69.76
1.3258	9	8 0 0	71.04
1.3156	3	7 4 0+	71.68
1.3055	9	5 5 4+	72.32
1.2959	12	7 3 3	72.94
1.2862	12	6 4 4	73.58
1.2770	5	7 4 2+	74.20
1.2677	1	6 5 3	74.84
1.2501	9	6 6 0	76.08

Palladium Selenium (Palladseite), Pd₁₇Se₁₅ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.2415	1	8 3 0+	76.70
1.2331	6	7 4 3	77.32
1.2248	5	7 5 1	77.94
1.2167	1	6 6 2	78.56
1.1858	3	8 4 0	81.02
1.1786	3	7 4 4+	81.62
1.1713	4	9 1 0	82.24
1.1643	1	9 1 1+	82.84
1.1573	5	8 4 2	83.46
1.1505	3	7 6 0	84.06
1.1437	7	7 6 1+	84.68

Calculated Pattern (Integrated)			
d(Å)	I	hkl	2θ(°) λ - 1.540598Å
5.30	4	2 0 0	16.70
4.744	2	2 1 0	18.69
4.330	1	2 1 1	20.49
3.750	3	2 2 0	23.71
3.536	3	2 2 1	25.17
3.354	38	3 1 0	26.55
3.198	79	3 1 1	27.87
3.062	3	2 2 2	29.14
2.942	16	3 2 0	30.36
2.835	47	3 2 1	31.53
2.573	44	4 1 0	34.85
2.573	16	3 2 2	34.85
2.500	29	4 1 1	35.89
2.4334	24	3 3 1	36.91
2.3718	23	4 2 0	37.90
2.3146	19	4 2 1	38.88
2.1214	5	4 3 0	42.58
2.1214	5	5 0 0	42.58
2.0802	5	5 1 0	43.47
2.0802	6	4 3 1	43.47
2.0413	6	5 1 1	44.34
2.0413	71	3 3 3	44.34
1.9366	1	5 2 1	46.88
1.8751	100	4 4 0	48.51
1.8464	2	5 2 2	49.31
1.8191	2	5 3 0	50.11
1.8191	7	4 3 3	50.11
1.7929	1	5 3 1	50.89
1.7678	36	6 0 0	51.66
1.7438	4	6 1 0	52.43
1.7207	6	6 1 1	53.19
1.7207	10	5 3 2	53.19
1.6771	6	6 2 0	54.68
1.6565	7	5 4 0	55.42
1.6565	3	6 2 1	55.42

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.6565	7	4 4 3	55.42
1.6367	15	5 4 1	56.15
1.6176	3	5 3 3	56.88
1.5812	3	5 4 2	58.31
1.5812	2	6 3 0	58.31
1.5310	2	4 4 4	60.42
1.5153	2	7 0 0	61.11
1.5001	3	7 1 0	61.80
1.5001	2	5 5 0	61.80
1.4853	1	5 5 1	62.48
1.4709	5	6 4 0	63.16
1.4570	2	6 4 1	63.83
1.4049	2	5 4 4	66.50
1.3928	2	7 3 0	67.16
1.3809	27	7 3 1	67.81
1.3581	5	6 4 3	69.11
1.3471	3	7 3 2	69.76
1.3471	3	6 5 1	69.76
1.3259	10	8 0 0	71.04
1.3156	3	7 4 0	71.68
1.3056	3	7 4 1	72.31
1.3056	1	8 1 1	72.31
1.3056	6	5 5 4	72.31
1.2959	13	7 3 3	72.94
1.2863	13	6 4 4	73.58
1.2769	4	7 4 2	74.20
1.2769	1	8 2 1	74.20
1.2678	1	6 5 3	74.83
1.2500	9	6 6 0	76.08
1.2330	6	7 4 3	77.32
1.2248	5	7 5 1	77.94
1.2167	1	6 6 2	78.56
1.1859	3	8 4 0	81.02
1.1786	2	7 4 4	81.63
1.1713	4	9 1 0	82.24
1.1643	1	9 1 1	82.85
1.1573	5	8 4 2	83.46
1.1505	3	7 6 0	84.06
1.1438	4	7 6 1	84.67
1.1438	3	9 2 1	84.67

Phencyclidine Hydrochloride, C₁₇H₂₆ClN

Synonyms

1. 1-(1-Phenylcyclohexyl) piperidine hydrochloride
2. Sernyl hydrochloride
3. Sernylan
4. PCP hydrochloride

CAS registry no.

956-90-1

Structure

Monoclinic, P₂₁/c (14), Z = 4. The structure was determined by Argos et al. [1970].

Atom positions

All atoms were in general positions [ibid.]

Lattice constants

a = 8.881(10) Å
b = 13.867(20)
c = 13.099(10)
β = 104.55(16)°

(published values: a = 8.881(10),
b = 13.866(20), c = 13.098(10),
β = 104°33'(10') [Argos et al., 1970])

CD cell: a = 13.099(10) Å, b = 13.867(20),
c = 8.881(10), β = 104.55(16)°; sp. gp. P₂₁/a;
a/b = 0.9446; c/b = 0.6404

Volume

1561.4 Å³

Density

(calculated) 1.190 g/cm³
(measured) 1.190(4) [Argos et al., 1970]

Thermal parameters

Isotropic B_i, estimated from β_{ij} for individual atoms.

Scattering factors

Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)

γ = 0.6975 × 10⁻³
I/I_{corundum} (calculated) = 0.751 for reflection
with hkl = 021.

Additional pattern

1. Folen [1975]

References

- Argos, P., Barr, R. E., and Weber, A. H.
(1970). Acta Crystallogr. B26, 53.
Folen, V. A. (1975). J. Forensic Sci. 20,
348.
International Tables for X-ray Crystallography,
III (1962). (The Kynoch Press, Birmingham,
Eng.) p. 202.

Calculated Pattern (Peak heights)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
9.34	16	0 1 1	9.46
8.58	57	1 0 0	10.30
6.93	6	0 2 0	12.76
6.34	15	0 0 2	13.96
6.08	100	0 2 1	14.56
5.80	15	1 1 1	15.26
5.76	22	0 1 2	15.36
5.39	2	-1 1 2	16.44
5.27	14	-1 2 1	16.80
4.68	18	0 2 2	18.96
4.47	19	-1 2 2	19.84
4.34	22	0 3 1	20.44
4.30	25	2 0 0	20.66
4.10	9	2 1 0	21.64
4.05	38	-1 1 3+	21.92
3.90	18	-2 1 2	22.80
3.82	26	1 2 2	23.26
3.73	11	-2 2 1	23.86
3.65	26	2 1 1+	24.34
3.62	23	-1 3 2+	24.54
3.36	2	1 1 3	26.52
3.33	11	2 2 1	26.78
3.25	3	1 3 2	27.40
3.21	3	1 4 0	27.74
3.16	24	-1 1 4+	28.18
3.12	23	0 3 3+	28.60
3.05	3	1 4 1	29.28
2.942	4	-1 2 4	30.36
2.895	9	-3 1 1+	30.86
2.864	7	-2 1 4+	31.20
2.773	4	1 3 3+	32.26
2.722	6	-2 4 1+	32.88
2.696	3	-2 2 4+	33.20
2.682	5	-1 4 3	33.38
2.624	7	-1 5 1	34.14
2.608	4	3 1 1	34.36
2.541	1	0 5 2+	35.30
2.510	1	2 2 3	35.74
2.493	3	-3 3 1+	36.00
2.455	3	-2 4 3+	36.58
2.368	2	1 3 4+	37.96
2.361	2	3 1 2	38.08
2.329	4	-2 2 5+	38.62
2.277	2	-1 3 5+	39.54
2.251	5	1 1 5	40.02
2.223	3	-1 6 1+	40.54
2.180	2	-2 3 5+	41.38
2.166	2	1 2 5+	41.66
2.149	2	4 0 0+	42.00
2.126	5	2 4 3	42.48

Phencyclidine Hydrochloride, C₁₇H₂₆ClN - (continued)

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
2.123	5	4 1 0+	42.54	
2.107	3	-4 2 1+	42.88	
2.053	4	4 2 0+	44.08	
2.026	4	-2 2 6+	44.70	
2.022	4	0 2 6	44.78	
2.015	5	4 1 1+	44.96	
1.995	2	-4 3 1+	45.42	
1.980	2	-3 3 5	45.78	
1.948	2	4 3 0+	46.58	
1.942	2	1 0 6	46.74	
1.930	5	1 7 0+	47.04	
1.926	4	-1 7 1+	47.16	
1.891	2	0 7 2+	48.08	
1.870	2	1 2 6+	48.64	
1.846	1	-2 5 5+	49.34	
1.818	1	3 4 3	50.14	
1.805	1	-1 2 7+	50.52	
1.794	1	0 7 3+	50.86	
1.762	1	1 5 5+	51.86	
1.756	2	2 7 1+	52.04	
1.750	1	-4 3 5	52.22	
1.719	1	2 1 6+	53.24	
1.700	2	-5 2 3+	53.88	
1.696	2	1 4 6+	54.02	
1.689	2	-5 1 4+	54.28	
1.672	1	0 8 2	54.86	
1.662	1	-1 8 2	55.22	
1.646	1	-1 4 7	55.82	
1.641	1	1 2 7+	56.00	
1.622	1	-1 1 8+	56.70	
1.614	1	-5 1 5+	57.00	
1.586	1	1 3 7+	58.10	
1.563	1	-3 0 8+	59.06	

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
9.36	16	0 1 1	9.44	
8.60	57	1 0 0	10.28	
7.01	1	-1 1 1	12.62	
6.93	6	0 2 0	12.76	
6.34	14	0 0 2	13.96	
6.08	100	0 2 1	14.55	
5.85	1	-1 0 2	15.13	
5.82	10	1 1 1	15.22	
5.77	19	0 1 2	15.36	
5.39	1	-1 1 2	16.43	

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
5.27	14	-1 2 1	16.80	
4.71	3	1 2 1	18.84	
4.68	17	0 2 2	18.95	
4.47	19	-1 2 2	19.84	
4.35	1	1 1 2	20.40	
4.34	21	0 3 1	20.43	
4.30	25	2 0 0	20.65	
4.11	7	2 1 0	21.63	
4.06	10	-2 0 2	21.86	
4.05	33	-1 1 3	21.91	
4.04	1	0 1 3	21.97	
4.02	4	-1 3 1	22.11	
3.90	19	-2 1 2	22.79	
3.82	28	1 2 2	23.25	
3.75	1	1 3 1	23.72	
3.73	11	-2 2 1	23.85	
3.66	16	2 1 1	24.32	
3.65	11	2 2 0	24.35	
3.63	17	-1 3 2	24.52	
3.62	9	-1 2 3	24.60	
3.61	1	0 2 3	24.65	
3.36	2	1 1 3	26.50	
3.33	12	2 2 1	26.78	
3.25	3	1 3 2	27.39	
3.22	2	1 4 0	27.72	
3.19	4	-1 4 1	27.96	
3.17	7	0 0 4	28.13	
3.17	20	-1 1 4	28.17	
3.15	9	2 3 0	28.33	
3.12	9	2 1 2	28.58	
3.12	15	0 3 3	28.60	
3.11	3	-2 2 3	28.66	
3.05	2	1 4 1	29.27	
2.943	5	-1 2 4	30.34	
2.908	2	2 2 2	30.72	
2.899	5	-3 0 2	30.82	
2.894	5	-3 1 1	30.87	
2.865	4	3 0 0	31.19	
2.863	4	-2 1 4	31.21	
2.781	2	-2 3 3	32.16	
2.772	3	1 3 3	32.27	
2.728	4	-2 4 1	32.80	
2.722	3	-3 2 1	32.88	
2.709	2	0 5 1	33.04	
2.696	2	-2 2 4	33.20	
2.683	4	-1 4 3	33.37	
2.639	2	1 5 0	33.94	
2.637	1	-2 4 2	33.97	
2.625	8	-1 5 1	34.13	
2.614	1	0 3 4	34.28	
2.608	3	3 1 1	34.36	
2.541	1	0 5 2	35.30	
2.511	1	2 2 3	35.73	
2.494	1	0 1 5	35.97	
2.492	3	-3 3 1	36.01	

Phencyclidine Hydrochloride, C₁₇H₂₆ClN - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.457	2	-2 4 3	36.54
2.454	1	-3 0 4	36.58
2.449	1	-1 2 5	36.67
2.368	1	1 3 4	37.96
2.360	1	3 1 2	38.10
2.337	1	-3 3 3	38.49
2.330	1	2 5 0	38.60
2.329	3	-2 2 5	38.63
2.321	1	-1 5 3	38.77
2.277	2	-1 3 5	39.54
2.260	1	2 1 4	39.85
2.251	5	1 1 5	40.02
2.223	3	-1 6 1	40.55
2.185	1	-4 1 1	41.29
2.180	2	-2 3 5	41.38
2.167	1	1 2 5	41.64
2.165	1	1 5 3	41.69
2.150	1	-1 6 2	42.00
2.149	2	4 0 0	42.01
2.127	5	2 4 3	42.46
2.124	2	4 1 0	42.53
2.121	1	-4 1 3	42.60
2.113	1	0 0 6	42.76
2.108	2	-4 2 1	42.87
2.053	4	4 2 0	44.08
2.053	1	2 3 4	44.08
2.032	1	-4 0 4	44.56
2.026	2	-2 2 6	44.69
2.024	1	-3 5 1	44.75
2.021	1	0 2 6	44.80
2.015	4	4 1 1	44.96
2.013	2	-2 5 4	45.00
1.996	1	-4 3 1	45.41
1.995	1	-4 3 2	45.43
1.980	3	-3 3 5	45.78
1.949	1	4 3 0	46.57
1.942	1	1 0 6	46.74
1.932	1	2 5 3	46.98
1.930	4	1 7 0	47.04
1.925	1	-1 7 1	47.19
1.893	1	1 7 1	48.03
1.891	1	0 7 2	48.08
1.870	1	1 2 6	48.65
1.867	1	0 6 4	48.72
1.818	1	3 4 3	50.13
1.805	1	-1 2 7	50.52
1.750	1	-4 3 5	52.24
1.701	1	-5 0 4	53.86
1.700	1	-5 2 3	53.88
1.688	1	-5 1 4	54.29

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
1.672	1	0 8 2	54.87
1.662	1	-1 8 2	55.22
1.646	1	-1 4 7	55.82
1.622	1	-1 1 8	56.70
1.586	1	1 3 7	58.10

Phenobarbital, form III, $C_{12}H_{12}N_2O_3$

Synonyms

1. 5-Ethyl-5-phenylbarbituric acid
2. Phenobarbitone
3. Luminal
4. Phenemal
5. Phenylethylmalonylurea

CAS registry no.

50-06-6

Structure

Monoclinic, $P2_1/c$ (14), $Z = 4$. The structure was determined by Williams [1974].

Atom positions

All atoms are in general positions 4(e) [ibid.].

Polymorphism

There may be as many as 12 anhydrous forms of phenobarbital, as well as the monohydrate and perhaps other hydrates [ibid.].

Lattice constants

$a = 9.535(2) \text{ \AA}$
 $b = 11.856(3)$
 $c = 10.795(3)$
 $\beta = 111.56(1)^\circ$

(published values: $a = 9.534(2) \text{ \AA}$,
 $b = 11.855(3)$, $c = 10.794(3)$, $\beta = 111.56(1)^\circ$
[Williams, 1974])

CD cell: $a = 10.795(3) \text{ \AA}$, $b = 11.856(3)$,
 $c = 9.535(2)$, $\beta = 111.56(1)^\circ$; sp. gp. $P2_1/a$;
 $a/b = 0.9105$; $c/b = 0.8042$

Volume

1135.0 $\text{\AA}^3$

Density

(calculated) 1.359 g/cm^3

Thermal parameters

Isotropic for hydrogen atoms [Williams, 1974].

Isotropic B_i for other atoms, estimated from
 U_{ij} for each atom.

Scattering factors

C^0 , H^0 , N^0 , O^0 [International Tables, 1962]

Scale factors (integrated intensities)

$\gamma = 1.581 \times 10^{-3}$

I/I_{corundum} (calculated) 0.610 for reflection
with $hkl = 202$

Additional pattern

1. PDF card 5-0324 [Huang, 1951]

References

- Huang, T.-Y. (1951). Acta Pharm. Int. 2, 43.
International Tables for X-ray Crystallography,
III (1962). (The Kynoch Press, Birmingham,
Eng.) p. 202.
Williams, P. P. (1974). Acta Crystallogr.
B30, 12.

Calculated Pattern (Peak heights)				
$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$	$\lambda - 1.540598 \text{\AA}$
8.86	30	1 0 0	9.98	
7.66	10	0 1 1	11.54	
7.10	40	1 1 0	12.46	
6.82	51	-1 1 1	12.98	
5.93	2	0 2 0	14.94	
5.273	40	-1 0 2	16.80	
5.104	86	0 2 1	17.36	
5.018	44	0 0 2	17.66	
4.924	14	1 2 0	18.00	
4.828	8	-1 2 1+	18.36	
4.619	3	0 1 2	19.20	
4.410	15	-2 1 1	20.12	
4.168	100	-2 0 2	21.30	
4.103	48	1 2 1	21.64	
3.808	15	1 0 2	23.34	
3.708	14	-2 2 1	23.98	
3.625	3	1 1 2	24.54	
3.551	10	2 2 0	25.06	
3.440	17	2 1 1	25.88	
3.245	3	1 3 1	27.46	
3.198	27	-2 1 3	27.88	
3.164	3	-1 3 2	28.18	
3.104	40	0 3 2	28.74	
3.040	2	-2 3 1	29.36	
2.949	26	2 3 0	30.28	
2.914	5	0 2 3	30.66	
2.841	2	0 4 1	31.46	
2.793	2	-3 2 1+	32.02	
2.733	5	1 1 3	32.74	
2.706	14	-3 1 3	33.08	
2.629	4	1 4 1	34.08	
2.552	3	0 4 2+	35.14	
2.516	4	-3 2 3	35.66	
2.510	5	0 0 4	35.74	
2.465	8	2 4 0+	36.42	
2.435	4	-3 3 2	36.88	
2.396	6	-3 0 4	37.50	
2.372	3	3 2 1	37.90	
2.368	2	3 3 0	37.96	
2.339	5	1 4 2	38.46	
2.334	4	-4 1 2	38.54	
2.308	1	2 3 2+	39.00	
2.287	7	-1 4 3+	39.36	
2.254	2	2 1 3	39.96	
2.232	3	-4 1 3	40.38	
2.218	1	0 4 3+	40.64	
2.212	2	1 0 4+	40.76	
2.194	2	-2 3 4	41.10	
2.189	2	1 5 1+	41.20	
2.174	2	1 1 4+	41.50	

Phenobarbital, form III, C₁₂H₁₂N₂O₃ - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.101	2	-1 1 5	43.02
2.084	1	-4 0 4	43.38
2.076	1	3 2 2+	43.56
2.061	1	-2 5 2	43.90
2.053	2	-4 1 4	44.08
2.036	2	-4 3 2	44.46
2.009	1	-1 2 5	45.10
1.980	4	2 5 1+	45.80
1.975	3	0 6 0+	45.90
1.967	3	-4 2 4	46.12
1.933	5	3 3 2+	46.98
1.898	1	-3 5 1	47.88
1.878	1	-1 3 5+	48.44
1.873	2	3 1 3	48.58
1.855	2	-5 1 3	49.06
1.846	4	-4 1 5	49.34
1.841	3	0 6 2	49.46
1.813	1	2 4 3+	50.30
1.804	1	2 6 0	50.54
1.798	2	1 1 5+	50.72
1.773	1	5 0 0+	51.50
1.754	1	1 6 2+	52.10
1.732	1	2 6 1+	52.82
1.715	1	-5 2 4+	53.38
1.685	1	-3 4 5	54.42
1.671	1	-4 5 1+	54.90
1.651	2	-5 1 5+	55.62
1.639	1	3 0 4	56.06
1.592	1	-2 5 5+	57.86
1.582	1	2 7 0+	58.28

Calculated Pattern (Integrated)			
d(Å)	I	hkl	2θ(°) λ - 1.540598Å
8.87	28	1 0 0	9.97
7.66	9	0 1 1	11.54
7.10	36	1 1 0	12.45
6.82	47	-1 1 1	12.97
5.93	2	0 2 0	14.93
5.278	38	-1 0 2	16.78
5.129	13	1 1 1	17.27
5.105	76	0 2 1	17.36
5.020	39	0 0 2	17.65
4.928	11	1 2 0	17.98
4.831	5	-1 2 1	18.35
4.822	2	-1 1 2	18.38
4.623	2	0 1 2	19.18
4.434	1	2 0 0	20.01
4.411	14	-2 1 1	20.11

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
4.169	100	-2 0 2	21.29
4.105	45	1 2 1	21.63
3.809	15	1 0 2	23.33
3.708	15	-2 2 1	23.98
3.627	3	1 1 2	24.53
3.551	10	2 2 0	25.06
3.443	3	-1 1 3	25.86
3.442	15	2 1 1	25.86
3.246	3	1 3 1	27.46
3.205	5	1 2 2	27.82
3.199	25	-2 1 3	27.87
3.164	1	-1 3 2	28.19
3.105	41	0 3 2	28.73
3.092	9	-3 0 2	28.85
3.076	1	-1 2 3	29.01
3.075	5	2 2 1	29.01
3.039	1	-2 3 1	29.37
2.956	3	3 0 0	30.21
2.950	26	2 3 0	30.27
2.914	4	0 2 3	30.65
2.843	2	0 4 1	31.44
2.794	2	-3 2 1	32.00
2.741	1	-3 2 2	32.64
2.733	5	1 1 3	32.74
2.706	15	-3 1 3	33.08
2.639	1	-2 0 4	33.94
2.629	4	1 4 1	34.08
2.554	1	0 3 3	35.11
2.552	2	0 4 2	35.13
2.517	4	-3 2 3	35.65
2.510	3	0 0 4	35.75
2.472	4	-3 3 1	36.31
2.464	7	2 4 0	36.43
2.435	4	-3 3 2	36.88
2.396	6	-3 0 4	37.50
2.373	2	3 2 1	37.88
2.367	1	3 3 0	37.98
2.339	5	1 4 2	38.45
2.330	2	-4 1 2	38.61
2.288	5	-1 4 3	39.35
2.287	3	2 4 1	39.36
2.254	2	2 1 3	39.96
2.232	3	-4 1 3	40.39
2.219	1	0 4 3	40.63
2.211	1	1 0 4	40.77
2.195	2	-2 3 4	41.09
2.189	1	1 5 1	41.21
2.178	1	3 1 2	41.42
2.174	1	1 1 4	41.50
2.101	2	-1 1 5	43.02

Phenobarbital, form III, $C_{12}H_{12}N_2O_3$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.085	1	-4 0 4	43.37
2.061	1	-2 5 2	43.89
2.053	2	-4 1 4	44.07
2.036	2	-4 3 2	44.45
2.008	1	-1 2 5	45.11
1.980	3	2 5 1	45.80
1.976	1	0 6 0	45.89
1.971	1	-2 4 4	46.01
1.967	2	-4 2 4	46.12
1.933	4	3 3 2	46.97
1.930	1	1 3 4	47.05
1.898	1	-3 5 1	47.88
1.878	1	-1 3 5	48.43
1.873	2	3 1 3	48.58
1.855	2	-5 1 3	49.06
1.846	4	-4 1 5	49.33
1.839	1	0 6 2	49.54
1.805	1	2 6 0	50.53
1.799	2	1 1 5	50.72
1.732	1	2 6 1	52.82
1.684	1	-3 4 5	54.43
1.671	1	-4 5 1	54.91
1.651	2	-5 1 5	55.61
1.649	1	2 5 3	55.68

Potassium Barium Iron Titanium Oxide, $K_{1.16}Ba_{0.72}Fe_{0.36}Ti_{5.58}O_{13}$

Structure

Monoclinic, C2/m (12), $Z = 2$. The structure was refined using data from a natural mineral found in the Kimberley Division of Western Australia [Bagshaw et al., 1977]. Electron microprobe analysis gave the composition listed [ibid.].

Atom positions

Bagshaw et al. [1977]

- 2(a) 2 oxygen
4(i) 4 oxygen in each of 6 different sites
4(i) 3.72 titanium and 0.24 iron in each of 3 different sites
4(i) 2.32 potassium and 1.44 barium

Lattice constants

$a = 15.454(2) \text{ \AA}$
 $b = 3.8370(7)$
 $c = 9.124(2)$
 $\beta = 99.25(1)^\circ$

$a/b = 4.0276$
 $c/b = 2.3779$

(published values: $a = 15.453(2) \text{ \AA}$,
 $b = 3.8368(7)$, $c = 9.123(2)$, $\beta = 99.25(1)^\circ$
[Bagshaw et al., 1977].

Volume $\text{\AA}^3$
533.99

Density g/cm^3
3.978

Thermal parameters

Isotropic B_i estimated from U_{ij} for individual atoms

Scattering factors

K^+ , Ba^{2+} , Fe^0 , Ti^0 , O^0 [Cromer and Mann, 1968].
K, Ba, Fe and Ti factors were corrected for dispersion [Cromer, 1965].

Scale factors (integrated intensities)

$\gamma = 0.1046 \times 10^{-3}$
 I/I_{corundum} (calculated) = 1.06 for reflection with $hkl = 310$.

References

Bagshaw, A. N., Doran, B. H., White, A. H., and Willis, A. C. (1977). Aust. J. Chem. 30, 1195.
Cromer, D. T. (1965). Acta Crystallogr. 18, 17.
Cromer, D. T. and Mann, J. B. (1968). Acta Crystallogr. A24, 321.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^\circ)$ $\lambda = 1.540598 \text{\AA}$
9.000	7	0 0 1	9.82
7.622	54	2 0 0	11.60
6.339	41	-2 0 1	13.96
5.401	10	2 0 1	16.40
4.498	33	0 0 2	19.72
4.180	1	-2 0 2	21.24
3.811	1	4 0 0	23.32
3.729	23	-4 0 1+	23.84
3.630	7	2 0 2	24.50
3.324	5	4 0 1	26.80
3.171	14	-4 0 2	28.12
3.062	96	3 1 0	29.14
2.988	100	-3 1 1	29.88
2.959	68	-2 0 3	30.18
2.925	30	-1 1 2	30.54
2.815	82	1 1 2+	31.76
2.703	44	4 0 2	33.12
2.653	26	-3 1 2+	33.76
2.556	30	-6 0 1	35.08
2.425	2	3 1 2	37.04
2.383	11	-1 1 3+	37.72
2.349	4	6 0 1	38.28
2.251	5	0 0 4+	40.02
2.239	10	5 1 1	40.24
2.115	4	-6 0 3	42.72
2.092	52	-4 0 4	43.22
2.075	47	6 0 2	43.58
2.047	14	3 1 3	44.22
1.9952	11	-5 1 3	45.42
1.9602	7	-1 1 4	46.28
1.9187	59	0 2 0	47.34
1.8939	11	1 1 4+	48.00
1.8604	2	2 2 0	48.92
1.8378	5	-6 0 4+	49.56
1.8145	2	4 0 4	50.24
1.8038	14	7 1 1+	50.56
1.7641	7	0 2 2+	51.78
1.7515	9	-5 1 4	52.18
1.7138	7	-7 1 3	53.42
1.7067	4	-4 2 1	53.66
1.6961	2	2 2 2	54.02
1.6927	1	2 0 5	54.14
1.6649	8	7 1 2	55.12
1.6615	6	4 2 1+	55.24
1.6419	3	-4 2 2	55.96
1.6227	4	-3 1 5	56.68
1.6164	4	0 2 3	56.92
1.6097	14	-2 2 3	57.18
1.5964	5	1 1 5+	57.70
1.5859	4	-8 0 4	58.12

Potassium Barium Iron Titanium Oxide, $K_{1.16}Ba_{0.72}Fe_{0.36}Ti_{5.58}O_{13}$ - (continued)

d(Å)	I	hkl	2θ(°)
λ - 1.540598Å			
1.5643	16	4 2 2	59.00
1.5609	18	-7 1 4	59.14
1.5547	6	2 2 3	59.40
1.5505	7	9 1 0	59.58
1.5346	20	-6 2 1+	60.26
1.5254	5	10 0 0	60.66
1.5209	14	-10 0 2	60.86
1.5097	5	7 1 3	61.36
1.5009	10	0 0 6	61.76

Calculated Pattern (Integrated)			
d(Å)	I	hkl	2θ(°)
λ - 1.540598Å			
9.005	6	0 0 1	9.81
7.627	48	2 0 0	11.59
6.345	38	-2 0 1	13.95
5.407	9	2 0 1	16.38
4.503	33	0 0 2	19.70
4.183	1	-2 0 2	21.22
3.813	1	4 0 0	23.31
3.734	20	-4 0 1	23.81
3.721	8	1 1 0	23.89
3.630	7	2 0 2	24.50
3.325	5	4 0 1	26.79
3.172	14	-4 0 2	28.11
3.063	100	3 1 0	29.13
3.002	9	0 0 3	29.74
2.989	100	-3 1 1	29.87
2.960	66	-2 0 3	30.17
2.925	28	-1 1 2	30.54
2.818	44	3 1 1	31.73
2.815	48	1 1 2	31.77
2.704	48	4 0 2	33.11
2.655	18	-3 1 2	33.73
2.652	11	2 0 3	33.77
2.556	33	-6 0 1	35.07
2.426	2	3 1 2	37.03
2.384	4	-5 1 1	37.71
2.382	8	-1 1 3	37.73
2.350	4	6 0 1	38.27
2.260	1	-2 0 4	39.85
2.256	1	-3 1 3	39.93
2.251	4	0 0 4	40.02
2.239	10	5 1 1	40.24
2.115	3	-6 0 3	42.72
2.091	58	-4 0 4	43.22
2.075	52	6 0 2	43.57
2.047	16	3 1 3	44.21

d(Å)	I	hkl	2θ(°)
λ - 1.540598Å			
1.9950	13	-5 1 3	45.43
1.9606	7	-1 1 4	46.27
1.9292	1	-8 0 1	47.07
1.9185	69	0 2 0	47.35
1.9087	4	-7 1 1	47.60
1.9041	1	-3 1 4	47.73
1.8948	3	7 1 0	47.97
1.8936	9	1 1 4	48.01
1.8605	1	2 2 0	48.92
1.8385	4	-6 0 4	49.54
1.8364	2	-2 2 1	49.60
1.8151	1	4 0 4	50.22
1.8081	1	2 2 1	50.43
1.8073	8	8 0 1	50.45
1.8041	10	7 1 1	50.55
1.8023	2	6 0 3	50.60
1.7650	4	0 2 2	51.75
1.7637	4	5 1 3	51.79
1.7518	10	-5 1 4	52.17
1.7141	8	-7 1 3	53.41
1.7064	4	-4 2 1	53.67
1.6962	1	2 2 2	54.02
1.6930	1	2 0 5	54.13
1.6652	10	7 1 2	55.11
1.6617	1	4 2 1	55.23
1.6416	3	-4 2 2	55.97
1.6227	4	-3 1 5	56.68
1.6165	3	0 2 3	56.92
1.6099	17	-2 2 3	57.17
1.5968	5	1 1 5	57.69
1.5956	1	-6 0 5	57.73
1.5861	4	-8 0 4	58.11
1.5668	5	-9 1 1	58.90
1.5652	1	6 0 4	58.96
1.5646	14	4 2 2	58.99
1.5612	12	-7 1 4	59.13
1.5544	4	2 2 3	59.42
1.5503	5	9 1 0	59.59
1.5371	7	-9 1 2	60.15
1.5360	12	4 0 5	60.20
1.5344	13	-6 2 1	60.27
1.5337	2	-5 1 5	60.30
1.5253	3	10 0 0	60.66
1.5209	13	-10 0 2	60.86
1.5197	2	-2 0 6	60.91
1.5099	5	7 1 3	61.35
1.5009	12	0 0 6	61.76

Procaine Hydrochloride, $C_{13}H_{21}ClN_2O_2$

Synonyms

1. Novocaine hydrochloride
2. p-Aminobenzoylethylaminoethanol hydrochloride
3. 2-Diethylaminoethyl p-aminobenzoate hydrochloride

CAS registry no.

51-05-8

Structure

Orthorhombic, $Pcab$ (61), $Z = 8$. The structure was studied by Beall, Herdtklotz and Sass [1970]. The parameters used here are from the refinement by Dexter [1972].

Atom positions

All atoms were in the general positions 8(c) [Dexter, 1972].

Lattice constants

$a = 25.019(1) \text{ \AA}$
 $b = 8.3060(5)$
 $c = 14.193(1)$

(published values: $a = 25.017(1) \text{ \AA}$,
 $b = 8.3050(5)$, $c = 14.192(1)$ [Dexter, 1972])

CD cell: $a = 14.193(1) \text{ \AA}$, $b = 25.019(1)$,
 $c = 8.3060(5)$; sp. gp. $Pcab$; $a/b = 0.5673$;
 $c/b = 0.3320$

Volume

$2949.4 \text{ \AA}^3$

Density

(calculated) 1.229 g/cm^3

Thermal parameters

Isotropic: hydrogen atoms, overall $B = 4.0$ [Dexter, 1972].

Isotropic B_i for other atoms, estimated from U_{ij} for each atom.

Scattering factors

C^0 , H^0 , N^0 , O^0 , Cl^- [International Tables, 1962]

Scale factors (integrated intensities)

$\gamma = 0.5173 \times 10^{-3}$

I/I_{corundum} (calculated) = 0.601, for reflection with $hkl = 113$.

Additional patterns

1. PDF card 27-1975 [Wang, P. Polytechnic Inst. of New York, 1975]
2. Folen [1975]

References

Beall, E., Herdtklotz, J., and Sass, R. L. (1970). Biochem. Biophys. Res. Commun. 39, 329.

Dexter, D. D. (1972). Acta Crystallogr. B28, 77.
 Folen, V. A. (1975). J. Forensic Sci. 20, 348.
 International Tables for X-ray Crystallography, III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.

Calculated Pattern (Peak heights)				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598\text{\AA}$
12.51	7	2 0 0	7.06	
7.09	6	0 0 2	12.48	
6.89	35	1 1 1	12.84	
6.22	37	2 1 1+	14.22	
5.434	79	3 1 1	16.30	
5.401	66	0 1 2	16.40	
4.951	4	2 1 2	17.90	
4.692	7	4 0 2	18.90	
4.423	16	2 0 3	20.06	
4.153	59	0 2 0	21.38	
4.100	33	5 1 1	21.66	
4.055	100	1 1 3	21.90	
3.9039	28	2 1 3	22.76	
3.7954	2	2 2 1	23.42	
3.7171	18	3 2 0	23.92	
3.6688	16	5 1 2	24.24	
3.6015	9	6 1 1	24.70	
3.5478	24	0 0 4	25.08	
3.4347	6	4 1 3	25.92	
3.4140	4	2 0 4	26.08	
3.3608	3	4 2 1	26.50	
3.2925	4	6 1 2+	27.06	
3.2618	15	0 1 4	27.32	
3.2362	8	1 1 4	27.54	
3.1975	17	7 1 1	27.88	
3.1752	31	5 1 3	28.08	
3.1272	15	6 0 3+	28.52	
3.0953	22	1 2 3	28.82	
3.0275	3	2 2 3	29.48	
2.9781	2	7 1 2	29.98	
2.9229	9	3 2 3+	30.56	
2.8662	5	8 1 1	31.18	
2.7929	2	4 2 3	32.02	
2.7677	1	2 0 5	32.32	
2.7170	3	6 2 2	32.94	
2.6979	12	0 2 4+	33.18	
2.6483	10	5 2 3	33.82	
2.6079	3	8 0 3	34.36	
2.5788	15	0 3 2+	34.76	
2.5253	6	2 3 2	35.52	
2.4927	6	4 3 1+	36.00	
2.4702	3	9 1 2	36.34	
2.4650	3	10 0 1	36.42	
2.3781	2	1 3 3	37.80	
2.3612	4	5 1 5+	38.08	

Procaine Hydrochloride, $C_{13}H_{21}ClN_2O_2$ - (continued)

d(Å)	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.3470	6	2 3 3+	38.32
2.3019	2	9 1 3+	39.10
2.2929	3	5 3 2	39.26
2.2762	5	6 3 1+	39.56
2.2652	5	1 1 6+	39.76
2.2587	5	6 1 5	39.88
2.2109	1	10 0 3	40.78
2.1934	2	6 3 2+	41.12
2.1822	3	0 3 4	41.34
2.1436	2	7 1 5+	42.12
2.0907	1	7 3 2	43.24
2.0851	2	12 0 0	43.36
2.0769	2	0 4 0	43.54
2.0439	4	10 0 4+	44.28
2.0283	1	2 2 6+	44.64
1.9952	3	11 2 0+	45.42
1.9903	3	11 1 3+	45.54
1.9594	2	7 2 5	46.30
1.9318	1	9 1 5+	47.00
1.9179	1	5 4 0+	47.36
1.8991	2	8 3 3+	47.86
1.8582	1	13 1 1+	48.98
1.8540	1	3 4 3	49.10
1.8385	2	10 3 1+	49.54
1.8344	2	5 1 7+	49.66
1.8166	1	1 2 7	50.18
1.8125	2	13 1 2	50.30
1.7978	3	0 3 6+	50.74
1.7899	4	6 3 5+	50.98
1.7814	3	7 4 1+	51.24
1.7776	2	5 4 3+	51.36
1.7566	1	2 0 8+	52.02
1.7429	2	13 1 3+	52.46
1.7300	2	1 1 8+	52.88
1.7120	2	5 2 7+	53.48
1.7073	2	4 0 8	53.64
1.6392	2	5 1 8+	56.06
1.6280	1	1 2 8	56.48
1.6222	2	2 3 7+	56.70
1.6180	1	3 5 1+	56.86
1.6040	1	2 5 2+	57.40
1.5667	2	5 5 1+	58.90
1.5600	1	0 4 6+	59.18
1.5547	1	10 3 5+	59.40

Calculated Pattern (Integrated)			
d(Å)	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
12.51	7	2 0 0	7.06
7.10	5	0 0 2	12.46
6.89	33	1 1 1	12.84
6.25	22	4 0 0	14.15
6.22	23	2 1 1	14.23
6.17	5	2 0 2	14.34
5.436	67	3 1 1	16.29
5.395	48	0 1 2	16.42
4.954	4	2 1 2	17.89
4.713	1	4 1 1	18.81
4.692	7	4 0 2	18.90
4.425	15	2 0 3	20.05
4.153	58	0 2 0	21.38
4.103	21	5 1 1	21.64
4.097	2	1 2 0	21.67
4.085	1	4 1 2	21.74
4.057	100	1 1 3	21.89
4.001	4	6 0 1	22.20
3.9415	1	2 2 0	22.54
3.9362	1	1 2 1	22.57
3.9054	28	2 1 3	22.75
3.7977	1	2 2 1	23.41
3.7176	17	3 2 0	23.92
3.6873	9	3 1 3	24.12
3.6689	13	5 1 2	24.24
3.6044	8	6 1 1	24.68
3.5843	2	0 2 2	24.82
3.5482	25	0 0 4	25.08
3.4353	5	4 1 3	25.91
3.4136	3	2 0 4	26.08
3.3614	3	4 2 1	26.50
3.2993	2	6 1 2	27.00
3.2931	1	3 2 2	27.06
3.2630	15	0 1 4	27.31
3.2356	7	1 1 4	27.55
3.1986	14	7 1 1	27.87
3.1764	31	5 1 3	28.07
3.1573	2	2 1 4	28.24
3.1282	8	6 0 3	28.51
3.1274	6	8 0 0	28.52
3.1177	1	5 2 1	28.61
3.0971	22	1 2 3	28.80
3.0862	2	4 0 4	28.91
3.0282	2	2 2 3	29.47
2.9797	2	7 1 2	29.96
2.9425	1	6 2 0	30.35
2.9231	9	3 2 3	30.56
2.9139	3	5 2 2	30.66
2.8665	5	8 1 1	31.18
2.7927	2	4 2 3	32.02

Procaine Hydrochloride, $C_{13}H_{21}ClN_2O_2$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.7682	1	2 0 5	32.31
2.7181	2	6 2 2	32.93
2.7016	1	1 3 1	33.13
2.6977	9	0 2 4	33.18
2.6973	3	7 1 3	33.19
2.6822	4	1 2 4	33.38
2.6610	4	7 2 1	33.65
2.6482	10	5 2 3	33.82
2.6371	1	2 2 4	33.97
2.6089	2	8 0 3	34.35
2.5849	5	4 0 5	34.68
2.5793	13	0 3 2	34.75
2.5668	4	3 2 4	34.93
2.5567	3	3 1 5	35.07
2.5309	1	7 2 2	35.44
2.5262	5	2 3 2	35.51
2.5019	4	10 0 0	35.86
2.4987	1	6 2 3	35.91
2.4924	4	4 3 1	36.01
2.4712	2	9 1 2	36.33
2.4639	1	10 0 1	36.44
2.3880	1	5 3 1	37.64
2.3787	2	1 3 3	37.79
2.3666	2	5 1 5	37.99
2.3622	2	10 1 1	38.06
2.3471	4	2 3 3	38.32
2.3465	2	6 0 5	38.33
2.3028	1	9 1 3	39.08
2.2926	2	5 3 2	39.27
2.2801	1	9 2 1	39.49
2.2767	4	6 3 1	39.55
2.2750	1	0 1 6	39.58
2.2657	3	1 1 6	39.75
2.2650	1	6 2 4	39.76
2.2581	3	6 1 5	39.89
2.2117	1	10 0 3	40.77
2.1936	1	6 3 2	41.12
2.1828	3	0 3 4	41.33
2.1473	1	7 1 5	42.04
2.1431	1	10 2 0	42.13
2.0916	1	7 3 2	43.22
2.0849	1	12 0 0	43.36
2.0765	2	0 4 0	43.55
2.0486	1	1 2 6	44.17
2.0447	3	10 0 4	44.26
2.0430	1	6 2 5	44.30
1.9971	1	6 1 6	45.37
1.9949	2	11 2 0	45.43
1.9902	2	11 1 3	45.54
1.9598	2	7 2 5	46.29

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.9317	1	9 1 5	47.00
1.9179	1	5 4 0	47.36
1.8987	2	8 3 3	47.87
1.8587	1	13 1 1	48.97
1.8538	1	3 4 3	49.10
1.8430	1	6 4 1	49.41
1.8406	1	10 3 1	49.48
1.8381	1	11 2 3	49.55
1.8172	1	1 2 7	50.16
1.8127	2	13 1 2	50.30
1.7985	2	0 3 6	50.72
1.7901	3	6 3 5	50.98
1.7876	1	1 4 4	51.05
1.7813	1	7 4 1	51.25
1.7774	1	5 4 3	51.36
1.7462	1	13 2 0	52.35
1.7430	2	13 1 3	52.46
1.7308	1	1 1 8	52.85
1.7121	2	5 2 7	53.48
1.7068	1	4 0 8	53.66
1.6392	1	5 1 8	56.06
1.6323	1	1 3 7	56.32
1.6280	1	1 2 8	56.48
1.6220	1	2 3 7	56.71
1.6041	1	2 5 2	57.40
1.5670	1	5 5 1	58.89
1.5667	1	13 2 4	58.90

Psilocin, C₁₂H₁₆N₂O

Synonyms

1. 3-(2-(Dimethylamino)ethyl)-indol-4-ol
2. 4-Hydroxy-N,N-dimethyltryptamine

CAS registry no.
520-53-6

Structure

Monoclinic, P₂₁/c (14), Z = 4. The structure was determined by Petcher and Weber [1974].

Atom positions

All the atoms were in general positions 4(e). For H(7), the value 0.273 was used for "z" as given in the Supplementary Publ. #SUP20980, referred to by Petcher and Weber [1974]. Bond length calculations indicated that the value of 0.014 for "z" for H(12) should be used.

Lattice constants

a = 10.60(3) Å
b = 8.53(2)
c = 12.51(3)
β = 91.25(30)°
[Petcher and Weber, 1974]

CD cell: a = 12.51(3) Å, b = 8.53(2),
c = 10.60(3), β = 91.25(30)°; sp. gp. P₂₁/a;
a/b = 1.4665, c/b = 1.2426

Volume
1131. Å³

Density

(calculated) 1.200 g/cm³
(measured) 1.19 [Petcher and Weber, 1974]

Thermal parameters

Isotropic B_i estimated from β_{ij} for individual atoms.

Scattering factors

Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)

γ = 3.259 × 10⁻³
I/I_{corundum} (calculated) = 1.06 for reflection with hkℓ = 112.

Additional pattern

1. PDF card 13-981 [Physical Data of Indole and Dihydroindole Alkaloids, edited by Neuss, Eli Lilly and Co., 1962]

References

International Tables for X-ray Crystallography, III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.
Petcher, T. J. and Weber, H. P. (1974). J. Chem. Soc. Perkin Trans. 2, 946.

Calculated Pattern (Peak heights)				
d(Å)	I	hkℓ	2θ(°)	λ - 1.540598 Å
10.59	51	1 0 0	8.34	
7.04	10	0 1 1	12.56	
6.64	6	1 1 0	13.32	
6.25	1	0 0 2	14.16	
5.89	5	-1 1 1	15.02	
5.83	9	1 1 1	15.18	
5.43	2	-1 0 2	16.30	
5.30	22	2 0 0	16.72	
5.04	12	0 1 2	17.58	
4.58	33	-1 1 2	19.36	
4.52	100	1 1 2	19.62	
4.26	22	0 2 0	20.82	
4.21	21	2 1 1	21.10	
4.08	4	-2 0 2	21.74	
4.00	3	2 0 2	22.22	
3.96	6	1 2 0	22.46	
3.76	47	1 2 1	23.64	
3.62	2	2 1 2	24.56	
3.51	2	1 1 3	25.36	
3.33	9	1 2 2	26.74	
3.26	1	3 1 0	27.32	
3.20	5	2 2 1	27.86	
3.09	1	-2 1 3	28.90	
3.05	2	3 0 2	29.30	
2.934	4	0 1 4	30.44	
2.917	6	2 2 2	30.62	
2.857	5	1 2 3	31.28	
2.773	5	0 3 1	32.26	
2.746	2	1 3 0	32.58	
2.648	1	3 2 1	33.82	
2.615	2	-2 2 3	34.26	
2.509	6	1 3 2+	35.76	
2.479	1	3 2 2	36.20	
2.461	2	-2 3 1+	36.48	
2.443	2	1 2 4	36.76	
2.367	1	-3 0 4	37.98	
2.317	1	2 3 2+	38.84	
2.281	1	-3 1 4	39.48	
2.261	2	2 2 4	39.84	
2.207	1	4 2 1	40.86	
2.138	1	2 3 3	42.24	
2.120	2	5 0 0	42.62	
2.079	1	3 3 2	43.50	
2.043	1	-4 0 4	44.30	
2.018	1	0 4 2	44.88	
1.995	2	-4 2 3+	45.42	
1.955	1	-2 0 6	46.42	
1.945	1	3 3 3	46.66	
1.796	1	3 3 4+	50.80	
1.669	1	-3 3 5+	54.96	
1.665	1	2 4 4	55.10	

Psilocin, C₁₂H₁₆N₂O - (continued)

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
10.60	47	1 0 0	8.34	
7.05	10	0 1 1	12.55	
6.64	5	1 1 0	13.31	
6.25	1	0 0 2	14.15	
5.90	4	-1 1 1	15.00	
5.84	8	1 1 1	15.17	
5.44	1	-1 0 2	16.29	
5.34	1	1 0 2	16.60	
5.30	21	2 0 0	16.72	
5.04	12	0 1 2	17.57	
4.59	28	-1 1 2	19.34	
4.52	100	1 1 2	19.61	
4.50	1	2 1 0	19.71	
4.26	18	0 2 0	20.81	
4.26	3	-2 1 1	20.83	
4.21	20	2 1 1	21.08	
4.09	3	-2 0 2	21.73	
4.00	3	2 0 2	22.21	
3.96	6	1 2 0	22.45	
3.76	51	1 2 1	23.62	
3.75	1	0 1 3	23.74	
3.62	2	2 1 2	24.56	
3.51	2	1 1 3	25.35	
3.36	2	-1 2 2	26.54	
3.33	10	1 2 2	26.74	
3.26	1	3 1 0	27.30	
3.20	5	2 2 1	27.86	
3.09	1	-2 1 3	28.90	
3.05	2	3 0 2	29.28	
3.03	1	2 1 3	29.45	
2.936	4	0 1 4	30.42	
2.918	6	2 2 2	30.62	
2.858	6	1 2 3	31.27	
2.773	5	0 3 1	32.26	
2.746	2	1 3 0	32.58	
2.649	1	3 2 1	33.81	
2.616	2	-2 2 3	34.25	
2.510	1	-3 2 2	35.74	
2.509	6	1 3 2	35.76	
2.479	1	3 2 2	36.20	
2.462	2	-2 3 1	36.47	
2.444	2	1 2 4	36.75	
2.367	1	-3 0 4	37.98	
2.317	1	2 3 2	38.83	
2.281	1	-3 1 4	39.48	
2.262	3	2 2 4	39.83	
2.208	1	4 2 1	40.84	
2.138	1	2 3 3	42.24	
2.119	2	5 0 0	42.62	
2.079	1	3 3 2	43.50	

d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
2.043	1	-4 0 4	44.29	
1.996	1	-4 2 3	45.40	
1.994	1	5 0 2	45.45	
1.954	1	-2 0 6	46.42	
1.945	1	3 3 3	46.66	
1.796	1	3 3 4	50.80	
1.782	1	2 4 3	51.23	
1.666	1	2 4 4	55.09	

Psilocybin Methanolate, C₁₃H₂₁N₂O₄P

Synonyms

1. Indocybin
2. 3-[2-(Dimethylamino)ethyl]indol-4-ol dihydrogen phosphate methanolate

CAS registry no.
520-52-5

Structure

Monoclinic, P2₁/c (14), Z = 8. The structure was determined by Weber and Petcher [1974].

Atom positions

All atoms were in general positions 4(e).

Lattice constants

a = 12.64(1) Å
b = 29.11(2)
c = 8.848(6)
β = 107.37(2)°

a/b = 0.4342
c/b = 0.3040

(published values: a = 12.64(1) Å,
b = 29.11(2), c = 8.847(6), β = 107.37(2)°
[Weber and Petcher, 1974])

Volume
3107 Å³

Density

(calculated) 1.352 g/cm³
(measured) 1.34 [Weber and Petcher, 1974]

Thermal parameters

Isotropic, for hydrogens [Weber and Petcher, 1974]. For all other atoms, B_i were estimated for β_{ij} for individual atoms.

Scattering factors

Zero ionization [International Tables, 1962]

Scale factors (integrated intensities)

γ = 0.5540 × 10⁻³
I/I_{corundum} (calculated) = 0.455 for reflection
with hkl = 120.

Additional patterns

1. PDF card 13-982 [Physical Data of Indole and Dihydroindole Alkaloids edited by Neuss, Eli Lilly and Co., 1962]
2. Folen [1975]

References

Folen, V. A. (1975). J. Forensic Sci. 20, 348.
International Tables for X-ray Crystallography, III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.
Weber, H. P. and Petcher, T. J. (1974). J. Chem. Soc. Perkin Trans. 2, p. 942.

Calculated Pattern (Peak heights)

d(Å)	I	hkl	2θ(°) λ = 1.540598 Å
14.52	1	0 2 0	6.08
12.07	2	1 0 0	7.32
11.13	2	1 1 0	7.94
9.28	100	1 2 0	9.52
8.11	24	0 1 1	10.90
7.56	4	1 3 0	11.70
7.27	41	0 4 0+	12.16
7.11	74	-1 2 1	12.44
6.23	5	-1 3 1+	14.20
5.98	38	1 1 1	14.80
5.63	14	1 2 1	15.72
5.51	50	0 4 1	16.08
5.43	14	-1 4 1	16.32
5.24	16	1 5 0	16.90
5.17	15	1 3 1	17.14
4.97	8	-2 3 1	17.82
4.79	3	0 5 1	18.50
4.74	2	-1 5 1	18.72
4.68	3	1 4 1	18.96
4.64	2	2 4 0	19.10
4.50	49	1 6 0	19.72
4.367	30	-1 1 2	20.32
4.283	7	2 1 1	20.72
4.219	35	0 0 2+	21.04
4.172	42	-1 6 1+	21.28
4.096	17	-3 1 1	21.68
4.041	46	-2 1 2+	21.98
3.983	18	-3 2 1+	22.30
3.955	15	2 3 1	22.46
3.928	19	1 7 0+	22.62
3.870	16	0 3 2	22.96
3.779	32	2 6 0+	23.52
3.708	18	-1 7 1+	23.98
3.657	30	1 0 2	24.32
3.599	11	-3 4 1	24.72
3.556	50	-2 4 2	25.02
3.450	11	-3 1 2	25.80
3.424	10	2 7 0+	26.00
3.376	5	-2 7 1+	26.38
3.339	6	0 8 1+	26.68
3.309	4	3 5 0	26.92
3.266	37	1 4 2+	27.28
3.184	2	0 6 2	28.00
3.149	3	-3 6 1	28.32
3.125	4	1 8 1+	28.54
3.097	12	1 5 2	28.80
3.019	9	0 9 1+	29.56
3.000	8	4 1 0+	29.76
2.953	8	4 2 0	30.24
2.921	2	1 6 2+	30.58

Psilocybin Methanolate, C₁₃H₂₁N₂O₄P - (continued)

d(Å)	I	hkl	2θ(°)
λ - 1.540598Å			
2.895	6	-4 0 2	30.86
2.882	6	-4 1 2+	31.00
2.852	4	1 9 1+	31.34
2.819	4	2 4 2+	31.72
2.776	3	-4 3 2+	32.22
2.741	5	-1 10 1	32.64
2.698	3	-2 4 3+	33.18
2.667	2	-3 7 2	33.58
2.618	3	-3 3 3	34.22
2.611	3	-1 9 2	34.32
2.592	4	2 9 1+	34.58
2.564	4	4 2 1+	34.96
2.548	3	-3 9 1+	35.20
2.535	3	0 5 3+	35.38
2.513	4	-4 7 1+	35.70
2.490	2	1 3 3+	36.04
2.462	2	-3 5 3	36.46
2.445	3	-4 1 3+	36.72
2.434	5	0 6 3	36.90
2.413	3	5 0 0+	37.24
2.398	2	-5 2 2+	37.48
2.378	3	4 5 1+	37.80
2.372	3	-2 10 2+	37.90
2.341	2	5 3 0+	38.42
2.327	1	-4 4 3	38.66
2.319	2	-5 5 1	38.80
2.290	4	5 4 0+	39.32
2.270	2	-2 8 3+	39.68
2.202	2	1 13 0+	40.96
2.193	4	2 4 3+	41.12
2.189	4	1 7 3+	41.20
2.173	2	-5 6 2+	41.52
2.160	2	-5 7 1+	41.78
2.140	3	2 5 3+	42.20
2.126	1	-1 12 2+	42.48
2.118	1	4 8 1+	42.66
2.103	1	1 13 1+	42.98

Calculated Pattern (Integrated)			
d(Å)	I	hkl	2θ(°)
λ - 1.540598Å			
14.55	1	0 2 0	6.07
12.06	2	1 0 0	7.32
11.14	2	1 1 0	7.93
9.29	100	1 2 0	9.51
8.11	24	0 1 1	10.90

d(Å)	I	hkl	2θ(°)
λ - 1.540598Å			
7.56	3	1 3 0	11.69
7.30	10	0 2 1	12.11
7.28	31	0 4 0	12.15
7.11	74	-1 2 1	12.43
6.24	3	-1 3 1	14.17
6.23	2	1 4 0	14.20
6.03	1	2 0 0	14.67
5.98	39	1 1 1	14.79
5.68	5	-2 1 1	15.58
5.64	12	1 2 1	15.71
5.51	52	0 4 1	16.06
5.43	11	-1 4 1	16.31
5.24	16	1 5 0	16.90
5.17	15	1 3 1	17.13
5.12	1	2 3 0	17.30
4.97	8	-2 3 1	17.82
4.79	3	0 5 1	18.50
4.74	1	-1 5 1	18.71
4.68	2	1 4 1	18.94
4.64	1	2 4 0	19.10
4.53	12	-2 4 1	19.57
4.50	51	1 6 0	19.71
4.368	32	-1 1 2	20.32
4.287	5	2 1 1	20.70
4.227	11	-1 2 2	21.00
4.222	23	0 0 2	21.02
4.189	16	2 5 0	21.19
4.179	14	0 1 2	21.25
4.170	23	-1 6 1	21.29
4.154	3	2 2 1	21.37
4.107	3	-2 5 1	21.62
4.101	10	-3 1 1	21.65
4.078	8	-2 0 2	21.78
4.055	26	0 2 2	21.90
4.038	31	-2 1 2	21.99
4.021	16	3 0 0	22.09
4.021	4	-1 3 2	22.09
3.984	8	-3 2 1	22.30
3.983	5	3 1 0	22.30
3.957	10	2 3 1	22.45
3.932	11	1 7 0	22.60
3.927	7	-2 2 2	22.63
3.872	16	0 3 2	22.95
3.810	4	-3 3 1	23.33
3.800	9	1 6 1	23.39
3.780	24	2 6 0	23.51
3.776	9	-1 4 2	23.54
3.731	5	0 7 1	23.83
3.724	2	2 4 1	23.88
3.715	8	3 3 0	23.94
3.705	10	-1 7 1	24.00
3.659	33	1 0 2	24.31
3.631	2	1 1 2	24.50
3.600	8	-3 4 1	24.71
3.557	57	-2 4 2	25.01

Psilocybin Methanolate, C₁₃H₂₁N₂O₄P - (continued)

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
3.520	1	3 4 0	25.28
3.519	2	-1 5 2	25.29
3.476	1	-3 0 2	25.61
3.451	11	-3 1 2	25.79
3.438	2	1 7 1	25.89
3.424	3	1 3 2	26.00
3.424	5	2 7 0	26.00
3.418	1	0 5 2	26.05
3.381	1	-3 2 2	26.34
3.378	2	-2 7 1	26.36
3.375	2	-3 5 1	26.39
3.342	3	0 8 1	26.65
3.340	3	-2 5 2	26.67
3.323	2	-1 8 1	26.81
3.309	2	3 5 0	26.93
3.272	1	-3 3 2	27.23
3.269	32	1 4 2	27.26
3.266	10	-1 6 2	27.28
3.251	7	3 1 1	27.41
3.232	2	2 6 1	27.57
3.185	1	0 6 2	27.99
3.150	2	-3 6 1	28.31
3.127	3	1 8 1	28.52
3.098	13	1 5 2	28.79
3.083	3	-4 2 1	28.94
3.081	5	-2 8 1	28.95
3.028	4	-1 7 2	29.48
3.020	7	0 9 1	29.55
3.000	6	4 1 0	29.76
3.000	2	-4 3 1	29.76
2.963	1	0 7 2	30.14
2.953	9	4 2 0	30.24
2.897	5	-4 0 2	30.84
2.883	3	-4 1 2	31.00
2.880	2	4 3 0	31.03
2.859	2	1 9 1	31.26
2.852	2	3 5 1	31.34
2.848	1	-2 2 3	31.38
2.824	2	-2 9 1	31.66
2.818	2	2 4 2	31.72
2.783	1	-2 3 3	32.14
2.776	1	-4 3 2	32.22
2.742	5	-1 10 1	32.64
2.728	1	-1 4 3	32.80
2.698	2	-2 4 3	33.18
2.667	3	-3 7 2	33.58
2.628	1	1 10 1	34.09
2.618	2	-3 3 3	34.23
2.610	2	-1 9 2	34.34
2.599	1	-2 5 3	34.48

d(Å)	I	hkl	2θ(°) λ - 1.540598Å
2.592	3	2 9 1	34.57
2.566	2	1 1 3	34.94
2.564	3	4 2 1	34.97
2.549	1	-3 9 1	35.17
2.547	1	-3 4 3	35.21
2.537	1	1 2 3	35.35
2.534	1	0 5 3	35.39
2.516	1	-1 6 3	35.66
2.513	1	-3 8 2	35.69
2.513	2	-4 7 1	35.70
2.490	2	1 3 3	36.04
2.463	1	-3 5 3	36.45
2.447	2	-4 1 3	36.70
2.446	1	-5 3 1	36.71
2.435	5	0 6 3	36.89
2.426	1	0 12 0	37.03
2.423	1	1 9 2	37.07
2.413	1	5 0 0	37.24
2.411	1	3 4 2	37.26
2.388	1	-5 4 1	37.64
2.382	1	-3 10 1	37.74
2.377	2	4 5 1	37.81
2.369	1	-2 10 2	37.95
2.341	2	5 3 0	38.41
2.327	1	-4 4 3	38.67
2.319	1	-5 5 1	38.81
2.295	2	4 6 1	39.23
2.290	3	5 4 0	39.31
2.278	1	1 10 2	39.53
2.270	1	-2 8 3	39.67
2.266	1	-4 8 2	39.74
2.202	1	1 13 0	40.96
2.194	2	2 4 3	41.11
2.194	2	-1 0 4	41.11
2.190	1	1 7 3	41.19
2.184	1	-2 2 4	41.31
2.173	1	-5 6 2	41.52
2.160	1	-5 7 1	41.78
2.140	2	2 5 3	42.20
2.126	1	-1 12 2	42.48
2.103	1	1 13 1	42.98

Sodium Barbital, $C_8H_{11}N_2NaO_3$

Synonyms

1. Sodium 5,5-diethylbarbiturate
2. Soluble barbital
3. Barbitone sodium
4. Sodium malonylurea

CAS registry no.

144-02-5

Structure

Orthorhombic, $P2_12_12_1$ (19), $Z = 4$. The structure was determined by Berking and Craven [1971]. It is isostructural with potassium barbital [Berthou et al., 1962].

Atom positions

All atoms were in general positions 4(a) [ibid.].

Lattice constants

$a = 6.724(1) \text{ \AA}$
 $b = 11.951(2)$
 $c = 12.130(2)$

(published values: $a = 6.724(1) \text{ \AA}$,
 $b = 11.950(2)$, $c = 12.129(2)$ [Berking and Craven, 1971])

CD cell: $a = 11.951(2) \text{ \AA}$, $b = 12.130(2)$,
 $c = 6.724(1)$; sp. gp. $P2_12_12_1$; $a/b = 0.9852$,
 $c/b = 0.5543$

Volume

$974.75 \text{ \AA}^3$

Density

(calculated) 1.405 g/cm^3
(measured) 1.408 g/cm^3 [Berking and Craven, 1971]

Thermal parameters

Isotropic for hydrogen atoms, anisotropic for non-hydrogen atoms [Berking and Craven, 1971]

Scattering factors

C^0 , H^0 , Na^0 , N^0 , O^0 [International Tables, 1962]

Scale factors (integrated intensities)

$\gamma = 1.519 \times 10^{-3}$
 I/I_{corundum} (calculated) = 0.877 for reflection with $hkl = 011$

Additional pattern

1. PDF card 9-512 [Parkes, E. B., South-Western Forensic Science Lab., Westbury on Trym, Bristol 9, Eng.]

References

- Berking, B. and Craven, B. M. (1971). Acta Crystallogr. B27, 1107.
Berthou, J., Cavelier, C., Marek, D., Rérat, B., and Rérat, C. (1962). C. R. Acad. Sci. 255, 1632.

International Tables for X-ray Crystallography, III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.

Calculated Pattern (Peak heights)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda = 1.540598\text{\AA}$
8.50	100	0 1 1	10.40
6.06	26	0 0 2	14.60
5.97	17	0 2 0	14.82
5.85	65	1 1 0	15.12
5.36	53	0 2 1	16.54
5.28	8	1 1 1	16.78
4.503	6	1 0 2	19.70
4.255	51	0 2 2	20.86
4.211	30	1 1 2+	21.08
3.783	9	0 3 1	23.50
3.596	4	1 2 2	24.74
3.464	4	1 0 3	25.70
3.427	2	1 3 0	25.98
3.329	30	0 3 2+	26.76
3.236	4	2 1 0+	27.54
3.127	27	2 1 1	28.52
3.032	1	0 0 4	29.44
2.986	9	0 4 0+	29.90
2.930	3	2 2 0	30.48
2.901	3	0 4 1	30.80
2.838	16	0 3 3	31.50
2.764	1	1 0 4	32.36
2.693	3	1 1 4	33.24
2.664	6	1 4 1	33.62
2.638	4	2 2 2	33.96
2.614	8	1 3 3	34.28
2.509	5	1 2 4	35.76
2.490	2	1 4 2	36.04
2.403	7	0 4 3	37.40
2.3720	3	2 2 3+	37.90
2.3446	2	0 5 1	38.36
2.2707	5	1 3 4	39.66
2.2663	4	1 4 3	39.74
2.2522	2	1 5 0+	40.00
2.2415	4	1 1 5	40.20
2.2234	1	0 5 2	40.54
2.2140	3	1 5 1+	40.72
2.2026	7	3 1 0+	40.94
2.1672	4	3 1 1+	41.64
2.1074	2	2 2 4+	42.88
2.0679	5	3 2 1	43.74
2.0581	3	0 5 3	43.96
2.0291	5	1 4 4	44.62
1.9804	3	1 3 5	45.78
1.9602	1	2 3 4+	46.28
1.9538	2	3 3 0	46.44
1.9349	2	3 1 3+	46.92
1.8924	2	0 6 2	48.04
1.8865	3	1 6 1	48.20
1.8777	2	0 5 4	48.44

Sodium Barbital, $C_8H_{11}N_2NaO_3$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
1.8683	2	2 2 5	48.77
1.8589	3	3 3 2	48.96
1.8420	2	1 2 6	49.44
1.7985	2	2 4 4	50.72
1.7737	1	3 4 1	51.48
1.7584	1	3 3 3	51.96
1.7547	2	2 5 3	52.08
1.7410	1	1 3 6	52.52
1.7324	1	2 0 6	52.80
1.7270	1	1 6 3+	52.98
1.7191	1	3 4 2	53.24
1.7150	2	2 1 6+	53.38
1.6615	1	1 1 7+	55.24
1.6489	2	2 6 2	55.70
1.6392	3	3 4 3+	56.06
1.6159	1	1 6 4+	56.94
1.6040	1	4 2 1+	57.40
1.5784	1	3 5 2+	58.42
1.5730	1	0 7 3	58.64

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
2.988	5	0 4 0	29.88
2.984	4	1 3 2	29.92
2.930	3	2 2 0	30.48
2.901	3	0 4 1	30.80
2.855	1	2 1 2	31.30
2.848	2	2 2 1	31.38
2.838	18	0 3 3	31.50
2.764	1	1 0 4	32.36
2.693	3	1 1 4	33.24
2.664	7	1 4 1	33.62
2.638	4	2 2 2	33.95
2.614	9	1 3 3	34.27
2.509	6	1 2 4	35.76
2.490	2	1 4 2	36.05
2.403	8	0 4 3	37.39
2.3775	2	0 1 5	37.81
2.3726	2	2 2 3	37.89
2.3658	1	2 3 2	38.00
2.3451	2	0 5 1	38.35
2.2711	6	1 3 4	39.65
2.2628	1	1 4 3	39.81
2.2521	1	1 5 0	40.00
2.2415	4	1 1 5	40.20
2.2237	1	0 5 2	40.53
2.2143	2	1 5 1	40.71
2.2040	2	3 0 1	40.91
2.2029	7	3 1 0	40.93
2.1685	2	2 3 3	41.61
2.1675	3	3 1 1	41.63
2.1113	1	1 5 2	42.80
2.1072	2	2 2 4	42.88
2.0720	1	0 3 5	43.65
2.0678	6	3 2 1	43.74
2.0576	2	0 5 3	43.97
2.0291	6	1 4 4	44.62
1.9801	4	1 3 5	45.79
1.9603	1	2 3 4	46.28
1.9534	2	3 3 0	46.45
1.9361	1	1 0 6	46.89
1.9344	2	3 1 3	46.93
1.8924	2	0 6 2	48.04
1.8866	3	1 6 1	48.20
1.8772	1	0 5 4	48.45
1.8686	2	2 2 5	48.69
1.8593	3	3 3 2	48.95
1.8418	3	1 2 6	49.45
1.7983	3	2 4 4	50.73
1.7736	1	3 4 1	51.48
1.7589	1	3 3 3	51.95
1.7550	2	2 5 3	52.07

Calculated Pattern (Integrated)			
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$ $\lambda - 1.540598\text{\AA}$
8.51	100	0 1 1	10.38
6.06	25	0 0 2	14.59
5.98	12	0 2 0	14.81
5.88	8	1 0 1	15.05
5.86	61	1 1 0	15.11
5.36	55	0 2 1	16.52
5.28	5	1 1 1	16.79
4.504	6	1 0 2	19.70
4.257	53	0 2 2	20.85
4.214	24	1 1 2	21.06
4.191	17	1 2 1	21.18
3.785	10	0 3 1	23.49
3.597	4	1 2 2	24.73
3.465	5	1 0 3	25.69
3.427	1	1 3 0	25.98
3.362	1	2 0 0	26.49
3.349	12	0 2 3	26.60
3.330	20	0 3 2	26.75
3.328	12	1 1 3	26.77
3.298	1	1 3 1	27.01
3.240	2	2 0 1	27.51
3.236	2	2 1 0	27.54
3.127	32	2 1 1	28.52
3.032	1	0 0 4	29.43
2.998	5	1 2 3	29.78

Sodium Barbitol, $C_8H_{11}N_2NaO_3$ - (continued)

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$
			$\lambda - 1.540598\text{\AA}$
1.7413	1	1 3 6	52.51
1.7325	1	2 0 6	52.80
1.7194	1	3 4 2	53.23
1.7146	2	2 1 6	53.39
1.6780	1	1 0 7	54.65
1.6617	1	1 1 7	55.23
1.6491	2	2 6 2	55.69
1.6390	1	2 5 4	56.07
1.6390	2	3 4 3	56.07
1.5728	1	0 7 3	58.65

Δ^9 -Tetrahydrocannabinolic Acid B, $C_{22}H_{30}O_4$

Synonyms

1. delta (sup 9) - THC acid B
2. 6,6,9-trimethyl-3-pentyl-7,8,9,10-tetrahydro-6H-dibenzo(b,d)pyran-1-ol

Structure

Orthorhombic, $P2_12_12_1$ (19), $Z = 4$. The structure was refined by Rosenqvist and Ottersen [1975].

Atom positions

All atoms were in general positions 4(a).

Lattice constants

$a = 16.515(2) \text{ \AA}$
 $b = 14.325(2)$
 $c = 8.744(1)$

(published values: $a = 16.514(2) \text{ \AA}$,
 $b = 14.324(2)$, $c = 8.744(1)$ [Rosenqvist and Ottersen, 1975])

CD cell: $a = 14.325(2) \text{ \AA}$, $b = 16.514(2)$,
 $c = 8.744(1)$. sp. gp. $P2_12_12_1$; $a/b = 0.8674$;
 $c/b = 0.5295$.

Volume

$2068.6 \text{ \AA}^3$

Density

(calculated) 1.151 g/cm^3
(measured) 1.12 g/cm^3 [Rosenqvist and Ottersen, 1975]

Thermal parameters

For hydrogen: isotropic B_i [Rosenqvist and Ottersen, 1975]
For other atoms, isotropic B_i estimated from β_{ij} for individual atoms.

Scattering factors

H^0 [Stewart et al., 1965]
 C^0, O^0 [Doyle and Turner, 1968]

Scale factors (integrated intensities)

$\gamma = 3.492 \times 10^{-3}$
 I/I_{corundum} (calculated) = 1.20 for reflection with $hkl = 110$.

References

- Doyle, P. A. and Turner, P. S. (1968). Acta Crystallogr. **A24**, 390.
Rosenqvist, E. and Ottersen, T. (1975). Acta Chem. Scand. **B29**, 379.
Stewart, R. F., Davidson, E. R., and Simpson, W. T. (1965). J. Chem. Phys. **42**, 3175.

Calculated Pattern (Peak heights)				
$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda - 1.540598 \text{ \AA}$
10.80	100	1 1 0	8.18	
8.25	6	2 0 0	10.72	
7.72	22	1 0 1	11.46	
7.46	17	0 1 1	11.86	
7.16	9	0 2 0	12.36	
6.79	10	1 1 1	13.02	
6.56	8	1 2 0	13.48	
5.53	29	0 2 1+	16.00	
5.13	4	3 1 0	17.26	
4.65	3	3 0 1	19.06	
4.59	8	2 2 1+	19.32	
4.371	63	0 0 2	20.30	
4.223	4	1 0 2	21.02	
4.130	3	2 3 0+	21.50	
4.052	43	1 1 2+	21.92	
3.966	4	4 1 0	22.40	
3.864	1	2 0 2	23.00	
3.729	13	0 2 2+	23.84	
3.639	11	1 2 2	24.44	
3.582	1	0 4 0	24.84	
3.399	4	2 2 2	26.20	
3.329	4	3 1 2	26.76	
3.314	3	4 2 1+	26.88	
3.123	1	4 3 0	28.56	
3.089	2	3 2 2	28.88	
2.855	4	0 1 3	31.30	
2.840	2	3 4 1+	31.48	
2.704	2	4 4 0+	33.10	
2.664	1	1 2 3	33.62	
2.585	2	4 4 1+	34.68	
2.541	1	3 5 0+	35.30	
2.535	1	3 1 3	35.38	
2.3008	1	5 3 2+	39.12	
2.2807	1	1 6 1+	39.48	
2.2490	1	7 1 1	40.06	
2.1965	1	3 5 2	41.06	
2.1642	1	5 5 0+	41.70	
2.1244	1	3 6 1+	42.52	
2.0907	1	0 2 4+	43.24	
2.0742	1	1 2 4	43.60	
2.0554	1	7 1 2+	44.02	
2.0266	1	2 2 4+	44.68	
1.9894	1	8 1 1+	45.56	
1.9538	1	3 2 4+	46.44	
1.9349	1	2 7 1+	46.92	
1.8690	1	4 6 2+	48.68	

Δ^9 -Tetrahydrocannabinolic Acid B, C₂₂H₃₀O₄ - (continued)

Calculated Pattern (Integrated)				
d(Å)	I	hkl	2 θ (°)	λ - 1.540598Å
10.82	100	1 1 0	8.16	
8.26	6	2 0 0	10.71	
7.73	22	1 0 1	11.44	
7.46	16	0 1 1	11.85	
7.16	9	0 2 0	12.35	
6.80	10	1 1 1	13.01	
6.57	7	1 2 0	13.46	
5.54	19	0 2 1	15.98	
5.54	11	2 1 1	15.99	
5.14	4	3 1 0	17.24	
4.66	3	3 0 1	19.04	
4.60	6	2 2 1	19.28	
4.59	4	1 3 0	19.33	
4.430	4	3 1 1	20.03	
4.372	69	0 0 2	20.30	
4.226	4	1 0 2	21.00	
4.134	2	2 3 0	21.48	
4.062	16	1 3 1	21.86	
4.054	35	1 1 2	21.91	
3.967	3	4 1 0	22.39	
3.864	1	2 0 2	23.00	
3.737	2	2 3 1	23.79	
3.732	10	0 2 2	23.83	
3.731	3	2 1 2	23.83	
3.640	12	1 2 2	24.43	
3.613	1	4 1 1	24.62	
3.581	1	0 4 0	24.84	
3.424	1	3 0 2	26.01	
3.401	4	2 2 2	26.18	
3.330	4	3 1 2	26.75	
3.314	1	0 4 1	26.88	
3.311	2	4 2 1	26.91	
3.123	2	4 3 0	28.56	
3.089	2	3 2 2	28.88	
2.856	4	0 1 3	31.29	
2.839	2	3 4 1	31.48	
2.705	2	4 4 0	33.09	
2.700	1	0 2 3	33.16	
2.664	1	1 2 3	33.61	
2.584	1	4 4 1	34.68	
2.535	1	3 1 3	35.38	
2.2496	1	7 1 1	40.05	
2.1972	1	3 5 2	41.05	
2.1643	1	5 5 0	41.70	
2.1427	1	1 1 4	42.14	
2.1247	1	3 6 1	42.51	
2.0742	1	1 2 4	43.60	
2.0268	1	2 2 4	44.67	
1.9897	1	8 1 1	45.55	

Vinbarbital, Form I, C₁₁H₁₆N₂O₃

Synonyms

1. 5-Ethyl-5(1-methyl-1-butenyl) barbituric acid

Structure

Monoclinic, P₂₁/c (14), Z = 4. The structure was determined by Craven and Cusatis [1969].

Atom positions

All atoms are in general positions 4(e). The reference was lacking data for H(221); it was omitted from these calculations.

Polymorphism

Two polymorphs (melting points 129° and 106°) have been reported but they are very difficult to prepare from melt or solution [Craven and Cusatis, 1969].

Lattice constants

a = 14.396(5) Å
b = 6.822(3)
c = 12.541(7)
β = 107.43(3)°

a/b = 2.1102
c/b = 1.8383

(published values: a = 14.395(5) Å,
b = 6.822(3), c = 12.540(7), β = 107° 26(2)'
[Craven and Cusatis, 1969])

Volume

1175.1 Å³

Density

(calculated) 1.268 g/cm³

Thermal parameters

Anisotropic for non-hydrogen atoms [Craven and Cusatis, 1969]. Overall B = 5.0 for hydrogen atoms.

Scattering factors

C⁰, H⁰, N⁰, O⁰ [International Tables, 1962]

Scale factors (integrated intensities)

γ = 2.068 × 10⁻³

I/I_{corundum} (calculated) = 0.799 for reflection with hkl = 110.

Additional pattern

1. PDF card 9-555 [Parkes, E. B., South Western Forensic Science Lab., Westbury-on-Trym, Bristol, Eng.]

References

Craven, B. M. and Cusatis, C. (1969). Acta Crystallogr. B25, 2291.
International Tables for X-ray Crystallography, III (1962). (The Kynoch Press, Birmingham, Eng.) p. 202.

Calculated Pattern (Peak heights)				
d(Å)	I	hkl	2θ(°)	λ - 1.540598Å
13.71	99	1 0 0	6.44	
6.87	10	2 0 0	12.88	
6.20	26	-1 0 2	14.28	
6.10	100	1 1 0	14.50	
5.981	34	0 0 2	14.80	
5.925	33	0 1 1	14.94	
5.757	4	-1 1 1	15.38	
4.962	22	1 0 2	17.86	
4.839	38	2 1 0	18.32	
4.591	35	-1 1 2	19.32	
4.498	4	0 1 2	19.72	
4.308	5	-3 0 2	20.60	
4.188	17	2 1 1	21.20	
4.015	1	1 1 2	22.12	
3.914	6	-3 1 1	22.70	
3.799	3	3 1 0	23.40	
3.645	2	-3 1 2	24.40	
3.562	2	-1 1 3	24.98	
3.445	20	0 1 3+	25.84	
3.388	2	3 1 1	26.28	
3.309	3	1 2 0	26.92	
3.281	4	0 2 1	27.16	
3.202	17	3 0 2	27.84	
3.125	19	-1 0 4+	28.54	
3.056	9	2 2 0+	29.20	
2.988	14	-1 2 2	29.88	
2.963	7	0 2 2	30.14	
2.897	2	3 1 2	30.84	
2.870	11	2 2 1	31.14	
2.840	4	-5 0 2+	31.48	
2.812	13	1 2 2	31.80	
2.746	1	5 0 0	32.58	
2.642	6	-1 2 3	33.90	
2.592	5	0 2 3+	34.58	
2.569	3	3 2 1	34.90	
2.472	4	-4 2 1+	36.32	
2.464	4	3 1 3	36.44	
2.420	3	4 2 0	37.12	
2.362	2	5 1 1	38.06	
2.335	2	-1 1 5+	38.52	
2.295	1	-4 2 3+	39.22	
2.253	2	0 1 5+	39.98	
2.244	1	1 3 0	40.16	
2.227	3	-3 2 4	40.48	
2.196	2	-5 2 1	41.06	
2.186	1	1 3 1	41.26	
2.139	2	5 2 0	42.22	
2.063	1	-1 0 6	43.84	
2.052	2	-5 1 5+	44.10	
2.009	2	-1 2 5+	45.10	

Vinbarbital, form I, $C_{11}H_{16}N_2O_3$ - (continued)

d(Å)	I	hkl	2θ(°)
			λ - 1.540598Å
2.005	2	-4 0 6	45.18
1.972	1	2 3 2+	45.98
1.963	1	7 0 0+	46.22
1.915	2	1 3 3+	47.44
1.898	2	4 2 3+	47.88
1.880	2	5 2 2	48.38
1.854	1	-7 1 4+	49.10
1.782	1	-2 2 6+	51.22
1.722	1	0 2 6+	53.16
1.710	1	-6 2 5	53.56

Calculated Pattern (Integrated)

d(Å)	I	hkl	2θ(°)
			λ - 1.540598Å
13.73	96	1 0 0	6.43
6.87	10	2 0 0	12.88
6.21	19	-1 0 2	14.26
6.11	100	1 1 0	14.49
5.983	26	0 0 2	14.80
5.926	27	0 1 1	14.94
5.761	2	-1 1 1	15.37
4.967	23	1 0 2	17.84
4.840	40	2 1 0	18.32
4.591	37	-1 1 2	19.32
4.498	3	0 1 2	19.72
4.312	5	-3 0 2	20.58
4.224	1	-2 1 2	21.02
4.190	19	2 1 1	21.19
4.016	1	1 1 2	22.12
3.915	7	-3 1 1	22.69
3.802	3	3 1 0	23.38
3.645	2	-3 1 2	24.40
3.564	2	-1 1 3	24.96
3.459	13	-4 0 2	25.74
3.457	4	-2 1 3	25.75
3.443	15	0 1 3	25.86
3.434	1	4 0 0	25.93
3.426	5	2 1 2	25.99
3.388	1	3 1 1	26.28
3.310	3	1 2 0	26.91
3.280	4	0 2 1	27.16
3.202	19	3 0 2	27.84
3.183	1	-4 1 1	28.01
3.174	1	-3 1 3	28.09
3.153	2	1 1 3	28.28
3.133	10	1 2 1	28.47
3.124	15	-1 0 4	28.55
3.067	4	4 1 0	29.09
3.055	8	2 2 0	29.21

d(Å)	I	hkl	2θ(°)
			λ - 1.540598Å
2.991	2	0 0 4	29.85
2.989	15	-1 2 2	29.86
2.963	6	0 2 2	30.13
2.940	1	-3 0 4	30.38
2.899	1	3 1 2	30.82
2.870	12	2 2 1	31.14
2.840	1	-1 1 4	31.47
2.840	2	-5 0 2	31.48
2.825	1	-2 1 4	31.64
2.824	1	-4 1 3	31.66
2.812	14	1 2 2	31.80
2.797	5	4 1 1	31.98
2.747	1	5 0 0	32.57
2.655	2	4 0 2	33.74
2.647	1	-5 1 1	33.84
2.643	6	-1 2 3	33.89
2.592	5	0 2 3	34.57
2.585	1	2 2 2	34.68
2.569	3	3 2 1	34.90
2.476	2	-4 2 1	36.26
2.471	2	-3 2 3	36.32
2.463	3	3 1 3	36.45
2.420	3	4 2 0	37.12
2.362	2	5 1 1	38.06
2.336	1	-1 1 5	38.50
2.335	1	3 2 2	38.53
2.258	1	0 1 5	39.89
2.254	1	5 0 2	39.98
2.243	1	1 3 0	40.16
2.227	4	-3 2 4	40.48
2.197	2	-5 2 1	41.06
2.186	1	1 3 1	41.27
2.139	2	5 2 0	42.21
2.063	1	-1 0 6	43.84
2.056	1	-6 1 4	44.01
2.052	2	-5 1 5	44.10
2.009	2	-1 2 5	45.08
2.008	1	2 2 4	45.12
2.005	1	-4 0 6	45.19
1.962	1	7 0 0	46.23
1.916	1	-4 2 5	47.42
1.916	1	1 3 3	47.42
1.914	1	0 1 6	47.46
1.899	2	4 2 3	47.87
1.880	2	5 2 2	48.37
1.854	1	-7 1 4	49.10
1.782	1	-2 2 6	51.22
1.722	1	0 2 6	53.16
1.710	1	-6 2 5	53.55

INORGANIC NAMES

	Vol. or Sec.	Page		Vol. or Sec.	Page
Aluminum, Al	1	11	Ammonium aluminum selenate hydrate, NH ₄ Al(SeO ₄) ₂ ·12H ₂ O	9m	6
Aluminum antimony, AlSb	4	72	Ammonium aluminum sulfate, NH ₄ Al(SO ₄) ₂	10m	5
Aluminum bismuth oxide, Al ₄ Bi ₂ O ₉ ..	11m	5	Ammonium aluminum sulfate hydrate (tschermigite), NH ₄ Al(SO ₄) ₂ ·12H ₂ O	6	3
Aluminum chloride, AlCl ₃	9m	61	Ammonium azide, NH ₄ N ₃	9	4
Aluminum chloride hydrate (chloraluminite), AlCl ₃ ·6H ₂ O	7	3	Ammonium beryllium fluoride, (NH ₄) ₂ BeF ₄	3m	5
Aluminum copper, Al ₄ Cu ₉	11m	79	Ammonium boron fluoride, NH ₄ BF ₄ ...	3m	6
Aluminum fluoride hydroxide silicate, topaz, Al ₂ (F,OH) ₂ SiO ₄	1m	4	Ammonium bromide, NH ₄ Br	2	49
Aluminum iron antimony oxide, bahianite, Al _{5.66} Fe _{0.09} Sb _{2.95} O ₁₆	16m	87	Ammonium cadmium bromide, (NH ₄) ₄ CdBr ₆	15m	9
Aluminum iron oxide, AlFeO ₃	15m	7	Ammonium cadmium chloride, NH ₄ CdCl ₃	5m	6
Aluminum lithium, Al ₄ Li ₉	10m	98	Ammonium cadmium sulfate, (NH ₄) ₂ Cd ₂ (SO ₄) ₃	7m	5
Aluminum nickel, AlNi	6m	82	Ammonium cadmium sulfate hydrate, (NH ₄) ₂ Cd(SO ₄) ₂ ·6H ₂ O	8m	5
Aluminum nitride, AlN	12m	5	Ammonium calcium sulfate, (NH ₄) ₂ Ca ₂ (SO ₄) ₃	8m	7
Aluminum nitrate hydrate, Al(NO ₃) ₃ ·9H ₂ O	11m	6	Ammonium chlorate, NH ₄ ClO ₄		
Aluminum oxide (corundum), α-Al ₂ O ₃	9	3	(orthorhombic)	7	6
Aluminum oxide hydrate (boehmite), α-Al ₂ O ₃ ·H ₂ O	3	38	Ammonium chloride (salammoniac), NH ₄ Cl	1	59
Aluminum oxide hydrate, diaspore, β-Al ₂ O ₃ ·H ₂ O	3	41	Ammonium chromium sulfate hydrate, NH ₄ Cr(SO ₄) ₂ ·12H ₂ O	6	7
Aluminum phosphate, Al(PO ₃) ₃	2m	3	Ammonium cobalt (II) chloride, NH ₄ CoCl ₃	6m	5
Aluminum phosphate (berlinite), AlPO ₄ (trigonal)	10	3	Ammonium cobalt fluoride, NH ₄ CoF ₃	8m	9
Aluminum phosphate, AlPO ₄ (orthorhombic)	10	4	Ammonium copper bromide hydrate, (NH ₄) ₂ CuBr ₄ ·2H ₂ O	10m	6
Aluminum plutonium, Al ₃ Pu	15m	77	Ammonium copper chloride, NH ₄ CuCl ₃	7m	7
Aluminum rhenium, AlRe	15m	79	Ammonium copper chloride hydrate, (NH ₄) ₂ CuCl ₄ ·2H ₂ O	12m	6
Aluminum rhenium, Al ₁₂ Re	15m	80	Ammonium copper fluoride, NH ₄ CuF ₃	11m	8
Aluminum rhodium, AlRh	15m	82	Ammonium gallium sulfate hydrate, NH ₄ Ga(SO ₄) ₂ ·12H ₂ O	6	9
Aluminum ruthenium, AlRu	15m	83	Ammonium germanium fluoride, (NH ₄) ₂ GeF ₆	6	8
Aluminum ruthenium, Al ₆ Ru	15m	84	Ammonium hydrogen arsenate, NH ₄ H ₂ AsO ₄	16m	9
Aluminum samarium, AlSm ₂	15m	86	Ammonium hydrogen carbonate (teschemacherite), (NH ₄)HCO ₃	9	5
Aluminum samarium, AlSm ₃	15m	88	Ammonium hydrogen phosphate, NH ₄ H ₂ PO ₄	4	64
Aluminum samarium, Al ₂ Sm	15m	90	Ammonium iodate, NH ₄ IO ₃	10m	7
Aluminum samarium, Al ₃ Sm	15m	91	Ammonium iodide, NH ₄ I	4	56
Aluminum silicate (mullite), Al ₆ Si ₂ O ₁₃	3m	3	Ammonium iridium chloride, (NH ₄) ₂ IrCl ₆	8	6
Aluminum sulfate, Al ₂ (SO ₄) ₃	15m	8	Ammonium iron chloride hydrate, (NH ₄) ₂ FeCl ₅ ·H ₂ O	14m	7
Aluminum technetium, Al ₆ Tc	15m	93	Ammonium iron fluoride, (NH ₄) ₃ FeF ₆	9m	9
Aluminum terbium, Al ₂ Tb	15m	95	Ammonium iron sulfate, NH ₄ Fe(SO ₄) ₂	10m	8
Aluminum terbium, Al ₂ Tb ₃	15m	96	Ammonium iron sulfate hydrate, NH ₄ Fe(SO ₄) ₂ ·12H ₂ O	6	10
Aluminum thorium uranium, Al ₆ ThU ..	15m	98	Ammonium lead chloride, (NH ₄) ₂ PbCl ₆	11m	10
Aluminum tungsten, Al ₅ W, δ-phase ..	15m	100	Ammonium magnesium aluminum fluoride, NH ₄ MgAlF ₆	10m	9
Aluminum tungsten oxide, Al ₂ (WO ₄) ₃	11m	7	Ammonium magnesium chromium oxide hydrate, (NH ₄) ₂ Mg(CrO ₄) ₂ ·6H ₂ O	8m	10
Aluminum vanadium, Al ₁₀ V	15m	102	Ammonium magnesium phosphate hydrate (struvite), NH ₄ MgPO ₄ ·6H ₂ O	3m	41
Aluminum vanadium, Al _{10.25} V	15m	104	Ammonium manganese chloride hydrate, (NH ₄) ₂ MnCl ₄ ·2H ₂ O	11m	11
Aluminum vanadium, Al ₂₃ V ₄	15m	106			
Aluminum vanadium, Al ₄₅ V ₇ , α'-phase	15m	108			
Aluminum ytterbium, Al ₂ Yb	15m	111			
Aluminum yttrium, Al ₃ Y	15m	112			
Ammonium aluminum fluoride, (NH ₄) ₃ AlF ₆	9m	5			

Further work on this program is in progress, and it is anticipated that additional sections will be issued. Therefore, the cumulative index here is not necessarily the concluding index for the project.

m - Monograph 25.

A mineral name in () indicates a synthetic sample.

	Vol. or Sec.	Page		Vol. or Sec.	Page
Ammonium manganese(II) fluoride, NH ₄ MnF ₃	5m	8	Antimony iron titanium oxide hydroxide, derbylite, SbFe ₄ Ti ₃ O ₁₃ (OH).....	16m	89
Ammonium manganese sulfate, (NH ₄) ₂ Mn ₂ (SO ₄) ₃	7m	8	Antimony lanthanum, LaSb.....	4m	42
Ammonium manganese sulfate hydrate, (NH ₄) ₂ Mn(SO ₄) ₂ ·6H ₂ O	8m	12	Antimony neodymium, NdSb.....	4m	43
Ammonium mercury chloride, NH ₄ HgCl ₃	8m	14	Antimony(III) oxide (senarmontite), Sb ₂ O ₃ (cubic)	3	31
Ammonium molybdenum oxide phosphate hydrate, (NH ₄) ₃ (MoO ₃) ₁₂ PO ₄ ·4H ₂ O ..	8	10	Antimony(III) oxide, valentinite, Sb ₂ O ₃ (orthorhombic)	10	6
Ammonium nickel(II) chloride, NH ₄ NiCl ₃	6m	6	Antimony(IV) oxide (cervantite), Sb ₂ O ₄	10	8
Ammonium nickel chromium oxide hydrate, (NH ₄) ₂ Ni(CrO ₄) ₂ ·6H ₂ O	8m	16	Antimony(V) oxide, Sb ₂ O ₅	10	10
Ammonium nitrate (nitrammite), NH ₄ NO ₃	7	4	Antimony oxide, Sb ₆ O ₁₃	16m	14
Ammonium osmium bromide, (NH ₄) ₂ OsBr ₆	3	71	Antimony praseodymium, PrSb.....	4m	43
Ammonium osmium chloride, (NH ₄) ₂ OsCl ₆	1m	6	Antimony scandium, SbSc.....	4m	44
Ammonium palladium chloride, (NH ₄) ₂ PdCl ₄	6	6	Antimony selenide, Sb ₂ Se ₃	3m	7
Ammonium palladium chloride, (NH ₄) ₂ PdCl ₆	8	7	Antimony silver sulfide, AgSbS ₂ (cubic).....	5m	48
Ammonium platinum bromide, (NH ₄) ₂ PtBr ₆	9	6	Antimony silver sulfide (miargyrite), AgSbS ₂ (monoclinic).....	5m	49
Ammonium platinum chloride, (NH ₄) ₂ PtCl ₆	5	3	Antimony silver sulfide (pyrargyrite), Ag ₃ SbS ₃ (trigonal).....	5m	51
Ammonium potassium iron chloride hydrate (kremersite), (NH ₄ ,K) ₂ FeCl ₅ ·H ₂ O	14m	8	Antimony silver telluride, AgSbTe ₂ .	3m	47
Ammonium rhenium oxide, NH ₄ ReO ₄ ...	9	7	Antimony(III) sulfide (stibnite), Sb ₂ S ₃	5	6
Ammonium selenium bromide, (NH ₄) ₂ SeBr ₆	8	4	Antimony telluride, Sb ₂ Te ₃	3m	8
Ammonium silicon fluoride (cryptohalite), (NH ₄) ₂ SiF ₆	5	5	Antimony terbium, SbTb.....	5m	61
Ammonium strontium chromium oxide, (NH ₄) ₂ Sr(CrO ₄) ₂	14m	9	Antimony thorium, SbTh.....	4m	44
Ammonium strontium sulfate, (NH ₄) ₂ Sr(SO ₄) ₂	15m	11	Antimony thulium, SbTm.....	4m	45
Ammonium sulfate (mascagnite), (NH ₄) ₂ SO ₄	9	8	Antimony tin, SbSn.....	16m	15
Ammonium tellurium bromide, (NH ₄) ₂ TeBr ₆	8	5	Antimony ytterbium, SbYb.....	4m	45
Ammonium tellurium chloride, (NH ₄) ₂ TeCl ₆	8	8	Antimony yttrium, SbY.....	4m	46
Ammonium tin chloride, (NH ₄) ₂ SnCl ₆	5	4	Arsenic, As	3	6
Ammonium titanium fluoride, (NH ₄) ₂ TiF ₆	16m	10	Arsenic cerium, AsCe.....	4m	51
Ammonium vanadium oxide, NH ₄ VO ₃ ..	8	9	Arsenic(III) iodide, AsI ₃	13m	7
Ammonium zinc chloride, (NH ₄) ₃ ZnCl ₅	15m	12	Arsenic oxide (arsenolite), As ₂ O ₃ (cubic)	1	51
Ammonium zinc fluoride, NH ₄ ZnF ₃ ...	8m	18	Arsenic oxide, claudetite, As ₂ O ₃ (monoclinic)	3m	9
Ammonium zirconium fluoride, (NH ₄) ₃ ZrF ₇	6	14	Barium, Ba	4	7
Antimonic acid, H ₁₄ Sb ₁₄ O ₂₁ (OH) ₄₂ ...	16m	13	Barium aluminum oxide, BaAl ₂ O ₄	5m	11
Antimony, Sb	3	14	Barium aluminum oxide, Ba ₃ Al ₂ O ₆ ...	12m	7
Antimony bromide, α-SbBr ₃	15m	13	Barium arsenate, Ba ₃ (AsO ₄) ₂	2m	6
Antimony cerium, CeSb.....	4m	40	Barium borate, BaB ₄ O ₇	4m	6
Antimony cobalt, CoSb.....	15m	121	Barium borate, high form, BaB ₂ O ₄ ..	4m	4
Antimony cobalt, CoSb ₂	15m	122	Barium borate, BaB ₈ O ₁₃	7m	10
Antimony cobalt titanium, CoSbTi...	15m	124	Barium bromate hydrate, Ba(BrO ₃) ₂ ·H ₂ O	8m	19
Antimony cobalt vanadium, CoSbV....	15m	125	Barium bromide, BaBr ₂	10m	63
Antimony dysprosium, DySb.....	4m	41	Barium bromide fluoride, BaBrF	10m	10
Antimony erbium, ErSb.....	4m	41	Barium bromide hydrate, BaBr ₂ ·H ₂ O	3m	10
Antimony(III) fluoride, SbF ₃	2m	4	Barium bromide hydrate, BaBr ₂ ·2H ₂ O	16m	16
Antimony gadolinium, GdSb.....	4m	42	Barium cadmium chloride hydrate, BaCdCl ₄ ·4H ₂ O.....	15m	14
Antimony gallium, GaSb.....	6	30	Barium calcium nitrate, Ba _{.25} Ca _{.75} (NO ₃) ₂	12m	38
Antimony gold (aurostibite), AuSb ₂	7	18	Barium calcium nitrate, Ba _{.50} Ca _{.50} (NO ₃) ₂	12m	38
Antimony indium, InSb.....	4	73	Barium calcium nitrate, Ba _{.75} Ca _{.25} (NO ₃) ₂	12m	38
Antimony(III) iodide, SbI ₃	6	16	Barium calcium tungsten oxide, Ba ₂ CaWO ₆	9m	10
			Barium carbonate (witherite), BaCO ₃ (orthorhombic)	2	54
			Barium carbonate, BaCO ₃ (cubic) at 1075 °C	10	11
			Barium chlorate, Ba(ClO ₃) ₂	16m	17

	Vol. or Sec.	Page		Vol. or Sec.	Page
Barium chlorate hydrate, Ba(ClO ₄) ₂ ·3H ₂ O	2m	7	Beryllium calcium iron magnesium aluminum phosphate hydroxide		
Barium chlorate hydrate, Ba(ClO ₃) ₂ ·H ₂ O	8m	21	hydrate, roscherite (monoclinic), Be ₂ Ca(Fe ₃ Mg ₇) ₂ Al ₆₇ (PO ₄) ₃ (OH) ₃ ·2H ₂ O	16m	96
Barium chloride, BaCl ₂ , (cubic) ...	9m	13	Beryllium calcium manganese		
Barium chloride, BaCl ₂ , (orthorhombic)	9m	11	aluminum iron phosphate hydroxide		
Barium chloride fluoride, BaClF ...	10m	11	hydrate, roscherite (triclinic), Be ₄ Ca ₂ (Mn _{3.91} Mg _{0.04} Ca _{0.05})(Al _{1.13} Fe _{0.42}		
Barium chloride hydrate, BaCl ₂ ·2H ₂ O	12m	9	Mn ₁₂)(PO ₄) ₆ (OH) ₄ ·6H ₂ O	16m	100
Barium chromium oxide, Ba ₃ (CrO ₄) ₂	15m	16	Beryllium calcium oxide, Be ₁₇ Ca ₁₂ O ₂₉	7m	89
Barium fluoride, BaF ₂	1	70	Beryllium chromium oxide, BeCr ₂ O ₄	10	12
Barium hydroxide phosphate, Ba ₅ (OH)(PO ₄) ₃	11m	12	Beryllium cobalt, BeCo	5m	62
Barium iodide, BaI ₂	10m	66	Beryllium germanium oxide, Be ₂ GeO ₄	10	13
Barium iodide hydrate, BaI ₂ ·2H ₂ O...	16m	18	Beryllium lanthanum oxide, Be ₂ La ₂ O ₅	9m	65
Barium lead chloride, BaPbCl ₄	11m	13	Beryllium niobium, Be ₂ Nb	7m	92
Barium lead nitrate, Ba ₃₃ Pb ₆₇ (NO ₃) ₂	12m	40	Beryllium oxide (bromellite), BeO	1	36
Barium lead nitrate, Ba ₆₇ Pb ₃₃ (NO ₃) ₂	12m	40	Beryllium palladium, BePd	5m	62
Barium manganese oxide, Ba(MnO ₄) ₂	15m	17	Beryllium silicate, phenakite, Be ₂ SiO ₄	8	11
Barium molybdenum oxide, BaMoO ₄ ...	7	7	Beryllium sulfate, BeSO ₄	15m	20
Barium molybdenum oxide, Ba ₂ MoO ₅ ..	12m	10	Bismuth, Bi	3	20
Barium nitrate (nitrobarite), Ba(NO ₃) ₂	11m	14	Bismuth bromide oxide, BiOBr	8	14
Barium nitrite hydrate, Ba(NO ₂) ₂ ·H ₂ O	15m	18	Bismuth cerium, BiCe	4m	46
Barium oxide, BaO	9m	63	Bismuth chloride oxide (bismoclite), BiOCl	4	54
Barium oxide, BaO ₂	6	18	Bismuth dysprosium, BiDy	4m	47
Barium phosphate, Ba ₂ P ₂ O ₇ , (high form)	16m	19	Bismuth erbium, BiEr	4m	47
Barium phosphate, Ba ₃ (PO ₄) ₂	12m	12	Bismuth fluoride, BiF ₃	1m	7
Barium selenide, BaSe	5m	61	Bismuth holmium, BiHo	4m	48
Barium silicate, β-BaSiO ₃	13m	8	Bismuth(III) iodide, BiI ₃	6	20
Barium silicate (sanbornite), β-BaSi ₂ O ₅	13m	10	Bismuth iodide oxide, BiOI	9	16
Barium silicate, Ba ₂ SiO ₄	13m	12	Bismuth lanthanum, BiLa	4m	48
Barium silicate, Ba ₂ Si ₃ O ₈	13m	13	Bismuth neodymium, BiNd	4m	49
Barium silicate, Ba ₃ SiO ₅	13m	15	Bismuth oxide (bismite), α-Bi ₂ O ₃ ..	3m	16
Barium silicate, Ba ₃ Si ₅ O ₁₃	13m	17	Bismuth phosphate, BiPO ₄ (monoclinic)	3m	11
Barium silicon fluoride, BaSiF ₆ ...	4m	7	Bismuth phosphate, BiPO ₄ (trigonal)	3m	13
Barium strontium nitrate, Ba ₂₅ Sr ₇₅ (NO ₃) ₂	12m	42	Bismuth praseodymium, BiPr	4m	49
Barium strontium nitrate, Ba ₅₀ Sr ₅₀ (NO ₃) ₂	12m	42	Bismuth sulfide (bismuthinite), Bi ₂ S ₃	5m	13
Barium strontium nitrate, Ba ₇₅ Sr ₂₅ (NO ₃) ₂	12m	42	Bismuth telluride, BiTe	4m	50
Barium sulfate (baryte), BaSO ₄	10m	12	Bismuth telluride (tellurobis- muthite), Bi ₂ Te ₃	3m	16
Barium sulfide, BaS	7	8	Bismuth vanadium oxide, low form, BiVO ₄ (tetragonal)	3m	14
Barium thiosulfate hydrate, BaS ₂ O ₃ ·H ₂ O	16m	20	Bismuth vanadium oxide, high form, BiVO ₄ (monoclinic)	3m	14
Barium tin oxide, BaSnO ₃	3m	11	Boron oxide, B ₂ O ₃ , phase 1	10m	70
Barium titanium oxide, BaTiO ₃	3	45	Cadmium, Cd	3	10
Barium titanium silicate (fresnoite), Ba ₂ TiSi ₂ O ₈	9m	14	Cadmium ammine chloride, Cd(NH ₃) ₂ Cl ₂	10m	14
Barium tungsten oxide, BaWO ₄	7	9	Cadmium borate, CdB ₄ O ₇	16m	24
Barium tungsten oxide, Ba ₂ WO ₅	12m	14	Cadmium bromide, CdBr ₂	9	17
Barium vanadium oxide, Ba ₃ (VO ₄) ₂ ..	14m	10	Cadmium bromide chloride, CdBrCl ..	11m	15
Barium zirconium oxide, BaZrO ₃	5	8	Cadmium carbonate (otavite), CdCO ₃	7	11
Beryllium, alpha, Be	9m	64	Cadmium cerium, CdCe	5m	63
Beryllium aluminum oxide (chrysoberyl), BeAl ₂ O ₄	9	10	Cadmium chlorate hydrate, Cd(ClO ₄) ₂ ·6H ₂ O	3m	19
Beryllium aluminum silicate, beryl, Be ₃ Al ₂ (SiO ₃) ₆	9	13	Cadmium chloride, CdCl ₂	9	18
			Cadmium chromium oxide, CdCr ₂ O ₄ ...	5m	16
			Cadmium copper, Cd ₈ Cu ₅	11m	81
			Cadmium cyanide, Cd(CN) ₂	2m	8
			Cadmium fluoride, CdF ₂	10m	15
			Cadmium iron oxide, CdFe ₂ O ₄	9m	16
			Cadmium lanthanum, CdLa	5m	63
			Cadmium manganese oxide, CdMn ₂ O ₄ ..	10m	16
			Cadmium molybdenum oxide, CdMoO ₄ ..	6	21

	Vol. or Sec.	Page		Vol. or Sec.	Page
Cadmium nitrate hydrate, Cd(NO ₃) ₂ ·4H ₂ O	7m	93	Calcium gallium germanium oxide, Ca ₃ Ga ₂ (GeO ₄) ₃	10	18
Cadmium oxide, CdO	2	27	Calcium hydrogen phosphate hydrate, Ca ₈ H ₂ (PO ₄) ₆ ·5H ₂ O	13m	21
Cadmium oxide, CdO (ref. standard)	8m	2	Calcium hydrogen phosphate sulfate hydrate, Ca ₂ HPO ₄ SO ₄ ·4H ₂ O	16m	109
Cadmium phosphate, Cd ₂ P ₂ O ₇	16m	26	Calcium hydroxide (portlandite), Ca(OH) ₂	1	58
Cadmium phosphate, Cd ₃ (PO ₄) ₂	16m	27	Calcium iodate (lautarite), Ca(IO ₃) ₂	14m	12
Cadmium praseodymium, CdPr	5m	64	Calcium iodate hydrate, Ca(IO ₃) ₂ ·6H ₂ O	14m	13
Cadmium selenide (cadmoselite), CdSe (hexagonal)	7	12	Calcium iron germanium oxide, Ca ₃ Fe ₂ (GeO ₄) ₃	10	19
Cadmium silicate, Cd ₂ SiO ₄	13m	19	Calcium iron silicate (andradite), Ca ₃ Fe ₂ Si ₃ O ₁₂	9	22
Cadmium silicate, Cd ₃ SiO ₅	13m	20	Calcium iron silicate hydroxide, julgoldite, Ca ₂ Fe ₃ Si ₃ O ₁₀ (OH,O) ₂ (OH) ₂	10m	72
Cadmium sulfate, CdSO ₄	3m	20	Calcium lead nitrate, Ca ₃₃ Pb ₆₇ (NO ₃) ₂	12m	44
Cadmium sulfate hydrate, 3CdSO ₄ ·8H ₂ O	6m	8	Calcium lead nitrate, Ca ₆₇ Pb ₃₃ (NO ₃) ₂	12m	44
Cadmium sulfate hydrate, CdSO ₄ ·H ₂ O	6m	10	Calcium magnesium silicate (diopside), CaMg(SiO ₃) ₂	5m	17
Cadmium sulfide (greenockite), CdS	4	15	Calcium molybdenum oxide (powellite), CaMoO ₄	6	22
Cadmium telluride, CdTe	3m	21	Calcium nitrate, Ca(NO ₃) ₂	7	14
Cadmium titanium oxide, CdTiO ₃	15m	21	Calcium oxide (lime), CaO	1	43
Cadmium tungsten oxide, CdWO ₄	2m	8	Calcium oxide (lime), CaO (calculated pattern)	14m	49
Calcium, Ca	9m	68	Calcium oxide phosphate, Ca ₄ O(PO ₄) ₂	12m	17
Calcium aluminum germanium oxide, Ca ₃ Al ₂ (GeO ₄) ₃	10	15	Calcium phosphate, β-Ca ₂ P ₂ O ₇	7m	95
Calcium aluminum hydroxide, Ca ₃ Al ₂ (OH) ₁₂	11m	16	Calcium platinum oxide, Ca ₄ PtO ₆	10m	18
Calcium aluminum iron oxide (brownmillerite), Ca ₄ Al ₂ Fe ₂ O ₁₀	16m	28	Calcium selenide, CaSe	5m	64
Calcium aluminum oxide, Ca ₃ Al ₂ O ₆	5	10	Calcium strontium nitrate, Ca ₃₃ Sr ₆₇ (NO ₃) ₂	12m	46
Calcium aluminum oxide (mayenite), Ca ₁₂ Al ₁₄ O ₃₃	9	20	Calcium strontium nitrate, Ca ₆₇ Sr ₃₃ (NO ₃) ₂	12m	46
Calcium aluminum sulfate hydrate (ettringite), Ca ₆ Al ₂ S ₃ O ₁₈ ·3H ₂ O	8	3	Calcium sulfate (anhydrite), CaSO ₄	4	65
Calcium borate, CaB ₂ O ₄	15m	136	Calcium sulfide (oldhamite), CaS	7	15
Calcium borate hydrate, hexahydroborite, Ca[B(OH) ₄] ₂ ·2H ₂ O	16m	104	Calcium telluride, CaTe	4m	50
Calcium boride, CaB ₆	16m	29	Calcium titanium oxide (perovskite), CaTiO ₃	9m	17
Calcium bromide, CaBr ₂	11m	70	Calcium tungsten oxide, Ca ₃ WO ₆	9m	19
Calcium bromide hydrate, CaBr ₂ ·6H ₂ O	8	15	Calcium tungsten oxide, scheelite, CaWO ₄	6	23
Calcium carbonate (aragonite), CaCO ₃ (orthorhombic)	3	53	Carbon, diamond, C	2	5
Calcium carbonate (aragonite), CaCO ₃ (orthorhombic, calculated pattern)	14m	44	Cerium arsenate, CeAsO ₄	4m	8
Calcium carbonate (calcite), CaCO ₃ (hexagonal)	2	51	Cerium(III) chloride, CeCl ₃	1m	8
Calcium chloride (hydrophilite), CaCl ₂	11m	18	Cerium cobalt, CeCo ₂	13m	50
Calcium chloride fluoride, CaClF	10m	17	Cerium cobalt, Ce ₂₄ Co ₁₁	13m	51
Calcium chloride hydrate, CaCl ₂ ·4H ₂ O	11m	73	Cerium copper, CeCu ₆	7m	99
Calcium chloride hydrate (antarcticite), CaCl ₂ ·6H ₂ O	12m	16	Cerium(III) fluoride, CeF ₃	8	17
Calcium chromium germanium oxide, Ca ₃ Cr ₂ (GeO ₄) ₃	10	16	Cerium gallium, CeGa ₂	13m	54
Calcium chromium iron titanium oxide, loveringite, Ca ₇₂ RE ₃₃ (Y, Th,U,Pb) ₀₅ Ti ₁₂ ·48Fe ₃ ·38Cr ₂ ·24 Mg ₉₂ Zr ₅₈ Al ₃₉ V ₂₁ Mn ₀₄ O ₃₈	16m	106	Cerium magnesium, CeMg	5m	65
Calcium chromium oxide (chromatite), CaCrO ₄	7	13	Cerium magnesium, CeMg ₃	13m	56
Calcium chromium oxide, Ca ₃ (CrO ₄) ₂	15m	22	Cerium nickel, CeNi ₂	13m	58
Calcium chromium silicate (uvarovite), Ca ₃ Cr ₂ (SiO ₄) ₃	10	17	Cerium niobium titanium oxide (aeschnynte), CeNbTiO ₆	3m	24
Calcium fluoride (fluorite), CaF ₂	1	69	Cerium nitride, CeN	4m	51
Calcium fluoride phosphate (fluorapatite), Ca ₅ F(PO ₄) ₃	3m	22	Cerium(IV) oxide (cerianite), CeO ₂	1	56
Calcium fluoride phosphate hydrate, CaFPO ₃ ·2H ₂ O	15m	24	Cerium phosphide, CeP	4m	52
			Cerium thallium, CeTl	13m	59
			Cerium thallium, CeTl ₃	13m	60
			Cerium thallium, Ce ₃ Tl	13m	61
			Cerium(III) vanadium oxide, CeVO ₄	1m	9
			Cerium zinc, CeZn	5m	65

	Vol. or Sec.	Page		Vol. or Sec.	Page
Cerium zinc, CeZn_3	14m	50	Cesium osmium chloride, Cs_2OsCl_6 ..	2m	11
Cerium zinc, CeZn_5	14m	53	Cesium platinum bromide, Cs_2PtBr_6	8	19
Cerium zinc, $\text{Ce}_2\text{Zn}_{17}$	14m	55	Cesium platinum chloride, Cs_2PtCl_6	5	14
Cesium aluminum sulfate hydrate, $\text{CsAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	25	Cesium platinum fluoride, Cs_2PtF_6	6	27
Cesium antimony fluoride, CsSbF_6 ..	4m	9	Cesium selenium bromide, Cs_2SeBr_6	8	20
Cesium beryllium fluoride, CsBeF_3	9m	69	Cesium silicon fluoride, Cs_2SiF_6	5	19
Cesium boron fluoride, CsBF_4	8	22	Cesium strontium chloride, CsSrCl_3	6m	13
Cesium bromate, CsBrO_3	8	18	Cesium sulfate, Cs_2SO_4	7	17
Cesium bromide, CsBr	3	49	Cesium tellurium bromide, Cs_2TeBr_6	9	24
Cesium cadmium bromide, CsCdBr_3 (hexagonal)	10m	20	Cesium tin chloride, Cs_2SnCl_6	5	16
Cesium cadmium chloride, CsCdCl_3 (hexagonal)	5m	19	Cesium vanadium sulfate hydrate, $\text{CsV}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	1m	11
Cesium calcium chloride, CsCaCl_3 ..	5m	21	Cesium zinc sulfate hydrate, $\text{Cs}_2\text{Zn}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	25
Cesium calcium fluoride, CsCaF_3	8m	25	Chromium, Cr	5	20
Cesium calcium sulfate, $\text{Cs}_2\text{Ca}_2(\text{SO}_4)_3$	7m	12	Chromium chloride, CrCl_2	11m	77
Cesium cerium chloride, Cs_2CeCl_6 ..	14m	58	Chromium chloride hydrate, $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$	16m	31
Cesium chlorate, CsClO_3	8	20	Chromium cobalt niobium, CoCrNb ...	15m	140
Cesium chlorate, CsClO_4 , (orthorhombic)	1m	10	Chromium cobalt silicide,		
Cesium chloride, CsCl	2	44	$\text{Co}_9\text{Cr}_{15}\text{Si}_6$	14m	62
Cesium chromium oxide, Cs_2CrO_4	3m	25	Chromium cobalt tantalum, CoCrTa ..	15m	142
Cesium chromium sulfate hydrate, $\text{CsCr}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	8	21	Chromium fluoride, CrF_2	10m	81
Cesium cobalt(II) chloride, CsCoCl_3	6m	11	Chromium fluoride, Cr_2F_5	7m	108
Cesium cobalt chloride, Cs_2CoCl_4 ..	11m	19	Chromium(III) fluoride hydrate, $\text{CrF}_3 \cdot 3\text{H}_2\text{O}$	5m	25
Cesium copper(II) chloride, CsCuCl_3	5m	22	Chromium iridium, Cr_3Ir	6m	14
Cesium copper chloride, Cs_2CuCl_4 ..	11m	20	Chromium(III) oxide, Cr_2O_3	5	22
Cesium copper sulfate hydrate, $\text{Cs}_2\text{Cu}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	14	Chromium phosphate, $\alpha\text{-CrPO}_4$	2m	12
Cesium fluoride, CsF	3m	26	Chromium phosphate, $\beta\text{-CrPO}_4$	9	26
Cesium gallium sulfate hydrate, $\text{CsGa}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	8	23	Chromium phosphate hydrate, $\text{CrPO}_4 \cdot 6\text{H}_2\text{O}$	15m	27
Cesium germanium fluoride, Cs_2GeF_6	5	17	Chromium rhodium, Cr_3Rh	6m	15
Cesium iodate, CsI_2O_3	15m	26	Chromium silicide, Cr_3Si	6	29
Cesium iodide, CsI	4	47	Chromium sulfate, $\text{Cr}_2(\text{SO}_4)_3$	16m	33
Cesium iodine bromide, CsI_2Br	7m	103	Cobalt, Co (cubic)	4m	10
Cesium iodine chloride, CsICl_2	3	50	Cobalt aluminum oxide, CoAl_2O_4	9	27
Cesium iron chloride hydrate, $\text{Cs}_2\text{FeCl}_5 \cdot \text{H}_2\text{O}$	14m	14	Cobalt ammine iodide, $\text{Co}(\text{NH}_3)_6\text{I}_3$..	10m	83
Cesium iron sulfate hydrate, $\text{Cs}_2\text{Fe}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	16	Cobalt antimony oxide, CoSb_2O_6	5m	26
Cesium iron sulfate hydrate, $\text{CsFe}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	28	Cobalt arsenide, CoAs_2	4m	10
Cesium lead(II) chloride, CsPbCl_3 (tetragonal)	5m	24	Cobalt arsenide (skutterudite), CoAs_3	10	21
Cesium lead fluoride, CsPbF_3	8m	26	Cobalt borate, $\text{Co}_3(\text{BO}_3)_2$	12m	20
Cesium lithium cobalt cyanide, $\text{CsLiCo}(\text{CN})_6$	10m	79	Cobalt bromide hydrate, $\text{CoBr}_2 \cdot 6\text{H}_2\text{O}$	12m	21
Cesium lithium fluoride, CsLiF_2 ...	7m	105	Cobalt(II) carbonate (sphaero- cobaltite), CoCO_3	10	24
Cesium magnesium chromium oxide, $\text{Cs}_2\text{Mg}_2(\text{CrO}_4)_3$	8m	27	Cobalt chlorate hydrate, $\text{Co}(\text{ClO}_4)_2 \cdot 6\text{H}_2\text{O}$	3m	28
Cesium magnesium chromium oxide hydrate, $\text{Cs}_2\text{Mg}(\text{CrO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	29	Cobalt chloride hydrate, $\text{CoCl}_2 \cdot 2\text{H}_2\text{O}$	11m	22
Cesium magnesium sulfate hydrate, $\text{Cs}_2\text{Mg}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	18	Cobalt chloride hydrate, $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$	11m	23
Cesium manganese fluoride, CsMnF_3	10m	21	Cobalt chromium oxide, CoCr_2O_4	9m	21
Cesium manganese sulfate hydrate, $\text{Cs}_2\text{Mn}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	20	Cobalt copper tin, CoCu_2Sn	14m	64
Cesium mercury chloride, CsHgCl_3 ..	7m	22	Cobalt dysprosium, Co_2Dy	13m	63
Cesium nickel(II) chloride, CsNiCl_3	6m	12	Cobalt erbium, Co_2Er	13m	64
Cesium nickel sulfate hydrate, $\text{Cs}_2\text{Ni}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	23	Cobalt erbium, Co_7Er_2	13m	65
Cesium nitrate, CsNO_3	9	25	Cobalt fluoride, CoF_2	10m	85
Cesium osmium(IV) bromide, Cs_2OsBr_6	2m	10	Cobalt fluoride hydrate, $\text{CoF}_2 \cdot 4\text{H}_2\text{O}$	11m	24
			Cobalt gadolinium, CoGd_3	13m	68
			Cobalt gadolinium, Co_2Gd	13m	71
			Cobalt gadolinium, Co_7Gd_2	13m	72
			Cobalt gallium hafnium, Co_2GaHf ...	14m	65
			Cobalt gallium manganese, Co_2GaMn	13m	75
			Cobalt gallium niobium, $\text{Co}_{1.5}\text{Ga}_{0.5}\text{Nb}$	15m	144
			Cobalt gallium niobium, Co_2GaNb ...	14m	66
			Cobalt gallium oxide, CoGa_2O_4	10	27
			Cobalt gallium tantalum, $\text{Co}_{1.5}\text{Ga}_{0.5}\text{Ta}$	15m	146

	Vol. or Sec.	Page		Vol. or Sec.	Page
Cobalt gallium tantalum, Co_2GaTa	13m	76	Cobalt ruthenium sulfide, Co_8RuS_8 ..	14m	100
Cobalt gallium titanium, Co_2GaTi ..	13m	77	Cobalt samarium, Co_2Sm	15m	173
Cobalt gallium vanadium, Co_2GaV ...	13m	78	Cobalt samarium, Co_5Sm	13m	90
Cobalt germanium, Co_3Ge_2	14m	67	Cobalt silicate, Co_2SiO_4		
Cobalt germanium, Co_5Ge_7	15m	148	(orthorhombic)	4m	11
Cobalt germanium hafnium,			Cobalt silicon fluoride hydrate,		
$\text{Co}_{16}\text{Ge}_7\text{Hf}_6$	14m	69	$\text{CoSiF}_6 \cdot 6\text{H}_2\text{O}$	3m	27
Cobalt germanium manganese,			Cobalt sulfate, $\beta\text{-CoSO}_4$	2m	14
Co_2GeMn	13m	79	Cobalt tantalum silicide,		
Cobalt germanium niobium,			$\text{Co}_{16}\text{Ta}_6\text{Si}_7$	14m	102
$\text{Co}_{1.5}\text{Ge}_{0.5}\text{Nb}$	15m	150	Cobalt thorium, $\text{Co}_{17}\text{Th}_2$	12m	64
Cobalt germanium niobium,			Cobalt tin, Co_3Sn_2	13m	92
$\text{Co}_{16}\text{Ge}_7\text{Nb}_6$	14m	71	Cobalt tin oxide, Co_2SnO_4	15m	30
Cobalt germanium oxide, Co_2GeO_4 ...	10	27	Cobalt tin vanadium, Co_2SnV	15m	174
Cobalt germanium tantalum,			Cobalt tin zirconium, Co_2SnZr	15m	175
$\text{Co}_{1.5}\text{Ge}_{0.5}\text{Ta}$	15m	152	Cobalt titanium oxide, CoTiO_3	4m	13
Cobalt germanium tantalum,			Cobalt titanium silicide,		
$\text{Co}_{16}\text{Ge}_7\text{Ta}_6$	14m	73	$\text{Co}_{16}\text{Ti}_6\text{Si}_7$	14m	104
Cobalt germanium titanium, Co_2GeTi	13m	80	Cobalt tungsten oxide, CoWO_4	4m	13
Cobalt hafnium tin, Co_2HfSn	14m	75	Cobalt vanadium silicide, Co_2VSi ..	15m	176
Cobalt holmium, Co_2Ho	14m	76	Copper, Cu	1	15
Cobalt holmium, $\text{Co}_{9.2}\text{Ho}_{12}$	15m	154	Copper ammine selenate,		
Cobalt hydroxide, $\beta\text{-Co(OH)}_2$	15m	29	$\text{Cu(NH}_3)_4\text{SeO}_4$	10m	87
Cobalt indium, CoIn_3	13m	81	Copper ammine sulfate hydrate,		
Cobalt iodide, CoI_2	4m	52	$\text{Cu(NH}_3)_4\text{SO}_4 \cdot \text{H}_2\text{O}$	10m	90
Cobalt iron arsenide			Copper antimony oxide, CuSb_2O_6	5m	27
(safflorite), CoFeAs_4	10	28	Copper arsenate (trippkeite),		
Cobalt iron oxide, CoFe_2O_4	9m	22	CuAs_2O_4	16m	120
Cobalt iron sulfide, Co_8FeS_8	14m	77	Copper(I) bromide, CuBr	4	36
Cobalt iron vanadium,			Copper(I) chloride (nantokite),		
$\text{Co}_{4.35}\text{Fe}_{13.47}\text{V}_{12.18}$	14m	79	CuCl	4	35
Cobalt lanthanum, CoLa_3	13m	83	Copper fluoride hydrate, $\text{CuF}_2 \cdot 2\text{H}_2\text{O}$	11m	25
Cobalt lutetium, Co_2Lu	13m	86	Copper hydrogen phosphite hydrate,		
Cobalt magnesium, Co_2Mg	15m	156	$\text{CuHPO}_3 \cdot 2\text{H}_2\text{O}$	11m	83
Cobalt manganese silicide, Co_2MnSi	14m	81	Copper hydroxide carbonate,		
Cobalt mercury thiocyanate,			azurite, $\text{Cu}_3(\text{OH})_2(\text{CO}_3)_2$	10	30
$\text{Co}[\text{Hg(CNS)}_4]$	2m	13	Copper hydroxide carbonate		
Cobalt molybdenum, Co_2Mo	14m	82	(malachite), $\text{Cu}_2(\text{OH})_2\text{CO}_3$	10	31
Cobalt molybdenum, Co_2Mo_3	15m	158	Copper(I) iodide (marshite), CuI ..	4	38
Cobalt molybdenum, Co_7Mo_6	15m	160	Copper lead hydroxide sulfate,		
Cobalt molybdenum silicide,			linarite, $\text{CuPb(OH)}_2(\text{SO}_4)$	16m	34
$\text{Co}_3\text{Mo}_2\text{Si}$	15m	162	Copper(I) oxide (cuprite), Cu_2O ...	2	23
Cobalt neodymium, Co_2Nd	13m	87	Copper(II) oxide (tenorite), CuO ..	1	49
Cobalt nickel tin,			Copper phosphate, $\text{Cu(PO}_3)_2$	14m	15
$\text{Co}_{.75}\text{Ni}_{.75}\text{Sn}_{.75}$	13m	88	Copper phosphate, $\alpha\text{-Cu}_2\text{P}_2\text{O}_7$	7m	113
Cobalt niobium silicide, $\text{Co}_3\text{Nb}_4\text{Si}_7$	15m	164	Copper sulfate (chalcocyanite),		
Cobalt niobium tin, Co_2NbSn	15m	166	CuSO_4	3m	29
Cobalt nitrate hydrate,			Copper(II) sulfide (covellite), CuS	4	13
$\alpha\text{-Co(NO}_3)_2 \cdot 6\text{H}_2\text{O}$	12m	22	Copper uranium oxide, CuUO_4	10m	93
Cobalt(II) oxide, CoO	9	28	Dichlorotetraaquo chromium (III)		
Cobalt(II,III) oxide, Co_3O_4	9	29	chloride dihydrate, $[\text{Cr(H}_2\text{O)}_4\text{Cl}_2]$		
Cobalt phosphate, $\text{Co(PO}_3)_2$	13m	23	$\text{Cl} \cdot 2\text{H}_2\text{O}$	16m	31
Cobalt phosphide, CoP	14m	83	Dysprosium arsenate, DyAsO_4	3m	30
Cobalt phosphide, CoP_3	14m	85	Dysprosium arsenide, DyAs	4m	53
Cobalt platinum, CoPt (disordered)	15m	167	Dysprosium gallium oxide,		
Cobalt platinum, CoPt (ordered) ...	15m	168	$\text{Dy}_3\text{Ga}_5\text{O}_{12}$	2m	15
Cobalt platinum, CoPt_3			Dysprosium gold, DyAu	5m	66
(disordered)	15m	169	Dysprosium nitride, DyN	4m	53
Cobalt platinum, CoPt_3 (ordered)...	15m	170	Dysprosium oxide, Dy_2O_3	9	30
Cobalt plutonium, CoPu_2	14m	87	Dysprosium silver, DyAg	5m	66
Cobalt plutonium, CoPu_3	15m	171	Dysprosium telluride, DyTe	4m	54
Cobalt plutonium, CoPu_6	14m	89	Dysprosium vanadium oxide, DyVO_4 ..	4m	15
Cobalt plutonium, Co_2Pu	14m	91	Erbium arsenate, ErAsO_4	3m	31
Cobalt plutonium, Co_3Pu	14m	92	Erbium arsenide, ErAs	4m	54
Cobalt plutonium, $\text{Co}_{17}\text{Pu}_2$	14m	94	Erbium gallium oxide, $\text{Er}_3\text{Ga}_5\text{O}_{12}$...	1m	12
Cobalt praseodymium, Co_2Pr	14m	97	Erbium manganese oxide, ErMnO_3	2m	16
Cobalt rhodium sulfide, Co_8RhS_8	14m	98	Erbium nitride, ErN	4m	55

	Vol. or Sec.	Page		Vol. or Sec.	Page
Erbium oxide, Er_2O_3	8	25	Hydrogen amidosulfate, $\text{H}_2\text{NSO}_3\text{H}$	7	54
Erbium phosphate, ErPO_4	9	31	Hydrogen arsenate, $\text{H}_5\text{As}_3\text{O}_{10}$	7m	84
Erbium silver, ErAg	5m	67	Hydrogen borate, $\beta\text{-HBO}_2$ (monoclinic)	9m	71
Erbium telluride, ErTe	4m	55	Hydrogen borate (metaborite),		
Erbium vanadium oxide, ErVO_4	5m	29	HBO_2 (cubic)	4m	27
Europium arsenate, EuAsO_4	3m	32	Hydrogen iodate, HIO_3	5	28
Europium(III) chloride, EuCl_3	1m	13	Hydrogen iodate, HI_3O_8	8m	104
Europium chloride oxide, EuClO	1m	13	Hydrogen phosphate hydrate,		
Europium gallium oxide,			$\text{H}_3\text{PO}_4 \cdot 0.5\text{H}_2\text{O}$	12m	56
$\text{Eu}_3\text{Ga}_5\text{O}_{12}$	2m	17	Hydrogen tellurate, H_6TeO_6	12m	34
Europium nitride, EuN	4m	56	Indium, In	3	12
Europium oxide, EuO	4m	56	Indium arsenide, InAs	3m	35
Europium phosphate, EuPO_4	11m	26	Indium oxide, In_2O_3	5	26
Europium(III) vanadium oxide, EuVO_4	4m	16	Indium phosphate, InPO_4	8	29
Gadolinium arsenate, GdAsO_4	4m	17	Indium sulfide, In_2S_3	11m	30
Gadolinium arsenide, GdAs	4m	57	Iodine, I_2	3	16
Gadolinium chloride hydrate,			Iridium, Ir	4	9
$\text{GdCl}_3 \cdot 6\text{H}_2\text{O}$	7m	118	Iridium niobium, IrNb_3	6m	19
Gadolinium chloride oxide, GdClO ..	1m	17	Iridium oxide, IrO_2	4m	19
Gadolinium fluoride, GdF_3	1m	14	Iridium titanium, IrTi_3	6m	20
Gadolinium gallium oxide,			Iridium vanadium, IrV_3	6m	21
$\text{Gd}_3\text{Ga}_5\text{O}_{12}$	2m	18	Iron, $\alpha\text{-Fe}$	4	3
Gadolinium indium, GdIn	5m	67	Iron arsenide, FeAs	1m	19
Gadolinium nitride, GdN	4m	57	Iron arsenide (loellingite), FeAs_2	10	34
Gadolinium oxide, Gd_2O_3	1m	16	Iron bromide, FeBr_2	4m	59
Gadolinium silver, GdAg	6m	87	Iron carbonate, siderite, FeCO_3 ...	15m	32
Gadolinium titanium oxide, Gd_2TiO_5	8m	32	Iron chloride hydrate, $\text{FeCl}_2 \cdot 2\text{H}_2\text{O}$	11m	32
Gadolinium vanadium oxide, GdVO_4 ..	5m	30	Iron fluoride hydrate, $\text{FeF}_2 \cdot 4\text{H}_2\text{O}$	11m	90
Gallium, Ga	2	9	Iron hydroxide sulfate hydrate,		
Gallium arsenide, GaAs	3m	33	butlerite, $\text{Fe}(\text{OH})\text{SO}_4 \cdot 2\text{H}_2\text{O}$	10m	95
Gallium lutetium oxide, $\text{Ga}_5\text{Lu}_3\text{O}_{12}$	2m	22	Iron iodide, FeI_2	4m	60
Gallium magnesium, Ga_2Mg	12m	48	Iron(II,III) oxide (magnetite),		
Gallium magnesium, Ga_5Mg_2	12m	51	Fe_3O_4	5m	31
Gallium neodymium oxide, $\text{Ga}_5\text{Nd}_3\text{O}_{12}$	1m	34	Iron phosphate, FePO_4	15m	33
Gallium oxide, $\alpha\text{-Ga}_2\text{O}_3$	4	25	Iron phosphate hydrate (vivianite),		
Gallium phosphate (α -quartz type),			$\text{Fe}_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$	16m	38
GaPO_4	8	27	Iron sulfate, $\text{Fe}_2(\text{SO}_4)_3$	16m	39
Gallium phosphate hydrate,			Iron sulfate hydrate (melanterite),		
$\text{GaPO}_4 \cdot 2\text{H}_2\text{O}$	8m	34	$\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$	8m	38
Gallium samarium oxide, $\text{Ga}_5\text{Sm}_3\text{O}_{12}$	1m	42	Iron sulfide (pyrite), FeS_2	5	29
Gallium ytterbium oxide, $\text{Ga}_5\text{Yb}_3\text{O}_{12}$	1m	49	Iron thorium, $\text{Fe}_{17}\text{Th}_2$	12m	67
Gallium yttrium oxide, $\text{Ga}_5\text{Y}_3\text{O}_{12}$...	1m	50	Iron titanium oxide (ilmenite),		
Germanium, Ge	1	18	FeTiO_3	15m	34
Germanium iodide, GeI_2	4m	58	Lanthanum arsenate, LaAsO_4	3m	36
Germanium(IV) iodide, GeI_4	5	25	Lanthanum arsenide, LaAs	4m	60
Germanium oxide, GeO_2 (hexagonal)			Lanthanum borate, LaBO_3	1m	20
(low form)	1	51	Lanthanum chloride, LaCl_3	1m	20
Germanium oxide, GeO_2			Lanthanum chloride oxide, LaClO ...	7	22
(tetragonal) (high form)	8	28	Lanthanum fluoride, LaF_3	7	21
Gold, Au	1	33	Lanthanum magnesium, LaMg	5m	69
Gold chloride, AuCl	16m	37	Lanthanum niobium titanium oxide,		
Gold(I) cyanide, AuCN	10	33	LaNbTiO_6	3m	37
Gold holmium, AuHo	5m	68	Lanthanum nitrate hydrate,		
Gold magnesium, AuMg	6m	83	$\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$	8m	40
Gold niobium, AuNb_3	6m	16	Lanthanum nitride, LaN	4m	61
Gold potassium cyanide, $\text{AuK}(\text{CN})_2$..	8m	36	Lanthanum oxide, La_2O_3	3	33
Gold tin, AuSn	7	19	Lanthanum phosphide, LaP	5m	69
Gold titanium, AuTi_3	6m	17	Lanthanum selenide, LaSe	4m	61
Gold vanadium, AuV_3	6m	18	Lanthanum titanium oxide, $\text{La}_2\text{Ti}_2\text{O}_7$	15m	35
Hafnium, Hf	3	18	Lanthanum zinc, LaZn	5m	70
Holmium arsenate, HoAsO_4	3m	34	Lead, Pb	1	34
Holmium fluoride, HoF_3	10m	23	Lead borate, PbB_4O_7	4m	19
Holmium nitride, HoN	4m	58	Lead bromide, PbBr_2	2	47
Holmium oxide, Ho_2O_3	9	32	Lead bromide chloride, PbBrCl	11m	33
Holmium selenide, HoSe	4m	59	Lead bromide fluoride, PbBrF	10m	25
Holmium silver, HoAg	5m	68	Lead bromide hydroxide, $\text{PbBr}(\text{OH})$..	16m	40
Holmium vanadium oxide, HoVO_4	4m	18	Lead bromide oxide, $\text{Pb}_3\text{O}_2\text{Br}_2$	5m	32

	Vol. or Sec.	Page		Vol. or Sec.	Page
Lead carbonate (cerussite), PbCO_3	2	56	Lithium phosphate, low form (lithiophosphate), Li_3PO_4	4m	21
Lead chloride (cotunnite), PbCl_2	12m	23	Lithium phosphate, high form, Li_3PO_4	3m	39
Lead chloride fluoride (matlockite), PbClF	13m	25	Lithium potassium sulfate, KLiSO_4	3m	43
Lead chromium oxide, Pb_2CrO_5	14m	16	Lithium rubidium fluoride, LiRbF_2	7m	128
Lead fluoride, $\alpha\text{-PbF}_2$ (orthorhombic)	5	31	Lithium selenide, Li_2Se	10m	100
Lead fluoride, $\beta\text{-PbF}_2$ (cubic)	5	33	Lithium silicate, Li_2SiO_3	14m	19
Lead fluoride iodide, PbFI	10m	26	Lithium silver bromide, $\text{Li}_{.2}\text{Ag}_{.8}\text{Br}$	12m	55
Lead hydrogen arsenate (schultenite), PbHAsO_4	14m	18	Lithium silver bromide, $\text{Li}_{.4}\text{Ag}_{.6}\text{Br}$	12m	55
Lead hydrogen phosphate, PbHPO_4	15m	37	Lithium silver bromide, $\text{Li}_{.6}\text{Ag}_{.4}\text{Br}$	12m	55
Lead hydroxide phosphate, $\text{Pb}_5\text{OH}(\text{PO}_4)_3$	8	33	Lithium silver bromide, $\text{Li}_{.8}\text{Ag}_{.2}\text{Br}$	12m	55
Lead(II) iodide, PbI_2	5	34	Lithium sodium aluminum fluoride, cryolithionite, $\text{Li}_3\text{Na}_3\text{Al}_2\text{F}_{12}$	9m	23
Lead molybdenum oxide (wulfenite), PbMoO_4	7	23	Lithium sodium sulfate, LiNaSO_4 ...	6m	24
Lead nitrate, $\text{Pb}(\text{NO}_3)_2$	5	36	Lithium sulfate, Li_2SO_4	6m	26
Lead oxide (litharge), PbO (red, tetragonal)	2	30	Lithium sulfate hydrate, $\text{Li}_2\text{SO}_4 \cdot \text{H}_2\text{O}$	4m	22
Lead oxide (massicot), PbO (yellow, orthorhombic)	2	32	Lithium sulfide, Li_2S	10m	101
Lead(II,III) oxide (minium), Pb_3O_4	8	32	Lithium tantalum oxide, LiTaO_3	14m	20
Lead oxide sulfate, $\text{Pb}_5\text{O}_5\text{SO}_4$	10m	27	Lithium telluride, Li_2Te	10m	102
Lead selenide (clausthalite), PbSe	5	38	Lithium tin oxide, Li_2SnO_3	16m	45
Lead strontium nitrate, $\text{Pb}_{.33}\text{Sr}_{.67}(\text{NO}_3)_2$	12m	53	Lithium tungsten oxide, Li_2WO_4 (trigonal)	1m	25
Lead strontium nitrate, $\text{Pb}_{.67}\text{Sr}_{.33}(\text{NO}_3)_2$	12m	53	Lithium tungsten oxide hydrate, $\text{Li}_2\text{WO}_4 \cdot 0.5\text{H}_2\text{O}$	2m	20
Lead sulfate (anglesite), PbSO_4 ...	3	67	Lithium uranium fluoride, LiUF_5 ...	7m	131
Lead sulfide (galena), PbS	2	18	Lutetium arsenate, LuAsO_4	5m	36
Lead tin oxide, Pb_2SnO_4	10m	29	Lutetium manganese oxide, LuMnO_3 ..	2m	23
Lead titanium oxide (macedonite), PbTiO_3	5	39	Lutetium nitride, LuN	4m	62
Lead tungsten oxide (stolzite), PbWO_4 (tetragonal)	5m	34	Lutetium oxide, Lu_2O_3	1m	27
Lead uranium oxide, Pb_3UO_6	8m	109	Lutetium vanadium oxide, LuVO_4	5m	37
Lithium aluminum fluoride, $\alpha\text{-Li}_3\text{AlF}_6$	8m	111	Magnesium, Mg	1	10
Lithium arsenate, Li_3AsO_4	2m	19	Magnesium aluminum oxide (spinel), MgAl_2O_4	9m	25
Lithium azide, LiN_3	8m	113	Magnesium aluminum silicate (low cordierite), $\text{Mg}_2\text{Al}_4\text{Si}_5\text{O}_{18}$ (orthorhombic)	1m	28
Lithium barium fluoride, LiBaF_3 ...	5m	35	Magnesium aluminum silicate (indialite) $\text{Mg}_2\text{Al}_4\text{Si}_5\text{O}_{18}$ (hexagonal)	1m	29
Lithium beryllium fluoride, Li_2BeF_4	7m	126	Magnesium aluminum silicate (pyrope), $\text{Mg}_3\text{Al}_2(\text{SiO}_4)_2$	4m	24
Lithium borate, $\text{Li}_2\text{B}_4\text{O}_7$	8m	114	Magnesium borate, $\text{Mg}_2\text{B}_2\text{O}_5$ (triclinic)	4m	25
Lithium bromide, LiBr	4	30	Magnesium bromide, MgBr_2	4m	62
Lithium calcium aluminum boron hydroxy silicate, liddicoatite, $\text{Ca}(\text{Li},\text{Al})_3\text{Al}_6\text{B}_3\text{Si}_6\text{O}_{27}(\text{O},\text{OH})_3(\text{OH},\text{F})$	16m	42	Magnesium bromide hydrate, $\text{MgBr}_2 \cdot 6\text{H}_2\text{O}$	11m	35
Lithium carbonate, Li_2CO_3	8m	42	Magnesium carbonate (magnesite), MgCO_3	7	28
Lithium chlorate hydrate, $\text{LiClO}_4 \cdot 3\text{H}_2\text{O}$	8	34	Magnesium cerium nitrate hydrate, $\text{Mg}_3\text{Ce}_2(\text{NO}_3)_{12} \cdot 24\text{H}_2\text{O}$	10	20
Lithium chloride, LiCl	1	62	Magnesium chlorate hydrate, $\text{Mg}(\text{ClO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	30
Lithium chromium oxide hydrate, $\text{Li}_2\text{CrO}_4 \cdot 2\text{H}_2\text{O}$	16m	44	Magnesium chloride (chloro- magnesite), MgCl_2	11m	94
Lithium fluoride, LiF	1	61	Magnesium chloride hydrate, $\text{MgCl}_2 \cdot 12\text{H}_2\text{O}$	7m	135
Lithium gallium oxide, LiGaO_2	10m	31	Magnesium chloride hydrate (bischofite), $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$	11m	37
Lithium hydroxide hydrate, $\text{LiOH} \cdot \text{H}_2\text{O}$	11m	92	Magnesium chromium oxide (magnesiocromite), MgCr_2O_4	9	34
Lithium iodate, LiIO_3 (hexagonal)	7	26			
Lithium iodate, LiIO_3 (tetragonal)	10m	33			
Lithium molybdenum oxide, Li_2MoO_4 (trigonal)	1m	23			
Lithium niobium oxide, LiNbO_3	6m	22			
Lithium nitrate, LiNO_3	7	27			
Lithium oxide, Li_2O	1m	25			
Lithium phosphate hydrate, $\text{Li}_3\text{P}_3\text{O}_9 \cdot 3\text{H}_2\text{O}$	2m	20			

	Vol. or Sec.	Page		Vol. or Sec.	Page
Magnesium chromium oxide hydrate, MgCrO ₄ ·5H ₂ O	15m	39	Manganese iron oxide (jacobsonite), MnFe ₂ O ₄	9	36
Magnesium fluoride (sellaite), MgF ₂	4	33	Manganese(II) oxide (manganosite), MnO	5	45
Magnesium fluoride silicate (humite), Mg ₇ F ₂ Si ₃ O ₁₂	1m	30	Manganese oxide (pyrolusite), β-MnO ₂	10m	39
Magnesium fluoride silicate (norbergite), Mg ₃ F ₂ SiO ₄	10	39	Manganese oxide (bixbyite), α-Mn ₂ O ₃	11m	95
Magnesium gallium oxide, MgGa ₂ O ₄ ..	10	36	Manganese oxide (hausmannite), Mn ₃ O ₄	10m	38
Magnesium germanium oxide, Mg ₂ GeO ₄ (cubic)	10	37	Manganese oxide hydroxide, groutite, α-MnOOH	11m	97
Magnesium germanium oxide, Mg ₂ GeO ₄ (orthorhombic)	10	38	Manganese phosphate, Mn(PO ₃) ₂	14m	21
Magnesium hydrogen phosphate hydrate, newberyite, MgHPO ₄ ·3H ₂ O	7m	139	Manganese phosphate, Mn ₂ P ₂ O ₇	15m	41
Magnesium hydroxide (brucite), Mg(OH) ₂	6	30	Manganese phosphate, Mn ₃ (PO ₄) ₂	16m	47
Magnesium iron hydroxide carbonate hydrate, pyroaurite, Mg ₆ Fe ₂ (OH) ₁₆ CO ₃ ·4H ₂ O (rhomb.)	10m	104	Manganese selenide, MnSe	10	41
Magnesium iron hydroxide carbonate hydrate, sjögrenite, Mg ₆ Fe ₂ (OH) ₁₆ CO ₃ ·4H ₂ O, (hexag.) ...	10m	103	Manganese sulfate hydrate (szmikite), MnSO ₄ ·H ₂ O	16m	49
Magnesium lanthanum nitrate hydrate, Mg ₃ La ₂ (NO ₃) ₁₂ ·24H ₂ O	1m	22	Manganese sulfide (alabandite), α-MnS	4	11
Magnesium manganese oxide, MgMn ₂ O ₄	10m	35	Manganese titanium oxide (pyrophanite), MnTiO ₃	15m	42
Magnesium mercury, MgHg	6m	84	Manganese(II) tungsten oxide (huebnerite), MnWO ₄	2m	24
Magnesium molybdenum oxide, MgMoO ₄	7m	28	Manganese vanadium oxide, Mn ₂ V ₂ O ₇	9m	75
Magnesium nickel oxide, MgNiO ₂	10m	36	Mercury amide chloride, HgNH ₂ Cl ...	10m	40
Magnesium oxide (periclase), MgO ..	1	37	Mercury ammine chloride, Hg(NH ₃) ₂ Cl ₂	11m	39
Magnesium phosphate, Mg(PO ₃) ₂	13m	26	Mercury bromate, Hg(BrO ₃) ₂	10m	107
Magnesium phosphate, α-Mg ₂ P ₂ O ₇	9m	73	Mercury bromide, HgBr ₂	10m	110
Magnesium selenide, MgSe	5m	70	Mercury bromide, Hg ₂ Br ₂	7	33
Magnesium selenite hydrate, MgSeO ₃ ·6H ₂ O	8m	116	Mercury chloride, HgCl ₂	13m	29
Magnesium silicate, enstatite, MgSiO ₃	6	32	Mercury chloride (calomel), Hg ₂ Cl ₂	13m	30
Magnesium silicate (forsterite), Mg ₂ SiO ₄	1	83	Mercury chloride sulfide, α-Hg ₃ Cl ₂ S ₂	8m	118
Magnesium sulfate hydrate (kieserite), MgSO ₄ ·H ₂ O	16m	46	Mercury(II) cyanide, Hg(CN) ₂	6	35
Magnesium sulfate hydrate (epsomite), MgSO ₄ ·7H ₂ O	7	30	Mercury(II) fluoride, HgF ₂	2m	25
Magnesium sulfide, MgS	7	31	Mercury(I) iodide, HgI	4	49
Magnesium sulfite hydrate, MgSO ₃ ·6H ₂ O	9m	26	Mercury(II) iodide, HgI ₂ (tetragonal)	7m	32
Magnesium tin, Mg ₂ Sn	5	41	Mercury(II) oxide (montroydite), HgO	9	39
Magnesium tin oxide, Mg ₂ SnO ₄	10m	37	Mercury(II) selenide (tiemannite), HgSe	7	35
Magnesium titanium oxide (geikielite), MgTiO ₃	5	43	Mercury sulfate, HgSO ₄	16m	50
Magnesium titanium oxide, Mg ₂ TiO ₄	12m	25	Mercury sulfite, Hg ₂ SO ₄	16m	52
Magnesium tungsten oxide, MgWO ₄ ...	13m	27	Mercury(II) sulfide (cinnabar), HgS (hexagonal)	4	17
Manganese, α-Mn	7m	142	Mercury(II) sulfide (metacinnabar), HgS (cubic)	4	21
Manganese aluminum oxide (galaxite), MnAl ₂ O ₄	9	35	Molybdenum, Mo	1	20
Manganese bromide, MnBr ₂	4m	63	Molybdenum arsenide, Mo ₂ As ₃	10m	115
Manganese(II) carbonate (rhodochrosite), MnCO ₃	7	32	Molybdenum osmium, Mo ₃ Os	6m	28
Manganese chloride (scacchite), MnCl ₂	8m	43	Molybdenum oxide (molybdite), MoO ₃	3	30
Manganese chloride hydrate, MnCl ₂ ·2H ₂ O	11m	38	Molybdenum sulfide (molybdenite), MoS ₂	5	47
Manganese chloride hydrate, MnCl ₂ ·4H ₂ O	9m	28	Neodymium arsenate, NdAsO ₄	4m	28
Manganese cobalt oxide, MnCo ₂ O ₄ ...	9m	30	Neodymium arsenide, NdAs	4m	64
Manganese fluoride, MnF ₂	10m	105	Neodymium borate, NdBO ₃	1m	32
Manganese iodide, MnI ₂	4m	63	Neodymium chloride, NdCl ₃	1m	33
			Neodymium chloride oxide, NdOCl	8	37
			Neodymium fluoride, NdF ₃	8	36
			Neodymium oxide, Nd ₂ O ₃	4	26
			Neodymium phosphate, NdPO ₄	11m	40
			Neodymium selenide, NdSe	5m	71
			Neodymium silver, NdAg	5m	71
			Neodymium vanadium oxide, NdVO ₄ ...	4m	30
			Neptunium nitride, NpN	4m	64
			Nickel, Ni	1	13

	Vol. or Sec.	Page		Vol. or Sec.	Page
Nickel aluminum oxide, NiAl_2O_4	9	42	Potassium barium nickel nitrite, $\text{K}_2\text{BaNi}(\text{NO}_2)_6$	9m	32
Nickel arsenide (rammelsbergite), NiAs_2	10	42	Potassium borate hydroxide hydrate, $\text{K}_2\text{B}_4\text{O}_5(\text{OH})_4 \cdot 2\text{H}_2\text{O}$	15m	46
Nickel arsenic sulfide (gersdorffite), NiAsS	1m	35	Potassium boron hydride, KBH_4	9	44
Nickel bromide, NiBr_2	10m	119	Potassium bromate, KBrO_3	7	38
Nickel(II) carbonate, NiCO_3 (trigonal)	1m	36	Potassium bromide, KBr	1	66
Nickel chloride, NiCl_2	9m	81	Potassium bromide chloride, $\text{KBr}_{0.5}\text{Cl}_{0.5}$	8m	46
Nickel chloride hydrate, $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$	11m	42	Potassium bromide iodide, $\text{KBr}_{.33}\text{I}_{.67}$	11m	44
Nickel fluoride, NiF_2	10m	121	Potassium bromide iodide, $\text{KBr}_{.67}\text{I}_{.33}$	11m	45
Nickel fluoride hydrate, $\text{NiF}_2 \cdot 4\text{H}_2\text{O}$	11m	43	Potassium cadmium fluoride, KCaF_3	8m	47
Nickel gallium oxide, NiGa_2O_4	10	45	Potassium cadmium sulfate, $\text{K}_2\text{Cd}_2(\text{SO}_4)_3$	7m	34
Nickel germanium oxide, Ni_2GeO_4 ...	9	43	Potassium calcium carbonate (fairchildite), $\text{K}_2\text{Ca}(\text{CO}_3)_2$	8m	48
Nickel iron oxide (trevorite), NiFe_2O_4	10	44	Potassium calcium chloride, KCaCl_3	7m	36
Nickel nitrate hydrate, $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$	12m	26	Potassium calcium fluoride, KCaF_3	8m	49
Nickel(II) oxide (bunsenite), NiO	1	47	Potassium calcium magnesium sulfate, $\text{K}_2\text{CaMg}(\text{SO}_4)_3$	7m	37
Nickel phosphate, $\text{Ni}(\text{PO}_3)_2$	14m	22	Potassium calcium nickel nitrite, $\text{K}_2\text{CaNi}(\text{NO}_2)_6$	9m	33
Nickel phosphide, Ni_{12}P_5	9m	83	Potassium calcium sulfate, $\text{K}_2\text{Ca}_2(\text{SO}_4)_3$	7m	39
Nickel silicon fluoride hydrate, $\text{NiSiF}_6 \cdot 6\text{H}_2\text{O}$	8	38	Potassium calcium sulfate hydrate (syngenite), $\text{K}_2\text{Ca}(\text{SO}_4)_2 \cdot \text{H}_2\text{O}$	14m	25
Nickel sulfate, NiSO_4	2m	26	Potassium cerium fluoride, $\beta\text{-KCeF}_4$	12m	59
Nickel sulfate hydrate (retgersite), $\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$	7	36	Potassium chlorate, KClO_3	3m	42
Nickel sulfide, millerite, NiS	1m	37	Potassium chlorate, KClO_4	6	43
Nickel tungsten oxide, NiWO_4	2m	27	Potassium chloride (sylvite), KCl	1	65
Nickel yttrium, Ni_3Y	10m	123	Potassium chromium oxide, K_3CrO_8 ..	3m	44
Niobium chloride oxide, NbCl_3O	7m	148	Potassium chromium oxide (lopezite), $\text{K}_2\text{Cr}_2\text{O}_7$	15m	47
Niobium osmium, Nb_3Os	6m	30	Potassium chromium oxide sulfate, $\text{K}_2(\text{CrO}_4)_{.33}(\text{SO}_4)_{.67}$	12m	28
Niobium platinum, Nb_3Pt	6m	31	Potassium chromium oxide sulfate, $\text{K}_2(\text{CrO}_4)_{.67}(\text{SO}_4)_{.33}$	12m	27
Niobium silicide, NbSi_2	8	39	Potassium chromium sulfate, $\text{KCr}(\text{SO}_4)_2$	16m	58
Niobium silicide, $\alpha\text{-Nb}_5\text{Si}_3$	15m	43	Potassium chromium sulfate hydrate, $\text{KCr}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	39
Niobium silicide, $\beta\text{-Nb}_5\text{Si}_3$	15m	44	Potassium cobalt(II) fluoride, KCoF_3	6m	37
Osmium, Os	4	8	Potassium cobalt fluoride, K_2CoF_4	11m	46
Osmium titanium, OsTi	6m	85	Potassium cobalt nitrite, $\text{K}_3\text{Co}(\text{NO}_2)_6$	9	45
Palladium, Pd	1	21	Potassium cobalt(II) sulfate, $\text{K}_2\text{Co}_2(\text{SO}_4)_3$	6m	35
Palladium hydride, $\text{PdH}_{0.706}$	5m	72	Potassium copper chloride, KCuCl_3	7m	41
Palladium oxide, PdO	4	27	Potassium copper chloride hydrate (mitscherlichite), $\text{K}_2\text{CuCl}_4 \cdot 2\text{H}_2\text{O}$..	9m	34
Palladium selenium (palladseite), $\text{Pd}_{17}\text{Se}_{15}$	16m	139	Potassium copper(II) fluoride, KCuF_3	6m	38
Palladium vanadium, PdV_3	6m	32	Potassium cyanate, KCNO	7	39
Phosphorus bromide, PBr_7	7m	150	Potassium cyanide, KCN	1	77
Phosphorus oxide (stable form I), P_2O_5 (orthorhombic)	9m	86	Potassium fluoride, KF	1	64
Phosphorus oxide (stable form II), P_2O_5 (orthorhombic)	9m	88	Potassium germanium fluoride, K_2GeF_6	6	41
Phosphorus oxide (metastable form), P_4O_{10} (rhombohedral)	9m	91	Potassium hydrogen arsenate, KH_2AsO_4	1m	38
Platinum, Pt	1	31	Potassium hydrogen phosphate, KH_2PO_4	3	69
Platinum titanium, PtTi_3	6m	33	Potassium hydroxide, KOH at 300 °C	4m	66
Platinum vanadium, PtV_3	6m	34	Potassium iodate, KIO_3	15m	48
Plutonium arsenide, PuAs	4m	65	Potassium iodate, KIO_4	7	41
Plutonium phosphide, PuP	4m	65			
Plutonium telluride, PuTe	4m	66			
Potassium aluminum sulfate, $\text{KAl}(\text{SO}_4)_2$	9m	31			
Potassium aluminum sulfate hydrate (potash alum), $\text{KAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$...	6	36			
Potassium barium chromium oxide, $\text{K}_2\text{Ba}(\text{CrO}_4)_2$	14m	23			
Potassium barium iron titanium oxide, $\text{K}_{1.16}\text{Ba}_{0.72}\text{Fe}_{0.36}\text{Ti}_{5.58}\text{O}_{13}$..	16m	147			
Potassium barium molybdenum oxide, $\text{K}_2\text{Ba}(\text{MoO}_4)_2$	14m	24			

	Vol. or Sec.	Page		Vol. or Sec.	Page
Potassium iodide, KI	1	68	Potassium silicon fluoride (hieratite), K_2SiF_6	5	50
Potassium iron chloride hydrate (erythrosiderite), $K_2FeCl_5 \cdot H_2O$...	14m	27	Potassium silver cyanide, $KAg(CN)_2$	8m	78
Potassium iron cyanide, $K_3Fe(CN)_6$	9m	35	Potassium sodium aluminum fluoride (elpasolite), K_2NaAlF_6	9m	43
Potassium iron(II) fluoride, $KFeF_3$	6m	39	Potassium sodium bromide, K_2Na_8Br	12m	62
Potassium iron fluoride, K_3FeF_6 ...	9m	37	Potassium sodium bromide, K_4Na_6Br	12m	62
Potassium iron sulfate (yavapaiite), $KFe(SO_4)_2$	16m	59	Potassium sodium bromide, K_6Na_4Br	12m	62
Potassium lead chloride, KPb_2Cl_5 ..	13m	33	Potassium sodium bromide, K_8Na_2Br	12m	62
Potassium lead chromium oxide, $K_2Pb(CrO_4)_2$	14m	28	Potassium sodium chloride, K_2Na_8Cl	12m	63
Potassium lead molybdenum oxide, $K_2Pb(MoO_4)_2$	14m	29	Potassium sodium chloride, K_4Na_6Cl	12m	63
Potassium lead phosphate, $K_2Pb(PO_3)_4$	15m	50	Potassium sodium chloride, K_6Na_4Cl	12m	63
Potassium lead selenate, $K_2Pb(SeO_4)_2$	15m	52	Potassium sodium chloride, K_8Na_2Cl	12m	63
Potassium lead sulfate (palmierite), $K_2Pb(SO_4)_2$	14m	30	Potassium sodium sulfate, $K_{.67}Na_{1.33}SO_4$	6m	48
Potassium magnesium chloride hydrate (carnallite), $KMgCl_3 \cdot 6H_2O$	8m	50	Potassium sodium sulfate, $KNaSO_4$..	6m	50
Potassium magnesium chromium oxide, $K_2Mg_2(CrO_4)_3$	8m	52	Potassium sodium sulfate (aphthitalite), $K_3Na(SO_4)_2$	6m	52
Potassium magnesium fluoride, $KMgF_3$	6m	42	Potassium strontium chromium oxide, $K_2Sr(CrO_4)_2$	15m	57
Potassium magnesium fluoride, K_2MgF_4	10m	42	Potassium strontium selenate, $K_2Sr(SeO_4)_2$	15m	58
Potassium magnesium selenate hydrate, $K_2Mg(SeO_4)_2 \cdot 6H_2O$	10m	43	Potassium strontium sulfate (kalistrontite), $K_2Sr(SO_4)_2$	14m	31
Potassium magnesium sulfate (langbeinite), $K_2Mg_2(SO_4)_3$	6m	40	Potassium sulfate, $K_2S_2O_7$	9m	99
Potassium magnesium sulfate hydrate (picromerite), $K_2Mg(SO_4)_2 \cdot 6H_2O$	8m	54	Potassium sulfate (arcanite), K_2SO_4	3	62
Potassium manganese(II) fluoride, $KMnF_3$	6m	45	Potassium sulfide, K_2S	10m	127
Potassium manganese oxide, $KMnO_4$	7	42	Potassium telluride, K_2Te	10m	128
Potassium manganese(II) sulfate (manganolangbeinite), $K_2Mn_2(SO_4)_3$	6m	43	Potassium thiocyanate, $KCNS$	8	44
Potassium molybdenum oxide, K_2MoO_4	15m	53	Potassium tin chloride, K_2SnCl_6 ...	6	38
Potassium molybdenum oxide phos- phate hydrate, $K_3(MoO_3)_2 \cdot 4H_2O$	8	43	Potassium titanium fluoride, K_2TiF_6	7	40
Potassium nickel fluoride, $KNiF_3$	7m	42	Potassium tungsten oxide, K_2WO_4 ...	11m	47
Potassium nickel fluoride, K_2NiF_4	10m	45	Potassium vanadium oxide, KV_3O_8 ...	8m	56
Potassium nickel(II) sulfate, $K_2Ni_2(SO_4)_3$	6m	46	Potassium zinc bromide hydrate, $KZnBr_3 \cdot 2H_2O$	11m	104
Potassium niobium fluoride, K_2NbF_7	8m	120	Potassium zinc fluoride, $KZnF_3$	5	51
Potassium nitrate (niter), KNO_3 ...	3	58	Potassium zinc fluoride, K_2ZnF_4 ...	10m	46
Potassium nitrite, KNO_2	9m	38	Potassium zinc iodide hydrate, $KZnI_3 \cdot 2H_2O$	11m	107
Potassium nitrosyl ruthenium chloride, $K_2NORuCl_5$	16m	61	Potassium zinc sulfate, $K_2Zn_2(SO_4)_3$	6m	54
Potassium oxide, K_2O	10m	125	Potassium zinc sulfate hydrate, $K_2Zn(SO_4)_2 \cdot 6H_2O$	7m	43
Potassium platinum bromide, K_2PtBr_6	8	40	Potassium zinc vanadium oxide hydrate, $K_2Zn_2V_{10}O_{28} \cdot 16H_2O$	3m	45
Potassium platinum chloride, K_2PtCl_6	13m	34	Potassium zirconium fluoride, K_3ZrF_7	9	46
Potassium platinum fluoride, K_2PtF_6	6	42	Praseodymium arsenate, $PrAsO_4$	4m	32
Potassium rhenium chloride, K_2ReCl_6	2m	28	Praseodymium arsenide, $PrAs$	4m	67
Potassium rhenium oxide, $KReO_4$	8	41	Praseodymium chloride, $PrCl_3$	1m	39
Potassium rubidium chloride, $K_{.5}Rb_{.5}Cl$	8m	76	Praseodymium chloride oxide, $PrOCl$	9	47
Potassium rubidium chromium oxide, $KRbCrO_4$	12m	29	Praseodymium fluoride, PrF_3	5	52
Potassium ruthenium chloride, K_2RuCl_6	10	46	Praseodymium sulfide, PrS	4m	67
Potassium ruthenium oxide chloride hydrate, $K_4Ru_2OCl_{10} \cdot H_2O$	10	47	Praseodymium vanadium oxide, $PrVO_4$	5m	40
Potassium selenate, K_2SeO_4	9m	41	Praseodymium zinc, $PrZn$	5m	72
Potassium selenide, K_2Se	10m	126	Rhenium, Re	2	13
Potassium selenium bromide, K_2SeBr_6	8	41	Rhodium, Rh	3	9
		174	Rhodium vanadium, RhV_3	6m	56
			Rubidium aluminum sulfate hydrate, $RbAl(SO_4)_2 \cdot 12H_2O$	6	44

	Vol. or Sec.	Page		Vol. or Sec.	Page
Rubidium amide, RbNH_2	5m	73	Rubidium selenate, Rb_2SeO_4	9m	44
Rubidium barium chromium oxide, $\text{Rb}_2\text{Ba}(\text{CrO}_4)_2$	14m	32	Rubidium silicon fluoride, Rb_2SiF_6	6	49
Rubidium barium molybdenum oxide, $\text{Rb}_2\text{Ba}(\text{MoO}_4)_2$	15m	59	Rubidium strontium chloride, RbSrCl_3	7m	54
Rubidium bromate, RbBrO_3	8	45	Rubidium strontium chromium oxide, $\text{Rb}_2\text{Sr}(\text{CrO}_4)_2$	15m	64
Rubidium bromide, RbBr	7	43	Rubidium strontium sulfate, $\text{Rb}_2\text{Sr}(\text{SO}_4)_2$	15m	65
Rubidium cadmium chloride, high form, RbCdCl_3 (tetragonal)	5m	43	Rubidium sulfate, Rb_2SO_4	8	48
Rubidium cadmium chloride, low form, RbCdCl_3 (orthorhombic)	5m	41	Rubidium tellurium bromide, Rb_2TeBr_6	8	46
Rubidium cadmium sulfate, $\text{Rb}_2\text{Cd}_2(\text{SO}_4)_3$	7m	45	Rubidium tellurium chloride, Rb_2TeCl_6	8	48
Rubidium calcium chloride, RbCaCl_3	7m	47	Rubidium tin chloride, Rb_2SnCl_6 ...	6	46
Rubidium calcium fluoride, RbCaF_3	8m	57	Rubidium zinc fluoride, RbZnF_3	7m	57
Rubidium calcium sulfate, $\text{Rb}_2\text{Ca}_2(\text{SO}_4)_3$	7m	48	Rubidium zinc sulfate hydrate, $\text{Rb}_2\text{Zn}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	55
Rubidium chlorate, RbClO_3	8	47	Ruthenium, Ru	4	5
Rubidium chlorate, RbClO_4	2m	30	Ruthenium titanium, RuTi	6m	86
Rubidium chloride, RbCl	4	41	Samarium arsenate, SmAsO_4	4m	33
Rubidium chromium oxide, Rb_2CrO_4 ..	3m	46	Samarium arsenide, SmAs	4m	68
Rubidium chromium oxide, $\text{Rb}_2\text{Cr}_2\text{O}_7$..	15m	60	Samarium chloride, SmCl_3	1m	40
Rubidium chromium sulfate hydrate, $\text{RbCr}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	47	Samarium chloride oxide, SmOCl	1m	43
Rubidium cobalt(II) chloride, RbCoCl_3	6m	57	Samarium fluoride, SmF_3	1m	41
Rubidium cobalt fluoride, RbCoF_3 ..	8m	58	Samarium oxide, Sm_2O_3 (cubic)	4m	34
Rubidium cobalt sulfate, $\text{Rb}_2\text{Co}_2(\text{SO}_4)_3$	8m	59	Samarium silver, SmAg	5m	73
Rubidium copper chloride hydrate, $\text{Rb}_2\text{CuCl}_4 \cdot 2\text{H}_2\text{O}$	10m	47	Samarium tin oxide, $\text{Sm}_2\text{Sn}_2\text{O}_7$	8m	77
Rubidium copper sulfate hydrate, $\text{Rb}_2\text{Cu}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	61	Samarium vanadium oxide, SmVO_4	5m	47
Rubidium fluoride, RbF	8m	63	Scandium arsenate, ScAsO_4	4m	35
Rubidium iodate, RbIO_3	15m	62	Scandium arsenide, ScAs	4m	68
Rubidium iodate, RbIO_4	2m	31	Scandium oxide, Sc_2O_3	3	27
Rubidium iodide, RbI	4	43	Scandium phosphate, ScPO_4	8	50
Rubidium iron chloride hydrate, $\text{Rb}_2\text{FeCl}_5 \cdot \text{H}_2\text{O}$	14m	33	Scandium silicate (thortveitite), $\text{Sc}_2\text{Si}_2\text{O}_7$	7m	58
Rubidium iron sulfate hydrate, $\text{Rb}_2\text{Fe}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	64	Selenium, Se	5	54
Rubidium lead chromium oxide, $\text{Rb}_2\text{Pb}(\text{CrO}_4)_2$	14m	34	Selenium oxide (selenolite), SeO_2 ..	7m	60
Rubidium lead molybdenum oxide, $\text{Rb}_2\text{Pb}(\text{MoO}_4)_2$	15m	63	Silicon, Si	13m	35
Rubidium magnesium chromium oxide, $\text{Rb}_2\text{Mg}_2(\text{CrO}_4)_3$	8m	66	Silicon, Si (reference standard) ..	12m	2
Rubidium magnesium chromium oxide hydrate, $\text{Rb}_2\text{Mg}(\text{CrO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	68	Silicon nitride, $\beta\text{-Si}_3\text{N}_4$	14m	116
Rubidium magnesium sulfate, $\text{Rb}_2\text{Mg}_2(\text{SO}_4)_3$	7m	50	Silicon oxide (α or low cristobalite), SiO_2 (tetragonal)	10	48
Rubidium magnesium sulfate hydrate, $\text{Rb}_2\text{Mg}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	70	Silicon oxide (α or low cristobalite), SiO_2 (tetragonal) (calculated pattern)	15m	180
Rubidium manganese(II) fluoride, RbMnF_3	5m	44	Silicon oxide (α or low quartz), SiO_2 (hexagonal)	3	24
Rubidium manganese sulfate, $\text{Rb}_2\text{Mn}_2(\text{SO}_4)_3$	7m	52	Silicon oxide (β or high cristobalite), SiO_2 (cubic)	1	42
Rubidium nickel(II) chloride, RbNiCl_3	6m	58	Silver, Ag	1	23
Rubidium nickel sulfate, $\text{Rb}_2\text{Ni}_2(\text{SO}_4)_3$	8m	72	Silver, Ag (reference standard) ...	8m	2
Rubidium nickel sulfate hydrate, $\text{Rb}_2\text{Ni}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	74	Silver arsenate, Ag_3AsO_4	5	56
Rubidium nitrate, RbNO_3 (trigonal)	5m	45	Silver arsenic sulfide, xanthoconite, Ag_3AsS_3	8m	126
Rubidium platinum chloride, Rb_2PtCl_6	5	53	Silver bromate, AgBrO_3	5	57
Rubidium platinum fluoride, Rb_2PtF_6 ..	6	48	Silver bromide (bromargyrite), AgBr ..	4	46
			Silver carbonate, Ag_2CO_3	13m	36
			Silver chlorate, AgClO_3	7	44
			Silver chloride (chlorargyrite), AgCl	4	44
			Silver chromium oxide, Ag_2CrO_4	12m	30
			Silver cyanide, AgCN	9m	48
			Silver fluoride, Ag_2F	5m	53
			Silver iodate, AgIO_4	9	49
			Silver iodide (iodargyrite), AgI (hexagonal)	8	51
			Silver iodide, $\gamma\text{-AgI}$ (cubic)	9	48
			Silver manganese oxide, AgMnO_4	7m	155

	Vol. or Sec.	Page		Vol. or Sec.	Page
Silver molybdenum oxide, Ag_2MoO_4 ..	7	45	Sodium chromium oxide hydrate, $\text{Na}_2\text{CrO}_4 \cdot 4\text{H}_2\text{O}$	9m	50
Silver nitrate, AgNO_3	5	59	Sodium chromium oxide hydrate, $\text{Na}_2\text{Cr}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$	7m	62
Silver nitrite, AgNO_2	5	60	Sodium chromium oxide sulfate, $\text{Na}_4(\text{CrO}_4)(\text{SO}_4)$	11m	55
Silver oxide, Ag_2O	1m	45	Sodium cobalt nitrite, $\text{Na}_3\text{Co}(\text{NO}_2)_6$	15m	70
Silver(II) oxide nitrate, $\text{Ag}_7\text{O}_8\text{NO}_3$	4	61	Sodium cobalt(II) sulfate hydrate, $\text{Na}_2\text{Co}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	61
Silver phosphate, Ag_3PO_4	5	62	Sodium cyanate, NaCNO	2m	33
Silver rhenium oxide, AgReO_4	8	53	Sodium cyanide, NaCN (cubic)	1	78
Silver selenate, Ag_2SeO_4	2m	32	Sodium cyanide, NaCN (orthorhombic) at 6 °C	1	79
Silver sodium chloride, $\text{Ag}_{0.5}\text{Na}_{0.5}\text{Cl}$	8m	79	Sodium fluoride (villiaumite), NaF	1	63
Silver sulfate, Ag_2SO_4	13m	37	Sodium hydrogen carbonate hydrate, trona, $\text{Na}_3\text{H}(\text{CO}_3)_2 \cdot 2\text{H}_2\text{O}$	15m	71
Silver sulfide (acanthite), Ag_2S ..	10	51	Sodium hydrogen fluoride, NaHF_2 ...	5	63
Silver terbium, AgTb	5m	74	Sodium hydrogen phosphate, $\text{Na}_3\text{H}(\text{PO}_3)_4$	10m	130
Silver thiocyanate, AgCNS	16m	62	Sodium hydrogen silicate hydrate, $\text{Na}_2\text{H}_2\text{SiO}_4 \cdot 4\text{H}_2\text{O}$	7m	163
Silver thulium, AgTm	5m	74	Sodium hydrogen sulfate hydrate, $\text{NaHSO}_4 \cdot \text{H}_2\text{O}$	9m	52
Silver yttrium, AgY	5m	75	Sodium hydroxide, NaOH at 300 °C ..	4m	69
Sodium, Na	9m	105	Sodium iodate, NaIO_3	7	47
Sodium aluminum chloride silicate, sodalite, $\text{Na}_8\text{Al}_6\text{Cl}_2(\text{SiO}_4)_6$	7m	158	Sodium iodate, NaIO_4	7	48
Sodium aluminum fluoride (chiolite), $\text{Na}_5\text{Al}_3\text{F}_{14}$	16m	63	Sodium iodide, NaI	4	31
Sodium aluminum sulfate hydrate (soda alum), $\text{NaAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	15m	68	Sodium iron fluoride, Na_3FeF_6	9m	54
Sodium azide, $\alpha\text{-NaN}_3$, at -90 to -100 °C	8m	129	Sodium lanthanum fluoride silicate, $(\text{Na}_2\text{La}_8)_2\text{F}_2(\text{SiO}_4)_6$	7m	64
Sodium azide, $\beta\text{-NaN}_3$	8m	130	Sodium lanthanum molybdenum oxide, $\text{NaLa}(\text{MoO}_4)_2$	10m	49
Sodium beryllium calcium aluminum fluoride oxide silicate, meliphanite, $(\text{Na}_{0.63}\text{Ca}_{1.37})\text{Be}(\text{Al}_{0.13}\text{Si}_{1.87})$ $(\text{F}_{0.75}\text{O}_{6.25})$	8m	135	Sodium magnesium aluminum boron hydroxide silicate, dravite, $\text{NaMg}_3\text{Al}_6\text{B}_3(\text{OH})_4\text{Si}_6\text{O}_{27}$	3m	47
Sodium beryllium calcium fluoride silicate, leucophanite, $\text{NaBeCaFSi}_2\text{O}_6$	8m	138	Sodium magnesium carbonate (eitelite), $\text{Na}_2\text{Mg}(\text{CO}_3)_2$	11m	56
Sodium borate, $\text{Na}_2\text{B}_4\text{O}_7$	16m	64	Sodium magnesium sulfate (vanthoffite), $\text{Na}_6\text{Mg}(\text{SO}_4)_4$	15m	72
Sodium borate, $\text{Na}_2\text{B}_8\text{O}_{13}$	7m	160	Sodium magnesium sulfate hydrate, bloedite, $\text{Na}_2\text{Mg}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	63
Sodium borate hydroxide hydrate (borax), $\text{Na}_2\text{B}_4\text{O}_5(\text{OH})_2 \cdot 8\text{H}_2\text{O}$	16m	66	Sodium magnesium sulfate hydrate (loeweite), $\text{Na}_{12}\text{Mg}_7(\text{SO}_4)_{13} \cdot 15\text{H}_2\text{O}$	14m	35
Sodium boron hydride, NaBH_4	9	51	Sodium manganese(II) fluoride, NaMnF_3	6m	65
Sodium bromate, NaBrO_3	5	65	Sodium manganese sulfate hydrate, $\text{Na}_{12}\text{Mn}_7(\text{SO}_4)_{13} \cdot 15\text{H}_2\text{O}$	14m	37
Sodium bromide, NaBr	3	47	Sodium mercury(II) chloride hydrate, $\text{NaHgCl}_3 \cdot 2\text{H}_2\text{O}$	6m	66
Sodium bromide chloride, $\text{NaBr}_{.33}\text{Cl}_{.67}$	11m	49	Sodium molybdenum oxide, Na_2MoO_4 ..	1m	46
Sodium bromide chloride, $\text{NaBr}_{.67}\text{Cl}_{.33}$	11m	50	Sodium molybdenum oxide, $\text{Na}_2\text{Mo}_2\text{O}_7$	9m	110
Sodium calcium aluminum fluoride hydrate, thomsenolite, $\text{NaCaAlF}_6 \cdot \text{H}_2\text{O}$	8m	132	Sodium neodymium fluoride silicate, $(\text{Na}_2\text{Nd}_8)_2\text{F}_2(\text{SiO}_4)_6$	7m	66
Sodium calcium carbonate hydrate, pirssonite, $\text{Na}_2\text{Ca}(\text{CO}_3)_2 \cdot 2\text{H}_2\text{O}$	9m	106	Sodium nickel(II) sulfate hydrate, $\text{Na}_2\text{Ni}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	68
Sodium calcium phosphate, $\beta\text{-NaCaPO}_4$	15m	69	Sodium nitrate (soda niter), NaNO_3	6	50
Sodium calcium silicate, $\text{Na}_2\text{CaSiO}_4$	10m	48	Sodium nitrite, NaNO_2	4	62
Sodium calcium sulfate (glauberite), $\text{Na}_2\text{Ca}(\text{SO}_4)_2$	6m	59	Sodium oxide, Na_2O	10m	134
Sodium carbonate hydrate (thermo- natrite), $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$	8	54	Sodium phosphate, $\text{Na}_3\text{P}_3\text{O}_9$	3m	49
Sodium carbonate sulfate, $\text{Na}_4\text{CO}_3\text{SO}_4$	11m	51	Sodium phosphate hydrate, $\text{Na}_3\text{P}_3\text{O}_9 \cdot \text{H}_2\text{O}$	3m	50
Sodium carbonate sulfate (burkeite), $\text{Na}_6\text{CO}_3(\text{SO}_4)_2$	11m	52	Sodium phosphate hydrate, $\alpha\text{-Na}_4\text{P}_4\text{O}_{12} \cdot 4\text{H}_2\text{O}$ (monoclinic)	13m	39
Sodium carbonate sulfate, $\text{Na}_6\text{CO}_3(\text{SO}_4)_2$	11m	53	Sodium phosphate hydrate, $\beta\text{-Na}_4\text{P}_4\text{O}_{12} \cdot 4\text{H}_2\text{O}$ (triclinic)	2m	35
Sodium carbonate sulfate, $\text{Na}_6(\text{CO}_3)_2\text{SO}_4$	11m	54	Sodium phosphate hydrate, $\text{Na}_6\text{P}_6\text{O}_{18} \cdot 6\text{H}_2\text{O}$	5m	54
Sodium chlorate, NaClO_3	3	51			
Sodium chlorate, NaClO_4 (orthorhombic)	7	49			
Sodium chloride (halite), NaCl	2	41			
Sodium chromium oxide, Na_2CrO_4	9m	48			

	Vol. or Sec.	Page		Vol. or Sec.	Page
Sodium praseodymium fluoride silicate, (Na ₂ Pr ₈)F ₂ (SiO ₄) ₆	7m	68	Strontium silicate, Sr ₃ SiO ₅	13m	44
Sodium selenate, Na ₂ SeO ₄	9m	55	Strontium sulfate (celestite), SrSO ₄	2	61
Sodium selenide, Na ₂ Se	10m	135	Strontium sulfide, SrS	7	52
Sodium silicate, α(III), Na ₂ Si ₂ O ₅	8m	141	Strontium telluride, SrTe	4m	69
Sodium silicate, β-Na ₂ Si ₂ O ₅	10m	136	Strontium tin oxide, SrSnO ₃	8m	80
Sodium silicon fluoride (malladrite), Na ₂ SiF ₆	16m	68	Strontium titanium oxide, SrTiO ₃ ..	3	44
Sodium sulfate, Na ₂ SO ₄	11m	57	Strontium tungsten oxide, SrWO ₄ ...	7	53
Sodium sulfate (thenardite), Na ₂ SO ₄	2	59	Strontium tungsten oxide, Sr ₂ WO ₅ ..	12m	32
Sodium sulfide, Na ₂ S	10m	140	Strontium vanadium oxide, Sr ₃ (VO ₄) ₂	15m	73
Sodium sulfite, Na ₂ SO ₃	3	60	Strontium zirconium oxide, SrZrO ₃	9	51
Sodium telluride, Na ₂ Te	10m	141	Sulfamic acid, H ₂ NSO ₃ H	7	54
Sodium tin fluoride, NaSn ₂ F ₅	7m	166	Sulfur, S (orthorhombic)	9	54
Sodium titanium oxide, Na ₂ Ti ₃ O ₇ ...	16m	69	Tantalum, Ta	1	29
Sodium tungsten oxide, Na ₂ WO ₄	1m	47	Tantalum silicide, TaSi ₂	8	59
Sodium tungsten(VI) oxide hydrate, Na ₂ WO ₄ ·2H ₂ O	2m	33	Tellurium, Te	1	26
Sodium zinc fluoride, NaZnF ₃	6m	74	Tellurium(IV) oxide (paratellurite), TeO ₂ (tetragonal)	7	56
Sodium zinc sulfate hydrate, Na ₂ Zn(SO ₄) ₂ ·4H ₂ O	6m	72	Tellurium(IV) oxide, paratellurite, TeO ₂ (tetragonal)	10	55
Sodium zirconium fluoride, Na ₂ Zr ₆ F ₃₁	8m	144	Tellurium(IV) oxide, tellurite, TeO ₂ (orthorhombic)	9	57
Strontium aluminum hydroxide, Sr ₃ Al ₂ (OH) ₁₂	10m	50	Terbium arsenate, TbAsO ₄	3m	54
Strontium aluminum oxide, Sr ₃ Al ₂ O ₆	10m	52	Terbium arsenide, TbAs	5m	75
Strontium arsenate, Sr ₃ (AsO ₄) ₂	2m	36	Terbium nitride, TbN	4m	70
Strontium azide, Sr(N ₃) ₂	8m	146	Terbium phosphide, TbP	5m	76
Strontium borate, SrB ₂ O ₄	3m	53	Terbium selenide, TbSe	5m	76
Strontium borate, SrB ₄ O ₇	4m	36	Terbium sulfide, TbS	5m	77
Strontium bromide fluoride, SrBrF	10m	54	Terbium telluride, TbTe	5m	77
Strontium bromide hydrate, SrBr ₂ ·6H ₂ O	4	60	Terbium vanadium oxide, TbVO ₄	5m	56
Strontium carbonate (strontianite), SrCO ₃	3	56	Thallium, α-Tl	16m	73
Strontium chloride, SrCl ₂	4	40	Thallium aluminum sulfate hydrate, TlAl(SO ₄) ₂ ·12H ₂ O	6	53
Strontium chloride fluoride, SrClF	10m	55	Thallium(I) arsenate, Tl ₃ AsO ₄	2m	37
Strontium chloride hydrate, SrCl ₂ ·2H ₂ O	11m	58	Thallium azide, TlN ₃	8m	82
Strontium chloride hydrate, SrCl ₂ ·6H ₂ O	4	58	Thallium(I) bromate, TlBrO ₃	8	60
Strontium chloride hydroxide phosphate, Sr ₅ Cl _{1.65} (OH) _{1.35} (PO ₄) ₃	11m	60	Thallium bromide, TlBr	7	57
Strontium chromium oxide, Sr ₂ CrO ₄	16m	71	Thallium cadmium sulfate, Tl ₂ Cd ₂ (SO ₄) ₃	8m	83
Strontium fluoride, SrF ₂	5	67	Thallium(I) chlorate, TlClO ₄	2m	38
Strontium hydroxide, Sr(OH) ₂	13m	41	Thallium(I) chlorate, TlClO ₃	8	61
Strontium hydroxide hydrate, Sr(OH) ₂ ·H ₂ O	13m	42	Thallium(I) chloride, TlCl	4	51
Strontium hydroxide hydrate, Sr(OH) ₂ ·8H ₂ O	13m	43	Thallium chromium oxide, Tl ₂ CrO ₄ ..	3m	54
Strontium indium hydroxide, Sr ₃ In ₂ (OH) ₁₂	6m	76	Thallium chromium sulfate hydrate, TlCr(SO ₄) ₂ ·12H ₂ O	6	55
Strontium iodide hydrate, SrI ₂ ·6H ₂ O	8	58	Thallium cobalt sulfate, Tl ₂ Co ₂ (SO ₄) ₃	8m	85
Strontium manganese oxide, SrMnO ₃ (cubic)	10m	56	Thallium cobalt sulfate hydrate, Tl ₂ Co(SO ₄) ₂ ·6H ₂ O	7m	70
Strontium manganese oxide, SrMnO ₃ (hexagonal)	10m	58	Thallium copper sulfate hydrate, Tl ₂ Cu(SO ₄) ₂ ·6H ₂ O	7m	72
Strontium molybdenum oxide, SrMoO ₄	7	50	Thallium fluoride, TlF	16m	74
Strontium nitrate, Sr(NO ₃) ₂	12m	31	Thallium gallium sulfate hydrate, TlGa(SO ₄) ₂ ·12H ₂ O	6	57
Strontium oxide, SrO	5	68	Thallium(I) iodate, TlIO ₃	8	62
Strontium oxide, SrO ₂	6	52	Thallium(I) iodide, TlI (orthorhombic)	4	53
Strontium oxide hydrate, SrO ₂ ·8H ₂ O	11m	61	Thallium iron sulfate hydrate, Tl ₂ Fe(SO ₄) ₂ ·6H ₂ O	8m	87
Strontium phosphate, α-Sr ₂ P ₂ O ₇	11m	62	Thallium lead sulfate, Tl ₂ Pb(SO ₄) ₂	15m	74
Strontium phosphate, α-Sr ₃ (PO ₄) ₂	11m	64	Thallium magnesium chromium oxide, Tl ₂ Mg ₂ (CrO ₄) ₃	8m	89
Strontium scandium oxide hydrate, Sr ₃ Sc ₂ O ₆ ·6H ₂ O	6m	78	Thallium magnesium sulfate hydrate, Tl ₂ Mg(SO ₄) ₂ ·6H ₂ O	7m	74
			Thallium manganese sulfate, Tl ₂ Mn ₂ (SO ₄) ₃	7m	76

	Vol. or Sec.	Page		Vol. or Sec.	Page
Thallium nickel sulfate hydrate, $\text{Tl}_2\text{Ni}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	78	Yttrium arsenide, YAs	4m	74
Thallium(I) nitrate, TlNO_3	6	58	Yttrium chloride oxide, YClO	1m	51
Thallium oxide (avicennite), Tl_2O_3	16m	77	Yttrium oxide, Y_2O_3	3	28
Thallium(III) oxide, Tl_2O_3	2	28	Yttrium phosphate (xenotime), YPO_4	8	67
Thallium(I) phosphate, Tl_3PO_4	7	58	Yttrium sulfide, YS	5m	80
Thallium(III) phosphate, TlPO_4	7	59	Yttrium telluride, YTe	4m	75
Thallium platinum chloride, Tl_2PtCl_6	5	70	Yttrium titanium oxide, Y_2TiO_5	11m	113
Thallium silicon fluoride, Tl_2SiF_6	6	56	Yttrium vanadium oxide, YVO_4	5m	59
Thallium strontium sulfate, $\text{Tl}_2\text{Sr}(\text{SO}_4)_2$	15m	75	Zinc, Zn	1	16
Thallium(I) sulfate, Tl_2SO_4	6	59	Zinc aluminum oxide (gahnite), ZnAl_2O_4	2	38
Thallium(I) thiocyanate, TlCNS	8	63	Zinc ammine bromide, $\text{Zn}(\text{NH}_3)_2\text{Br}_2$	11m	68
Thallium tin chloride, Tl_2SnCl_6	6	54	Zinc ammine chloride, $\text{Zn}(\text{NH}_3)_2\text{Cl}_2$	10m	59
Thallium(I) tungsten oxide, Tl_2WO_4	1m	48	Zinc antimony oxide, ZnSb_2O_4	4m	39
Thallium zinc sulfate hydrate, $\text{Tl}_2\text{Zn}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	80	Zinc borate, $\text{Zn}_4\text{B}_6\text{O}_{13}$	13m	48
Thorium arsenide, ThAs	4m	70	Zinc carbonate, smithsonite, ZnCO_3	8	69
Thorium oxide (thorianite), ThO_2 ..	1	57	Zinc chlorate hydrate, $\text{Zn}(\text{ClO}_4)_2 \cdot 6\text{H}_2\text{O}$	16m	79
Thulium arsenate, TmAsO_4	3m	56	Zinc chromium oxide, ZnCr_2O_4	9m	59
Thulium arsenide, TmAs	4m	71	Zinc cobalt oxide, ZnCo_2O_4	10m	60
Thulium nitride, TmN	4m	71	Zinc cyanide, $\text{Zn}(\text{CN})_2$	5	73
Thulium oxide, Tm_2O_3	9	58	Zinc fluoride, ZnF_2	6	60
Thulium telluride, TmTe	4m	72	Zinc fluoride hydrate, $\text{ZnF}_2 \cdot 4\text{H}_2\text{O}$..	11m	69
Thulium vanadium oxide, TmVO_4	5m	57	Zinc germanium oxide, Zn_2GeO_4	10	56
Tin, α -Sn (cubic)	2	12	Zinc hydroxide silicate hydrate, hemimorphite, $\text{Zn}_4(\text{OH})_2\text{Si}_2\text{O}_7 \cdot \text{H}_2\text{O}$..	2	62
Tin, β -Sn (tetragonal)	1	24	Zinc iodide, ZnI_2	9	60
Tin arsenide, SnAs	4m	37	Zinc iron oxide (franklinite), ZnFe_2O_4	9m	60
Tin arsenide, $\text{Sn}_{3.8}\text{As}_3$	15m	76	Zinc manganese oxide (hetaerolite), ZnMn_2O_4	10m	61
Tin(II) fluoride, SnF_2	3m	51	Zinc molybdenum oxide, $\text{Zn}_2\text{Mo}_3\text{O}_8$...	7m	173
Tin hydrogen phosphate, SnHPO_4	13m	46	Zinc nitrate hydrate, α - $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$	12m	36
Tin(IV) iodide, SnI_4	5	71	Zinc oxide (zincite), ZnO	2	25
Tin(II) oxide (romarchite), SnO ...	4	28	Zinc phosphate, α - $\text{Zn}_3(\text{PO}_4)_2$	16m	80
Tin(IV) oxide (cassiterite), SnO_2 ..	1	54	Zinc phosphate, β - $\text{Zn}_3(\text{PO}_4)_2$	16m	81
Tin sulfide (berndtite), β - SnS_2 ...	9m	57	Zinc phosphate, γ - $\text{Zn}_3(\text{PO}_4)_2$	16m	83
Tin(II) telluride, SnTe	7	61	Zinc phosphate hydrate (hopeite), $\text{Zn}_3(\text{PO}_4)_2 \cdot 4\text{H}_2\text{O}$	16m	85
Titanium, Ti	3	4	Zinc selenide, ZnSe	3	23
Titanium(III) oxide, $\text{TiO}_{1.515}$	9	59	Zinc silicate (willemite), Zn_2SiO_4 ..	7	62
Titanium oxide (anatase), TiO_2	7m	82	Zinc silicon fluoride hydrate, $\text{ZnSiF}_6 \cdot 6\text{H}_2\text{O}$	8	70
Titanium oxide, brookite, TiO_2 (orthorhombic)	3m	57	Zinc sulfate (zinkosite), ZnSO_4 ...	7	64
Titanium oxide (rutile), TiO_2	7m	83	Zinc sulfate hydrate (goslarite), $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$	8	71
Titanium silicide, Ti_5Si_3	8	64	Zinc sulfide (wurtzite), α -ZnS (hexagonal)	2	14
Titanium sulfide, TiS_2	4m	72	Zinc sulfide (sphaelerite), β -ZnS (cubic)	2	16
Titanium sulfide, Ti_2S	8m	149	Zinc telluride, ZnTe	3m	58
Tungsten, W	1	28	Zinc tin oxide, Zn_2SnO_4	10m	62
Tungsten, W (reference standard) ..	8m	2	Zinc titanium oxide, ZnTiO_3	13m	49
Tungsten sulfide (tungstenite), WS_2 ..	8	65	Zinc titanium oxide, Zn_2TiO_4	12m	37
Uranium oxide, UO	5m	78	Zinc tungsten oxide (sanmartinite), ZnWO_4	2m	40
Uranium oxide (uraninite), UO_2	2	33	Zirconium, α -Zr	2	11
Uranium selenide, USe	5m	78	Zirconium hydride, ZrH_2	5m	60
Uranium telluride, UTe	4m	73	Zirconium iodate, $\text{Zr}(\text{IO}_3)_4$	1m	51
Vanadium, V	9m	58	Zirconium nitride, ZrN	5m	80
Vanadium(V) oxide (shcherbinaite), V_2O_5	8	66	Zirconium oxide, ZrO	5m	81
Vanadium sulfide, α - V_3S	14m	118	Zirconium phosphide, ZrP	4m	75
Vanadium sulfide, β - V_3S	14m	120	Zirconium silicate, zircon, ZrSiO_4 ..	4	68
Ytterbium arsenate, YbAsO_4	4m	38	Zirconium sulfate hydrate (zircosulfate), $\text{Zr}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	7	66
Ytterbium arsenide, YbAs	4m	73			
Ytterbium nitride, YbN	4m	74			
Ytterbium oxide, Yb_2O_3	6m	80			
Ytterbium selenide, YbSe	5m	79			
Ytterbium telluride, YbTe	5m	79			
Ytterbium(III) vanadium oxide, YbVO_4	5m	58			
Yttrium arsenate, YAsO ₄	2m	39			

CUMULATIVE ORGANIC FORMULA INDEX

		Vol. or Sec.	Page
CH ₄ N ₂ O	Urea	7	61
CH ₅ NO ₂	Ammonium formate	11m	9
C ₂ Ag ₂ O ₄	Silver oxalate	9m	47
C ₂ FeO ₄ ·2H ₂ O	Iron oxalate hydrate (humboldtine)	10m	24
C ₂ H ₂ CaO ₄	Calcium formate	8	16
C ₂ H ₂ O ₄ ·2H ₂ O	Oxalic acid hydrate	16m	55
C ₂ H ₂ O ₄ Pb	Lead formate	8	30
C ₂ H ₂ O ₄ Sr	Strontium formate	8	55
C ₂ H ₂ O ₄ Sr·2H ₂ O	Strontium formate hydrate (orthorhombic)	8	56
C ₂ H ₃ KO ₄	Potassium formate-formic acid complex	9m	93
C ₂ H ₃ NaO ₂ ·3H ₂ O	Sodium acetate hydrate	15m	66
C ₂ H ₄ N ₂ O ₂	Glyoxime	8m	102
C ₂ H ₇ NO ₂	Ammonium acetate	8m	95
C ₂ H ₈ N ₂ O ₄ ·H ₂ O	Ammonium oxalate hydrate (oxammite)	7	5
C ₂ K ₂ O ₄ ·H ₂ O	Potassium oxalate hydrate	9m	39
C ₂ Li ₂ O ₄	Lithium oxalate	10m	34
C ₂ Na ₂ O ₄	Sodium oxalate	6m	70
C ₂ O ₄ Rb ₂ ·H ₂ O ₂	Rubidium oxalate perhydrate	9m	102
C ₃ H ₇ NO ₂	L-Alanine	8m	93
C ₃ H ₇ NO ₂ S	L-Cysteine	11m	86
C ₃ H ₁₀ ClN	Trimethylammonium chloride	9m	113
C ₄ H ₄ CaO ₅ ·2H ₂ O	Calcium malate hydrate	10m	76
C ₄ H ₄ KNaO ₆ ·4H ₂ O	Potassium sodium tartrate hydrate	15m	55
C ₄ H ₄ NO ₈ Y·H ₂ O	Ammonium yttrium oxalate hydrate	8m	97
C ₄ H ₄ Na ₂ O ₆ ·2H ₂ O	Sodium D-tartrate hydrate	11m	110
C ₄ H ₆ CoO ₄ ·4H ₂ O	Cobalt acetate hydrate	12m	19
C ₄ H ₆ NiO ₄ ·4H ₂ O	Nickel acetate hydrate	13m	31
C ₄ H ₆ O ₆	D-Tartaric acid	7m	168
C ₄ H ₇ N ₃ O	Creatinine	15m	31
C ₄ H ₈ N ₈ O ₈	α-HMX	11m	100
C ₄ H ₈ N ₈ O ₈	β-HMX	11m	102
C ₄ H ₈ N ₈ O ₈	Octahydro-1,3,5,7-tetranitro- 1,3,5,7-tetrazocine, alpha-	11m	100
C ₄ H ₈ N ₈ O ₈	Octahydro-1,3,5,7-tetranitro- 1,3,5,7-tetrazocine, beta-	11m	102
C ₄ H ₂₂ B ₂ O	bis-(o-Dodecacarborane)	6m	7
C ₅ H ₄ N ₄ O ₃	Uric acid, phase 1 (calc. pattern)	8m	154
C ₅ H ₄ N ₄ O ₃	Uric acid, phase 1	16m	78
C ₅ H ₇ CuNO ₄ ·2H ₂ O	Copper glutamate hydrate	7m	110
C ₅ H ₇ NO ₄ Zn·2H ₂ O	Zinc glutamate hydrate	7m	170
C ₆ H ₃ N ₃ O ₇	Picric acid	16m	56
C ₆ H ₅ NO ₂	Nicotinic acid	16m	54
C ₆ H ₆ O ₂	γ-Hydroquinone	8m	107
C ₆ H ₈ Cl ₂ N ₄ Zn	Zinc diimidazole chloride	7m	123
C ₆ H ₈ O ₆	L-Ascorbic acid	8m	99
C ₆ H ₁₂ O ₆	Dextrose	11m	28
C ₆ H ₁₂ O ₆	α-D-Glucose	11m	28
C ₆ H ₁₅ HoO ₁₂ S ₃ ·9H ₂ O	Holmium ethylsulfate hydrate	1m	18
C ₆ H ₁₅ NdO ₁₂ S ₃ ·9H ₂ O	Neodymium ethylsulfate hydrate	9	41
C ₇ H ₅ BrO ₂	o-Bromobenzoic acid	16m	22
C ₇ H ₅ ClO ₂	m-Chlorobenzoic acid	16m	30
C ₇ H ₅ FO ₂	p-Fluorobenzoic acid	16m	36
C ₇ H ₉ NO ₂ S	Methyl sulfonanilide	9m	78
C ₇ H ₁₂ O ₄	Pimelic acid	7m	153
C ₈ H ₄ Hg ₂ O ₄	Mercury o-phthalate	10m	113
C ₈ H ₅ KO ₄	Potassium hydrogen o-phthalate	4m	30
C ₈ H ₅ O ₄ Tl	Thallium hydrogen phthalate	16m	75
C ₈ H ₇ N ₃ O ₇	2,4,6-Trinitrophenetole	8m	152
C ₈ H ₈ O ₃	p-Anisic acid	16m	11
C ₈ H ₉ NO	Acetanilide (calc. pattern)	14m	38
C ₈ H ₉ NO	Acetanilide	16m	7
C ₈ H ₁₁ N ₂ NaO ₃	Sodium barbital	16m	157
C ₈ H ₁₂ N ₂ O ₃	Barbital, form I	15m	126
C ₈ H ₁₂ N ₂ O ₃	Barbital, form II	15m	128

		Vol. or Sec.	Page
C ₈ H ₁₂ N ₂ O ₃	Barbital, form IV	15m	130
C ₉ H ₁₄ N ₂ O ₃	Metharbital	15m	177
C ₁₀ H ₁₂ N ₂ O ₃	Allobarbital	14m	41
C ₁₀ H ₁₆ ClNO	(-)-Ephedrine hydrochloride	16m	124
C ₁₁ H ₁₆ N ₂ O ₃	Vinbarbital, form I	16m	162
C ₁₁ H ₁₈ N ₂ O ₃	Amobarbital, form I	15m	114
C ₁₁ H ₁₈ N ₂ O ₃	Amobarbital, form II	15m	117
C ₁₂ H ₁₀ N ₂	Azobenzene	7m	86
C ₁₂ H ₁₂ N ₂ O ₃	Phenobarbital, form III	16m	144
C ₁₂ H ₁₆ Cl ₂ CuN ₈	Copper tetrapyrazole chloride	8m	31
C ₁₂ H ₁₆ Cl ₂ N ₈ Ni	Nickel tetrapyrazole chloride	8m	44
C ₁₂ H ₁₆ CuN ₁₀ O ₆	Copper tetraimidazole nitrate	13m	24
C ₁₂ H ₁₆ N ₂	(N,N)-Dimethyltryptamine	14m	109
C ₁₂ H ₁₆ N ₂ O	Bufotenine	15m	133
C ₁₂ H ₁₆ N ₂ O	Psilocin	16m	152
C ₁₂ H ₂₂ O ₁₁	Sucrose	11m	66
C ₁₂ H ₂₆ N ₂ O ₄	Hexamethylenediammonium adipate	7m	121
C ₁₃ H ₂₁ ClN ₂ O ₂	Procaine hydrochloride	16m	149
C ₁₃ H ₂₁ N ₂ O ₄ P	Psilocybin methanolate	16m	154
C ₁₄ H ₁₁ FO	4-Acetyl-2'-fluorodiphenyl	8m	91
C ₁₄ H ₂₀ ClN ₃ S	Methapyrilene hydrochloride	14m	112
C ₁₅ H ₁₂ O ₂	Dibenzoylmethane	7m	115
C ₁₆ H ₁₃ ClN ₂ O	Diazepam	14m	106
C ₁₆ H ₁₃ N	N-Phenyl-2-naphthylamine	6m	29
C ₁₇ H ₁₉ ClN ₂ S	Chlorpromazine	14m	60
C ₁₇ H ₂₀ ClNO ₃ ·3H ₂ O	Morphine hydrochloride hydrate	16m	133
C ₁₇ H ₂₂ ClNO ₄	L-Cocaine hydrochloride	16m	114
C ₁₇ H ₂₆ ClN	Phencyclidine hydrochloride	16m	141
C ₁₈ H ₂₂ BrNO ₃ ·2H ₂ O	Codeine hydrobromide hydrate	16m	117
C ₁₈ H ₂₄ CdN ₁₄ O ₆	Cadmium hexaimidazole nitrate	8m	23
C ₁₈ H ₂₄ N ₁₄ NiO ₆	Nickel hexaimidazole nitrate	7m	27
C ₁₈ H ₂₈ N ₂ O ₄ S	(+)-Amphetamine sulfate	15m	119
C ₁₉ H ₂₂ ClNO ₄ ·2H ₂ O	Naloxone hydrochloride hydrate	16m	136
C ₁₉ H ₂₅ ClN ₂	Imipramine hydrochloride	16m	129
C ₂₀ H ₂₆ ClNO ₃	Benactyzine hydrochloride	16m	92
C ₂₀ H ₃₄	α-Dihydrophyllocladene, hartite (or bombiccite)	16m	122
C ₂₁ H ₂₃ ClFNO ₂	Haloperidol	16m	127
C ₂₁ H ₃₀ O ₂	Cannabidiol	16m	111
C ₂₂ H ₃₀ O ₄	Δ ⁹ -Tetrahydrocannabinolic acid B	16m	160
C ₂₄ H ₃₂ N ₂ O ₂ Pd	Palladium bis-(N-isopropyl-3- ethylsalicylaldiminate)	7m	144
C ₂₅ H ₁₅ N ₆	N-Methylphenazinium-7,7,8,8- tetracyanoquinodimethanide	7m	146
C ₃₃ H ₄₀ N ₂ O ₉	Reserpine	8m	123

CUMULATIVE ORGANIC NAME INDEX

		Vol. or Sec.	Page
Acetanilide	C_8H_9NO (calc. pattern)	14m	38
Acetanilide	C_8H_9NO	16m	7
4-Acetyl-2'-fluorodiphenyl	$C_{14}H_{11}FO$	8m	91
Alanine, L-	$CH_3CHNH_2CO_2H$	8m	93
Allobarbitol	$C_{10}H_{12}N_2O_3$	14m	41
Amobarbital, form I	$C_{11}H_{18}N_2O_3$	15m	114
Amobarbital, form II	$C_{11}H_{18}N_2O_3$	15m	117
Ammonium acetate	$NH_4 \cdot CH_3CO_2$	8m	95
Ammonium formate	NH_4HCO_2	11m	9
Ammonium oxalate hydrate (oxammite)	$(NH_4)_2C_2O_4 \cdot H_2O$	7	5
Ammonium yttrium oxalate hydrate	$NH_4Y(C_2O_4)_2 \cdot H_2O$	8m	97
Amphetamine sulfate, (+)-	$C_{18}H_{28}N_2O_4S$	15m	119
p-Anisic acid	$C_8H_8O_3$	16m	11
Ascorbic acid, L-	$C_6H_8O_6$	8m	99
Azobenzene	$C_6H_5NNC_6H_5$	7m	86
Barbital, form I	$C_8H_{12}N_2O_3$	15m	126
Barbital, form II	$C_8H_{12}N_2O_3$	15m	128
Barbital, form IV	$C_8H_{12}N_2O_3$	15m	130
Benactyzine hydrochloride	$C_{20}H_{26}ClNO_3$	16m	92
o-Bromobenzoic acid	$C_7H_5BrO_2$	16m	22
Bufotenine	$C_{12}H_{16}N_2O$	15m	133
Cadmium hexaimidazole nitrate	$Cd(C_3H_4N_2)_6(NO_3)_2$	8m	23
Calcium formate	$Ca(HCO_2)_2$	8	16
Calcium malate hydrate	$Ca(O_2C)_2(CH_2CHOH) \cdot 2H_2O$	10m	76
Cannabidiol	$C_{21}H_{30}O_2$	16m	111
m-Chlorobenzoic acid	$C_7H_5ClO_2$	16m	30
Chlorpromazine	$C_{17}H_{19}ClN_2S$	14m	60
Cobalt acetate hydrate	$Co(C_2H_3O_2)_2 \cdot 4H_2O$	12m	19
Cocaine hydrochloride, L-	$C_{17}H_{22}ClNO_4$	16m	114
Codeine hydrobromide hydrate	$C_{18}H_{22}BrNO_3 \cdot 2H_2O$	16m	117
Copper glutamate hydrate	$Cu(O_2C)_2(H_2NCHCH_2CH_2) \cdot 2H_2O$	7m	110
Copper tetraimidazole nitrate	$Cu(C_3H_4N_2)_4(NO_3)_2$	13m	24
Copper tetrapyrazole chloride	$Cu(C_3H_4N_2)_4Cl_2$	8m	31
Creatinine	$C_4H_7N_3O$	15m	31
Cysteine, L-	$HSCH_2 \cdot CH(NH_2) \cdot COOH$	11m	86
Dextrose	$C_6H_{12}O_6$	11m	28
Diazepam	$C_{16}H_{13}ClN_2O$	14m	106
Dibenzoylmethane	$(C_6H_5CO)_2CH_2$	7m	115
α -Dihydrophyllocladene, hartite (or bombiccite)	$C_{20}H_{34}$	16m	122
(N,N)-Dimethyltryptamine	$C_{12}H_{16}N_2$	14m	109
bis-(o-Dodecacarborane)	$C_{40}B_{20}H_{22}$	6m	7
Ephedrine hydrochloride, (-)-	$C_{10}H_{16}ClNO$	16m	124
p-Fluorobenzoic acid	$C_7H_5FO_2$	16m	36
Glucose, α -D-	$C_6H_{12}O_6$	11m	28
Glyoxime	$H_2C_2(OH)_2$	8m	102
Haloperidol	$C_{21}H_{23}ClFNO_2$	16m	127
Hexamethylenediammonium adipate	$(CH_2)_4(CO_2H_3N)_2(CH_2)_6$	7m	121
α -HMX	$C_4H_8N_8O_8$	11m	100
β -HMX	$C_4H_8N_8O_8$	11m	102
Holmium ethylsulfate hydrate	$Ho[(C_2H_5)SO_4]_3 \cdot 9H_2O$	1m	18
Hydroquinone	$\gamma-HOC_6H_4OH$	8m	107
Imipramine hydrochloride	$C_{19}H_{25}ClN_2$	16m	129
Iron oxalate hydrate (humboldtine)	$FeC_2O_4 \cdot 2H_2O$	10m	24
Lead formate	$Pb(HCO_2)_2$	8	30
Lithium oxalate	$Li_2C_2O_4$	10m	34
Mercury o-phthalate	$C_6H_4(CO_2Hg)_2$	10m	113
Methapyrilene hydrochloride	$C_{14}H_{20}ClN_3S$	14m	112
Metharbital	$C_9H_{14}N_2O_3$	15m	177
Methyl sulfonanilide	$C_6H_5NHOSO_2CH_3$	9m	78
N-Methylphenazinium-7,7,8,8-tetra- cyanoquinodimethanide	$C_{25}H_{15}N_6$	7m	146
Morphine hydrochloride hydrate	$C_{17}H_{20}ClNO_3 \cdot 3H_2O$	16m	133
Naloxone hydrochloride hydrate	$C_{19}H_{22}ClNO_4 \cdot 2H_2O$	16m	136

		Vol. or Sec.	Page
2-Naphthylamine, N-phenyl-	$C_{10}H_7NHC_6H_5$	6m	29
Neodymium ethylsulfate hydrate	$Nd[(C_2H_5)SO_4]_3 \cdot 9H_2O$	9	41
Nickel acetate hydrate	$Ni(C_2H_3O_2)_2 \cdot 4H_2O$	13m	31
Nickel hexaimidazole nitrate	$Ni(C_3H_4N_2)_6(NO_3)_2$	7m	27
Nickel tetrapyrazole chloride	$Ni(C_3H_4N_2)_4Cl_2$	8m	44
Nicotinic acid	$C_6H_5NO_2$	16m	54
Octahydro-1,3,5,7-tetranitro- 1,3,5,7-tetrazocine (α -HMX)	$C_4H_8N_8O_8$	11m	100
Octahydro-1,3,5,7-tetranitro- 1,3,5,7-tetrazocine (β -HMX)	$C_4H_8N_8O_8$	11m	102
Oxalic acid hydrate	$C_2H_2O_4 \cdot 2H_2O$	16m	55
Palladium bis-(N-isopropyl-3- ethylsalicylaldiminate)	$Pd(C_{12}H_{16}NO)_2$	7m	144
Phencyclidine hydrochloride	$C_{17}H_{26}ClN$	16m	141
Phenobarbital, form III	$C_{12}H_{12}N_2O_3$	16m	144
Picric acid	$C_6H_3N_3O_7$	16m	56
Pimelic acid	$(CH_2)_5(CO_2H)_2$	7m	153
Potassium formate-formic acid complex	$KO_2CH \cdot HO_2CH$	9m	93
Potassium hydrogen o-phthalate	$C_6H_4(COOH)(COOK)$	4m	30
Potassium oxalate hydrate	$K_2C_2O_4 \cdot H_2O$	9m	39
Potassium oxalate perhydrate	$K_2C_2O_4 \cdot H_2O_2$	9m	96
Potassium sodium tartrate hydrate	$C_4H_4KNaO_6 \cdot 4H_2O$	15m	55
Procaine hydrochloride	$C_{13}H_{21}ClN_2O_2$	16m	149
Psilocin	$C_{12}H_{16}N_2O$	16m	152
Psilocybin methanolate	$C_{13}H_{21}N_2O_4P$	16m	154
Reserpine	$C_{33}H_{40}N_2O_9$	8m	123
Rubidium oxalate perhydrate	$Rb_2C_2O_4 \cdot H_2O_2$	9m	102
Silver oxalate	$Ag_2C_2O_4$	9m	47
Sodium acetate hydrate	$C_2H_3NaO_2 \cdot 3H_2O$	15m	66
Sodium barbital	$C_8H_{11}N_2NaO_3$	16m	157
Sodium D-tartrate hydrate	$(CHOH-CO_2Na)_2 \cdot 2H_2O$	11m	110
Sodium oxalate	$Na_2C_2O_4$	6m	70
Strontium formate	$Sr(CHO_2)_2$	8	55
Strontium formate hydrate	$Sr(CHO_2)_2 \cdot 2H_2O$ (orthorhombic)	8	56
Sucrose	$C_{12}H_{22}O_{11}$	11m	66
Tartaric acid, D-	$(CHOHCO_2H)_2$	7m	168
Δ^9 -Tetrahydrocannabinolic acid B	$C_{22}H_{30}O_4$	16m	160
Thallium hydrogen phthalate	$C_8H_5O_4Tl$	16m	75
Trimethylammonium chloride	$(CH_3)_3NHC1$	9m	113
2,4,6-Trinitrophenetole	$C_2H_5OC_6H_2(NO_2)_3$	8m	152
Urea	$CO(NH_2)_2$	7	61
Uric acid, phase 1, (calc. pattern)	$C_5H_4N_4O_3$	8m	154
Uric acid (phase 1)	$C_5H_4N_4O_3$	16m	78
Vinbarbital, form I	$C_{11}H_{16}N_2O_3$	16m	162
Zinc diimidazole chloride	$Zn(C_3H_4N_2)_2Cl_2$	7m	123
Zinc glutamate hydrate	$Zn(O_2CCHNH_2CH_2CH_2CO_2) \cdot 2H_2O$	7m	170

CUMULATIVE MINERAL INDEX

	Vol. or Sec.	Page		Vol. or Sec.	Page
Acanthite, Ag ₂ S	10	51	Clinobisvanite, BiVO ₄	3m	14
Aeschnite CeNbTiO ₆	3m	24	Copper, Cu	1	15
Alabandite, MnS	4	11	Cordierite, Mg ₂ Al ₄ Si ₅ O ₁₈	1m	28
Anatase, TiO ₂	7m	82	Corundum, Al ₂ O ₃	9	3
Andradite, Ca ₃ Fe ₂ Si ₃ O ₁₂	9	22	Cotunnite, PbCl ₂	12m	23
Anglesite, PbSO ₄	3	67	Covellite, CuS	4	13
Anhydrite, CaSO ₄	4	65	Cristobalite (α or low) SiO ₂ (tetragonal)	10	48
Antarcticite, CaCl ₂ ·6H ₂ O	12m	16	Cristobalite (α or low) SiO ₂ (tetragonal, calculated pattern)	15m	180
Antimony, Sb	3	14	Cristobalite (β or high) SiO ₂ (cubic)	1	42
Aphthitalite, K ₃ Na(SO ₄) ₂	6m	52	Cryolithionite, Li ₃ Na ₃ Al ₂ F ₁₂	9m	23
Aragonite, CaCO ₃	3	53	Cryptohalite, (NH ₄) ₂ SiF ₆	5	5
Aragonite, CaCO ₃ (calculated pattern)	14m	44	Cuprite, Cu ₂ O	2	23
Arcanite, K ₂ SO ₄	3	62	*Derbylite, SbFe ₄ Ti ₃ O ₁₃ (OH)	16m	89
Arsenic, As	3	6	*Diamond, C	2	5
Arsenolite, As ₂ O ₃	1	51	*Diaspore, Al ₂ O ₃ ·H ₂ O	3	41
Aurostibite, AuSb ₂	7	18	Diopside, CaMg(SiO ₃) ₂	5m	17
Avicennite, Tl ₂ O ₃	16m	77	*Dravite, NaMg ₃ Al ₆ B ₃ Si ₆ O ₂₇ (OH) ₄ ...	3m	47
*Azurite, Cu ₃ (OH) ₂ (CO ₃) ₂	10	30	Eitelite, Na ₂ Mg(CO ₃) ₂	11m	56
*Bahianite, Al _{5.66} Fe _{0.09} Sb _{2.95} O ₁₆ ..	16m	87	Elpasolite, K ₂ NaAlF ₆	9m	43
Baryte, BaSO ₄	10m	12	*Enstatite, MgSiO ₃	6	32
Berlinite, AlPO ₄	10	3	Epsomite, MgSO ₄ ·7H ₂ O	7	30
Berndtite, SnS ₂	9m	57	Erythrosiderite, K ₂ FeCl ₅ ·H ₂ O	14m	27
*Beryl, Be ₃ Al ₂ Si ₆ O ₁₈	9	13	Eskolaite, Cr ₂ O ₃	5	22
Bischofite, MgCl ₂ ·6H ₂ O	11m	37	Ettringite, Ca ₆ Al ₂ S ₃ O ₁₈ ·31H ₂ O	8	3
Bismite, α-Bi ₂ O ₃	3m	17	Fairchildite, K ₂ Ca(CO ₃) ₂	8m	48
Bismoclite, BiOCl	4	54	Fluorapatite, Ca ₅ F(PO ₄) ₃	3m	22
Bismuth, Bi	3	20	Fluorite, CaF ₂	1	69
Bismuthinite, Bi ₂ S ₃	5m	13	Forsterite, Mg ₂ SiO ₄	1	83
Bixbyite, α-Mn ₂ O ₃	11m	95	Franklinite, ZnFe ₂ O ₄	9m	60
*Bloedite, Na ₂ Mg(SO ₄) ₂ ·4H ₂ O	6m	63	Fresnoite, Ba ₂ TiSi ₂ O ₈	9m	14
Boehmite, Al ₂ O ₃ ·H ₂ O	3	38	Gahnite, ZnAl ₂ O ₄	2	38
*Bombycite, C ₂₀ H ₃₄	16m	122	Galaxite, MnAl ₂ O ₄	9	35
Borax, Na ₂ B ₄ O ₅ (OH) ₂ ·8H ₂ O	16m	66	Galena, PbS	2	18
Bromargyrite, AgBr	4	46	Gaspeite, NiCO ₃	1m	36
Bromellite, BeO	1	36	Geikielite, MgTiO ₃	5	43
*Brookite, TiO ₂	3m	57	Gersdorffite, NiAsS	1m	35
Brownmillerite, Ca ₄ Al ₂ Fe ₂ O ₁₀	16m	28	Glauberite, Na ₂ Ca(SO ₄) ₂	6m	59
Brucite, Mg(OH) ₂	6	30	Gold, Au	1	33
Bunsenite, NiO	1	47	Goslarite, ZnSO ₄ ·7H ₂ O	8	71
Burkeite, Na ₆ CO ₃ (SO ₄) ₂	11m	52	Greenockite, CdS	4	15
*Butlerite, Fe(OH)SO ₄ ·2H ₂ O	10m	95	*Groutite, MnO(OH)	11m	97
Cadmoseelite, CdSe	7	12	Halite, NaCl	2	41
Calcite, CaCO ₃	2	51	*Hartite, C ₂₀ H ₃₄	16m	122
Calomel, Hg ₂ Cl ₂	13m	30	Hausmannite, Mn ₃ O ₄	10m	38
Carnallite, KMgCl ₃ ·6H ₂ O	8m	50	*Hemimorphite, Zn ₄ (OH) ₂ Si ₂ O ₇ ·H ₂ O ..	2	62
Carobbiite, KF	1	64	Hetaerolite, ZnMn ₂ O ₄	10m	61
Cassiterite, SnO ₂	1	54	*Hexahydroborite, Ca[B(OH) ₄] ₂ ·2H ₂ O ..	16m	104
Celestine, SrSO ₄	2	61	Hieratite, K ₂ SiF ₆	5	50
Cerianite, CeO ₂	1	56	Hopeite, Zn ₃ (PO ₄) ₂ ·4H ₂ O	16m	85
Cerussite, PbCO ₃	2	56	Huebnerite, MnWO ₄	2m	24
Cervantite, Sb ₂ O ₄	10	8	Humboldtine, FeC ₂ O ₄ ·2H ₂ O	10m	24
Chalcokyanite, CuSO ₄	3m	29	Humite, Mg ₇ F ₂ Si ₃ O ₁₂	1m	30
Chernovite, YAsO ₄	2m	39	Hydrophilite, CaCl ₂	11m	18
Chiolite, Na ₅ Al ₃ F ₁₄	16m	63	Ilmenite, FeTiO ₃	15m	34
Chloraluminite, AlCl ₃ ·6H ₂ O	7	3	Indialite, Mg ₂ Al ₄ Si ₅ O ₁₈	1m	29
Chlorargyrite, AgCl	4	44	Iodargyrite, AgI	8	51
Chloromagnesite, MgCl ₂	11m	94	Iron, α-Fe	4	3
Chromatite, CaCrO ₄	7	13	Jacobsite, MnFe ₂ O ₄	9	36
Chrysoberyl, BeAl ₂ O ₄	9	10	*Jugoldite,		
Cinnabar, HgS	4	17	Ca ₂ Fe ₃ Si ₃ O ₁₀ (OH, O) ₂ (OH) ₂	10m	72
Claudetite, As ₂ O ₃	3m	9	Kalistrontite, K ₂ Sr(SO ₄) ₂	14m	31
Clausthalite, PbSe	5	38			

* Natural mineral

	Vol. or Sec.	Page		Vol. or Sec.	Page
Kieserite, $\text{MgSO}_4 \cdot \text{H}_2\text{O}$	16m	46	Portlandite, $\text{Ca}(\text{OH})_2$	1	58
Kremersite, $(\text{NH}_4, \text{K})_2\text{FeCl}_5 \cdot \text{H}_2\text{O}$	14m	8	Potash alum, $\text{KAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	36
Langbeinite, $\text{K}_2\text{Mg}_2(\text{SO}_4)_3$	6m	40	Powellite, CaMoO_4	6	22
Lautarite, $\text{Ca}(\text{IO}_3)_2$	14m	12	Pyrargyrite, Ag_3SbS_3	5m	51
Lead, Pb	1	34	Pyrite, FeS_2	5	29
*Leucophanite, $\text{NaCaBeFSi}_2\text{O}_6$	8m	138	*Pyroaurite, $\text{Mg}_6\text{Fe}_2\text{CO}_3(\text{OH})_{16} \cdot 4\text{H}_2\text{O}$	10m	104
*Liddicoatite, $\text{Ca}(\text{Li}, \text{Al})_3\text{Al}_6\text{B}_3\text{Si}_6\text{O}_{27}$ (O, OH) ₃ (OH, F)	16m	42	Pyrolusite, $\beta\text{-MnO}_2$	10m	39
Lime, CaO	1	43	Pyrope, $\text{Mg}_3\text{Al}_2(\text{SiO}_4)_3$	4m	24
Lime, CaO (calculated pattern)	14m	49	Pyrophanite, MnTiO_3	15m	42
*Linarite, $\text{CuPb}(\text{OH})_2(\text{SO}_4)$	16m	34	*Quartz, SiO_2 (α or low)	3	24
Litharge, PbO (red)	2	30	Rammelsbergite, NiAs_2	10	42
Lithiophosphate, Li_3PO_4	4m	21	Retgersite, $\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$	7	36
Loellingite, FeAs_2	10	34	Rhodochrosite, MnCO_3	7	32
Loewite, $\text{Na}_{12}\text{Mg}_7(\text{SO}_4)_{13} \cdot 15\text{H}_2\text{O}$	14m	35	Romarchite, SnO	4	28
Lopezite, $\text{K}_2\text{Cr}_2\text{O}_7$	15m	47	*Roscherite, (monoclinic), Be_2Ca ($\text{Fe}_{.3}\text{Mg}_{.7}$) ₂ $\text{Al}_{.67}(\text{PO}_4)_3 \cdot 2\text{H}_2\text{O}$..	16m	96
*Loveringite, $\text{Ca}_{.72}\text{RE}_{.33}(\text{Y}, \text{Th}, \text{U},$ $\text{Pb})_{.05}\text{Ti}_{12.48}\text{Fe}_{3.38}\text{Cr}_{2.24}\text{Mg}_{.92}$ $\text{Zr}_{.58}\text{Al}_{.39}\text{V}_{.21}\text{Mn}_{.04}\text{O}_{.38}$	16m	106	*Roscherite, (triclinic), Be_4Ca_2 ($\text{Mn}_{3.91}\text{Mg}_{.04}\text{Ca}_{.05}$)($\text{Al}_{.13}\text{Fe}_{.42}\text{Mn}_{.12}$) (PO_4) ₆ (OH) ₄ · 6H ₂ O	16m	100
Macedonite, PbTiO_3	5	39	Rutile, TiO_2	7m	83
Magnesiochromite, MgCr_2O_4	9	34	Safflorite, CoFeAs_4	10	28
Magnesite, MgCO_3	7	28	Salamoniac, NH_4Cl	1	59
Magnetite, Fe_3O_4	5m	31	Sanbornite, $\beta\text{-BaSi}_2\text{O}_5$	13m	10
Malachite, $\text{Cu}_2(\text{OH})_2\text{CO}_3$	10	31	Sanmartinite, ZnWO_4	2m	40
Malladrite, Na_2SiF_6	16m	68	Scacchite, MnCl_2	8m	43
Manganolangbeinite, $\text{K}_2\text{Mn}_2(\text{SO}_4)_3$..	6m	43	*Scheelite, CaWO_4	6	23
Manganosite, MnO	5	45	Schultenite, PbHAsO_4	14m	18
Marshite, CuI	4	38	Selenium, Se	5	54
Mascagnite, $(\text{NH}_4)_2\text{SO}_4$	9	8	Selenolite, SeO_2	7m	60
Massicot, PbO (yellow)	2	32	Sellaite, MgF_2	4	33
Matlockite, PbFCl	13m	25	Senarmontite, Sb_2O_3	3	31
Matteuccite, $\text{NaHSO}_4 \cdot \text{H}_2\text{O}$	9m	52	Shcherbinaite, V_2O_5	8	66
Mayenite, $\text{Ca}_{12}\text{Al}_{14}\text{O}_{33}$	9	20	*Siderite, FeCO_3	15m	32
Melanterite, $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$	8m	38	Silver, Ag	1	23
*Meliphanite, $\text{Na}_{.63}\text{Ca}_{1.37}\text{BeAl}_{.13}\text{Si}_{1.87}\text{O}_{6.25}\text{F}_{.75}$	8m	135	Silver, Ag (reference standard) ...	8m	2
Metaborite, HBO_2	4m	27	*Sjögrenite, $\text{Mg}_6\text{Fe}_2\text{CO}_3(\text{OH})_{16} \cdot 4\text{H}_2\text{O}$	10m	103
Metacinnabar, HgS	4	21	Skutterudite, CoAs_3	10	21
Miargyrite, AgSbS_2	5m	49	*Smithsonite, ZnCO_3	8	69
*Millerite, NiS	1m	37	Soda alum, $\text{NaAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	15m	68
Minium, Pb_3O_4	8	32	*Sodalite, $\text{Na}_8\text{Si}_6\text{Al}_6\text{O}_{24}\text{Cl}_2$	7m	158
Mitscherlichite, $\text{K}_2\text{CuCl}_4 \cdot 2\text{H}_2\text{O}$	9m	34	Soda niter, NaNO_3	6	50
Molybdenite, MoS_2	5	47	Sphaerocobaltite, CoCO_3	10	24
Molybdenite, MoO_3	3	30	Sphalerite, ZnS	2	16
Monteponite, CdO	2	27	Spinel, MgAl_2O_4	9m	25
Montroydite, HgO	9	39	Stibnite, Sb_2S_3	5	6
Mullite, $\text{Al}_6\text{Si}_2\text{O}_{13}$	3m	3	Stilleite, ZnSe	3	23
Nantokite, CuCl	4	35	Stolzite, PbWO_4	5m	34
*Newberyite, $\text{MgHPO}_4 \cdot 3\text{H}_2\text{O}$	7m	139	Strontianite, SrCO_3	3	56
Niter, KNO_3	3	58	Struvite, $\text{MgNH}_4\text{PO}_4 \cdot 6\text{H}_2\text{O}$	3m	41
Nitrammite, NH_4NO_3	7	4	Sulfur, S (orthorhombic)	9	54
Nitrobarite, $\text{Ba}(\text{NO}_3)_2$	11m	14	Sylvite, KCl	1	65
Norbergite, $\text{Mg}_3\text{F}_2\text{SiO}_4$	10	39	Syngenite, $\text{K}_2\text{Ca}(\text{SO}_4)_2 \cdot \text{H}_2\text{O}$	14m	25
Oldhamite, CaS	7	15	Szimeke, $\text{MnSO}_4 \cdot \text{H}_2\text{O}$	16m	49
Otavite, CdCO_3	7	11	Tellurantimony, Sb_2Te_3	3m	8
Oxammit, $(\text{NH}_4)_2\text{C}_2\text{O}_4 \cdot \text{H}_2\text{O}$	7	5	*Tellurite, TeO_2	9	57
Palladium, Pd	1	21	Tellurium, Te	1	26
Palladseite, $\text{Pd}_{17}\text{Se}_{15}$	16m	139	Tellurobismuthite, Bi_2Te_3	3m	16
Palmierite, $\text{K}_2\text{Pb}(\text{SO}_4)_2$	14m	30	Tenorite, CuO	1	49
*Paratellurite, TeO_2	10	55	Teschemacherite, NH_4HCO_3	9	5
Paratellurite, TeO_2	7	56	Thenardite, Na_2SO_4	2	59
Periclase, MgO	1	37	Thermonatrite, $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$	8	54
Perovskite, CaTiO_3	9m	17	*Thomsenolite, $\text{NaCaAlF}_6 \cdot \text{H}_2\text{O}$	8m	132
*Phenakite, Be_2SiO_4	8	11	Thorianite, ThO_2	1	57
Picromerite, $\text{K}_2\text{Mg}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	54	Thortveitite, $\text{Sc}_2\text{Si}_2\text{O}_7$	7m	58
*Pirssonite, $\text{Na}_2\text{Ca}(\text{CO}_3)_2 \cdot 2\text{H}_2\text{O}$	9m	106	Tiemannite, HgSe	7	35
Platinum, Pt	1	31	Tin, $\alpha\text{-Sn}$ (cubic)	2	12
			Tin, $\beta\text{-Sn}$ (tetragonal)	1	24

	Vol. or Sec.	Page
*Topaz, $\text{Al}_2\text{SiO}_4(\text{F},\text{OH})_2$	1m	4
Trevorite, NiFe_2O_4	10	44
Trippkeite, CuAs_2O_4	16m	120
*Trona, $\text{Na}_3\text{H}(\text{CO}_3)_2 \cdot 2\text{H}_2\text{O}$	15m	71
Tschermigite, $\text{NH}_4\text{Al}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$...	6	3
Tungstenite, WS_2	8	65
Unnamed mineral, $\text{K}_{1.16}\text{Ba}_{.72}\text{Fe}_{.36}$ $\text{Ti}_{5.58}\text{O}_{13}$	16m	147
Uraninite, UO_2	2	33
Uvarovite, $\text{Ca}_3\text{Cr}_2(\text{SiO}_4)_3$	10	17
*Valentinite, Sb_2O_3	10	6
Vanthoffite, $\text{Na}_6\text{Mg}(\text{SO}_4)_4$	15m	72
Villiaumite, NaF	1	63
Vivianite, $\text{Fe}_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$	16m	38
Wakefieldite, YVO_4	5m	59
Willemite, Zn_2SiO_4	7	62
Witherite, BaCO_3	2	54
Wulfenite, PbMoO_4	7	23
Wurtzite, ZnS	2	14
*Xanthoconite, Ag_3AsS_3	8m	126
Xenotime, YPO_4	8	67
Yavapaiite, $\text{KFe}(\text{SO}_4)_2$	16m	59
Zinc, Zn	1	16
Zincite, ZnO	2	25
Zinkosite, ZnSO_4	7	64
*Zircon, ZrSiO_4	4	68
Zircosulfate, $\text{Zr}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	7	66

Vol. or
Sec. Page

U.S. DEPT. OF COMM. BIBLIOGRAPHIC DATA SHEET		1. PUBLICATION OR REPORT NO. NBS Monograph 25 - Section 16	2. Gov't Accession No.	3. Recipient's Accession No.
4. TITLE AND SUBTITLE Standard X-ray Diffraction Powder Patterns Section 16 - Data for 86 Substances			5. Publication Date October 1979	
			6. Performing Organization Code	
7. AUTHOR(S) M. C. Morris, H. F. McMurdie, E. H. Evans, J. H. de Groot, B. Paretzkin, C. R. Hubbard, S. J. Carmel			8. Performing Organ. Report No.	
9. PERFORMING ORGANIZATION NAME AND ADDRESS NATIONAL BUREAU OF STANDARDS JCPDS--International Centre DEPARTMENT OF COMMERCE for Diffraction Data WASHINGTON, DC 20234 Swarthmore, PA 19081			10. Project/Task/Work Unit No.	
			11. Contract/Grant No.	
12. SPONSORING ORGANIZATION NAME AND COMPLETE ADDRESS (Street, City, State, ZIP) Same as above			13. Type of Report & Period Covered Final	
			14. Sponsoring Agency Code	
15. SUPPLEMENTARY NOTES Library of Congress Catalog Card Number: 53-61386 ☐ Document describes a computer program; SF-185, FIPS Software Summary, is attached.				
16. ABSTRACT (A 200-word or less factual summary of most significant information. If document includes a significant bibliography or literature survey, mention it here.) Standard x-ray diffraction patterns are presented for 87 substances. Fifty-nine of these patterns represent experimental data and 28 are calculated. The experimental x-ray powder diffraction patterns were obtained with an x-ray diffractometer. All d-values were assigned Miller indices determined by comparison with computed interplanar spacings consistent with space group extinctions. The densities and lattice constants were calculated and the refractive indices were measured whenever possible. The calculated x-ray powder diffraction patterns were computed from published crystal structure data. Both peak height and integrated intensities are reported for the calculated patterns.				
17. KEY WORDS (six to twelve entries; alphabetical order; capitalize only the first letter of the first key word unless a proper name; separated by semicolons) Crystal structure; integrated intensities; lattice constants; peak intensities; powder patterns; reference intensities; standard; x-ray diffraction.				
18. AVAILABILITY ☒ Unlimited ☐ For Official Distribution. Do Not Release to NTIS ☒ Order From Sup. of Doc., U.S. Government Printing Office, Washington, DC 20402, SD Stock No. SN003-003-02128-8 ☐ Order From National Technical Information Service (NTIS), Springfield, VA. 22161		19. SECURITY CLASS (THIS REPORT) UNCLASSIFIED		21. NO. OF PRINTED PAGES 190
		20. SECURITY CLASS (THIS PAGE) UNCLASSIFIED		22. Price \$5.00

CRYSTAL DATA

Jointly by the National Bureau of Standards, the U.S. Department of Commerce and the JCPDS-International Centre for Diffraction Data.

Volumes 3 & 4 Now Available

Most reliable source
for identification
of crystalline
materials

Important
for materials
characterization,
phase analysis,
alloy and solid
solution studies,
and materials
design

Compiled at the National Bureau of Standards, the Cambridge Crystallographic Data Centre (England), and the U.S. Geological Survey.

Two new volumes have been added to the popular Third Edition Series of **Crystal Data—Determinative Tables** to update and expand the coverage of this essential reference work for the characterization of crystalline materials.

Volume 3 continues the coverage of Volume 1 on organic and organometallic crystals with data on over 12,000 substances published from 1967 to 1974. Volume 4 continues the coverage of Volume 2 on inorganic and mineral crystals with listings for more than 11,000 substances from 1967 to 1969.

Cell dimensions, space group or diffraction aspect, the number of formula units per unit cell, crystal structure (whether determined), measured density, and x-ray calculated density are given for each entry.

The name of the compound, chemical formula, literature references, and the transformation matrix are also given.

When available, data on crystal structure type, crystal habit, cleavages, twinning, color, optical properties, indices of refraction, melting point, and transition point are included.

Contains
information
on inorganics,
organics,
organometallics,
minerals, drugs,
pesticides,
metals, and
intermetallics

essential
chemists,
metallurgists,
mineralogists, solid
state physicists,
petrologists,
crystallographers,
biochemists

ORDERING INFORMATION

Address all orders to:
JCPDS—International Centre
for Diffraction Data
1601 Park Lane
Swarthmore, Pa. 19081

Materials	Years of Coverage	Number of Entries	Price
Organics, Organometallics	thru 1966	8,000	\$30
Inorganics, Metals, Minerals	thru 1966	16,000	\$50
Organics, Organometallics	1967-74	12,000	\$65
Inorganics, Metals, Minerals	1967-69	11,000	\$65

Full price for 4 volume set \$185.
Payments required on foreign orders.

Please accept my order for:

CRYSTAL DATA—DETERMINATIVE TABLES THIRD EDITION

Ship volumes 1 ☐, 2 ☐, 3 ☐, 4 ☐, or
entire set ☐. (Check appropriate boxes)
To:

Name _____

Organization _____

Address _____

City _____

State _____ Zip Code _____

NBS TECHNICAL PUBLICATIONS

PERIODICALS

JOURNAL OF RESEARCH—The Journal of Research of the National Bureau of Standards reports NBS research and development in those disciplines of the physical and engineering sciences in which the Bureau is active. These include physics, chemistry, engineering, mathematics, and computer sciences. Papers cover a broad range of subjects, with major emphasis on measurement methodology and the basic technology underlying standardization. Also included from time to time are survey articles on topics closely related to the Bureau's technical and scientific programs. As a special service to subscribers each issue contains complete citations to all recent Bureau publications in both NBS and non-NBS media. Issued six times a year. Annual subscription: domestic \$17; foreign \$21.25. Single copy, \$3 domestic; \$3.75 foreign.

NOTE: The Journal was formerly published in two sections: Section A "Physics and Chemistry" and Section B "Mathematical Sciences."

DIMENSIONS/NBS—This monthly magazine is published to inform scientists, engineers, business and industry leaders, teachers, students, and consumers of the latest advances in science and technology, with primary emphasis on work at NBS. The magazine highlights and reviews such issues as energy research, fire protection, building technology, metric conversion, pollution abatement, health and safety, and consumer product performance. In addition, it reports the results of Bureau programs in measurement standards and techniques, properties of matter and materials, engineering standards and services, instrumentation, and automatic data processing. Annual subscription: domestic \$11; foreign \$13.75.

NONPERIODICALS

Monographs—Major contributions to the technical literature on various subjects related to the Bureau's scientific and technical activities.

Handbooks—Recommended codes of engineering and industrial practice (including safety codes) developed in cooperation with interested industries, professional organizations, and regulatory bodies.

Special Publications—Include proceedings of conferences sponsored by NBS, NBS annual reports, and other special publications appropriate to this grouping such as wall charts, pocket cards, and bibliographies.

Applied Mathematics Series—Mathematical tables, manuals, and studies of special interest to physicists, engineers, chemists, biologists, mathematicians, computer programmers, and others engaged in scientific and technical work.

National Standard Reference Data Series—Provides quantitative data on the physical and chemical properties of materials, compiled from the world's literature and critically evaluated. Developed under a worldwide program coordinated by NBS under the authority of the National Standard Data Act (Public Law 90-396).

NOTE: The principal publication outlet for the foregoing data is the Journal of Physical and Chemical Reference Data (JPCRD) published quarterly for NBS by the American Chemical Society (ACS) and the American Institute of Physics (AIP). Subscriptions, reprints, and supplements available from ACS, 1155 Sixteenth St., NW, Washington, DC 20056.

Building Science Series—Disseminates technical information developed at the Bureau on building materials, components, systems, and whole structures. The series presents research results, test methods, and performance criteria related to the structural and environmental functions and the durability and safety characteristics of building elements and systems.

Technical Notes—Studies or reports which are complete in themselves but restrictive in their treatment of a subject. Analogous to monographs but not so comprehensive in scope or definitive in treatment of the subject area. Often serve as a vehicle for final reports of work performed at NBS under the sponsorship of other government agencies.

Voluntary Product Standards—Developed under procedures published by the Department of Commerce in Part 10, Title 15, of the Code of Federal Regulations. The standards establish nationally recognized requirements for products, and provide all concerned interests with a basis for common understanding of the characteristics of the products. NBS administers this program as a supplement to the activities of the private sector standardizing organizations.

Consumer Information Series—Practical information, based on NBS research and experience, covering areas of interest to the consumer. Easily understandable language and illustrations provide useful background knowledge for shopping in today's technological marketplace.

Order the above NBS publications from: Superintendent of Documents, Government Printing Office, Washington, DC 20402.

Order the following NBS publications—FIPS and NBSIR's—from the National Technical Information Services, Springfield, VA 22161.

Federal Information Processing Standards Publications (FIPS PUB)—Publications in this series collectively constitute the Federal Information Processing Standards Register. The Register serves as the official source of information in the Federal Government regarding standards issued by NBS pursuant to the Federal Property and Administrative Services Act of 1949 as amended, Public Law 89-306 (79 Stat. 1127), and as implemented by Executive Order 11717 (38 FR 12315, dated May 11, 1973) and Part 6 of Title 15 CFR (Code of Federal Regulations).

NBS Interagency Reports (NBSIR)—A special series of interim or final reports on work performed by NBS for outside sponsors (both government and non-government). In general, initial distribution is handled by the sponsor; public distribution is by the National Technical Information Services, Springfield, VA 22161, in paper copy or microfiche form.

BIBLIOGRAPHIC SUBSCRIPTION SERVICES

The following current-awareness and literature-survey bibliographies are issued periodically by the Bureau:

Cryogenic Data Center Current Awareness Service. A literature survey issued biweekly. Annual subscription: domestic \$25; foreign \$30.

Liquefied Natural Gas. A literature survey issued quarterly. Annual subscription: \$20.

Superconducting Devices and Materials. A literature survey issued quarterly. Annual subscription: \$30. Please send subscription orders and remittances for the preceding bibliographic services to the National Bureau of Standards, Cryogenic Data Center (736) Boulder, CO 80303.

U.S. DEPARTMENT OF COMMERCE
National Bureau of Standards
Washington, D.C. 20234

OFFICIAL BUSINESS

Penalty for Private Use, \$300

POSTAGE AND FEES PAID
U.S. DEPARTMENT OF COMMERCE
COM-215



SPECIAL FOURTH-CLASS RATE
BOOK
