

NAT'L INST. OF STAND & TECH



A11106 794479













UNITED STATES  
DEPARTMENT OF  
COMMERCE  
NATIONAL BUREAU OF STANDARDS



# NBS SPECIAL PUBLICATION 400-1

National Bureau of Standards  
Library, E-01 Admin. Bldg.

OCT 1 1981

191025

## Semiconductor Measurement Technology

U.S.  
DEPARTMENT  
OF  
COMMERCE  
National  
Bureau  
of  
Standards

### Quarterly Report

July 1 to September 30, 1973

## NATIONAL BUREAU OF STANDARDS

The National Bureau of Standards<sup>1</sup> was established by an act of Congress March 3, 1901. The Bureau's overall goal is to strengthen and advance the Nation's science and technology and facilitate their effective application for public benefit. To this end, the Bureau conducts research and provides: (1) a basis for the Nation's physical measurement system, (2) scientific and technological services for industry and government, (3) a technical basis for equity in trade, and (4) technical services to promote public safety. The Bureau consists of the Institute for Basic Standards, the Institute for Materials Research, the Institute for Applied Technology, the Institute for Computer Sciences and Technology, and the Office for Information Programs.

**THE INSTITUTE FOR BASIC STANDARDS** provides the central basis within the United States of a complete and consistent system of physical measurement; coordinates that system with measurement systems of other nations; and furnishes essential services leading to accurate and uniform physical measurements throughout the Nation's scientific community, industry, and commerce. The Institute consists of a Center for Radiation Research, an Office of Measurement Services and the following divisions:

Applied Mathematics — Electricity — Mechanics — Heat — Optical Physics — Nuclear Sciences<sup>2</sup> — Applied Radiation<sup>2</sup> — Quantum Electronics<sup>3</sup> — Electromagnetics<sup>2</sup> — Time and Frequency<sup>2</sup> — Laboratory Astrophysics<sup>2</sup> — Cryogenics<sup>2</sup>.

**THE INSTITUTE FOR MATERIALS RESEARCH** conducts materials research leading to improved methods of measurement, standards, and data on the properties of well-characterized materials needed by industry, commerce, educational institutions, and Government; provides advisory and research services to other Government agencies; and develops, produces, and distributes standard reference materials. The Institute consists of the Office of Standard Reference Materials and the following divisions:

Analytical Chemistry — Polymers — Metallurgy — Inorganic Materials — Reactor Radiation — Physical Chemistry.

**THE INSTITUTE FOR APPLIED TECHNOLOGY** provides technical services to promote the use of available technology and to facilitate technological innovation in industry and Government; cooperates with public and private organizations leading to the development of technological standards (including mandatory safety standards), codes and methods of test; and provides technical advice and services to Government agencies upon request. The Institute consists of a Center for Building Technology and the following divisions and offices:

Engineering and Product Standards — Weights and Measures — Invention and Innovation — Product Evaluation Technology — Electronic Technology — Technical Analysis — Measurement Engineering — Structures, Materials, and Life Safety<sup>4</sup> — Building Environment<sup>4</sup> — Technical Evaluation and Application<sup>4</sup> — Fire Technology.

**THE INSTITUTE FOR COMPUTER SCIENCES AND TECHNOLOGY** conducts research and provides technical services designed to aid Government agencies in improving cost effectiveness in the conduct of their programs through the selection, acquisition, and effective utilization of automatic data processing equipment; and serves as the principal focus within the executive branch for the development of Federal standards for automatic data processing equipment, techniques, and computer languages. The Institute consists of the following divisions:

Computer Services — Systems and Software — Computer Systems Engineering — Information Technology.

**THE OFFICE FOR INFORMATION PROGRAMS** promotes optimum dissemination and accessibility of scientific information generated within NBS and other agencies of the Federal Government; promotes the development of the National Standard Reference Data System and a system of information analysis centers dealing with the broader aspects of the National Measurement System; provides appropriate services to ensure that the NBS staff has optimum accessibility to the scientific information of the world. The Office consists of the following organizational units:

Office of Standard Reference Data — Office of Information Activities — Office of Technical Publications — Library — Office of International Relations.

<sup>1</sup> Headquarters and Laboratories at Gaithersburg, Maryland, unless otherwise noted; mailing address Washington, D.C. 20234.

<sup>2</sup> Part of the Center for Radiation Research.

<sup>3</sup> Located at Boulder, Colorado 80302.

<sup>4</sup> Part of the Center for Building Technology.



# Semiconductor Measurement Technology

Quarterly Report, July 1 to September 30, 1973

*Special Publication No. 400-1*  
National Bureau of Standards

MAY 6 1974

W. Murray Bullis, Editor

Electronic Technology Division  
Institute for Applied Technology  
National Bureau of Standards  
Washington, D.C. 20234

C.2

Jointly Supported by:  
The National Bureau of Standards,  
The Defense Nuclear Agency, and  
The Defense Advanced Research Projects Agency



U.S. DEPARTMENT OF COMMERCE, Frederick B. Dent, Secretary

NATIONAL BUREAU OF STANDARDS, Richard W. Roberts, Director

Issued March 1974

Library of Congress Catalog Number: 74-600040

National Bureau of Standards Special Publication 400-1

Nat. Bur. Stand. (U.S.), Spec. Publ. 400-1, 68 pages (Mar. 1974)

CODEN: XNBSAV

U.S. GOVERNMENT PRINTING OFFICE  
WASHINGTON: 1974

---

For sale by the Superintendent of Documents, U.S. Government Printing Office, Washington, D.C. 20402  
(Order by SD Catalog No. C13.10:400-1). Price \$1.15

# TABLE OF CONTENTS

## SEMICONDUCTOR MEASUREMENT TECHNOLOGY

	PAGE
Preface . . . . .	viii
1. Introduction . . . . .	1
2. Highlights . . . . .	3
3. Resistivity; Dopant Profiles . . . . .	6
3.1. Spreading Resistance Methods . . . . .	6
3.2. Junction Capacitance-Voltage Method . . . . .	6
3.3. Mathematical Models of Doping Profiles . . . . .	9
3.4. Diffused Layer Sheet Resistance . . . . .	11
3.5. Silicon Resistivity Standards . . . . .	12
4. Crystal Defects and Contaminants . . . . .	16
4.1. Thermally Stimulated Current and Capacitance Measurements . . . . .	16
4.2. Energy Level Model for Gold-Doped Silicon . . . . .	19
5. Insulator Films . . . . .	20
6. Test Patterns . . . . .	22
6.1. Process Development . . . . .	22
6.2. Metal-To-Base Contact Resistor Study . . . . .	22
7. Photolithography . . . . .	26
7.1. Introduction . . . . .	26
7.2. Mask Inspection . . . . .	26
7.3. Photoresist Materials . . . . .	26
8. Metallization . . . . .	28
9. Wafer Inspection and Test . . . . .	31
10. Die Attachment . . . . .	32
10.1. Heat Flow Analysis . . . . .	32
10.2. Void Detection in Transistor Die Attachment . . . . .	32
10.3. Summary . . . . .	33
11. Interconnection Bonding . . . . .	35
11.1. Metallurgical Systems for Ultrasonic Bonding . . . . .	35
11.2. Burn-out Characteristics of Fine Bonding Wire . . . . .	35
11.3. Dissemination Activities . . . . .	39
12. Hermeticity . . . . .	40
13. Thermal Properties of Devices . . . . .	41
13.1. Thermal Resistance Methods . . . . .	41

# TABLE OF CONTENTS

	PAGE
13.2. Analysis . . . . .	41
13.3. Standardization Activities . . . . .	41
14. Microwave Diodes . . . . .	41
14.1. Repeatability Studies . . . . .	41
14.2. Radiation Hardness Study . . . . .	41
15. High-Frequency Measurements . . . . .	41
16. References . . . . .	41
Appendix A. Semiconductor Technology Program Staff . . . . .	51
Appendix B. Semiconductor Technology Program Publications . . . . .	51
Appendix C. Workshop and Symposium Schedule . . . . .	51
Appendix D. Standards Committee Activities . . . . .	51
Appendix E. Solid-State Technology & Fabrication Services . . . . .	51

# LIST OF FIGURES

PAGE

1. Dopant density profiles on the heavily- and lightly-doped sides of a $p$ - $n$ junction as determined from idealized C-V data modified to simulate a random, normally distributed error with standard deviation of 0.05 percent in the measurement of C and V . . . . .	7
2. Dopant density profiles on the lightly-doped side of a $p$ - $n$ junction as determined from idealized C-V data corrected and not corrected to take account of the penetration of the space charge layer on the heavily-doped side . . . . .	8
3. Schematic diagram of dopant distribution in silicon-oxide structure showing both laboratory coordinate, $y$ , and moving coordinate, $z$ . . . . .	10
4. Surface dopant density of a $p$ -type Gaussian diffused layer in uniformly doped $n$ -type silicon as a function of the product of sheet resistance and junction depth for various background dopant densities, $N_b$ . . . . .	13
5. Surface dopant density of an $n$ -type Gaussian diffused layer in uniformly doped $p$ -type silicon as a function of the product of sheet resistance and junction depth for various background dopant densities, $N_b$ . . . . .	14
6. Surface dopant density of a $p$ -type Gaussian diffused layer in uniformly doped $n$ -type silicon as a function of the product of sheet resistance and junction depth for various background dopant densities, $N_b$ , showing the effect of using different relationships between hole mobility and impurity density in the calculation . . . . .	15
7. Dynathermal response of a gold-doped silicon $n$ -MOS capacitor showing features due to the gold acceptor . . . . .	17
8. Isothermal, equilibrium, high-frequency capacitance response of a gold-doped silicon $n$ -MOS capacitor measured at room temperature . . . . .	17
9. Dynathermal response of a gold-doped silicon $n$ -MOS capacitor showing phase I current and phase II current and capacitance response of the gold acceptor as a function of initial gate voltage, $V_{g1}$ , for a heating rate of 9.3 K/s and final gate voltage of -30 V . . . . .	18
10. Hall effect activation energy plot for the gold acceptor in $n$ -type silicon . . . . .	18
11. Photomicrograph of the metal-to-base contact resistor, test structure No. 16 of test pattern NBS-2 . . . . .	24
12. Schematic view of a section through the contact window of the metal-to-base contact resistor test structure pictured in figure 11 . . . . .	24



# LIST OF FIGURES

	PAGE
13. Percent increase in junction-to-case temperature difference of diodes with voids over that of their respective controls measured under steady state and transient conditions as a function of percent effective void area in the diode die attachment . . . . .	33
14. Bond pull strength of ultrasonically bonded, 1-mil diameter aluminum wire, single-level, double bonds as a function of the peak-to-peak vibration amplitude of the bonding tool tip . . . . .	36
15. Scanning electron micrograph of the surface of the thick-film gold metallization used in these ultrasonic bonding experiments . . . . .	37
16. Scanning electron micrograph of a 5-mil diameter aluminum wire after burn out on heating to about 1100°C for 3 min showing the oxide surface coating . . . . .	39

# LIST OF TABLES

	PAGE
1. Mobility Equation Constants . . . . .	12
2. Measurements on Test Pattern NBS-2; Run No. 2.3 . . . . .	23
3. Burn-Out Current for 10-mm Length of Gold Wire . . . . .	37
4. Burn-Out Current for 10-mm Length of Aluminum Wire . . . . .	38
5. Comparison of Infrared and Electrical Thermal Resistance Measurements . . . . .	43
6. Comparison of Infrared and Electrical Thermal Resistance Measurements for the Round-Robin Test Devices . . . . .	43
7. Change in Conversion Loss on Repetitive Measurements of 1N23-Equivalent Schottky-Barrier Diodes . . . . .	45
8. Change in Conversion Loss on Repetitive Measurements of 1N23-Equivalent Schottky-Barrier Diodes Selected for Radiation Hardness Study . . . . .	45
9. Variability of Typical S-Parameter Measurements . . . . .	48

# PREFACE

The Semiconductor Technology Program serves to focus NBS efforts to enhance the performance, interchangeability, and reliability of discrete semiconductor devices and integrated circuits through improvements in measurement technology for use in controlling device fabrication processes and in specifying materials and devices in national and international commerce. Its major thrusts are the development of carefully evaluated and well documented test procedures and associated technology, for use on production lines and in the exchange of devices and materials, and the dissemination of such information to the electronics community. Application of the output by industry is expected to contribute to higher yields, lower cost, and higher reliability of semiconductor devices. In addition, the improvements in measurement technology will lead to greater economy in government procurement and will provide a basis for controlled improvements in fabrication processes and in essential device characteristics.

The Program receives direct financial support principally from three major sponsors: the Defense Advanced Research Projects Agency (ARPA),<sup>\*</sup> the Defense Nuclear Agency (DNA),<sup>†</sup> and the National Bureau of Standards (NBS).<sup>×</sup> The ARPA-supported portion of the Program, Advancement of Reliability, Processing, and Automation for Integrated Circuits with the National Bureau of Standards (ARPA/IC/NBS), addresses critical Defense Department problems in the yield, reliability, and availability of integrated circuits. The DNA-supported portion of the Program emphasizes aspects of the work which relate to radiation response of electron devices for use in military systems. There is considerable overlap between the interests of DNA and ARPA and both interests parallel the measurement-oriented mission of NBS.

Cooperation with industrial users and suppliers of semiconductor devices is achieved through NBS participation in standardizing organizations; through direct consultations with device and material suppliers, government agencies, and other users; and through periodically scheduled symposia and workshops. In addition, progress reports, such as this one, are regularly prepared for issuance in the NBS Special Publication 400 sub-series. More detailed reports such as state-of-the-art reviews, literature compilations, and summaries of technical efforts conducted within the Program are issued as these activities are completed. Reports of this type which are published by NBS also appear in the Special Publication 400 sub-series. Announcements of availability of all publications in this sub-series are sent by the Government Printing Office to those who have requested this service. A request form for this purpose may be found at the end of this report.

---

\* Through ARPA Order 2397, Program Code 4D10 (NBS Cost Center 4259555).

† Through Inter-Agency Cost Reimbursement Order 74-811 (NBS Cost Center 4259522).

×

Through Scientific and Technical Research Services Cost Centers 4251126, 4252128, and 4254115.

# SEMICONDUCTOR MEASUREMENT TECHNOLOGY

## QUARTERLY REPORT JULY 1 TO SEPTEMBER 30, 1973

*Abstract:* This quarterly progress report, twenty-first of a series, describes NBS activities directed toward the development of methods of measurement for semiconductor materials, process control, and devices. Principal accomplishments during this reporting period include (1) extension of the technique for measuring thermally stimulated current and capacitance to include measurements on MOS capacitors, (2) completion of the development of the thermal response method for evaluation of transistor die attachment, (3) analysis of the interlaboratory comparison of transistor scattering parameter measurements, (4) preliminary review of measurement problems in the photolithographic aspects of semiconductor device processing, of problems associated with certain hermeticity testing procedures, and of methods for evaluating metallization step coverage, and (5) initiation of new activity on characterization of oxide films in MOS structures and analysis of diffusion profiles. Results are also reported on spreading resistance, capacitance-voltage, and sheet resistance measurements; the activation energy of the gold acceptor in silicon; evaluation of the base-to-metal contact resistor test structure; metallurgical systems for ultrasonic bonding; burn-out characteristics of fine gold and aluminum bonding wire; transistor thermal resistance measurements; and microwave diode conversion loss measurements. Supplementary data concerning staff, publications, workshops and symposia, standards committee activities, and technical services are also included as appendices.

*Key Words:* Contact resistance; die attachment; dopant profiles; electrical properties; electronics; gold-doped silicon; hermeticity; metallization; methods of measurement; microelectronics; microwave diodes; mobility; MOS devices; oxide films; photomasks; photoresist; resistivity; resistivity standards; scanning electron microscopy; semiconductor devices; semiconductor materials; semiconductor process control; sheet resistance; silicon; S-parameters; spreading resistance; test patterns; thermal resistance; thermally stimulated capacitance; thermally stimulated current; wire bonds.

## 1. INTRODUCTION

This is the twenty-first quarterly report to the sponsors of the Semiconductor Technology Program. It summarizes work on a wide variety of measurement methods for semiconductor materials, process control, and devices that are being studied at the National Bureau of Standards. The Program is a continuing one, and the results and conclusions reported here are subject to modification and refinement.

The work of the Program is divided into a number of tasks, each directed toward the study of a particular material or device property or measurement technique. This report is divided according to these tasks. Highlights of activity during the quarter are given in Section 2. Subsequent sections deal with each specific task area. References cited are listed in the final section of the report.

## INTRODUCTION

The report of each task includes a narrative description of progress made during this reporting period. Additional information concerning the material reported may be obtained directly from individual staff members identified with the task in the report. The organization of the Program staff and telephone numbers are listed in Appendix A.

Background material on the Program and individual tasks may be found in earlier quarterly reports as listed in Appendix B. From time to time, publications are prepared which describe some aspect of the program in greater detail. Current publications of this type are also listed in Appendix B. Reprints or copies of such publications are usually available on request to the author.

Communication with the electronics community is a critical aspect both for receiving guidance in planning future program activities and for disseminating results of the work to potential users. Formal channels for such communication occur in the form of workshops and symposia sponsored or co-sponsored by NBS. Currently scheduled seminars and workshops are listed in Appendix C. In addition, the availability of proceedings from past workshops and seminars is indicated in the appendix.

An important part of the work that frequently goes beyond the task structure is participation in the activities of various technical standardizing committees. The list of personnel involved with this work given in Appendix D suggests the extent of this participation. In many cases, details of standardization efforts are reported in connection with the work of a particular task. Current standardization activities, including those not associated with a particular task, are summarized at the end of section 2.

Technical services in areas of competence are provided to other NBS activities and other government agencies as they are requested. Usually these are short-term, specialized services that cannot be obtained through normal commercial channels. To indicate the kinds of technology available to the program such services provided during the period covered by this report are listed in Appendix E.



## 2. HIGHLIGHTS

Considerable expansion in the scope of the program occurred during this reporting period with the inclusion of a new effort on Advancement of Reliability, Processing, and Automation Integrated Circuits with the National Bureau of Standards (ARPA/IC/NBS) funded by the Defense Advanced Research Projects Agency. New tasks were established in the areas of insulators, films, photolithography, and hermeticity.

Significant technical accomplishments during this reporting period included:

1. extension of the technique for measuring thermally stimulated current and capacitance to include measurements on metal-oxide-semiconductor (MOS) capacitors,
2. completion of the development of the thermal response method for evaluation of transistor die attachment,
3. analysis of the interlaboratory comparison of transistor scattering parameter measurements, and
4. preliminary review of measurement problems in the photolithographic aspects of semiconductor device processing, of problems associated with certain hermeticity testing procedures, and of methods for evaluating metallization step coverage.

In addition, the first of a series of workshops to aid in communication with the electronics community was held. This workshop, on measurement needs for controlling integrated circuit processing and assembly, had the dual objectives of formally announcing the ARPA/IC/NBS program to the semiconductor industry and of giving the industry a forum to provide additional input for use in program definition and planning. The results of the workshop are reported in detail elsewhere [1].

Following are highlights of other activities during this quarter.

Resistivity, Dopant Characterization — Development of calibration curves for the NBS spreading resistance system continued with generation of the curve for  $n$ -type silicon in the range 0.1 to 100  $\Omega \cdot \text{cm}$ . Theoretical study of the application of the junction capacitance-voltage method for measuring diffusion profiles continued with evaluation of the effect of random errors in the measured values of capacitance and voltage on the derived net dopant density on either side of the junction. Mathematical analysis of the boron redistribution problem began with formulation of the problem for both uniform and nonuniform initial distributions. The effect of uncertainty in mobility value on diffusion profiles derived from incremental sheet resistance measurements was studied by comparing results obtained with the use of two different relationships for hole mobility as a function of impurity density in  $p$ -type silicon. A multipass round-robin experiment between NBS and six experienced laboratories was designed to test the stability and multilaboratory precision to be expected from the silicon resistivity standard reference materials now available.

Crystal Defects and Contaminants — The dynathermal current and capacitance responses of a gold-doped  $n$ -MOS capacitor were found to display two distinct features: one, which is

similar to the feature in the junction response, is characteristic of electron emission from the gold acceptor, and a second at higher temperature, which is not found in the junction response, is characteristic of hole emission from the gold acceptor. Additional Hall effect measurements on a specimen of *n*-type silicon with a phosphorus density about  $10^{15} \text{ cm}^{-3}$  and a gold density about three times greater yielded an activation energy within less than 1 meV of that obtained earlier on a less heavily doped specimen.

Insulator Films — Studies of silicon oxide films by ion microprobe mass analysis, electron spectroscopy for chemical analysis, and Auger spectroscopy are being initiated. Apparatus is being designed and constructed for use in studying the bias-temperature stress test for characterizing oxide stability. At the request of one of the major sponsors, a program has been initiated to document procedures and tests necessary to achieve radiation-hardened MOS integrated circuits.

Test Patterns — Several modifications were made in the processing procedure as part of a continuing task to demonstrate the application of test patterns in improving and controlling fabrication processes. Although some improvements were made, further iterations are needed to achieve desired values for various characteristics. Study of the metal-to-base contact resistor test structure showed that although the normalization of the measured contact resistance is uncertain, this structure is suitable for identifying deviations from nominal values of contact resistance which might occur in a production run.

Wafer Inspection and Test — Construction was begun of an optical flying-spot scanner for use in evaluating damage to device structures during inspection or test with a scanning electron microscope.

Interconnection Bonding — Characterization of metallurgical systems for ultrasonic bonding continued with confirmation of the previously reported high bond strength for gold wire on aluminum pads, tentative establishment of suitable bonding conditions for gold wire on gold thick-film metallization, and determination of compatible schedules for bonding aluminum wire both to aluminum thin-film bonding pads on silicon dioxide over silicon and to gold thick-film metallization on alumina substrates. A brief study was carried out on the burn out of fine gold and aluminum wire as a result of Joule heating. In addition to the technical effort, dissemination of the methods and technology developed for controlling and testing ultrasonic wire bonding continued at a high level throughout this period.

Thermal Properties of Devices — Repeatability tests of the emitter-base voltage, emitter-only switching technique for measuring thermal resistance of transistors were completed. Additional calculations with a somewhat more complex model were carried out to establish an appropriate extrapolation procedure for use in analyzing thermal resistance measurements; as in the simpler case, a plot of the logarithm of surface temperature as a function of time results in the most nearly straight lines over the appropriate range of delay times.

Microwave Diodes — Additional repeatability studies of the conversion loss measurement system were made using Schottky-barrier mixer diodes. Groups of diodes were selected for use in a study of the effect of gamma and neutron irradiation on the noise characteristics of these diodes.

Standardization Activities — Fifteen staff members participated in the fall meetings of the ASTM Committee F-1 on Electronics, held in Palo Alto, California, on September 5-7. Most also assisted with the first ARPA/NBS Workshop, held on the final day of the Committee meetings.

Editorial work was carried out on five ASTM Committee F-1 draft documents and was initiated on an EIA-JEDEC document. Two documents were reviewed technically for other standards groups. Work continued on two round-robin experiments being conducted by ASTM Committee F-1.

Dissemination Activities — Organizational activities were undertaken for a workshop on Radiation Effects in MOS Technology. This workshop, cosponsored by the IEEE Nuclear and Plasma Sciences Society, the IEEE Electron Devices Group, and NBS, is scheduled for December 6 and 7, 1973, at Washington, D. C. No proceedings of this Workshop are to be printed.

Planning activity also continued for the Spreading Resistance Symposium, scheduled for June 13-14, 1974, at Gaithersburg, Maryland (NBS Tech. Note 788, p. 64). This symposium is sponsored by ASTM Committee F-1 and NBS. It will immediately follow the June meeting of the committee.

Hermeticity was selected as the subject of the second ARPA/NBS Workshop, which is scheduled to be held on March 29, 1974, at Gaithersburg, Maryland. Topic areas to be discussed include failure due to leaks (correlation of leak rate and failure, failure mechanisms, contamination analysis, and nature of leaks) and evaluation and intercomparison of leak rate measurement procedures (helium mass spectrograph, radioisotope, and new methods).

The third ARPA/NBS Workshop was tentatively scheduled for September 5 and 6 in Scottsdale, Arizona. The subject of this Workshop is design, evaluation, and use of test patterns. It is designed to follow and supplement an informal mini-symposium on test patterns planned for the January meeting of ASTM Committee F-1 in New Orleans.



### 3. RESISTIVITY; DOPANT PROFILES

#### 3.1. Spreading Resistance Methods

In preparation for constructing a calibration curve for phosphorus-doped silicon, a series of wafers was screened for radial uniformity using the spreading resistance instrument. Each wafer was freshly chem-mechanically polished on the surface to be probed by spreading resistance and lapped on the opposite side. Four-probe resistivity measurements were made on the lapped surface of 13 wafers which showed less than 10 percent variation in spreading resistance within the central half-radius region. These had room temperature resistivity in the range from about 0.1 to 100  $\Omega \cdot \text{cm}$ . There was a linear relationship between spreading resistance and resistivity as measured by the four-probe method, but there were discrepancies of as much as 30 percent from the line of regression. No further work will be undertaken until a more complete set of specimens of *n*-type material is available to fill out the calibration curve.

Discrepancies of 50 to 80 percent in the calibration of spreading resistance for high resistivity boron-doped wafers, previously reported, have not yet been explained. A set of wafers adjacent to those which yielded some of the most discrepant points previously observed in this *p*-type material was prepared by the same chem-mechanical polishing treatment as before but measurement of these wafers has not yet been completed.

(J. R. Ehrstein and D. R. Ricks)

#### 3.2. Junction Capacitance-Voltage Method

Theoretical investigation continued into the feasibility of using capacitance-voltage (C-V) measurements to profile a layer diffused into homogeneous background material. Previously, it was shown that this method requires the background dopant density,  $N_b$ , to be known to 1 percent or better in order to obtain a reasonably accurate diffused-layer profile (NBS Tech. Note 806, pp. 10-12). In the present phase, effects of variation in measurement of capacitance and voltage on the profile were studied. As an illustration, idealized C-V data corresponding to junction voltage between 0.3 V forward bias and 100 V reverse bias were generated for the case of a Gaussian diffusion in which the surface dopant density,  $N_0$ , was  $10^{17} \text{ cm}^{-3}$ , the junction depth,  $X_j$ , was 1.0  $\mu\text{m}$ , and  $N_b$  was  $10^{15} \text{ cm}^{-3}$ . The relative capacitance interval,  $\Delta C/C$ , was taken to be 10 percent around zero bias, decreasing to 6 percent at large reverse bias. These ideal data were permuted using random numbers to simulate a measurement error of 0.1 percent (two standard deviations) in both C and V. No systematic error was assumed. These permuted data were then processed to compute dopant profiles on both the lightly-doped (homogeneous) and the heavily-doped (diffused-layer) sides of the *p-n* junction. A composite of these profiles is shown in figure 1. It can be seen that the scatter in the diffused-layer profile significantly exceeds that of the profile on the homogeneous side. Larger and more commonly encountered errors in C would increase the scatter of both profiles but would have a more pronounced effect on the diffused-layer profile. For the conditions considered here the practical range over which one can profile a diffused layer is limited to dopant densities between 6 and 30 times the

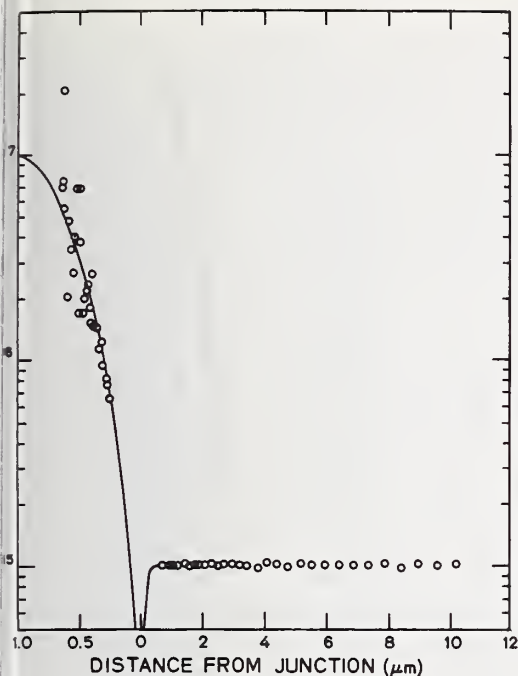


Figure 1. Dopant density profiles on the heavily- and lightly-doped sides of a  $p$ - $n$  junction as determined from idealized C-V data modified to simulate a random, normally distributed error with standard deviation of 0.05 percent in the measurement of C and V. (The doping density profile on the heavily-doped side was assumed to be Gaussian with surface doping density of  $10^{17}$  cm<sup>-3</sup> and junction depth of 1.0 μm as shown by the solid curve to the left of the origin. One point on the heavily-doped side of the junction,  $2.28 \times 10^{18}$  cm<sup>-3</sup> at 0.6 μm, fell outside the range of the plot. The doping density on the lightly-doped side was taken as  $10^{15}$  cm<sup>-3</sup>.)

background dopant density. In this range the measured value of the diffused-layer dopant density is within a factor of two of the true value.

In addition to errors introduced by measurement error in the capacitance and the relative capacitance ratio, which have been considered by Amron [2], the error in the computed diffused-layer profile is increased by the interaction of these two effects with the difference of large numbers called for in the data reduction algorithm. The net dopant density,  $N(A)$ , on the heavily-doped side of the junction at the edge of the space-charge region which penetrated a distance A from the junction is [3]

$$N(A)^{-1} = N(W)^{-1} - N(B)^{-1} \quad (1)$$

where  $N(A)$  is the total space-charge width  $W = A + B$  and  $N(B)$  is the net dopant density on the lightly-doped side of the junction at the edge of the space-charge region which has penetrated distance B from the junction. The quantities derived from capacitance-voltage values are  $N(A)$  and  $W$ . When  $N(A)$  becomes large compared to  $N(B)$ , as in the case of an abruptly diffused junction,  $N(B)$  and B approach  $N(W)$  and W, respectively. In the data reduction algorithm,  $N(A)$  and B are estimated. As  $N(B)$  and B approach  $N(W)$  and W, respectively, the calculated values of  $N(A)$  and A become much less reliable.

A theoretical study was also made of the error found in the profile of the lightly-doped side of various diffused junctions when the diffused-layer correction [3] is not applied. Such information is useful in quantifying these errors and in providing guidelines for developing diffusion schedules which will minimize the need for these corrections.

The diffused-layer correction accounts for the fact that the space-charge layer penetrates not only the lightly-doped side of the junction but also the heavily-doped diffused



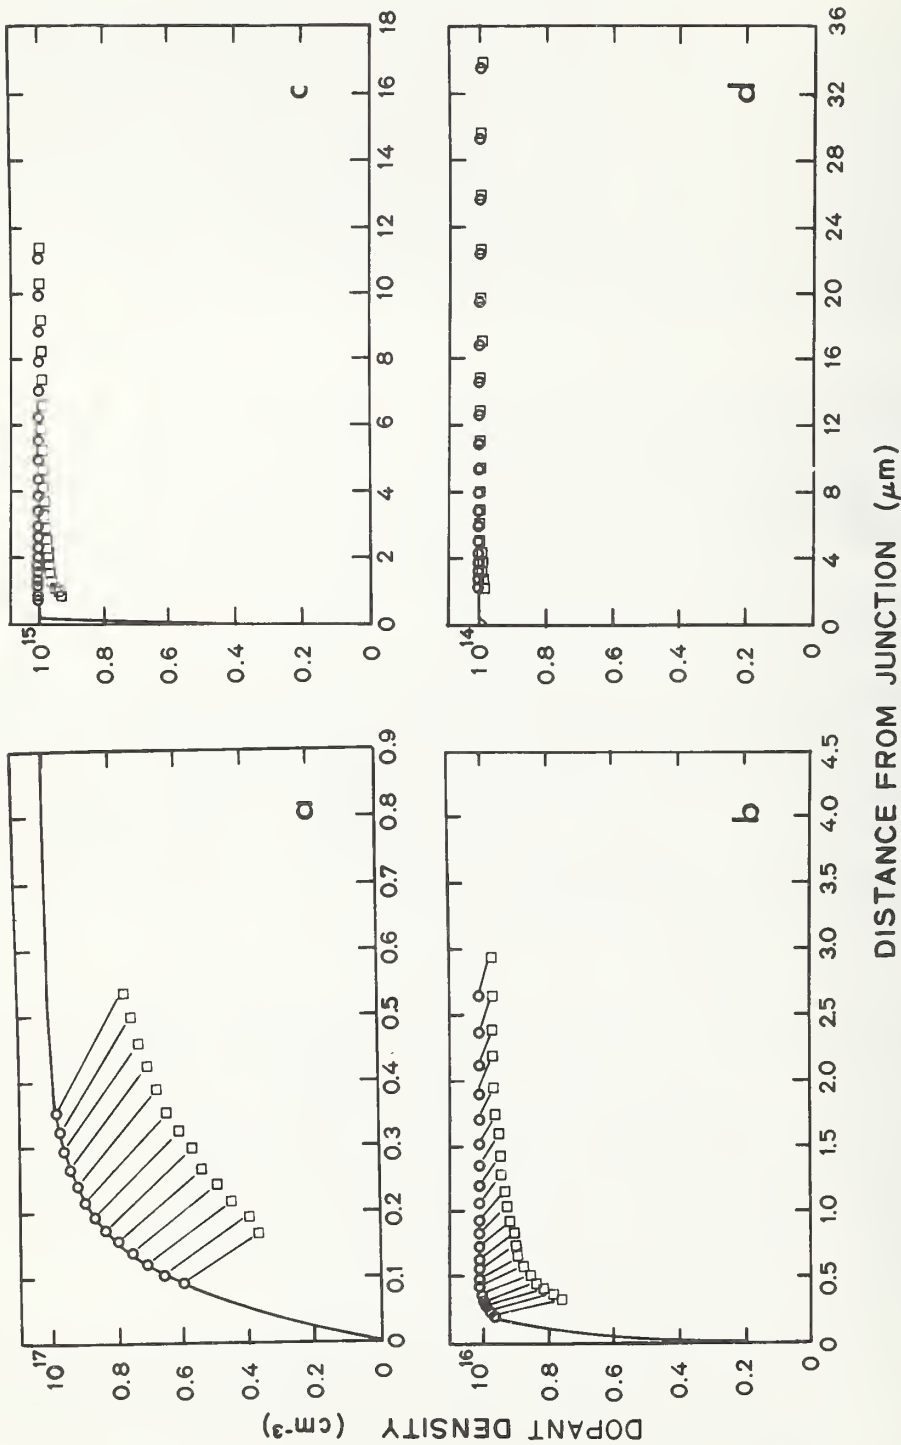


Figure 2. Dopant density profiles on the lightly-doped side of a  $p$ - $n$  junction as determined from idealized C-V data corrected (O) and not corrected ( $\square$ ) to take account of the penetration of the space charge layer on the heavily-doped side. (The dopant density profile on the heavily-doped side was assumed to be Gaussian with surface dopant density of  $10^{19} \text{ cm}^{-3}$  and junction depth of  $1.0 \text{ } \mu\text{m}$ . The dopant density on the lightly doped side was taken as  $10^{17} \text{ cm}^{-3}$  (a),  $10^{16} \text{ cm}^{-3}$  (b),  $10^{15} \text{ cm}^{-3}$  (c), and  $10^{14} \text{ cm}^{-3}$  (d).)

yer. As above, the junctions were assumed to be formed by a Gaussian diffusion into uniformly-doped background material. The junction depth,  $X_j$ , was taken as  $1.0 \mu\text{m}$  and the surface dopant density,  $N_0$ , was taken as  $10^{19} \text{ cm}^{-3}$ . Corrected and uncorrected profiles were calculated from idealized C-V data for which the voltage ranged from 0.3 V forward bias to breakdown or 100 V (whichever is smaller) and for which the capacitance was decremented approximately 10 percent for each successive C-V data pair. Profiles calculated for background dopant densities,  $N_b$ , of  $10^{14}$ ,  $10^{15}$ ,  $10^{16}$  and  $10^{17} \text{ cm}^{-3}$  are shown in figure 2.

The uncorrected profiles,  $N(W)$  vs.  $W$ , are represented by squares, and the corrected profiles,  $N(B)$  vs.  $B$ , are represented by circles. Connecting lines join data points obtained from the same C-V data pair. Note that the uncorrected profiles give erroneously low values of dopant density which gradually approach the correct  $N_b$  value at large distances from the junction. Note also that the uncorrected profiles give erroneously large values for the distance from the junction. This is important when profiling epitaxial layers, for it causes the epitaxial-substrate interface to appear farther from the junction than it actually is. Also illustrated is the fact that the errors increase as  $N_b$  approaches  $N_0$ .

The profiles of figure 2 are valid for both  $p^+n$  or  $n^+p$  junctions. Peripheral effects have been neglected and dopant impurities were assumed to be fully ionized. When calculating the capacitance and voltage, the dielectric constant of silicon was assumed constant with a value  $1.036 \times 10^{-12} \text{ F/cm}$  and the built-in voltage was taken as 0.7 V. For materials with a different dielectric constant, the respective loci of the  $N(W)$  vs.  $W$  and  $N(B)$  vs.  $B$  curves would be unchanged, but a particular point on a locus would correspond to a different capacitance-voltage pair.

(R. L. Mattis and M. G. Buehler)

### 3. Mathematical Models of Doping Profiles

To couple laboratory efforts on production and measurement of doping profiles in silicon, a mathematical study of the diffusion and oxidation processes was begun. The initial phase is directed toward solution of the problem of redistribution of impurities during the oxidation of silicon considering both uniform and nonuniform initial impurity distributions in the silicon.

When a silicon wafer is thermally oxidized, silicon comes from the wafer to form the silicon dioxide. This means that during the oxidation, the silicon surface moves with respect to its original position. As oxidation proceeds, dopant atoms in the silicon are in essence either rejected from the oxide or incorporated into the oxide. This effect causes dopant atoms to be redistributed within the silicon.

A mathematical description of the physical processes involved in this redistribution problem has been given elsewhere [4-7]. These authors consider the dopant impurities to be essentially uniformly distributed in the silicon prior to oxidation. It is the purpose of the present study to use numerical methods to solve for the final dopant profiles where initially the dopants are either uniformly or nonuniformly distributed within the silicon.

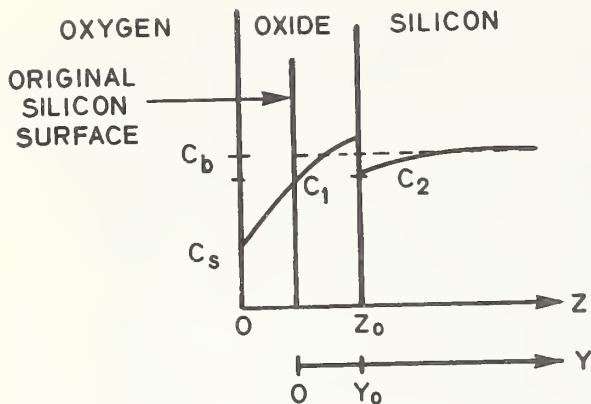


Figure 3. Schematic diagram of dopant distribution in silicon-oxide structure showing both laboratory coordinate,  $y$ , and moving coordinate,  $z$ .

As in previous work [4-7], the silicon is treated mathematically as a semi-infinite slab with its surface exposed to heated oxygen. As shown in figure 3, the  $y$ -axis of the laboratory frame extends into the slab perpendicularly to the surface. In this analysis, the oxide thickness,  $z_0(t)$ , is assumed to increase parabolically with time according to

$$z_0(t) = At^{1/2} \quad (2)$$

where  $A$  is a proportionality constant. The position of the oxide-silicon interface at time  $t$  with respect to the initial silicon surface is given by

$$y_0(t) = \alpha z_0(t) \quad (3)$$

where  $\alpha$  is some constant fraction.

The kinetics of the oxide-layer growth [6] are such that all the increase in volume undergone by a thin layer of silicon when it is oxidized takes place at the oxide-silicon interface. Away from this growth front the oxide is being uniformly convected to the left with a speed  $(1 - \alpha)dz_0(t)/dt$  relative to the laboratory frame. Consequently, there is both diffusive and convective transport of the impurity in the oxide. It is convenient to introduce a moving coordinate system,  $z = y + (1 - \alpha)z_0(t)$ , in the oxide layer with its origin at the oxide surface. Then the impurity concentration in the oxide,  $C_1(z, t)$ , obeys, in the moving frame, the simple diffusion equation

$$\partial C_1(z, t) / \partial t = D_1 \partial^2 C_1 / \partial z^2 \quad (4)$$

for  $0 < z < z_0(t)$ . In the silicon there is only diffusion; therefore, in the laboratory frame

$$\partial C_2(y, t) / \partial t = D_2 \partial^2 C_2 / \partial y^2 \quad (5)$$

for  $y > y_0(t)$  where  $C_2(y, t)$  is the impurity concentration in the silicon.

At the oxide-silicon interface,  $C_1$  and  $C_2$  are coupled for  $t > 0$  by the equilibrium condition

$$C_2[y_0(t), t] = mC_1[z_0(t), t] \quad (6)$$

where  $m$  is the specified segregation (or distribution) coefficient. Another condition, applicable to the oxide-silicon interface, follows from the conservation of mass:

$$C_2(y_0, t)(\alpha - m^{-1})dz_0/dt = D_1 \partial C_1 / \partial z \big|_{z=z_0} - D_2 \partial C_2 / \partial y \big|_{y=y_0}. \quad (7)$$

The boundary condition at the oxide-oxygen interface is assumed to be

$$C_1(0, t) = C_s \quad (8)$$

where  $C_s$  is a specified constant. This assumption is somewhat arbitrary; an alternative condition which could be assumed at this interface is  $\partial C_1 / \partial z = 0$  [6].

Equations (4) through (8) and the uniform initial condition,  $C_2(y, 0) = C_b$ , where  $C_b$  is constant background concentration, specify the uniform redistribution problem. It has analytic solutions given elsewhere [5,6] for specific cases. This class of problem is applicable to MOS devices. Equations (4) through (8) and the nonuniform initial condition for  $y > y_0$ ,  $C_2(y, 0) = C(y)$ , where  $C(y)$  is a nonuniform dopant concentration, specify the nonuniform redistribution problem. This class of problem is applicable to diffused and implanted layers in bipolar silicon devices.

With these formulations of the redistribution problem, it is possible to develop numerical solutions for a variety of cases including the oxidation of silicon slices both uniformly doped and diffused with boron. (S. R. Kraft\* and M. G. Buehler)

#### 4. Diffused Layer Sheet Resistance

In the fabrication of semiconductor devices it is common practice to obtain the surface dopant density,  $N_0$ , of a diffused layer from the measurement of the diffused-layer sheet resistance,  $R_s$ ; the junction depth,  $X_j$ ; the background dopant density,  $N_b$ ; and an assumed functional form for the diffused layer. Irvin [8] has expressed these relations graphically by using his well-known curves which relate resistivity, and hence carrier mobility,  $\mu$ , to dopant density,  $N_I$ , by means of straight-line approximations. Recently, empirical expressions [9] have appeared which relate the carrier mobility data of Irvin to dopant density. More recently, Wagner [10] has published a modified hole mobility expression based on his work on boron-implanted silicon. These expressions have the form

$$\mu = \mu_{\min} + (\mu_{\max} - \mu_{\min}) / [1 + N_I / N_{\text{ref}}]^\alpha \quad (9)$$

where the constants,  $\mu_{\max}$ ,  $\mu_{\min}$ ,  $N_{\text{ref}}$ , and  $\alpha$ , are listed in table 1.

The expression for the sheet resistance  $R_s$  of a diffused layer with a Gaussian profile

$$R_s^{-1} = q \int_0^{X_j} \mu (N - N_b) dx \quad (10)$$

where  $q$  is the electronic charge,  $\mu$  is given by eq (9) with  $N_I = N + N_b$ ,  $N = N_0 \exp(-x^2/L^2)$ ,



Table 1 — Mobility Equation Constants

Type	$\mu_{\max}$ , $\text{cm}^2/\text{V}\cdot\text{s}$	$\mu_{\min}$ , $\text{cm}^2/\text{V}\cdot\text{s}$	$\alpha$	$N_{\text{ref}}$ , $\text{cm}^{-3}$	Reference
<i>n</i>	1330	65	0.72	$8.5 \times 10^{16}$	[9]
<i>p</i>	495	47.7	0.76	$6.3 \times 10^{16}$	[9]
<i>p</i>	495	47.7	0.76	$1.9 \times 10^{17}$	[10]

and  $L = X_j [\ln(N_0/N_b)]^{1/2}$ . Surface dopant density is plotted as a function of the product of  $R_s$  and  $X_j$  in figure 4 for a *p*-type layer diffused into uniformly doped *n*-type silicon and in figure 5 for an *n*-type layer diffused into uniformly doped *p*-type silicon. This form of presentation is more convenient for direct use by a process engineer than the form employed by Irvin [8]. Since curves in figure 5 are based on Caughey and Thomas' fit to Irvin's data, the curves are similar to those which appear in Irvin [8], but differences occur for  $N_0 > 10^{20} \text{ cm}^{-3}$  where the expression of Caughey and Thomas fails to fit Irvin's data. The curves in figure 4 are based on Wagner's mobility expression.

The importance of the value of hole mobility assumed in computing the sheet resistance is illustrated in figure 6. For example, there is a difference of a factor of two between values for the surface dopant density for  $N_b = 10^{15} \text{ cm}^{-3}$  and  $R_s X_j = 1000 \Omega\cdot\mu\text{m}$  calculated using the two expressions. As indicated previously (NBS Tech. Note 806, pp. 21-23), the hole mobility at  $N_I = 10^{17} \text{ cm}^{-3}$  is about  $240 \text{ cm}^2/\text{V}\cdot\text{s}$  from Caughey and Thomas [9], whereas from Wagner [10] it is about  $340 \text{ cm}^2/\text{V}\cdot\text{s}$ . Similar differences occur throughout much of the impurity density range of interest.

(T. E. Griffin and M. G. Buehler)

### 3.5. Silicon Resistivity Standards

A simple multipass round-robin experiment has been designed to test both the stability and the multilaboratory precision which can be expected from the silicon resistivity standard reference materials now available from NBS (NBS Tech. Note 806, pp. 8, 66). This experiment is to involve NBS and six other laboratories who have previously collaborated with ASTM Committee F-1 on Electronics in the measurement of bulk silicon resistivity. In the experiment itself each laboratory is expected to measure two sets of standard reference material wafers to be circulated among the laboratories specifically for this test in addition to submitting data taken at specified intervals on the standard silicon wafers which it owns. The experiment is expected to begin soon after the participating laboratories obtain their sets of standards and to run for 12 to 18 months.

(J. R. Ehrstein and F. H. Brewer)



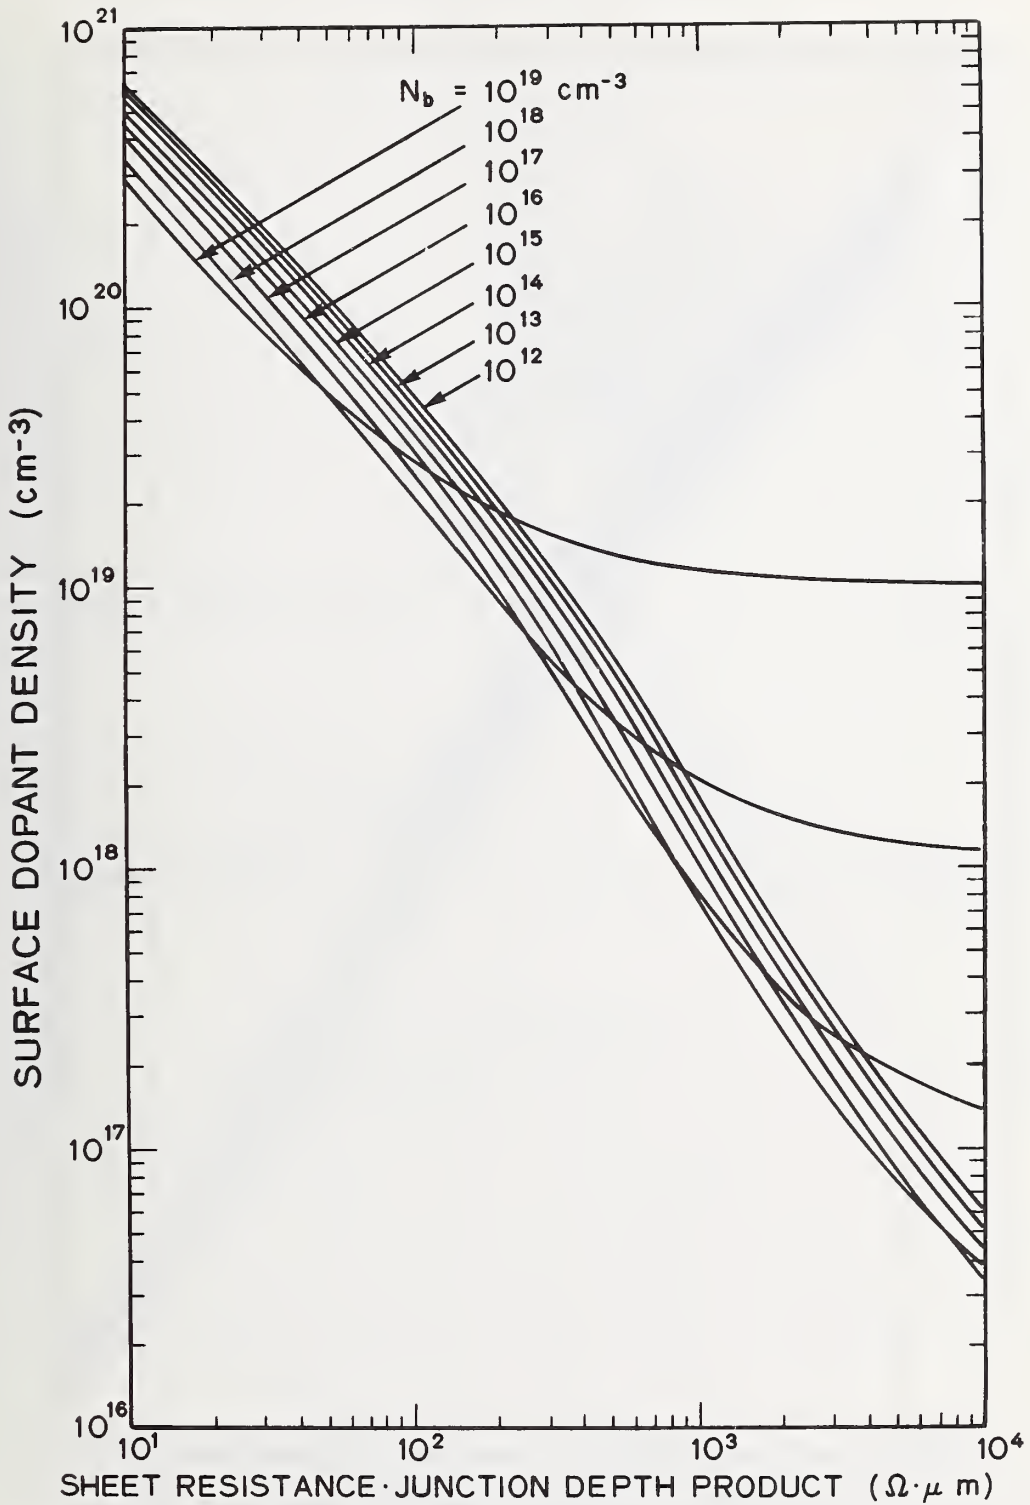


Figure 4. Surface dopant density of a  $p$ -type Gaussian diffused layer in uniformly doped  $n$ -type silicon as a function of the product of sheet resistance (300 K) and junction depth for various background dopant densities,  $N_b$ .

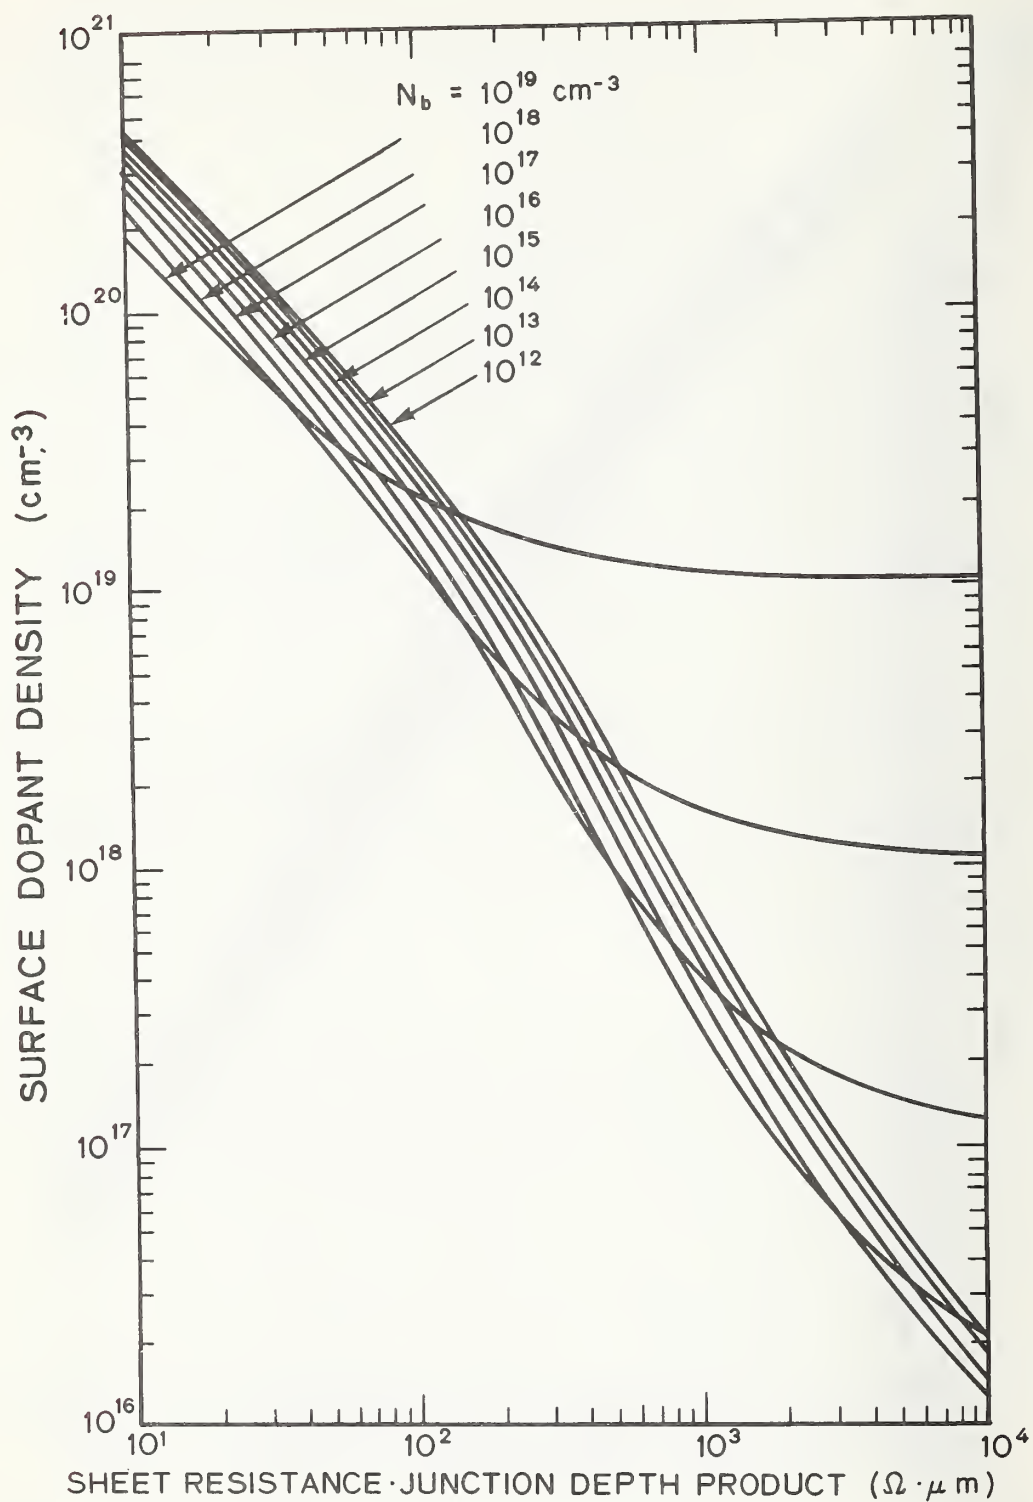


Figure 5. Surface dopant density of an  $n$ -type Gaussian diffused layer in uniformly doped  $p$ -type silicon as a function of the product of sheet resistance (300 K) and junction depth for various background dopant densities,  $N_b$ .

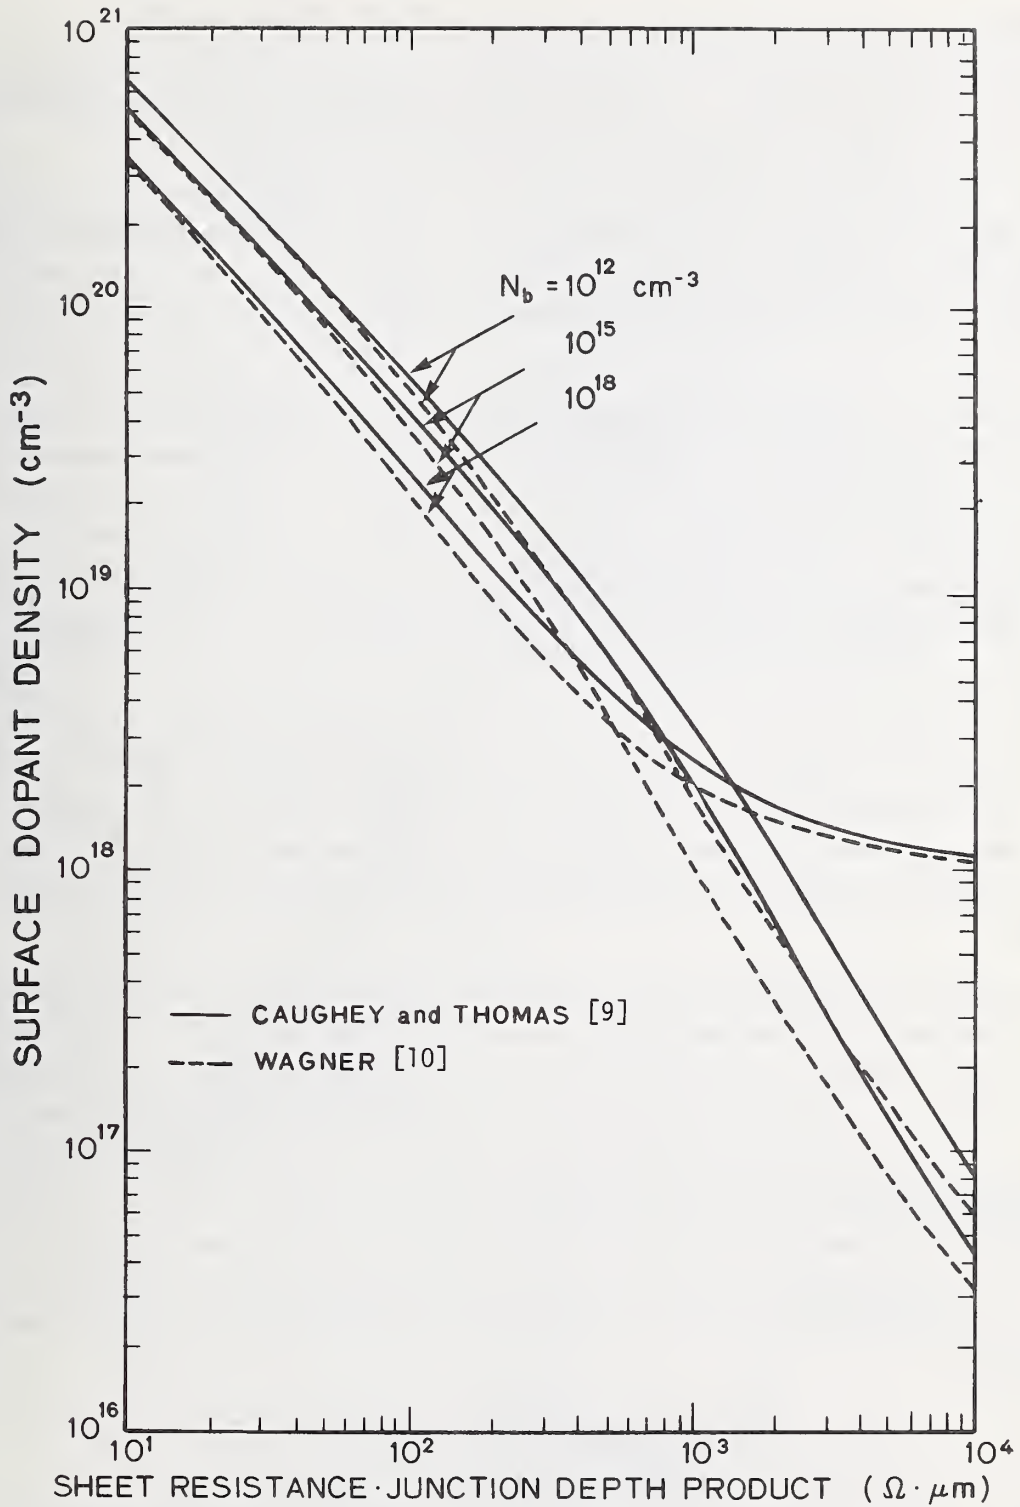


Figure 6. Surface dopant density of a *p*-type Gaussian diffused layer in uniformly doped *n*-type silicon as a function of the product of sheet resistance (300 K) and junction depth for various background dopant densities,  $N_b$ , showing the effect of using different relationships between hole mobility and impurity density in the calculation.

## 4. CRYSTAL DEFECTS AND CONTAMINANTS

### 4.1. Thermally Stimulated Current and Capacitance Measurements

The dynathermal current and capacitance response of the gold acceptor were measured in a gold-doped  $n$ -MOS capacitor. The capacitor was fabricated on the same gold-doped die as the previously studied gold-doped  $p^+n$  junction (NBS Tech. Note 806, p. 13). The MOS capacitor had a 20-mil (0.5-mm) diameter gate on a 0.5- $\mu$ m thick oxide which was thermally grown on a 10- $\Omega$ ·cm  $n$ -type silicon epitaxial layer. The capacitor was mounted on a TO-5 header along with a temperature sensing diode. This configuration and an inexpensive cryostat used for the measurements have been described previously (NBS Tech. Note 806, pp. 13-16).

The dynathermal current and capacitance response of the gold-doped  $n$ -MOS capacitor is shown for various heating rates in figure 7. The gold defect centers were charged by increasing the gate bias to  $V_{g2} = -30$  V from a value  $V_{g1} = -15$  V which was applied at room temperature and held on the capacitor as it was cooled to liquid nitrogen temperature. The value of  $V_{g1}$  was such that an inversion layer of holes is formed at the oxide-silicon interface. This layer prevents the fast surface states from acting as hole and electron generation centers. An isothermal C-V plot, shown in figure 8, illustrates the gate voltage for which inversion is achieved.

The dynathermal response of figure 7 indicates the presence of two distinct phenomena. The first occurs at about 225 K when electrons are released from the gold acceptor; this is termed the majority carrier, phase I response. The second occurs at about 280 K where holes govern the generation rate of the gold acceptor; this is termed the minority carrier, phase II response.

The heating rate dependence of the current and capacitance response, as illustrated in the figure, indicates that the peak in the current  $I_T$  during the majority carrier, phase I response occurs at emission temperatures which shift from 218 to 235 K. This is in good agreement with values obtained for the gold doped  $p^+n$  junction reported previously. The peak in the current during the minority carrier, phase II response occurs at emission temperatures which shift from 273 to 292 K depending upon the heating rate. The capacitance step also shifts with heating rate and for the majority carrier, phase I response, the shift is similar to that observed in the  $p^+n$  junction. From the capacitance values  $C_{2Ii}$  and  $C_{2If}$ , the gold density  $N_t$  can be found from the expression originally derived for the case of a  $p^+n$  junction [11]

$$N_t = \frac{2(V_{g2} - V_{g1}) C_1^4 (C_{2If}^2 - C_{2Ii}^2) (e_n + e_p)}{q\epsilon A^2 (C_1^2 - C_{2If}^2) (C_1^2 - C_{2Ii}^2) e_n} \quad (11)$$

where  $e_n$  and  $e_p$  are the electron and hole emission rates [12],  $q$  is the electronic charge,  $\epsilon$  is the dielectric constant of silicon, and  $A$  is the area of the MOS capacitor. For this MOS capacitor it was found that  $N_t = 2.2 \times 10^{13} \text{ cm}^{-3}$ . It is interesting to note that when

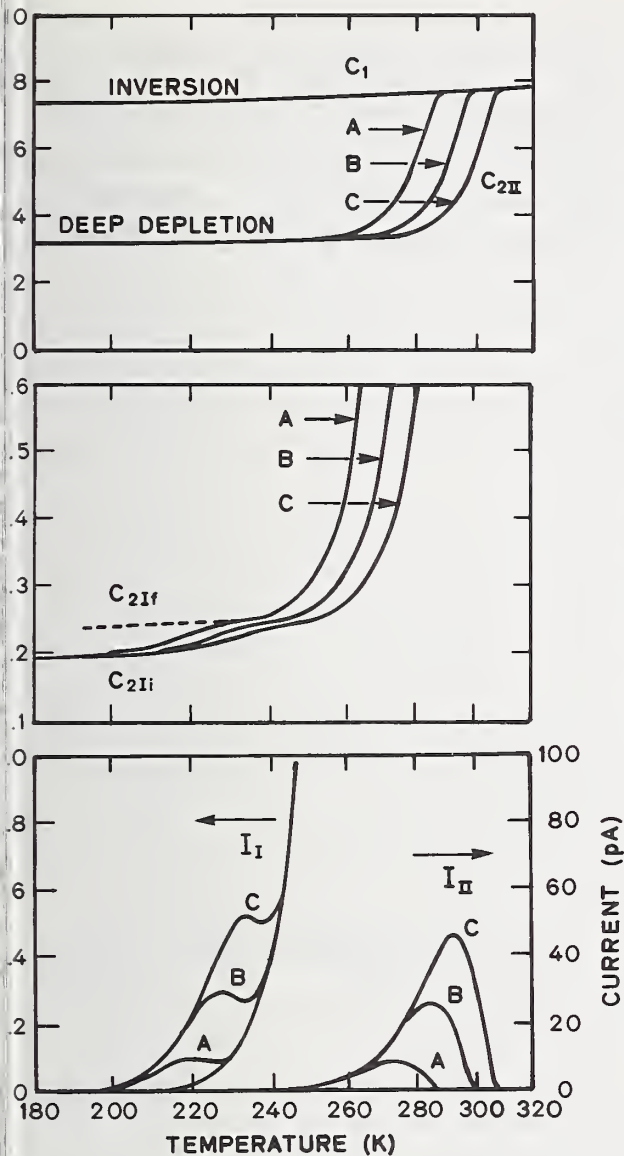
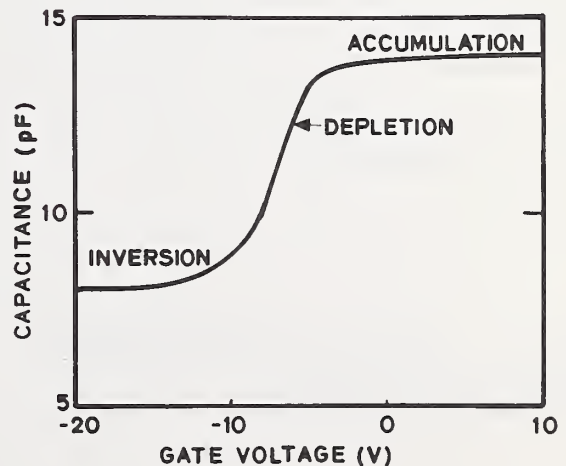


Figure 7. Dynathermal response of a gold-doped silicon  $n$ -MOS capacitor showing features due to the gold acceptor. (Heating rate: 1.6 K/s, curves A; 4.8 K/s, curves B; and 9.3 K/s, curves C; Device 2107.7. The left hand current scale refers to the curves labeled  $I_I$  and the right hand current scale to the curves labeled  $I_{II}$ . The scale of the lower capacitance curves is expanded to show the Phase I capacitance transition which cannot be distinguished on the upper curves. The deep depletion condition, as indicated by the label on the upper capacitance curves, occurs when the potential is changed in a time short compared with the emission time constant at the temperature of the change, in this case  $\sim 77$  K. The capacitance curves labeled  $C_{2II}$ ,  $C_{2If}$ , and  $C_{2II}$  were measured at a gate voltage of  $V_{g2} = -30$  V. The topmost capacitance curve,  $C_1$ , was measured at  $V_{g1} = V_{g2} = -30$  V, but would have been the same if measured at  $V_{g1} = V_{g2} = -15$  V.)

Figure 8. Isothermal, equilibrium, high-frequency capacitance response of a gold-doped silicon  $n$ -MOS capacitor measured at room temperature. (Device No. 2107.7.)





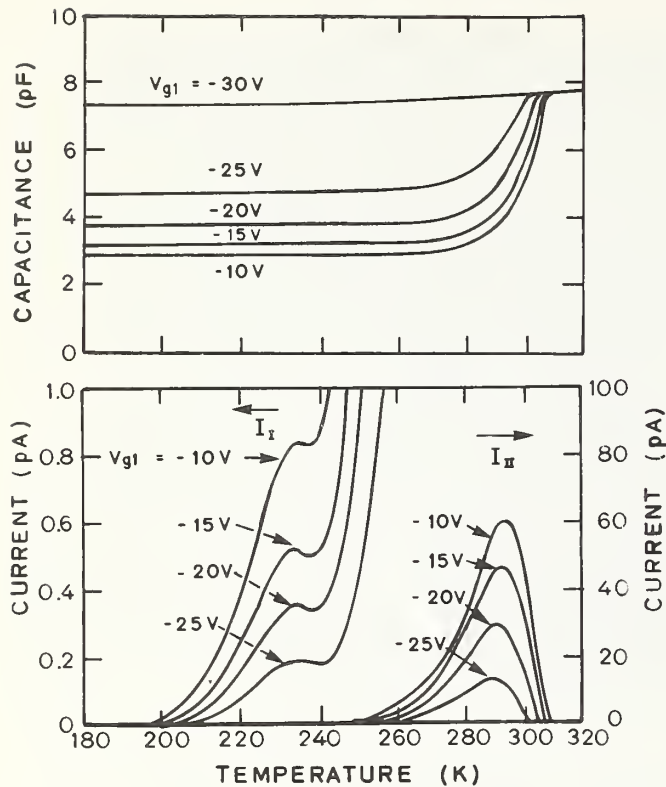


Figure 9. Dynathermal response of a gold-doped silicon  $n$ -MOS capacitor showing phase I current and phase II current and capacitance response of the gold acceptor as a function of initial gate voltage,  $V_{g1}$ , for a heating rate of 9.3 K/s and final gate voltage of -30 V. (Device No. 2107.7. The curves for  $V_{g1} = -15$  V, correspond to curves C in figure 7.)

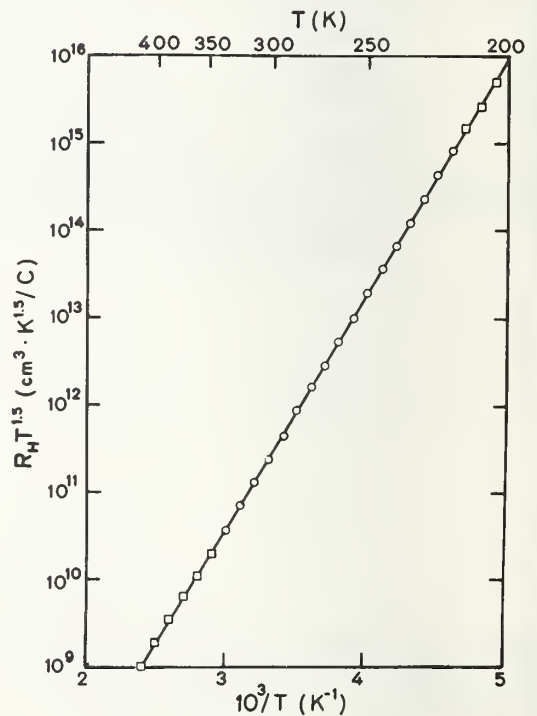


Figure 10. Hall effect activation energy plot for the gold acceptor in  $n$ -type silicon. (Specimen 5N950-144.)

the capacitance pulls out of deep depletion and reaches its inversion value, the current through the MOS capacitor shuts off.

The bias dependence of the current and capacitance dynathermal response is shown in figure 9 for a heating rate of 9.3 K/s and  $V_{g2} = -30$  V. Since  $V_{g1} = V_{g2}$  for the topmost capacitance curve, there is no charging of the space-charge layer. In the figure it is seen that the peak in the majority carrier phase I current,  $I_I$ , is independent of bias and occurs at 235 K. The peak in the minority carrier phase II current,  $I_{II}$ , is somewhat bias dependent, for this peak depends on the space-charge width which, as seen in the capacitance response, is bias dependent. If  $V_{g1}$  is more positive than -10 V, hole inversion does not occur at the oxide-silicon interface and the generation centers there cause excess leakage currents which greatly distort the current response. (W. E. Phillips and M. G. Buehler)

## 2. . Energy Level Model for Gold-Doped Silicon

The activation energy of the gold acceptor in silicon was determined from measurements of the Hall coefficient as a function of temperature on a phosphorus-doped specimen with an initial room temperature resistivity of  $5.3 \Omega \cdot \text{cm}$ . Gold was evaporated on both sides of the silicon wafer and diffused at  $950^\circ\text{C}$  for 144 h; then both wafer faces were lapped to a depth of 125  $\mu\text{m}$  to remove excess surface gold before ultrasonically cutting a Hall bar for the electrical measurements. The room temperature resistivity after gold diffusion was  $0.9 \times 10^4 \Omega \cdot \text{cm}$ . A gold density of  $3.3 \times 10^{15} \text{ cm}^{-3}$  was determined by neutron activation analysis on a specimen from the same wafer as the Hall bar.

The activation energy of the gold acceptor was computed from the data shown in figure 10 by means of a least squares analysis [13] for the slope. The data points included in the analysis are shown by circles; the points excluded because of their deviation from linearity are shown as squares. The calculated energy of  $0.5381 \pm 0.0004$  eV represents the value at zero kelvin of the energy difference between the conduction band edge and the gold acceptor level with the assumption that this difference is a linear function of temperature. The uncertainty in the energy is the square root of the estimated variance of the slope and does not take into account systematic errors which might be present [14]. The energy difference obtained from this specimen is in good agreement with the value of 0.5373 eV measured previously on another specimen (NBS Tech. Note 773, pp. 13-14).

(W. R. Thurber and M. G. Buehler)

## 5. INSULATOR FILMS

Characterization of silicon dioxide and other insulator films in metal-insulator-semiconductor (MIS) device structures is an essential aspect of obtaining the stable insulator characteristics needed for the reliable operation of MIS integrated circuits. One particularly critical class of problems relates to the radiation sensitivity of thermally grown silicon dioxide in MOS devices.

The observed instability of silicon which is induced by ionizing radiation and is manifested by the build up of positive charge is believed to be due to hole trapping [15]. Optical absorption measurements and electron parametric resonance data indicate that the density of hole traps in silicon dioxide tends to increase with increased sodium concentration. Non-bridging oxygen atoms are known to behave as hole traps and to be enhanced by the presence of alkali impurities [16]. Consequently, the increased density of non-bridging oxygen atoms arising from the presence of sodium contamination seems to be to blame for the observed oxide behavior.

Large concentrations of sodium are located at both the metal and silicon interfaces of dry, thermally grown silicon dioxide [17, 18]. Just how the sodium distribution relates to the radiation sensitivity of an MOS structure needs to be explored. Ion microprobe mass analysis (IMMA) is a highly sensitive technique with which the sodium profile can be examined. There is, however, some concern about perturbing the impurity atom profile during ion sputtering. To assess the nature of this and other problems associated with this application of IMMA, detailed study of this technique is being started in cooperation with the NBS Analytical Chemistry Division. Initially, measurements are being made of several silicon dioxide-silicon structures, one of which was implanted with 80 keV sodium ions to a density  $10^{15} \text{ cm}^{-2}$ .\* This study will employ the ion microprobe mass analyzer at NBS.

Another technique, electron spectroscopy for chemical analysis (ESCA), can lead to a basic understanding of the perturbing effects of sodium on silicon-oxygen bonding and hole trapping. With this technique only a very shallow surface layer is explored. A study of growth characteristics of silicon dioxide in the presence of impurities, such as sodium, is being planned in cooperation with the NBS Physical Chemistry Division.

(D. C. Lewis and A. G. Lieberman)

The vacuum capability of the apparatus to be used for this study has been improved by two orders of magnitude by replacing the elastomer O-rings by machined gold rings. As a consequence, the sensitivity level is now 5 percent of a monolayer or an impurity surface density of about  $10^{13} \text{ cm}^{-2}$ . Although sodium ion densities 100 times less than this can cause electrically observable effects in MOS devices, it is assumed that data obtained at detectable impurity densities can be extrapolated to situations of lesser density.

\*

These specimens consisting of a 0.3- $\mu\text{m}$  thick film of silicon dioxide, grown at 1000°C followed by a 20 min anneal in nitrogen, on a <100> surface of 7 to 13  $\Omega\cdot\text{cm}$ , p-type silicon were supplied by H. L. Hughes of the Naval Research Laboratory.

An Auger electron gun is available which can be added to this ESCA spectrometer to obtain resolutions as small as 0.7 eV, five times better than the resolution of commercially available Auger apparatus. (N. E. Erickson\* and J. T. Yates\*)

Oxide stability is most often characterized electrically by means of the bias-temperature stress test [19] in which shifts in flat-band voltage of an MOS capacitor are observed after stressing with an applied voltage at some elevated temperature. In preparation for detailed study of this test, a hot-cold stage with appropriate electrical feed-throughs is being designed and constructed. (M. G. Buehler and A. W. Stallings)

A substantial research effort to develop radiation hardened MOS integrated circuits has been supported by various government agencies for the past several years. The results of this work are reported in scattered locations and in a number of different formats. Consequently, it is difficult to obtain a complete picture of the process technologies proposed for producing such circuits and to ascertain their relative merits. At the request of one of the sponsors of the Program, an effort has been initiated to document process technology and test procedures which have been developed under government contract. (A. G. Lieberman and D. C. Lewis)



## 6. TEST PATTERNS

### 6.1. Process Development

Several modifications were made in the processing procedure as part of a continuing task to demonstrate the application of test patterns in improving and controlling fabrication processes. Run No. 2.3 was made on four  $3\text{-}\Omega\cdot\text{cm}$ ,  $n$ -type bulk silicon slices and four  $10\text{-}\Omega\cdot\text{cm}$ ,  $n/n^+$  epitaxial silicon slices; two slices of each type were doped with gold to a density of about  $10^{13}\text{ cm}^{-3}$ . The emitter-base junction depth was nominally  $0.5\text{ }\mu\text{m}$  and the base-collector junction depth was nominally  $1.7\text{ }\mu\text{m}$ . Representative electrical data from both bulk and epitaxial slices without gold doping are summarized in table 2.

Process changes were made to reduce the base and emitter sheet resistance, the metal-to-emitter contact resistance, the back-side contact resistance, and the fixed oxide charge density, each of which was previously higher than the respective target value (NBS Tech. Note 806, pp. 39-41). In most cases, further iterations appear to be required in order to achieve the target values.

It was found that use of a 0.6 percent antimony-doped gold layer evaporated onto the back side of the slice after etching in CP-6 and alloyed for 30 min at  $500^\circ\text{C}$  in a nitrogen atmosphere substantially reduced the back-side contact resistance. However, the value achieved on bulk slices remained higher than desired.

Elimination of the staining of the boron-diffused regions prior to phosphorous deposition failed to reduce the metal-to-emitter contact resistance to an acceptable value. The fixed oxide charge density remains at a higher level than desired on most slices. This is due to the poor quality of the deionized water ( $\rho \leq 7.5\text{ M}\Omega\cdot\text{cm}$ ) used in the clean-up and oxidation steps. Improved water treatment is expected to cure this problem.

(R. L. Mattis, M. G. Buehler, T. F. Leedy, and J. Krawczyk)

### 6.2. Metal-To-Base Contact Resistor Study

As part of a continuing study of the structures on test pattern NBS-2 (NBS Tech. Note 788, pp. 16-17), a series of measurements was made on the metal-to-base contact resistor, structure number 16 on the test pattern. This structure can be understood with the help of the photograph of figure 11 and the schematic cross-section of figure 12. A current,  $I$ , is passed through contact pads 1 and 4 and the voltage,  $V$ , is measured between contact pads 2 and 3. The substrate is allowed to float electrically during the measurement, and the current is reversed to check for linearity. The current path is indicated in figure 12. The metallization, as seen in the figure, lies on top of the oxide everywhere except in the contact window and in contact pads 1 and 3. Similarly, the  $p^+$  diffused region is under oxide everywhere except for the contact window and the contact pads 1 and 3. The measurement is therefore a Kelvin resistance measurement; the voltage-current ratio ( $V/I$ ) when multiplied by 6.45 yields the metal-to-base contact resistance in units of microhm $\cdot$ square centimetres for a square contact window 1.00 mil ( $25.4\text{ }\mu\text{m}$ ) on a side.



Table 2 — Measurements on Test Pattern NBS-2; Run No. 2.3

Test Structure <sup>a</sup>	Quantity Measured	Measured Value		Target Value
		Bulk	Epitaxial	
14	Base Sheet Resistance, $\Omega/\square$	73	87	100±20
15	Emitter Sheet Resistance, $\Omega/\square$	1.6	0.2	10±5
16	Metal-to-Base Contact Resistance, ( $\mu\Omega\cdot\text{cm}^2$ )	10.9	11.4	<50
17	Metal-to-Emitter Contact Resistance, ( $\mu\Omega\cdot\text{cm}^2$ )	38.4	43.8	<5
18	Back-side Contact Resistance, $\Omega$	9.0	0.25	<1
12	Fixed Oxide Charge Density, $\text{cm}^{-2}$	$5.5 \times 10^{11}$	$2.5 \times 10^{11}$	$(2.5\pm 0.5) \times 10^{11}$
12	Collector Oxide Thickness, nm	520	500	500±50
12	MOS C-V Collector Doping Density, $\text{cm}^{-3}$	$1.7 \times 10^{15}$	$5.5 \times 10^{14}$	—
6	Junction C-V Collector Doping Density, $\text{cm}^{-3}$	$1.7 \times 10^{15}$	$7.5 \times 10^{14}$	—
6	Junction Bulk Leakage @ 5 V, nA/cm <sup>2</sup>	29	17	<5
—	Base-Collector Junction Depth ( $\mu\text{m}$ )	1.71	1.92	

<sup>a</sup> See table 1 and figure 6, NBS Tech. Note 788, pp. 16-17 for identification of test structures.

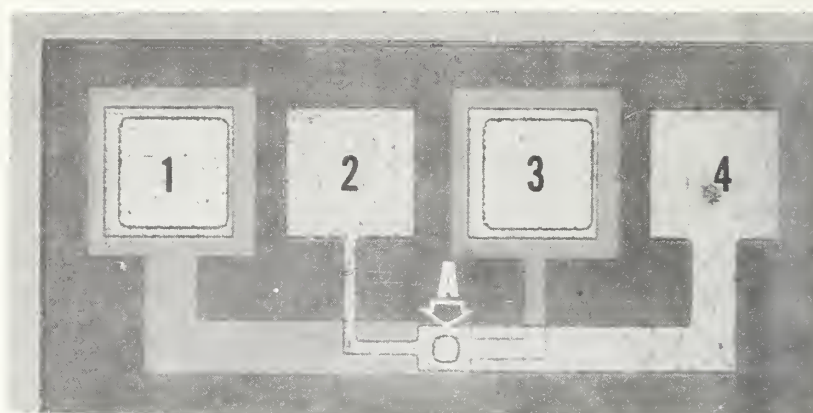


Figure 11. Photomicrograph of the metal-to-base contact resistor, test structure No. 16 of test pattern NBS-2. (The contact window (A) is nominally 1 mil ( $25\text{ }\mu\text{m}$ ) on a side. The center-to-center spacing between adjacent bonding pads (1, 2, 3, 4) is 11 mils ( $0.28\text{ mm}$ ).)

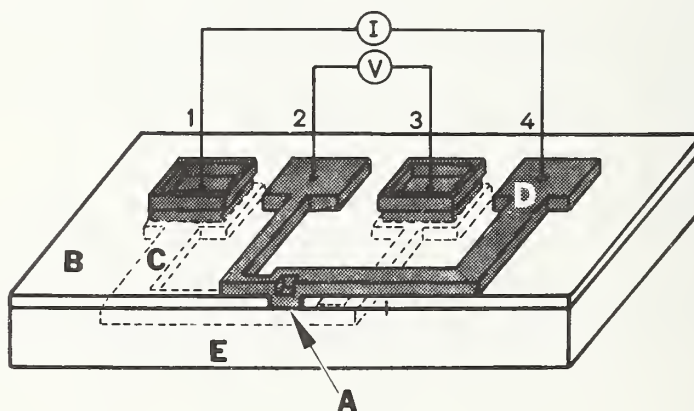


Figure 12. Schematic view of a section through the contact window of the metal-to-base contact resistor test structure pictured in figure 11. (The current path is through pad 4, the metallization stripe (D), the contact window (A), the  $p^+$  diffused layer (C), and contact pad 1. To measure the potential difference,  $V$ , contact is made to the metal side of the contact window through the narrow metallization stripe leading to pad 2 and to the diffused-layer side by the narrow diffused region leading to pad 3. The metallization is isolated from the diffused layer and the  $n$ -type silicon substrate (E) everywhere except at pads 1 and 3 and the contact window (A) by an oxide layer (B).)

## TEST PATTERNS

Several experiments were carried out on this test structure. In one experiment, the metal-to-base contact resistance was mapped over a specimen surface in a manner similar to the map of base sheet resistivity reported previously (NBS Tech. Note 806, pp. 41-43). Values of metal-to-base contact resistance were  $22.4 \pm 2.5 \mu\Omega \cdot \text{cm}^2$  for a base sheet resistance of  $182 \pm 6 \Omega/\square$ .<sup>\*</sup> This value for contact resistance and the values listed in table 2 are roughly 10 to 20 times larger than ideal values quoted in the literature [20,21] for aluminum on boron-doped silicon. This difference can be attributed, at least in part, to the geometry of the contact structure. Because the current path on either side of the contact is parallel with the plane of the contact interface, only a fraction of the contact area carries a significant current. Hence, the area used to normalize the volt-current ratio to contact resistance is actually substantially less than the window area which was used to obtain the values reported. Because of overetching, the contact windows may be somewhat larger than the nominal size. This also affects the normalization because the actual current carrying area is proportional to the length of the side of the contact area.

In a second experiment it was established that the *n*-type substrate of the test structure must be left floating with no electrical connections in order to confine the return current to the diffused layer.

A third experiment verified the linearity of  $\Delta V$  as a function of *I* over the range from 0.1 to 20 mA. This suggests that although it is nonuniform, the current distribution across the contact window area does not change over a considerable range. Consequently, the test structure appears to be suitable as a process monitor which can identify deviations from the nominal contact resistance even though it may not yield absolute values for normalized contact resistance.

(F. R. Kelly, R. L. Mattis, and M. G. Buehler)

---

The range of values quoted is for two sample standard deviations on Slice No. 3, Run No. 2.2. The base is a diffused boron layer, nominally 1.7  $\mu\text{m}$  deep.

## 7. PHOTOLITHOGRAPHY

### 7.1. Introduction

Failures in the photolithographic processing of semiconductor devices can cause both low production yields and poor device reliability. Most of these failures can be related either to faulty masks or failures of the photoresist to perform as desired. To establish the extent and nature of problems associated with the photolithographic processes, a literature search was initiated, and discussions were held with numerous individuals involved in the use of photolithography in various aspects of the microelectronics industry.

### 7.2. Mask Inspection

The need for mask inspection methods to detect faulty masks prior to their use in production was determined to be the most critical need. This criticality results from the relatively long time, several days to a few weeks, that is required for the replacement of a faulty mask. Also, because a mask or set of masks is used to produce many successive devices in production, a faulty mask, undetected for only a short time, can produce a relatively large number of defective devices.

For these reasons, the development of methods to inspect and detect faulty masks, prior to their use in production represents a potential cost per part reduction and an increase in yield. Such inspection methods need to include accurate and rapid dimensional measurements to insure the proper alignment and registration of masks used in the successive steps of device manufacture. In addition, these methods need to include a rapid, reliable means of detecting flaws such as pinholes, thereby assuring the use of only high quality masks.

Initial efforts are being directed toward examination of optical and micrometrology problems associated with mask making and mask inspection in the industry with the cooperation of the NBS Optical Physics Division.

### 7.3. Photoresist Materials

In these discussions it was also determined that measurements of photoresist properties are needed that can be made prior to the use of the resist and interpreted in terms of subsequent resist behavior. The performance and behavior of photoresists are ultimately controlled by the chemistry of the polymers. The most important performance characteristics and their relation to polymer properties are [22-24]:

Adhesion — If the polymer is composed of molecular fractions which are relatively short-chained, solvents, etches, and moisture can more easily permeate the polymer and attack the polymer-wafer surface bonding.

Resolution — Failure of the polymer to form sufficient cross linking can lead to poorly defined edges, low adhesion, and poor resolution through swelling caused by solvent permeation. Poor resolution can also be caused by the presence of large particles of gel or polymeric material. All of



these effects can lower the resistance of the photoresist to acid and moisture attack.

Pinhole propensity — This can be increased by the presence of gel and particulate polymeric material in the resist.

Photosensitivity — Polymer molecules of relatively short chain lengths or failure to have enough photoactive and cross linking sites will cause insufficient cross linking upon exposure and fail to adhere properly. Too many of these sites will cause excessive cross linking and lead to difficulty in completely removing the photoresist.

Wet and dry coating thicknesses — These properties are directly influenced by the viscosity and solids content, both of which are interrelated through the polymer characteristics.

Illumination characteristics also influence the performance of photoresist films. The interaction of light with the layers and interfaces of composite photoresist-coated wafers can result in light scattering and a subsequent loss in resolution. Light scattered into protected regions can also result in exposure of the photoresist in undesired regions. Non-uniform illumination across the mask-photoresist-wafer composite during exposure can lead to losses in resolution, and over- and under-exposed areas on the same wafer resulting in poor production yields.

Initially, the feasibility of using light scattering measurements to monitor the cleanliness, and gel and polymeric particle content of photoresists will be investigated. In addition, an improved mask is being obtained to facilitate completion of the development and evaluation of the test procedure for measuring velocity and acceleration of photoresist spinners (NBS Tech. Note 592, pp. 46-47).

(D. B. Novotny)



## 8. METALLIZATION

The study of tests and test patterns used to determine the adequacy of metal coverage over oxide steps was initiated by studying the literature and discussing the problems associated with quality-of-metallization tests with representatives of the microelectronics industry. One example of the magnitude of the problems associated with improper metallization and metal step coverage is given by Schnable and Keen [25] who reported that 25 percent of the failures observed in a group of bipolar integrated circuits that had undergone operating life tests at rated voltage at 125°C were attributable to open metal interconnections over oxide steps; this was the largest single cause of failure. These tests were reported in 1970; since that time many improvements have been made in metallization processes. For example, tapered oxide steps are now generally used rather than straight steps; properly done, this technique can eliminate thinning of metal over an oxide step [26]. At this time many manufacturers simply inspect metallization of their products on a periodic basis unless otherwise required by a parts buyer.

The different tests described in the literature for evaluating quality of metallization can be divided into three categories:

1. Examination of the metallization on a fabricated device using a scanning electron microscope (SEM).
2. Testing the metallization with a current pulse.
3. Measuring the noise associated with current passing through a metal test stripe.

The problem of metal step coverage has been studied and controlled most often through the use of the SEM [27]. The use of SEM inspection to discriminate between "good" and "bad" metallization has been widely used to design and optimize metallization processes. This technique is well developed and documented. Various standards for SEM inspection have been written; perhaps the most widely referenced is that prepared by Anstead and Adolphsen [28]. Other similar documents are those by Klippenstein and Devaney [29], and Beall [30]. Although the SEM is a useful tool it has several disadvantages which limit its utility in a production environment:

1. The instrument itself is expensive.
2. It requires a highly trained operator.
3. The inspection procedure is slow.
4. The interpretation is subjective.
5. The primary electron beam may damage the active semiconductor regions of the device being inspected.

Despite these drawbacks, it is doubtful that SEM inspection will be supplanted entirely even if other currently envisioned metallization tests are developed. Of the various metallization tests which have been proposed, only SEM inspection gives sufficient information to determine anything other than that the metallization failed.

The current pulse test was developed to circumvent the shortcomings of SEM inspection described above. In the pulse test, it is assumed that if metal is thinner, as at an oxide step, its local resistance is high. Hence, if the stripe is pulsed sufficiently rapidly there is local adiabatic heating at the thinned region which will result in metal burn out if the pulse is long enough and large enough. This is clearly a go/no-go test. The metal can fail this test for a variety of reasons, thinned oxide steps, scratches in the metal, etc.; it is not possible to ascertain why the metal failed from the results of a pulse test.

The current pulse test relies on Joule heating to melt the metallization locally. The heat must be generated adiabatically since the temperature distribution of a metal stripe in steady state is determined principally by parameters of the geometry, oxide, and metal rather than local defects in the metallization.

The utility of the current pulse test is the center of some dispute at this time. The central unresolved question is how short a current pulse is required to heat a metal defect adiabatically. Gurev has reported experiments in which the pulse test was able to discriminate between 30 and 45 percent metal step coverage [31]; however, in a subsequent series of experiments he was not able to correlate the results of his tests with the results of SEM inspection [32]. Crosthwait, Ghate, and Smith [33] have reported experiments in which the results of the current pulse test did not correlate with the results of SEM inspection. In all these experiments pulse widths of 50 ns or longer were used.

In comparing the results of these experiments with an adiabatic theory, it was found that the predictions of the theory were not consistent with the experimental results. On the other hand, a simple steady-state model, developed as part of this study, provides a consistent explanation of the results. This finding suggests that the pulse length used with the current pulse test must be shortened if the adiabatic approximation is to be valid. No reports of experiments have been found in which pulses shorter than 50 ns were used.

At least four variations of the pulse test have been considered:

1. Nondestructive single pulse — The pulse width and amplitude are adjusted so that acceptable metallization does not burn out; burn out of a test stripe constitutes failure.
2. Resistance change — The pulse width and amplitude are adjusted so that the resistance of a test stripe of acceptable metallization is not affected significantly by the pulse; the resistance is measured before and after the pulse, and a change greater than some specified amount constitutes failure.
3. Destructive single pulse — The pulse width and amplitude are adjusted to burn out even the best metallization; the quality of metallization is determined by the time required for burn out, longer times indicating better quality.

4. Destructive repetitive pulsing — Pulses of constant width are repeated with increasing amplitude until burn out occurs; the quality of metallization is determined by the pulse amplitude required for burn out, higher amplitude indicating better quality.

A difficulty in interpreting the results of the different types of current-pulse experiments is that there are no clear cut experimentally verified relationships between them.

In the current-noise test, current is passed through a metal stripe and the resulting noise is monitored. Experiments with molybdenum and aluminum [26,34] have shown that when the current density is sufficiently large, a metal stripe with defective metallization is much noisier than a stripe with good metallization.

The physical mechanisms which generate the noise are not well understood. To some extent thermal heating of the material may be responsible; however, the marked current dependence of the noise index suggests that other processes, in particular electromigration, may contribute to the noise. It would be desirable if the noise test could measure the propensity of a particular metallization to migrate since metal migration is a common failure mechanism.

(D. C. Lewis)

## 9. WAFER INSPECTION AND TEST

An optical flying-spot scanner is being assembled in preparation for examination of integrated circuits before and after exposure to the beam of a scanning electron microscope (SEM). Use of the scanner is expected to assist in evaluation of the susceptibility of integrated circuits to degradation during SEM inspection and in determination of appropriate operating conditions for use in such inspections.

The scanner is designed to use electromechanically driven mirrors to deflect the beam from a low-powered helium-neon laser in a raster pattern focussed on the integrated circuit to be examined. The electrical signal from the integrated circuit which results from the electron-hole pairs generated by the laser light is displayed on an oscilloscope with a raster sweep in synchronism with the laser raster. A scanner of this type has been described previously in the literature [35] and has been used to analyze the operation of functioning semiconductor devices [35] and to observe process-induced device degradation [36]. However, the present system has considerably improved characteristics including a spot size on the specimen of 1  $\mu\text{m}$  diameter, a choice of incident wavelength (0.633 or 1.15  $\mu\text{m}$ ), a range of raster frame times ( $10^{-3}$  to  $10^2$  s), and the capability of providing junction currents over the range  $10^{-11}$  to  $10^{-4}$  A. (D. E. Sawyer)

In a continuing search of the technical literature on SEM examination of semiconductor devices, several papers which discuss SEM-induced damage to, or changes in the electrical characteristics of, devices were collected. (M. J. Wirtz and D. E. Sawyer)



## 10. DIE ATTACHMENT

### 10.1. Heat Flow Analysis

The analysis of heat flow to determine the limitations of thermal response techniques for detecting poor die adhesion in mesa diodes bonded to TO-5 headers was completed using the TRUMP thermal analysis computer program [37]. The data given in figure 13 compare the results of the void detection study for mesa diode lots I, J, and L (NBS Tech. Note 717, p. 20) with those of calculations using TRUMP. The structure shown in the insert was used to approximate the true TO-5 header-chip structure. Cylindrical symmetry and circular, centrally located voids were assumed. The shaded area in the model indicates that part of the structure that has a temperature that is above the temperature of the reference point, the outside of the metal shell, for the 10-ms heating power pulse that was used in determining the transient thermal response. The solid curves give the calculated results for the percent increase in steady-state and transient thermal response of devices with a void above that of devices without voids as a function of void area in percent. The data points are the results of measurements performed on the mesa diode chips bonded to the TO-5 headers with various size voids. These points indicate the percent increase in transient thermal response of the devices with a void above the average response of their respective control devices as a function of effective void area in percent. Effective void area was determined by comparing the experimentally determined percent increase in steady-state thermal response of devices with a void above the average response of their respective control devices with the calculated curve. Most of the deviation from the calculated transient response curve is due to the fact that the voids were not all centrally located and that the area around the dimples were not always completely bonded. For example, the triangles represent devices with uncontrolled voids; these devices were analyzed with radiographic techniques and found to have large unbonded regions in addition to the dimpled area.

The approach taken in this analysis differed somewhat from that taken previously (NBS Tech. Note 727, pp. 25-27) where it was assumed that the approximate percent void area was based on the dimple area divided by the available chip bonding area as long as the voided devices were in control. This assumption was made due to the difficulty in accurately predicting the effects of variations in void location, in bonded area around the void, and in thickness of die attachment material itself on the device thermal response. The correspondence of the experimental points with the calculated transient response curve in the figure suggests that the simplified model satisfactorily represents the actual devices under test, so that the system can be calibrated by determining the effective void area from the calculated steady-state thermal response as was done in the present analysis.

### 10.2 Void Detection in Transistor Die Attachment

Study of the application of thermal response measurements to the detection of voids in transistor die attachment was completed. A second group of three sets of power transistor chips, 60-mils (1.52-mm) square, was bonded onto TO-66 headers with various size dimples ultrasonically machined into the bonding surface to produce, if the bonding were perfect,



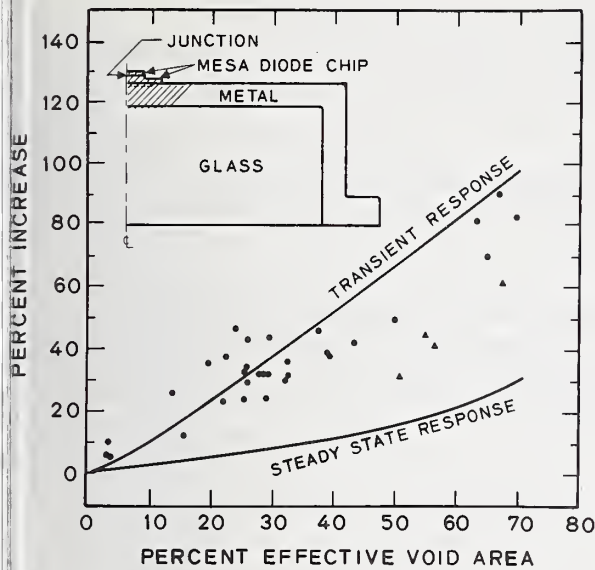


Figure 13. Percent increase in junction-to-case temperature difference of diodes with voids over that of their respective controls measured under steady state and transient conditions as a function of percent effective void area in the diode die attachment. (See text for identification of symbols.)

void sizes of 15, 25 or 40 percent of the chip bonding surface. Ten control devices with no intentional voids were bonded with each of three sets of devices with various diameter samples.

To determine the pulse width for maximum sensitivity to voids, measurements of steady-state thermal response and transient thermal response for heating power pulse widths ranging from 1 to 100 ms were made on devices with and without voids. The results indicated that for these transistors a 5-ms heating power pulse gave the maximum sensitivity. Measurements of the change in emitter-base voltage (NBS Tech. Note 743, pp. 23-24) indicated that while the devices without intentional voids were in control, the devices with various sizes of samples were not. The measured voltage change is proportional to the thermal response if the temperature coefficient of the emitter-base voltage is assumed to be constant.

The percent relative sample standard deviation for the transient thermal response measurement of the controls for the three sets of voided devices ranged from 1.2 to 1.6 percent. For the three sets of devices with voids, the percent relative sample standard deviation ranged from 14.8 to 16.9 percent. The percent increase in sensitivity to voids of transient thermal response over the steady-state thermal response measurements ranged from 57 to 69 percent; the grand average was approximately 100 percent. Even in this case where the attachment is so poor that the increase in sensitivity is less striking, the advantage of the transient thermal response technique over methods requiring heat sinking is nevertheless evident.

### 3. Summary

This concludes the laboratory phase of the semiconductor device die attachment evaluation study. Practical advantages of using the transient thermal response techniques for

## DIE ATTACHMENT

screening semiconductor devices for poor die attachment have been demonstrated over the course of this study. It was found that the technique is [38]:

1. Sensitive — It can be used to detect voids as small as 15 percent of the chip bonding area.
2. Convenient — It can be performed on finished devices and requires minimal, if any, heat sinking.
3. Fast — It can be automated.
4. Adaptable — It can be used for testing a wide variety of device types.

(F. F. Oettinger and R. L. Gladhill)

# 11. INTERCONNECTION BONDING

## 1. Metallurgical Systems for Ultrasonic Bonding

Characterization of various metallurgical bonding systems of interest for microelectronic devices continued. Last quarter a study was made of one manufacturer's gold wire ultrasonically bonded to thin film aluminum on silicon oxide substrates. This wire was found to yield a high bond strength over a very wide range of ultrasonic power (NBS Tech. Rept. 806, pp. 36-38). The result was verified during the present quarter with two more lots of gold wire of different manufacture, breaking strengths, and alloy composition.

Tentative results on the ultrasonic bonding characteristics were obtained for gold wire and gold thick-film metallization. A satisfactorily wide range of bonding force and ultrasonic power yielded strong bonds with these materials providing the bonding time was increased to about 500 ms or more.


The ultrasonic bonding characteristics of 1-mil (25- $\mu$ m) diameter aluminum (1% silicon) were studied on both aluminum thin-film metallization on silicon oxide over silicon and gold thick-film metallization on an alumina ceramic substrate. When bonding silicon dice to hybrid circuits, bonding machine constraints usually require that both the bond to the metallization on the die and the bond to the thick-film conductor be made with the same bonding force. An extensive bonding machine parameter optimization procedure, involving a range of bonding force, bonding time, and tool tip vibration amplitude, was carried out for both systems. From figure 14 it is seen that a 25 gf (0.25 N) bonding force, a 45-ms bonding time, and, for example, a 50- $\mu$ in. (1.3  $\mu$ m) peak-to-peak tool tip vibration amplitude produced satisfactory bonds on both metallizations. Somewhat stronger bonds were obtained on the thick-film gold when a bonding force of 30 gf (0.29 N) was used, but with this force the bonds to the thin-film aluminum were significantly weaker. The greater variability in strength of the bonds made to the thick-film gold occurred because of somewhat greater difficulty in controlling the loop height, and, perhaps more importantly, because of the irregular nature of the gold surface as illustrated in the scanning electron micrograph in figure 15.

Studies were also begun using platinum wire on thick-film gold and thin-film aluminum metallization. Initial results indicate that platinum wire can be bonded to these metallizations with bonding parameters similar to those of aluminum wire. If these results are confirmed by more complete studies and if no secondary complications occur, it may be that platinum wire should be given further consideration for use in hybrids, since it does not form intermetallic compounds with gold, which can be a major problem with aluminum wire [39].


(G. G. Harman and C. A. Main)

## 2. Burn-out Characteristics of Fine Bonding Wire

The current burn-out properties of round and ribbon aluminum and gold bonding wire were studied on 10-mm lengths of wire in air at 23°C. The aluminum wire specimens were obtained from two sources. They contained 1% silicon, 1% magnesium, or 2½% magnesium, or consisted of a proprietary alloy. No significant differences in burn out were observed among these alloys. The gold wire specimens were of 99.99% purity and were also obtained from two

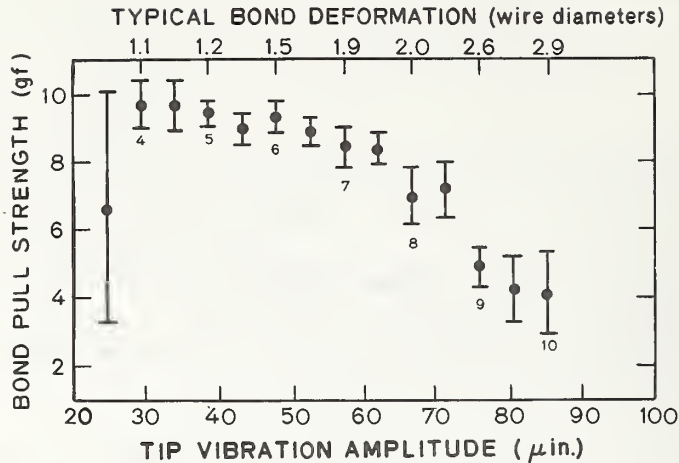

a) Aluminum wire bonded to thin-film aluminum metallization on silicon dioxide over silicon.

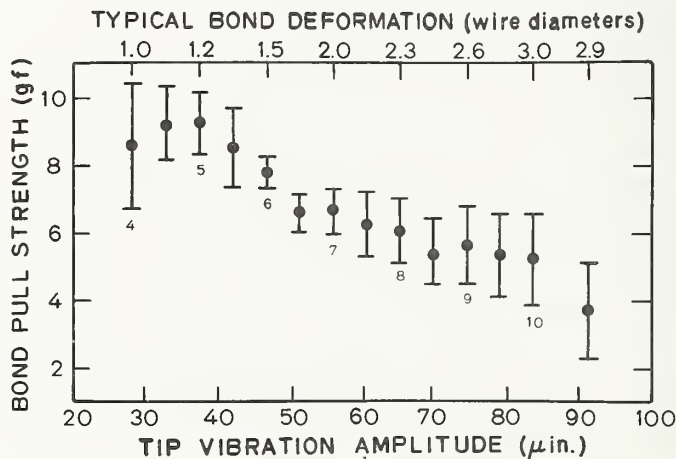

b) Aluminum wire bonded to a 90-percent gold, 10-percent glass binder thick-film metallization on an alumina substrate.

Figure 14. Bond pull strength of ultrasonically bonded, 1-mil (25-μm) diameter aluminum (1% silicon) wire, single-level, double bonds as a function of the peak-to-peak vibration amplitude of the bonding tool tip. (Increasing vibration amplitude corresponds to increasing power; the small numbers below the data points represent settings of the power control on the bonder. The bonding force was 25 gf (0.25 N) and the bonding time was 45 ms. Foot length of the bonding tool used was 4.5 mils (114 μm). The error bars represent one sample standard deviation above and below the mean of 10 to 15 values.)





Figure 15. Scanning electron micrograph of the surface of the thick-film gold metallization used in these ultrasonic bonding experiments. (Magnification:  $\sim 400\times$ .)

sources. The voltage across the 10-mm length of wire was increased gradually while monitoring the current until the wire burned out and ceased conducting.

The burn-out characteristics of the gold wire were as expected. Results are listed in Table 3 which shows the diameter or cross sectional dimensions, the cross sectional area, and the current at which the wire burned out.

The aluminum wire, however, burned out in an unusual manner. At one point in the voltage-current characteristic, the current decreased abruptly. At this point the wire, which glowed white hot, was far above the melting temperature of aluminum. Although the wire

Table 3 — Burn-Out Current for 10-mm Length of Gold Wire

Cross Sectional Dimensions, in.                      ( $\mu\text{m}$ )		Cross Sectional Area, $\text{in.}^2$ ( $\mu\text{m}^2$ )		Burn-Out Current, A
001 <sup>a</sup>	(25.)	$0.78 \times 10^{-6}$	$(5.0 \times 10^2)$	0.56
001 <sup>a</sup>	(25.)	0.78	(5.0     )	$\left\{ \begin{array}{l} 0.56 \\ 0.56 \end{array} \right.$
0015 $\times$ 0.0005	(38. $\times$ 13)	0.75	(4.8     )	0.52
0015 $\times$ 0.0005	(38. $\times$ 13)	0.75	(4.8     )	0.50
.003 $\times$ 0.0005	(76. $\times$ 13)	1.5	(9.7     )	0.89
.003 $\times$ 0.001	(76. $\times$ 25)	3.0	(19.     )	1.34
002 <sup>a</sup>	(51.)	3.1	(20.     )	1.39
.005 $\times$ 0.001	(130. $\times$ 25)	5.0	(32.     )	2.0
005 <sup>a</sup>	(130.)	20.	(130.     )	6.1

Diameter



Table 4 — Burn-Out Current for 10-mm Length of Aluminum Wire

Cross Sectional Dimensions,		Cross Sectional Area,		Composition	Burn-Out Current,
in.	( $\mu\text{m}$ )	in. <sup>2</sup>	( $\mu\text{m}^2$ )		
0.001 <sup>a</sup>	(25.)	$0.78 \times 10^{-6}$	( $5.0 \times 10^{-2}$ )	1% Si	0.49
0.001 <sup>a</sup>	(25.)	0.78	(5.0 )	1% Si	0.39
0.001 <sup>a</sup>	(25.)	0.78	(5.0 )	1% Si	{ 0.375 0.408
0.001 <sup>a</sup>	(25.)	0.78	(5.0 )	2.5% Mg	{ 0.35 0.355
0.0015 × 0.0005	(38. × 13)	0.75	(4.8 )	1% Si	0.392
0.0015 × 0.0005	(38. × 13)	0.75	(4.8 )	1% Si	{ 0.415 0.465
0.0015 × 0.0005	(38. × 13)	0.75	(4.8 )	1% Mg	0.375
0.0021 × 0.0004	(53. × 10)	0.84	(5.3 )	2.5% Mg	0.37
0.003 × 0.0005	(76. × 13)	1.5	(9.7 )	1% Mg	0.565
0.002 <sup>a</sup>	(51.)	3.1	(20. )	1% Si	{ 1.15 1.21
0.005 × 0.001	(30. × 20)	5.0	(32. )	1% Si	1.5
0.003 <sup>a</sup>	(76.)	9.1	(59. )	b	2.2
0.003 <sup>a</sup>	(76.)	9.1	(59. )	1% Si	2.2
0.005 <sup>a</sup>	(130.)	20.	(130. )	b	4.75
0.01 × 0.002	(250. × 51)	20.	(130. )	1% Si	4.5
0.01 <sup>a</sup>	(250.)	78.	(500. )	b	15.5
0.01 <sup>a</sup>	(250.)	78.	(500. )	1% Si	14.7
0.01 <sup>a</sup>	(250.)	78.	(500. )	1% Mg	14.6

<sup>a</sup> Diameter<sup>b</sup> 99% aluminum, impurities unspecified

melted, it apparently developed a thick aluminum oxide sheath that contained and protected the liquid metal. Up to 10 min was required for burn out under these conditions. However, after the melting point had been reached but before burn out, the wire would often open up when the current was switched off or reduced so that the wire temperature dropped below the melting point of aluminum. Consequently the current where the abrupt change occurred was chosen as the practical burn-out current. Data on the various aluminum wires tested are listed in table 4. Figure 16 is a scanning electron micrograph of a section of a 5-mil (1.3 mm) diameter aluminum wire after burn out. The cracked oxide sheath is evident.

(H. K. Kessler)

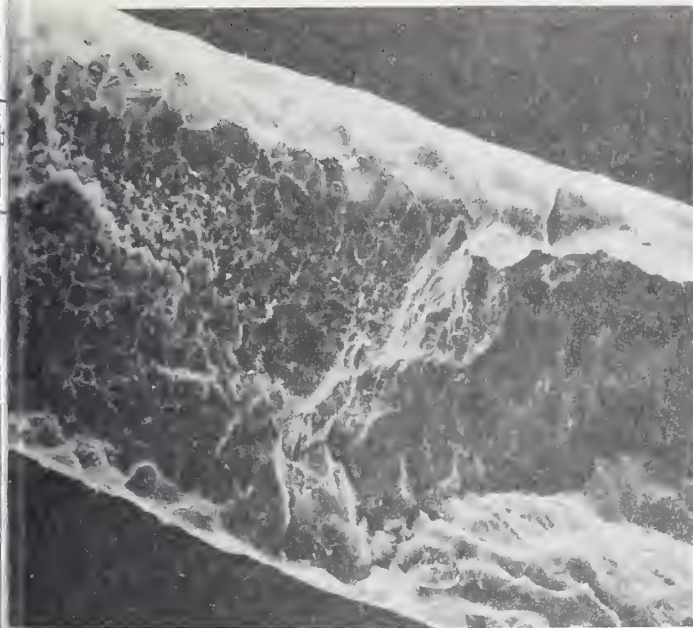


Figure 16. Scanning electron micrograph of a 5-mil (0.13-mm) diameter aluminum wire after burn out on heating to about 1100°C for 3 min showing the oxide surface coating. (Magnification: ~380 X.)

### 3. Dissemination Activities

In addition to the technical activities reported above, dissemination of the methods and technology developed for controlling the ultrasonic bonding process and for testing wire bonds continued at a high level throughout this period. Visits were made to five industrial organizations, and 23 people visited or called NBS to obtain information in this area. A summary report of the work carried out during the past five years was readied for publication [10].

(G. G. Harman and H. K. Kessler)

## 12. HERMETICITY

An assessment of the role of hermeticity and measurements needs was initiated based upon published papers, other agency reports, standards, and direct communications with industrial representatives. The effort to ensure hermeticity represents a significant fraction of device cost, including cost of appropriate package structures, of inspection of package components before assembly, and of fine and gross leak tests after assembly. Further device degradation due to contamination, principally water vapor, from outside the package is a widely recognized failure mode. Yet lack of measurement correlation for the same test method at different stations and for different test methods at the same station, discrepancies in the theory upon which standards for test procedures are based, subjective nature of some preferred test procedures, and scarcity of definitive data linking leak size to device failure were noted.

The theoretical models relating leak size to measured leak rate are in need of revision in several areas. Firstly, while current practice is to compute leak size by laminar (viscous) flow theory for the radioisotope method, and by free molecular flow theory for the helium leak detector method, it should be apparent that such a procedure can produce large differences in computed leak size for any given leak rate. For example, a difference of an order of magnitude or more for a leak in the  $10^{-6}$  atm·cm<sup>3</sup>/s range may result for usual conditions of initial pressurization. Transition flow analysis is more appropriate for leak sizes encountered in practice and should provide the basis for both procedures. Secondly, the rate of escape of gas from the package after pressurization needs better definition, particularly for extending the range of these methods to larger leak sizes. Thirdly, at the five and more atmospheres of pressurization often employed, the flow mechanism of helium or krypton tracer gas into the package may differ significantly. Finally, a better understanding of the passage of water vapor through small channels and the correlation to leak sizes determined from leak rates measured with a more ideal gas is needed. Examination of these factors is in progress.

Assistance is being given ASTM Committee F-1 on Electronics in the organization of an interlaboratory evaluation of the helium mass spectrometer method [41] for testing fine capillary leaks in large volume ( $\sim 1$  cm<sup>3</sup>) containers. The experiment is intended particularly to check the Howl and Mann theory [42] for relating measured to actual leak rate.

(S. Ruthberg)



# 13. THERMAL PROPERTIES OF DEVICES

## 1. Thermal Resistance Methods

Long-term, single-operator measurements, to check the repeatability of the equipment measuring thermal resistance of transistors by the  $V_{EB}$  emitter-only switching technique, are completed. These measurements confirmed the preliminary result reported previously (S. Tech. Note 806, pp. 51-53) that the repeatability is nearly independent of the magnitude of the measured thermal resistance, but that it is limited by a minimum resolvable junction-to-case temperature difference of a few hundredths degree Celsius.

Twenty-two sets of measurements were made on three single diffused transistors in TO-3 packages over a period of three weeks. During the heating, the collector current and voltage were 1 A and 20 V respectively; during calibration, the measuring current was 6 mA and the collector voltage was 2 V. The devices were tested with a case temperature of 60°C and a measuring current of 6 mA. The average value and the pooled sample standard deviation of the measured junction-to-case thermal resistance were 0.79 and 0.01°C/W, respectively. (S. Rubin)

Further studies were performed on 12 transistors to compare measurements of thermal resistance using the  $V_{EB}$  emitter-only switching technique with that of the thermal resistance derived from measurements of peak junction temperature made with the infrared microradiometer. Previously such comparisons have been reported for high-current, low-voltage conditions (NBS Tech. Note 773, pp. 28-29) and high-voltage, low-current conditions (NBS Tech. Note 788, pp. 48-50), both with case temperature of 25°C. In addition, current crowding in three of the devices under the high-voltage, low-current conditions was verified (NBS Tech. Note 806, pp. 47-49). In the present study, comparisons were made under high-current, low-voltage conditions at elevated case temperatures. The thermal resistance of each of the devices was measured with a collector-emitter voltage of 20 V and a case temperature sufficient to raise the junction temperature to approximately 80 percent of its rated value. The collector current was held at 1 A, except in the case of two low-gain devices for which the collector current was 0.5 A. The temperature coefficient of the emitter-base junction voltage,  $V_{EB}$ , used as the temperature sensitive parameter, was determined first between 25 and 100°C and then between the multiple of 25°C nearest to the case temperature used during the measurements and 175°C, except in the case of two low-gain devices for which the upper limit in the second determination was 150°C. It was found that the slope of  $V_{EB}$  as a function of  $T_C$  for constant collector-emitter voltage can vary slightly for temperatures above 125°C.

The results of the thermal resistance measurements are summarized in table 5, which lists the junction-to-case thermal resistance derived from measurements of  $V_{EB}$  using the calibration curves with the thermal resistance derived from the peak junction temperature measured with the infrared microradiometer. For the electrical measurements,  $V_{EB}$  was measured 50  $\mu$ s after the heating power was terminated. The difference between the electrically measured thermal resistance derived from the low- and high-temperature calibrations and that determined from the infrared measurements, expressed as a percentage of the latter, is listed in column 3, labeled  $\Delta_L$ , and column 4, labeled  $\Delta_H$ , respectively, of table 5. The



maximum difference between the data in columns 3 and 4 is less than 6 percentage points. The approximation of using the calibration curve for a temperature range between 25 and 100°C also gives a higher, and thus more conservative, value of thermal resistance. The advantage of this calibration procedure is that the temperature controlled heat sink need not be designed for temperatures higher than 100°C. (S. Rubin, D. L. Blackburn, and F. F. Oettinger)

### 13.2. Analysis

A preliminary study using the TRUMP [37] computer program, undertaken to determine the optimum extrapolation procedure for semiconductor device thermal resistance measurements, indicated that a log-linear extrapolation procedure is appropriate for use on devices that can be approximated by a circular silicon die on an infinite heat sink for the first few hundred microseconds of cooling (NBS Tech. Note 806, pp. 49-51). Further studies were performed taking into account the effects of the change in silicon thermal conductivity with temperature. In addition, a copper slab 0.15 cm thick and the same diameter as the silicon die was added between the silicon and the infinite heat sink which was assumed to be at 0°C. The TRUMP program was again used to calculate the peak surface temperature during the first 200  $\mu$ s of cooling for heat source areas 100, 42 and 22 percent of the silicon chip surface area. In addition, the average surface temperature of the heat source area,  $T_{JAVG}$ , was computed from the TRUMP results as in the previous calculations.

The four extrapolation procedures investigated were log-log, linear-linear, linear-log and log-linear. Again, the last of these, in which the logarithm of the surface temperature is plotted as a linear function of time, yielded the most nearly linear plot; the cooling curves were found to be approximately straight and parallel throughout the interval 20 to 100  $\mu$ s. The extrapolated values of average temperature, which is usually the quantity determined in electrical measurements of thermal resistance, were 20 and 24 percent lower than the calculated peak temperature at  $t = 0$  for the cases where the heat source area was 42 and 22 percent of the chip surface area, respectively. These values are about the same as found previously for the simpler model. For the case where the entire chip surface comprised the heat source area, the extrapolated value was only 5 percent lower than the computed peak temperature at  $t = 0$ . This difference is about half that found for the simpler model.

(F. F. Oettinger and R. L. Gladhill)

### 13.3. Standardization Activities

To compare the electrically measured thermal resistance with thermal resistance derived from the peak junction temperature, the peak junction temperature of the power transistors used in a preliminary round-robin experiment on thermal resistance measurements was measured with an infrared microradiometer. The results of the round-robin experiment, which was conducted in cooperation with JEDEC Committee JC-25 on Power Transistors, showed that the highest electrically measured thermal resistance is obtained with the  $V_{EB}$  emitter-only switching technique (NBS Tech. Note 806, pp. 45-47).

Table 5 — Comparison of Infrared and Electrical Thermal Resistance Measurements

Device No.	$R_{\theta JC}(IR)$ , °C/W	$\Delta_{\ell}$ , %	$\Delta_h$ , %
1	6.5	-19.7	-21.5
3	2.8	-12.1	-15.7
4	3.9	-34.6	-37.9
5	3.9	-15.1	-20.3
6	5.8	-16.7	-17.8
8	8.3	-22.8	-24.3
9	3.6	-8.6	-13.9
10	4.2	-34.5	-36.7
13	4.0	-20.3	-26.0
14	3.7	-12.7	-18.1
15	8.2	-6.3	-8.7
16	7.9	-5.9	-7.8

Table 6 — Comparison of Infrared and Electrical Thermal Resistance Measurements for the Round-Robin Test Devices

Device No.	Case Type	$R_{\theta JC}(IR)$ , °C/W	$\Delta$ , %
101	T0-3	0.70	-20.0
102	T0-3	0.70	-21.4
103	T0-3	0.78	-21.8
104	T0-3	0.89	-20.2
105	T0-3	1.05	-32.4
106	T0-3	1.61	-23.0
107	T0-3	1.65	-35.8
108	T0-3	1.88	-25.0
109	T0-66	2.03	-14.3
110	T0-66	2.65	-11.7
111	T0-66	2.72	-11.8

The results of the present experiments are presented in the last column of table 6 as the difference between the thermal resistance calculated from the junction temperature determined electrically 50  $\mu$ s after the termination of power by the  $V_{EB}$  emitter-only switching method and that determined from the infrared measurements, expressed as a percentage of the latter. For reference, thermal resistance,  $R_{\theta JC}(IR)$ , derived from the infrared measurements is also listed in the table. During the power portion of the electrical measurements, the collector-emitter voltage was 20 V and the collector current was 2.0 A, for the devices in T0-3 cases, or 1.0 A, for the devices in T0-66 cases. For a number of the devices tested, the hottest region on the chip was found to be near the emitter lead. The infrared measurement is therefore somewhat uncertain because of possible interference of the emitter lead with the optical path of the infrared microscope. For these measurements this was probably not a serious problem because under the operating conditions used in the study the temperature gradients across the active regions of the chip were small so that the hottest region of the chip was not well defined. (D. L. Blackburn, S. Rubin, and F. F. Oettinger)

Final revision of the proposed thermal resistance test method for signal diodes was completed in preparation for its circulation as JEDEC Semiconductor Committee Letter Ballot J-20-73-73. Comments were received on a users guide for making thermal characteristics tests on microelectronics devices, recently letter balloted in JEDEC Committee JC-11 on Mechanical Standardization, and modifications are being made to incorporate these comments.

(F. F. Oettinger)

## 14.1. Repeatability Studies

The mixer conversion loss repeatability studies were continued using a larger number of Schottky-barrier diodes from three manufacturers. These measurements are intended to delineate the measurement system repeatability and to provide a reference level for the diodes to be irradiated for a study of the radiation hardness of Schottky-barrier diodes designed as direct replacements for MIL-type 1N23 series X-band diodes (see 14.2.).

Fifty diodes have been measured to date, ten diodes from each of three manufacturers with a specified overall average noise figure limit of 6.0 dB, and ten diodes from each of two manufacturers with a limit of 6.5 dB. All of the diodes were measured twice for conversion loss, self-bias, local oscillator return loss (SWR), output conductance, and forward current (at a given d-c voltage). The 6.5 dB diodes had previously been measured twice for conversion loss and self-bias only. In addition, photographs were made of the current-voltage characteristics of all diodes, and the junction capacitance was measured at three values of reverse bias for all diodes except those which exhibited a high reverse conductance which reduced the capacitance sensitivity at some bias levels below a usable value at the small signal level required. Some diodes were unsuitable for use in the repeatability studies because they exhibited a high conversion loss ( $>6$  dB)\* at the initial or succeeding measurements.

The results of these measurements are summarized in table 7 which lists the mean value and sample standard deviation of the change from the previous measurement. (J. M. Kenney)

## 14.2. Radiation Hardness Study

At frequencies above several gigahertz, most receivers are now being designed to use Schottky-barrier diodes for mixing. A preliminary study to assess the permanent radiation damage to typical, commercially available, Schottky-barrier diodes on exposure to both fast neutrons ( $E > 10$  keV) and  $^{60}\text{Co}$  gamma rays was undertaken in cooperation with the Harry Diamond Laboratories.

The diodes to be studied are of the type designed as direct replacements for MIL type 1N23 series X-band diodes, as have been used in the repeatability studies (see 14.1.). In use, these diodes are mounted in fixed-tuned standard holders [43] which were designed to hold point-contact diodes of the 1N23 type. To facilitate mounting and to select diode polarity, a cap can be attached at either end of the diode.

Diodes for this study were selected from the lots measured in the repeatability study. Only diodes for which the measured conversion loss changed by less than 0.1 dB in repetitive measurements and for which the measured conversion loss never exceeded 6 dB were chosen. A summary of the conversion loss data for the selected diodes is listed in table 8. Diodes were selected in groups of multiples of three from each lot so that equal numbers of diodes

---

\* The measured conversion loss is approximately 1.5 dB lower than the overall average noise figure.

# MICROWAVE DIODES

Table 7 — Change in Conversion Loss on Repetitive Measurements of 1N23-Equivalent Schottky-Barrier Diodes

Lot	Specified Noise Figure Limit, dB	Measurement Repetition	Manufacturer	Mean, dB	Sample Standard Deviation, dB	Number of Measurable Diodes
1	6.0	1	A	-0.058	0.105	9
2	6.0	1	B	0.009	0.032	10
3	6.0	1	C	-0.004	0.027	8
4	6.5	1	A	0.011	0.172	7
4	6.5	2	A	-0.100	0.218	4
4	6.5	3	A	-0.139	0.113	2
5	6.5	1	B	0.001	0.040	9
5	6.5	2	B	0.019	0.051	9
5	6.5	3	B	-0.038	0.030	9

Table 8 — Change in Conversion Loss on Repetitive Measurements of 1N23-Equivalent Schottky-Barrier Diodes Selected for Radiation Hardness Study

Lot	Specified Noise Figure Limit, dB	Measurement Repetition	Manufacturer	Mean, dB	Sample Standard Deviation, dB	Number of Diodes
1	6.0	1	A	-0.002	0.051	6
2	6.0	1	B	0.003	0.029	9
3	6.0	1	C	0.007	0.020	6
4	6.5	1	B	-0.001	0.040	9
4	6.5	2	B	0.019	0.051	9
4	6.5	3	B	-0.038	0.030	9



from each lot could be used for a gamma irradiation group, for a neutron bombardment group, and for an unirradiated control group. An attempt was made to balance the three groups in terms of diode stability, and the assignment of the diodes within the groups was made at random after the groups were formed. It was found that many of the diodes from manufacturer A appeared to be unusually sensitive to mechanical shock, and all but one of the ten 6.5 dB diodes from this source were found not to be acceptable, so that this lot could not be represented.\*

In preparation for the irradiation, conversion loss measurements on three of the lots were repeated after removal and reattachment of the cap. Only the "forward" polarity was used, and care was taken to obtain the same cap orientation, in case of asymmetry. The repeatability seemed to be about the same despite this extra factor.. The diodes can, therefore, be irradiated without the caps, reducing the size and mass of the irradiated structure and also reducing the possibility of secondary radiation from the diode in the holder, from which only the cap protrudes.

(J. M. Kenney and N. J. Berg<sup>†</sup>)

---

\* Unfortunately, the first Schottky-barrier diode used in the repeatability studies (NBS Tech. Note 806, pp. 54-55) was from this lot.

† Harry Diamond Laboratories, Washington, D. C. 20438. (Contract S-402391-4.)

## 15. HIGH-FREQUENCY MEASUREMENTS

Analysis was completed of the results of the interlaboratory comparison of transistor scattering parameter measurements conducted for the Air Force Weapons Laboratory (NBS Tech. Notes 743, pp. 42-43; 754, p. 35; 773, pp. 34-36; 788, pp. 55-57; and 806, pp. 56-57) [44]. This test was designed to determine the extent of the agreement between transistor measurements made in different laboratories by different personnel using the procedure and equipment normally employed by the participating laboratory. To provide the necessary data each participating laboratory measured the S parameters of a set of selected transistors of three types. In addition, each laboratory measured a number of passive devices to provide data for the assessment of within-laboratory variability and to assist in identifying the source of unacceptably large variability if this proved to be necessary.

S parameters were measured in 100 MHz increments at frequencies from 200 to 2000 MHz. At each frequency the four measurements made on the passive devices by each laboratory were averaged to obtain a mean for the laboratory, and the within-laboratory sample standard deviation was calculated as a measure of the dispersion of the data about this mean. The means for each of the laboratories were then averaged to obtain the overall mean, and the sample standard deviation was calculated as a measure of the between-laboratory variability (NBS Tech. Note 788, p. 56).

The upper frequency limit for measurement of S-parameters on the transistors was 1000 to 1800 MHz depending on type. Only the between-laboratory variability of the transistor measurements was determined, because the transistors were measured only once at each bias frequency. For the magnitudes of the S and h parameters, the sample standard deviation was expressed as a percentage of the overall mean to obtain the relative standard deviation coefficient of variation. The sample standard deviation was used as a measure of the variability of the phase measurements.

As an illustration, the variability of the 17 measurements of each of the four S parameters made on each of the six 2N3960 transistors at a bias current of 2.5 mA by the five participating laboratories which used automatic network analyzers is summarized in table 9. The maximum, mean, and minimum sample standard deviations obtained in the 102 sets of data for each parameter are listed. In addition, the variability of  $h_{fe}$  and  $h_{ie}$ , calculated from the measured S parameters, is indicated. Measurements made by the laboratory which used manual equipment fell within the same range as those made on the automatic systems.

The extreme variability of the  $s_{11}$  measurements is due in large part to the variability introduced by the differences in calibration procedures employed by the participants when using the transistor fixture (NBS Tech. Note 773, p. 35). In addition, the variability of the magnitude of  $s_{21}$  was excessive because the signal level applied to the transistor base by one of the participants exceeded the requirements for small-signal conditions.

If these sources of variability are eliminated, for example, by specifying the calibration method to be used and by specifying a maximum signal level to the transistor under test, the variability of S-parameter measurements could be expected to be considerably reduced.

Table 9 — Variability of Typical S-Parameter Measurements

		All Laboratories		Three Laboratories	
		Magnitude, %	Phase, deg	Magnitude, %	Phase, deg
$s_{11}$	max	45.9	34.2	7.5	8.2
	mean	12.6	8.8	4.5	1.8
	min	3.5	0.7	0.6	0.1
$s_{21}$	max	9.9	3.3	5.4	1.7
	mean	2.9	1.1	2.7	0.7
	min	0.9	0.2	0.7	0.1
$s_{12}$	max	5.2	1.7	6.6	2.2
	mean	2.4	0.9	3.0	0.9
	min	0.9	0.2	0.2	0.1
$s_{22}$	max	8.9	3.1	4.8	3.5
	mean	4.4	2.0	2.8	2.0
	min	1.6	0.7	0.8	0.5
$h_{fe}$	max	8.6	5.0	7.0	3.0
	mean	3.4	1.6	2.2	1.1
	min	0.8	0.4	0.2	0.2
$h_{ie}$	max	23.1	12.0	2.6	3.0
	mean	5.2	3.1	1.0	1.6
	min	1.1	0.5	0.0	0.3

The extent of this reduction is suggested by analyzing the results of the measurements after excluding two laboratories because of apparent calibration anomalies and the 200 MHz data because of the excessive signal level used by one of the remaining laboratories. The last two columns of table 9 contain the results of this analysis.

Examination of data from the other transistor groups and at other biases shows that the results presented in the table are typical of the entire sample used in the interlaboratory comparison.

(G. J. Rogers)

## 16. REFERENCES

- Schafft, H. A., *Semiconductor Measurement Technology: ARPA/NBS Workshop I. Measurement Problems in Integrated Circuit Processing and Assembly*, NBS Spec. Publ. 400-3 (February 1974).
- Amron, I., Errors in Dopant Concentration Profiles Determined by Differential Capacitance Measurements, *Electrochem. Tech.* 5, 94-97 (1967).
- Buehler, M. G., Peripheral and Diffused Layer Effects on Doping Profiles, *IEEE Trans. Electron Devices* ED-19, 1171-1178 (1972).
- Attalla, M., and Tannenbaum, E., Impurity Redistribution and Junction Formation in Silicon by Thermal Oxidation, *Bell System Tech. J.* 39, 933-946 (1960).
- Grove, A., Leistiko, Jr., O., and Sah, C. T., Redistribution of Acceptor and Donor Impurities during Thermal Oxidation of Silicon, *J. Appl. Phys.* 35, 2695-2701 (1964).
- Ku, H., Redistribution of Solutes during Thermal Oxidation of Silicon, *J. Appl. Phys.* 35, 3391-3397 (1964).
- Margalit, S., Nevgroschel, A., and Bor-Lev, A., Redistribution of Boron and Phosphorus in Silicon After Two Oxidation Steps Used in MOST Fabrication, *IEEE Trans. Electron Devices* ED-19, 861-868 (1972).
- Irvin, J. C., Resistivity of Bulk Silicon and of Diffused Layers in Silicon, *Bell System Tech. J.* 41, 387-410 (1962).
- Caughey, D. M., and Thomas, R. E., Carrier Mobilities in Silicon Empirically Related to Doping and Field, *Proc. IEEE* 55, 2192-2193 (1967).
- Wagner, S., Diffusion of Boron from Shallow Ion Implants in Silicon, *J. Electrochem. Soc.* 119, 1570-1576 (1972).
- Buehler, M. G., Thermally Stimulated Measurements: The Characterization of Defects in Silicon *p-n* Junctions, *Semiconductor Silicon/1973*, H. R. Huff and R. R. Burgess, eds., pp. 549-560 (Electrochemical Society, Princeton, N. J., 1973).
- Sah, C. T., Forbes, L., Rosier, L. I., Tasch, Jr., A. F., and Tole, A. B., Thermal Emission Rates of Carriers At Gold Centers in Silicon, *Appl. Phys. Letters* 15, 145-148 (1969).
- Natrella, M. G., *Experimental Statistics*, NBS Handbook 91 (August 1, 1963), ¶5-5.1.3.
- Thurber, W. R., Lewis, D. C., and Bullis, W. M., Resistivity and Carrier Lifetime in Gold-Doped Silicon, AFCRL Report AFCRL-TR-73-0107, January 31, 1973, pp. 14-24. (Available from the National Technical Information Service, Springfield, Virginia 22151, Accession No. AD 760150.)
- Hughes, H. L., A Survey of Radiation-Induced Perturbations in Metal-Insulator-Semiconductor Structures, *9th Annual Proceedings, Reliability Physics 1971*, Las Vegas, Nevada, March 31-April 2, 1971, pp. 1-7. (Available from Publications Sales Dept., The IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 71-C-9-PHY.)
- Hughes, H. L., Baxter, R. D., and Phillips, B., Dependence of MOS Device Radiation Sensitivity on Oxide Impurities, *IEEE Trans. Nucl. Sci.* NS-19, No. 3, 256-263 (1972).
- Yon, E., Ko, W. H., and Kuper, A. B., Sodium Distribution in Thermal Oxide on Silicon by Radiochemical and MOS Analysis, *IEEE Trans. Electron Devices* ED-13, 276-280 (1966).
- Hofstein, S. R., Proton and Sodium Transport in  $\text{SiO}_2$  Films, *IEEE Trans. Electron Devices* ED-14, 749-759 (1967).



# REFERENCES

19. Schroen, W. H., Aiken, J. G., and Brown, G. A., Reliability Improvement by Process Control, *10th Annual Proceedings, Reliability Physics 1972*, Las Vegas, Nevada, April 5-7, 1972, pp. 42-48. (Available from Publication Sales Dept., The IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 72CH0628-8-PHY.)
20. Ting, C., and Chen, C. Y., A Study of the Contacts of a Diffused Resistor, *Solid-State Electronics* 14, 433-438 (1971).
21. Shepela, A., The Specific Contact Resistance of Pd<sub>2</sub>Si Contacts on n- and p-Si, *Solid-State Electronics* 16, 477-481 (1973).
22. Dunham, K. R., Solid-State Photoresist Technology, *Solid-State Technology* 14, No. 6, 41-46 (1971).
23. Clark, K. G., Properties and Processes for Photoresists in Semiconductor Manufacture, Parts 1 and 2, *Solid-State Technology* 14, No. 6, 52-56 and No. 9, 48-53 (1971).
24. Fremesser, J. A., Analytical Controls in Photoresist Manufacture, *Proc. Microelectronic Seminar*, San Diego, California, December 11-12, 1972, pp. 16-20. (Available from Eastman Kodak Co., Rochester, New York 14650, Kodak Publication No. P-312.)
25. Schnable, G. L., and Keen, R. S., On Failure Mechanisms in Large-Scale Integrated Circuits, *Advances in Electronics and Electron Physics*, Vol. 30, L. Marton, ed., pp. 79-138. (Academic Press, New York, 1971.)
26. Kern, W., Vossen, J. L., and Schnable, G. L., Improved Reliability of Electronic Devices Through Optimized Coverage of Surface Topography, *11th Annual Proceedings, Reliability Physics 1973*, Las Vegas, Nevada, April 3-5, 1973, pp. 214-273. (Available from Publications Sales Dept., The IEEE, 345 E. 47th Street, New York 10017, Catalog No. 73CH0755-9-PHY.)
27. Adolphsen, J. W., and Anstead, R. J., Use of the Scanning Electron Microscope As A Semiconductor Production Line Quality Control Tool, *Silicon Device Processing*, C. P. Marsden, ed., pp. 384-391, NBS Spec. Publ. 337 (November 1970).
28. Anstead, R. J., and Adolphsen, J. W., Specification for Scanning Electron Microscope Inspection of Semiconductor Device Metallization, GSFC-S 311-P-12A, NASA-Goddard Space Flight Center, Greenbelt, Maryland (12 November 1971).
29. Klippenstein, E. T., and Devaney, J. R., Scanning Electron Microscope Inspection Procedure for Microcircuits, JPL Procedure EP 505 978, Jet Propulsion Laboratory, Pasadena, California (September 1971).
30. Beall, J. R., Scanning Electron Microscope Microelectronic Inspection Criteria Report, Martin Marietta Corporation, Denver, Colorado (September 1972).
31. Gurev, H. S., A Current Pulse Screening Test for Metal Step Coverage, *11th Annual Proceedings, Reliability Physics 1973*, Las Vegas, Nevada, April 3-5, 1973, pp. 245-253. (Available from Publication Sales Dept., The IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 73CH0755-9-PHY.)
32. Gurev, H. S., A Current Pulse Screening Test for Metal Step Coverage, Air Force Weapons Laboratory Report AFWL-TR-73-107 (March 1973).
33. Crosthwait, Jr., D. L., Gbate, P. B., and Smith, D. M., Screening of Metallization Step Coverage on Integrated Circuits, *11th Annual Proceedings, Reliability Physics 1973*, Las Vegas, Nevada, April 3-5, 1973, pp. 254-256. (Available from Publication Sales Dept., The IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 73CH0755-9-PHY.)

## REFERENCES

- Vossen, J. L., Screening of Metal Film Defects by Current Noise Measurements, *Appl. Phys. Letters* 23, 287-289 (1973).
- Potter, C. N., and Sawyer, D. E., A Flying-Spot Scanner, *Rev. Sci. Instrum.* 39, 180-183 (1968).
- Potter, C. N., and Sawyer, D. E., Optical Scanning Techniques for Semiconductor Device Screening and Identification of Surface and Junction Phenomena, *Physics of Failure in Electronics*, Vol. 5, T. S. Shilliday and J. Vaccaro, eds., pp. 37-50 (1967). (Available from National Technical Information Service, Springfield, Virginia 22151, Accession No. AD 655397.)
- Edwards, A. L., TRUMP: A Computer Program for Transient and Steady-State Temperature Distributions in Multidimensional Systems, Lawrence Radiation Laboratory, Univ. of California, Livermore, California, UCRL-14754, Rev. II, 1 July 1969. (Available from National Technical Information Service, Springfield, Virginia 22151, Accession No. UCRL-14754.)
- Oettinger, F. F., and Gladhill, R. L., Thermal Response Measurements for Semiconductor Device Die Attachment Evaluation, *Technical Digest, 1973 Int. Electron Devices Meeting*, Washington, D. C., December 3-5, 1973, pp. 47-50. (Available from Publication Sales Dept., The IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 73CH0781-5-ED.)
- Goldfarb, S. Wire Bonds on Thick Film Conductors, *Proceedings 1971 21st Electronic Components Conference*, Washington, D. C., May 10-12, 1971, pp. 295-301. (Available from IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 71 C7-PMP.)
- Harman, G. G., Ed., *Semiconductor Measurement Technology: Microelectronic Ultrasonic Bonding*, NBS Spec. Publ. 400-2 (January 1974).
- Tentative Recommended Practices for Determining Hermeticity of Electron Devices with a Helium Mass Spectrometer Leak Detector, ASTM Designation F134-72T, *Annual Book of ASTM Standards*, Part 8. (Available as a separate reprint from American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pennsylvania 19103.)
- Howl, D. A., and Mann, C. A., The Back-Pressurising Technique of Leak-Testing, *Vacuum* 15, 347-352 (1965).
- Diode Test Holder, 9.375 GHz (X-Band), DESC Assembly Drawing D65019 and Sliding Load (X-Band), DESC Assembly Drawing C 65042. (Available from DESC-ES, 1507 Wilmington Pike, Dayton, Ohio 45401.)
- Sawyer, D. E., Rogers, G. J., and Huntley, L. E., Measurement of Transit Time and Related Transistor Characteristics, Air Force Weapons Laboratory Report AFWL-TR-73-54, October 1973. (Available from National Technical Information Service, Springfield, Virginia 22151, Accession No. AD 914258.)

APPENDIX A  
SEMICONDUCTOR TECHNOLOGY PROGRAM STAFF

Coordinator: J. C. French<sup>\*</sup>  
Secretary: Miss B. S. Hope<sup>\*</sup>  
Consultant: C. P. Marsden<sup>††</sup>

Semiconductor Characterization Section

(301) 921-3625

Dr. W. M. Bullis, Chief

F. H. Brewer  
Dr. M. G. Buehler  
Miss F. C. Butler<sup>+</sup>  
M. Cosman  
Mrs. K. E. Dodson<sup>+</sup>  
Dr. J. R. Ehrstein  
T. E. Griffin<sup>x</sup>

F. R. Kelly<sup>x</sup>  
Dr. R. Y. Koyama  
Mrs. K. O. Leedy<sup>#</sup>  
Dr. D. C. Lewis  
R. L. Mattis  
Dr. A. G. Lieberman<sup>††</sup>

Dr. W. E. Phillips  
Miss D. R. Ricks  
S. Ruthberg  
H. A. Schafft  
A. W. Stallings  
Mrs. M. L. Stream<sup>+</sup>  
W. R. Thurber

Semiconductor Processing Section

(301) 921-3541

Dr. A. H. Sher, Chief

H. E. Dyson  
G. G. Harman  
W. J. Keery  
H. K. Kessler

J. Krawczyk  
T. F. Leedy  
Y. M. Liu  
Miss C. A. Main<sup>§</sup>

Dr. D. B. Novotny  
R. L. Raybold  
L. M. Smith  
Mrs. E. Y. Trager<sup>+</sup>

Electron Devices Section

(301) 921-3622

F. F. Oettinger, Acting Chief

D. L. Blackburn  
V. L. Boxwell  
R. L. Gladhill  
Mrs. A. D. Glover<sup>+</sup>

J. M. Kenney  
Mrs. B. A. Oravec<sup>††</sup>  
M. K. Phillips  
M. C. Rhodes<sup>††</sup>  
G. J. Rogers

S. Rubin  
D. E. Sawyer  
L. R. Williams  
M. J. Wirtz<sup>x</sup>

---

† Part Time  
+ Secretary  
x Summer

\* Telephone: (301) 921-3357  
† Telephone: (301) 921-3621  
# Telephone: (301) 921-3622  
§ Telephone: (301) 921-3625

# APPENDIX B

## SEMICONDUCTOR TECHNOLOGY PROGRAM PUBLICATIONS

### or Reports

A review of the early work leading to this Program is given in Bullis, W. M., Measurement methods for the Semiconductor Device Industry — A Review of NBS Activity, NBS Tech. Note 511, December, 1969.

Quarterly reports covering the period July 1, 1968, through June 30, 1973, were published as NBS Technical Notes with the title Methods of Measurement for Semiconductor Materials, Process Control, and Devices. These reports may be obtained from the Superintendent of Documents (Catalog Number C.13.46:XXX) where XXX is the appropriate technical note number. Microfilm copies are available from the National Technical Information Service (NTIS), Springfield, Virginia 22151.

Quarter Ending	NBS Tech. Note	Date Issued	NTIS Accession No.
September 30, 1968	472	December 1968	AD 681330
September 31, 1968	475	February 1969	AD 683808
October 31, 1969	488	July 1969	AD 692232
September 30, 1969	495	September 1969	AD 695820
September 30, 1969	520	March 1970	AD 702833
September 31, 1969	527	May 1970	AD 710906
October 31, 1970	555	September 1970	AD 718534
September 30, 1970	560	November 1970	AD 719976
September 30, 1970	571	April 1971	AD 723671
September 31, 1970	592	August 1971	AD 728611
October 31, 1971	598	October 1971	AD 732553
September 30, 1971	702	November 1971	AD 734427
September 30, 1971	717	April 1972	AD 740674
September 31, 1971	727	June 1972	AD 744946
October 31, 1972	733	September 1972	AD 748640
September 30, 1972	743	December 1972	AD 753642
September 30, 1972	754	March 1973	AD 757244
September 31, 1972	773	May 1973	AD 762840
October 31, 1973	788	August 1973	AD 766918
September 30, 1973	806	November 1973	

### Recent Publications

As various phases of the work are completed, publications are prepared to summarize the results or to describe the work in greater detail. Copies of most such publications are available and can be obtained on request to the editor or the author.

Wyer, D. E., Rogers, G. J., and Huntley, L. E., Measurement of Transit Time and Related Transistor Characteristics, Air Force Weapons Laboratory Report AFRL-TR-73-54 (October 1973). Available from National Technical Information Services, Springfield, Virginia 22151, Accession No. AD 914258.

Wafft, H. A., Failure Analysis of Wire Bonds, *11th Annual Proceedings, Reliability Physics*, 3, Las Vegas, Nevada, April 3-5, 1973, pp. 98-104. (Available from Publication Sales Office, The IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 73CH0755-9-PHY.)



## APPENDIX B

Leedy, K. O., Scanning Electron Microscope Examination of Wire Bonds from High-Reliability Microelectronic Devices, NBS Tech. Note 785 (August 1973).

Oettinger, F. F., and Gladhill, R. L., Thermal Response Measurements for Semiconductor Device Die Attachment Evaluation, *Technical Digest, 1973 International Electron Devices Meeting*, Washington, D. C., December 3-5, 1973, pp. 47-50. (Available from Publications Sales Dept., The IEEE, 345 E. 47th Street, New York, New York 10017, Catalog No. 73CH0781-5ED.)

Harman, G. G., Ed., *Semiconductor Measurement Technology: Microelectronic Ultrasonic Bonding*, NBS Spec. Publ. 400-2 (January 1974).

Schafft, H. A., *Semiconductor Measurement Technology: ARPA/NBS Workshop I. Measurement Problems in Integrated Circuit Processing and Assembly*, NBS Spec. Publ. 400-3 (February 1974).

Forman, R. A., Thurber, W. R., and Aspnes, D. E., The Second Indirect Band Gap in Silicon, to be published in *Solid State Communications*.

APPENDIX C  
WORKSHOP AND SYMPOSIUM SCHEDULE

Proceedings or Reports of Past Events:

Symposium on Silicon Device Processing, Gaithersburg, Maryland, June 2-3, 1970 —  
Proceedings: NBS Spec. Publ. 337 (November 1970).

ARPA/NBS Workshop I. Measurement Problems in Integrated Circuit Processing and  
Assembly, Palo Alto, California, September 7, 1973 — Report: NBS Spec. Publ.  
400-3 (February 1974).

Calendar of Future Events:

ARPA/NBS Workshop II. Hermeticity, Gaithersburg, Maryland, March 29, 1974. For  
information, contact H. A. Schafft or S. Ruthberg (301) 921-3625.

Spreading Resistance Symposium, Gaithersburg, Maryland, June 13-14, 1974. (Cosponsored  
by ASTM Committee F-1 and NBS). For information, contact J. R. Ehrstein  
(301) 921-3625 or P. H. Langer (215) 439-7131.

ARPA/NBS Workshop III. Test Patterns, Scottsdale, Arizona, September 6, 1974.\* For  
information, contact H. A. Schafft or M. G. Buehler (301) 921-3625.

## APPENDIX D

### STANDARDS COMMITTEE ACTIVITIES

#### ASTM Committee F-1 on Electronics

- M. G. Buehler, Semiconductor Measurements Subcommittee; Process Controls Section
- W. M. Bullis, Editor, Semiconductor Crystals Subcommittee; Secretary, Editorial Subcommittee; Semiconductor Measurements, Semiconductor Processing Materials, Hybrid Microelectronics, and Quality and Hardness Assurance Subcommittees; Insulating Materials Section; Advisory Committee
- J. R. Ehrstein, Chairman, Resistivity Section; Semiconductor Crystals, Semiconductor Processing Materials, Semiconductor Measurements, and Hybrid Microelectronics Subcommittees
- J. C. French, Chairman, Editorial Subcommittee; Secretary, Advisory Committee; Semiconductor Crystals, Semiconductor Processing Materials, Semiconductor Measurements, Hybrid Microelectronics, and Quality and Hardness Assurance Subcommittees
- G. G. Harman, Secretary, Interconnection Bonding Section
- B. S. Hope, Committee Assistant Secretary
- K. O. Leedy, Chairman, Interconnection Bonding Section
- T. F. Leedy, Dielectrics Section
- D. C. Lewis, Semiconductor Crystals, Semiconductor Processing Materials, Semiconductor Measurements, Hybrid Microelectronics, and Quality and Hardness Assurance Subcommittees
- C. P. Marsden, Committee Secretary; Advisory Committee
- R. L. Mattis, Semiconductor Crystals, Semiconductor Measurements, and Editorial Subcommittees
- D. B. Novotny, Editor, Semiconductor Processing Materials Subcommittee
- W. E. Phillips, Chairman, Lifetime Section; Secretary, Semiconductor Crystals Subcommittee; Semiconductor Processing Materials, Semiconductor Measurements, and Hybrid Microelectronics Subcommittees
- S. Ruthberg, Semiconductor Processing Materials, Hybrid Microelectronics, and Quality and Hardness Assurance Subcommittees
- A. H. Sher, Semiconductor Crystals, Semiconductor Processing Materials, and Hybrid Microelectronics Subcommittees
- W. R. Thurber, Semiconductor Crystals and Semiconductor Measurements Subcommittees

#### ASTM Committee E-10 on Radioisotopes and Radiation Effects

- W. M. Bullis, Subcommittee 7, Radiation Effects on Electronic Materials
- J. C. French, Subcommittee 7, Radiation Effects on Electronic Materials

#### Electronic Industries Association: Solid State Products Division, Joint Electron Device Engineering Council (JEDEC)

- J. M. Kenney, Microwave Diode Measurements, Committee JC-21 on UHF and Microwave Diodes
- F. F. Oettinger, Chairman, Task Group JC-11.3-1 on Thermal Considerations for Micro-electronic Devices, Committee JC-11 on Mechanical Standardization; Technical

## APPENDIX D

Advisor, Thermal Resistance Measurements, Committees JC-22 on Rectifier Diodes and Thyristors, JC-20 on Signal and Regulator Diodes, JC-25 on Power Transistors, and JC-30 on Hybrid Integrated Circuits

S. Rubin, Chairman, Council Task Group on Galvanomagnetic Devices

D. E. Sawyer, Task Group JC-24-5 on Transistor Scattering Parameter Measurement Standards, Committee JC-24 on Low Power Transistors

H. A. Schafft, Technical Advisor, Second Breakdown and Related Specifications, Committee JC-25 on Power Transistors

### E Electron Devices Group

J. C. French, Standards Committee

J. M. Kenney, Chairman, Standards Committee Task Force on Microwave Solid-State Devices II (Mixer and Video Detector Diodes)

H. A. Schafft, Chairman, Standards Committee Task Force on Second Breakdown Measurement Standards

### E Magnetics Group

S. Rubin, Chairman, Galvanomagnetic Standards Subcommittee

### E Parts, Hybrids, and Packaging Group

W. M. Bullis, New Technology Subcommittee, Technical Committee on Hybrid Microelectronics

### Society of Automotive Engineers

J. C. French, Subcommittee A-2N on Radiation Hardness and Nuclear Survivability

W. M. Bullis, Planning Subcommittee of Committee H on Electronic Materials and Processes

F. F. Cettinger, Electronic Systems Steering Committee

### TC47, Semiconductor Devices and Integrated Circuits

S. Rubin, Technical Expert, Galvanomagnetic Devices; U.S. Specialist for Working Group 5 on Hall Devices and Magnetoresistive Devices



APPENDIX E  
SOLID-STATE TECHNOLOGY & FABRICATION SERVICES

Technical services in areas of competence are provided to other NBS activities and other government agencies as they are requested. Usually these are short-term, specialized services that cannot be obtained through normal commercial channels. Such services provided during the last quarter, which are listed below, indicate the kinds of technology available to the program.

1. Thin Metal Films (J. Krawczyk and T. F. Leedy)

Thin films of a gold-germanium alloy and nickel were evaporated onto gallium arsenide substrates for the Harry Diamond Laboratories.

Thin films of chromium were evaporated onto quartz flats for the NBS Dimensional Technology Section.

2. Ultrasonic Machining (J. Krawczyk and M. Cosman)

Holes were ultrasonically machined into sapphire plates for the Harry Diamond Laboratories.

Holes were ultrasonically machined in thermocouple junctions for the NBS Instrumentation Applications Section.

3. SEM Technical Services (W. J. Keery)

Scanning electron micrographs of marble specimens from the Lincoln Memorial were taken for the NBS Materials and Composites Section.

4. Channel Electron Multipliers and Silicon Nuclear Radiation Detectors (Y. M. Liu)\*

Evaluation of channel electron multipliers for the NASA Goddard Space Flight Center continued. The fatigue characteristics (degradation of gain and resolution as a function of radiation exposure) of a wide-mouth multiplier of the type to be used in sounding rocket auroral particle experiments were determined.

A commercial silicon surface barrier detector with keyhole-shaped electrodes on both sides was scanned first with a finely-collimated beam of 1.5-MeV protons to determine edge effects and then uncollimated 14-MeV protons to determine the counting sensitivity of the regions of the device outside the keyhole area.

5. Ribbon Wire Technology (H. K. Kessler)<sup>†</sup>

Assistance to the Naval Electronics Laboratory Center, San Diego, in the implementation of NBS-developed ribbon wire technology on their pilot production line continued. Pull strength measurements and analysis of data from NBS and NELC results were performed to aid NELC in achieving control of ribbon wire bonding parameters. A five-day visit was also made to NELC to implement control procedures.

\* NBS Cost Center 4254429

† NBS Cost Center 4254448

**Announcement of New Publications on  
Semiconductor Measurement Technology**

Superintendent of Documents,  
Government Printing Office,  
Washington, D.C. 20402

Dear Sir:

Please add my name to the announcement list of new publications to be issued in the series: National Bureau of Standards Special Publication 400-.

Name \_\_\_\_\_

Company \_\_\_\_\_

Address \_\_\_\_\_

City \_\_\_\_\_ State \_\_\_\_\_ Zip Code \_\_\_\_\_

(Notification Key N-413)

U.S. DEPT. OF COMM. BIBLIOGRAPHIC DATA SHEET	1. PUBLICATION OR REPORT NO.  NBS SP-400-1	2. Gov't Accession No.	3. Recipient's Accession No.
4. TITLE AND SUBTITLE  Semiconductor Measurement Technology: Quarterly Report July 1 to September 30, 1973.		5. Publication Date  March 1974	6. Performing Organization Code
7. AUTHOR(S)  W. Murray Bullis, Editor		8. Performing Organ. Report No.	
9. PERFORMING ORGANIZATION NAME AND ADDRESS  NATIONAL BUREAU OF STANDARDS DEPARTMENT OF COMMERCE WASHINGTON, D.C. 20234		10. Project/Task/Work Unit No.  See Item 15	11. Contract/Grant No. ARPA Order 2397, Pgm Code 4D10; DNA IACRO 74-811
12. Sponsoring Organization Name and Complete Address (Street, City, State, ZIP) NBS, Washington, D. C. 20234; Defense Advanced Research Projects Agency, 1400 Wilson Blvd., Arlington, Va. 22209; Defense Nuclear Agency, Washington, D. C. 20305.		13. Type of Report & Period Covered Interim July to September 30, 1973	14. Sponsoring Agency Code
15. SUPPLEMENTARY NOTES 4251126, 4252128, 4254115, 4259522, 4259555.			
16. ABSTRACT (A 200-word or less factual summary of most significant information. If document includes a significant bibliography or literature survey, mention it here.) This quarterly progress report, twenty-first of a series, describes NBS activities directed toward the development of methods of measurement for semiconductor materials, process control, and devices. Principal accomplishments during this reporting period include (1) extension of the technique for measuring thermally stimulated current and capacitance to include measurements on MOS capacitors (2) completion of the development of the thermal response method for evaluation of transistor die attachment, (3) analysis of the interlaboratory comparison of transistor scattering parameter measurements, (4) preliminary review of measurement problems in the photolithographic aspects of semiconductor device processing, of problems associated with certain hermeticity testing procedures, and of methods for evaluating metallization step coverage, and (5) initiation of new activity on characterization of oxide films in MOS structures and analysis of diffusion profiles. Results are also reported on spreading resistance, capacitance-voltage, and sheet resistance measurements; the activation energy of the gold acceptor in silicon; evaluation of the base-to-metal contact resistor test structure; metallurgical systems for ultrasonic bonding; burn-out characteristics of fine gold and aluminum bonding wire; transistor thermal resistance measurements; and microwave diode conversion loss measurements. Supplementary data concerning staff, publications, workshops and symposia, standards committee activities, and technical services are also included as appendices.			
17. KEY WORDS (six to twelve entries; alphabetical order; capitalize only the first letter of the first key word unless a proper name; separated by semicolons) Contact resistance; die attachment; dopant profiles; electrical properties; electronics; gold-doped silicon; hermeticity; metallization; methods of measurement; microelectronics; microwave diodes; mobility; MOS devices; oxide films; photo masks; photoresist; resistivity; resistivity standards; scanning electron microscopy; semiconductor devices; semiconductor materials; semiconductor process control; sheet resistance; silicon; S-parameters; spreading resistance; test patterns; thermal resistance; thermally stimulated capacitance; thermally stimulated current; wire bonds.			
18. AVAILABILITY  <input type="checkbox"/> For Official Distribution. Do Not Release to NTIS  <input checked="" type="checkbox"/> Order From Sup. of Doc., U.S. Government Printing Office Washington, D.C. 20402, SD Cat. No. C13.10:400-1  <input checked="" type="checkbox"/> Order From National Technical Information Service (NTIS) Springfield, Virginia 22151 (Microfiche only)	19. SECURITY CLASS (THIS REPORT)  UNCLASSIFIED	21. NO. OF PAGES  68	
	20. SECURITY CLASS (THIS PAGE)  UNCLASSIFIED	22. Price  \$1.15	



# NBS TECHNICAL PUBLICATIONS

## PERIODICALS

**JOURNAL OF RESEARCH** reports National Bureau of Standards research and development in physics, mathematics, and chemistry. Comprehensive scientific papers give complete details of the work, including laboratory data, experimental procedures, and theoretical and mathematical analyses. Illustrated with photographs, drawings, and charts. Includes listings of other NBS papers as issued.

*Published in two sections, available separately:*

### Physics and Chemistry (Section A)

Papers of interest primarily to scientists working in these fields. This section covers a broad range of physical and chemical research, with major emphasis on standards of physical measurement, fundamental constants, and properties of matter. Issued six times a year. Annual subscription: Domestic, \$17.00; Foreign, \$21.25.

### Mathematical Sciences (Section B)

Studies and compilations designed mainly for the mathematician and theoretical physicist. Topics in mathematical statistics, theory of experiment design, numerical analysis, theoretical physics and chemistry, logical design and programming of computers and computer systems. Short numerical tables. Issued quarterly. Annual subscription: Domestic, \$9.00; Foreign, \$11.25.

## DIMENSIONS, NBS

The best single source of information concerning the Bureau's measurement, research, developmental, cooperative, and publication activities, this monthly publication is designed for the layman and also for the industry-oriented individual whose daily work involves intimate contact with science and technology *for engineers, chemists, physicists, research managers, product-development managers, and company executives*. Annual subscription: Domestic, \$6.50; Foreign, \$8.25.

## NONPERIODICALS

**Applied Mathematics Series.** Mathematical tables, manuals, and studies.

**Building Science Series.** Research results, test methods, and performance criteria of building materials, components, systems, and structures.

**Handbooks.** Recommended codes of engineering and industrial practice (including safety codes) developed in cooperation with interested industries, professional organizations, and regulatory bodies.

**Special Publications.** Proceedings of NBS conferences, bibliographies, annual reports, wall charts, pamphlets, etc.

**Monographs.** Major contributions to the technical literature on various subjects related to the Bureau's scientific and technical activities.

**National Standard Reference Data Series.** NSRDS provides quantitative data on the physical and chemical properties of materials, compiled from the world's literature and critically evaluated.

**Product Standards.** Provide requirements for sizes, types, quality, and methods for testing various industrial products. These standards are developed cooperatively with interested Government and industry groups and provide the basis for common understanding of product characteristics for both buyers and sellers. Their use is voluntary.

**Technical Notes.** This series consists of communications and reports (covering both other-agency and NBS-sponsored work) of limited or transitory interest.

**Federal Information Processing Standards Publications.** This series is the official publication within the Federal Government for information on standards adopted and promulgated under the Public Law 89-306, and Bureau of the Budget Circular A-86 entitled, Standardization of Data Elements and Codes in Data Systems.

**Consumer Information Series.** Practical information, based on NBS research and experience, covering areas of interest to the consumer. Easily understandable language and illustrations provide useful background knowledge for shopping in today's technological marketplace.

## BIBLIOGRAPHIC SUBSCRIPTION SERVICES

The following current-awareness and literature-survey bibliographies are issued periodically by the Bureau:

**Cryogenic Data Center Current Awareness Service** (Publications and Reports of Interest in Cryogenics). A literature survey issued weekly. Annual subscription: Domestic, \$20.00; foreign, \$25.00.

**Liquefied Natural Gas.** A literature survey issued quarterly. Annual subscription: \$20.00.

**Superconducting Devices and Materials.** A literature survey issued quarterly. Annual subscription: \$20.00. Send subscription orders and remittances for the preceding bibliographic services to the U.S. Department of Commerce, National Technical Information Service, Springfield, Va. 22151.

**Electromagnetic Metrology Current Awareness Service** (Abstracts of Selected Articles on Measurement Techniques and Standards of Electromagnetic Quantities from D-C to Millimeter-Wave Frequencies). Issued monthly. Annual subscription: \$100.00 (Special rates for multi-subscriptions). Send subscription order and remittance to the Electromagnetic Metrology Information Center, Electromagnetics Division, National Bureau of Standards, Boulder, Colo. 80302.

Order NBS publications (except Bibliographic Subscription Services) from: Superintendent of Documents, Government Printing Office, Washington, D.C. 20402.



**U.S. DEPARTMENT OF COMMERCE**  
**National Bureau of Standards**  
Washington, D.C. 20234

OFFICIAL BUSINESS

Penalty for Private Use, \$300

POSTAGE AND FEES PAID  
U.S. DEPARTMENT OF COMMERCE  
COM-215

